

# Proposed Yeelirrie Development: Geochemical Assessment of Tailings and Mine Waste

Report prepared by



March 2011

Project Code: BHP047/1

---

# Proposed Yeelirrie Development Geochemical Assessment of Tailings and Mine Waste BHP047/1

BHP Billiton Yeelirrie Development Company Pty Ltd

SRK Consulting (Australasia) Pty Ltd  
Level 2, 44 Market Street  
Sydney NSW 2000

## SRK Report Distribution Record

Project Number: BHP047/1

Date Issued: 10 March 2011

Name/Title	Company
Keith Ashby	BHP Billiton Yeelirrie Development Company Pty Ltd

This document is protected by copyright vested in BHP Billiton Yeelirrie Development Company Pty Ltd (YDC). It may not be reproduced or transmitted in any form or by any means whatsoever to any person without the written permission of the copyright holder, YDC.

# Executive Summary

The proposed Yeelirrie Development for the recovery of uranium from carnotite, a uranium-vanadium mineral phase, would include permanent placement of tailings within a tailings storage facility (TSF) located within the mined out pit areas. Temporary storage areas for mine waste, ore and soil would be developed adjacent to the mine. Suitable stockpiled overburden materials would be used to progressively rehabilitate the process tailings. Any low grade stockpiles and waste material remaining at the end of mine life would be used to backfill any residual mine voids, with the low grade material placed preferentially at the base of the mine voids.

This report describes outcomes from a geochemical testing programme designed to:

- Evaluate the chemical composition of the materials to be stockpiled on site and assess the solute release from these materials;
- Assess the potential for solute release from the tailings in the short and the long term; and
- Determine the potential interaction between the solutes and the natural materials downstream of the mine facility.

The work programme included detailed chemical characterisation of selected Yeelirrie materials (ores, mine waste and tailings), and completing a series of bottle roll contact and column tests. Interpretation and modelling of the results were undertaken to develop an understanding of the water-rock interactions that could control solute mobility downstream of the mine area.

The outcomes of this programme were used in the predictive modelling of source terms at the site.

## Programme Outcomes

### Stockpiled Materials

Readily soluble phases leached in abundance on contact with water, including salts such as halite and sulphates. The contaminants released at significant concentrations include boron, barium, molybdenum, strontium, thallium, uranium, vanadium and zinc. Radionuclide analyses of leachate solutions showed that radium-226 could also be released during flushing.

The results further indicate that the potential for solute release is finite and depleted rapidly. The earliest pore volume exchanges tend to coincide with the highest solute concentrations; concentrations are much reduced in subsequent pore volume exchanges.

Carnotite solubility is expected to place an upper limit on uranium and vanadium concentrations. In many cases, the mass of available carnotite may be limited and the solutions could remain under-saturated with respect to this mineral. Sorption onto iron and aluminium oxy-hydroxides and clays may further limit release of some elements.

### Tailings

In the short-term, the tailings porewater quality would be dominated by process water (barren liquor). Barren liquor is alkaline and contains high concentrations of dissolved uranium and vanadium. The excess alkalinity is likely to lead to further dissolution over time of carnotite remaining in the tailings. This leaching will lead to increases in uranium and vanadium concentrations, until equilibrium is reached with carnotite, or until the residual carnotite has been depleted. In time, ion exchange processes would also result in lower dissolved sodium and potassium concentrations in the porewater, and alkalinity may also decrease due to the formation of secondary carbonate minerals. While decreasing potassium concentrations will result in increased carnotite solubility, it could be offset by lower alkalinity concentrations with the net effect that dissolved uranium and vanadium concentrations in the porewater would remain nearly constant.

Ion exchange reactions involving clay minerals may have a secondary outcome with respect to changing the physical characteristics of the materials. There is a correlation between exchange site occupancy and the swelling capacity of the clay. Replacing calcium with sodium will result in swelling, and consequently may reduce the permeability of the material. Reduced permeability in some materials affected the operation of some of the column tests. These effects could occur reduce the permeability of the tailings and affect the rate of porewater displacement.

## Downstream Interactions

Initial percolate from the TSF could contain high dissolved sodium concentrations which are likely to result in displacement of ions from exchange sites on clays downstream of the facility. The ion exchange reactions would release calcium, magnesium, barium and strontium to the porewater. The results indicate that, notably, radium-226 would not be released, and is instead attenuated in the clays.

Carnotite solubility is expected to play an important role in limiting the solubility of uranium and vanadium along flow paths downstream of the facility. Geochemical conditions downstream of the TSF are expected to result in carnotite precipitating from solution, leading to lower uranium and vanadium concentrations, principally due to the decrease in alkalinity expected downstream. Solubility controls that could apply to other elements are co-precipitation in sulphate or carbonate phases.

Contaminant transport may also be slowed due to sorption onto mineral surfaces (e.g. iron and aluminium oxyhydroxides and clays). Sorption is not strong under the relatively carbonate-rich conditions expected in Yeelirrie groundwater, however, moderate sorption is expected for many elements, except for the very high dissolved carbonate concentrations in tailings seepage in the near-zone of the TSF.

## Conclusions

The geochemical testing of the tailings and the stockpiled materials provide an indication of the potential for solute release from these materials under the conditions expected for the TSF and surrounding areas. These release rates may be used in conjunction with the site water flow conditions (such as recharge, porewater displacement, etc.) to develop source terms for each of the site components. The testing also provides insight into the potential mechanisms that may affect the concentrations and rate of transport of the solutes after they have been released from the tailings and other sources. This information may be used to infer the potential downstream controls on solute mobility that may limit the extent and rate of contaminant transport.

# Table of Contents

<b>Executive Summary</b> .....	<b>ii</b>
Programme Outcomes.....	ii
Conclusions.....	iii
<b>Disclaimer</b> .....	<b>vi</b>
<b>1. Introduction</b> .....	<b>1</b>
<b>2. Background</b> .....	<b>1</b>
2.1 Geological Setting.....	1
2.1.1 Bulk Chemistry of Soils and Underlying Rocks.....	5
2.1.2 Chemistry of Groundwater.....	7
2.2 Previous Mining Trials at Yeelirrie.....	9
2.3 Proposed Yeelirrie Project Development.....	10
2.3.1 Mining and Production.....	10
2.3.2 Ore Processing.....	10
2.3.3 Tailings Production and Storage.....	10
<b>3. Work Programme and Methods</b> .....	<b>11</b>
3.1 Objectives.....	11
3.2 Field Programme.....	11
3.3 Laboratory Programme.....	11
3.4 Geochemical Modelling.....	12
<b>4. Yeelirrie Rocks and Soils</b> .....	<b>13</b>
4.1 Introduction.....	13
4.2 Ore and Waste Materials.....	13
4.2.1 Mineralogy.....	13
4.2.2 Surface Characteristics.....	14
4.2.3 Particle Size Distribution.....	14
4.2.4 Bulk Chemistry.....	14
4.2.5 Solute Release (De-Ionised Water Extractions).....	18
4.3 Materials Underlying and Adjacent to the TSF.....	29
4.3.1 Mineralogy.....	29
4.3.2 Surface Characterisation.....	29
4.3.3 Particle Size Distribution.....	29
4.3.4 Bulk Chemistry.....	29
4.3.5 Interactions with Barren Liquor.....	33
4.4 Column Test Results.....	38
4.4.1 General Trends.....	40
4.4.2 Quantitative Comparisons between Column and Bottle Roll Test Results.....	44
4.5 Radionuclide Distribution and Behaviour.....	46
4.6 Geochemical Controls.....	49
4.6.1 Mineral Solubility.....	49
4.6.2 Sorption.....	51
4.6.3 Summary.....	61
<b>5. Tailings</b> .....	<b>62</b>
5.1 Introduction.....	62
5.2 Mineralogy.....	62
5.3 Surface Characteristics.....	62
5.4 Particle Size Distribution.....	62

5.5	Bulk Chemistry.....	62
5.6	Metal Leaching .....	65
5.7	Radionuclide Behaviour .....	68
5.8	Process Tailings Ageing.....	70
<b>6.</b>	<b>Tailings (Kalgoorlie Storage Facility) .....</b>	<b>74</b>
6.1	Mineralogy .....	74
6.2	Surface Characteristics .....	74
6.3	Bulk Chemistry.....	74
6.4	Metal Leaching .....	79
6.5	Radionuclide Distribution and Behaviour.....	81
6.6	Geochemical Controls.....	83
	6.6.1 Attenuation.....	83
	6.6.2 Solubility Controls .....	83
6.7	Kalgoorlie TSF as an Analogue for the Proposed Yeelirrie TSF .....	83
<b>7.</b>	<b>Conclusions.....</b>	<b>85</b>
<b>8.</b>	<b>References .....</b>	<b>87</b>

## List of Appendices

- Appendix 1: Field Programme
- Appendix 2: Laboratory Programme
- Appendix 3: Bulk Chemical Assays
- Appendix 4: Bottle Roll Test Results
- Appendix 5: Column Test Results
- Appendix 6: Tails Ageing Test Results
- Appendix 7: Particle Size Distributions

## Disclaimer

The opinions expressed in this Report have been based on the information supplied to SRK Consulting (Australasia) Pty Ltd (SRK) by BHP Billiton Yeelirrie Development Company (YDC), Amdel Limited, Australian Nuclear Science and Technology Organisation (ANSTO), Australian Laboratory Services (ALS) and Particle and Surface Sciences Pty Ltd. The opinions in this Report are provided in response to a specific request from YDC to do so. SRK has exercised all due care in reviewing the supplied information. Whilst SRK has compared key supplied data with expected values, the accuracy of the results and conclusions from the review are entirely reliant on the accuracy and completeness of the supplied data. SRK does not accept responsibility for any errors or omissions in the supplied information and does not accept any consequential liability arising from commercial decisions or actions resulting from them.

# 1. Introduction

The proposed Yeelirrie Development for the recovery of uranium from carnotite (a uranium-vanadium mineral phase) would include construction of a tailings storage facility (TSF) within the mined out pit areas. Temporary storage areas for mine waste, ore and soil would be developed adjacent to the mine. Suitable stockpiled overburden materials would be used to progressively rehabilitate the process tailings as each cell reaches completion. L grade stockpiles and waste material that may remain at the end of mine life would be backfilled to the residual mine voids. The low grade materials would be placed preferentially at the base of the voids approximating the distribution of the material prior to mining.

Processing would entail contacting the ore with a concentrated solution of soda ash to dissolve the carnotite and allow recovery of the uranium in solution. The processed tailings would therefore be alkaline in nature and may contain elevated concentrations of metals (e.g. vanadium) that leach concurrently with the uranium. Therefore, the process water that would be deposited with the tailings is likely to contain elevated concentrations of various solutes.

Similarly, the mine waste materials are likely to contain elevated concentrations of salts due to the presence of evaporites (accumulated salts) or saline porewater. These solutes may be released from the tailings and mine waste during operations and after closure. Solute release from the tailings and the stockpiled materials over time may have the potential to affect ground and surface water quality downstream of the site.

Historic gamma surveys collected for rehabilitated trial mining areas indicated that release of radionuclides from stockpiles was limited (at least over the 30 year period that those stockpiles were in place). It was however necessary to extend the understanding of potential effects to include other solutes, for a wider range of material types and geochemical conditions.

A previous SRK report (SRK, 2009) presented a conceptual geochemical model for the TSF based on the available historical information. The conceptual model considered the ore genesis, the proposed milling and leaching process for uranium recovery, as well as the results from historical testing and monitoring. Based on that understanding, a laboratory programme was initiated in 2009 to gather additional geochemical information describing the leaching and attenuation behaviour of contaminants at the Yeelirrie site. This report documents the outcomes of the laboratory programme. The results obtained by the current laboratory programme are to support predictive modelling of source terms at the site.

## 2. Background

### 2.1 Geological Setting

The regional geology of the area is dominated by Archaean granites, gneisses and other high grade metamorphic rocks. Since formation, these rocks have been subjected to prolonged weathering and erosion.

The Yeelirrie ore body is situated in alluvial sediments within the central drainage channel of a wide, shallow valley. The channel cuts into heavily weathered granite. In recent geological history (within the last 2 million years), the climate has become more arid and the current drainage channel comprises a series of clay pans and salt lakes. In the central parts of the channel, alluvial sediments have been replaced by calcrete deposits (the calcrete likely forming as part of near surface evaporative secondary mineral precipitation).

Twelve lithological types are identified in Yeelirrie logs as summarised in Table 2.1.



**Table 2.1: Lithological types included in logs of Yeelirrie materials**

Lithological Type	Code	Comment
Hardpan	H	
Carbonated hardpan	HT	
Loam	L	
Quartz-rich loam	LQ	
Carbonated quartz-rich loam	LQT	
Carbonated loam	LT	Ore-bearing
Calcrete	T	Ore-bearing
Transition calcrete	TCQ	Ore-bearing
Carbonated Clay-Quartz	CQT	
Arkosic Clay-Quartz	CQA	
Clay-Quartz	CQ	
Granite	G	

Figure 2.1 shows an idealised lithological profile and a cross-section of the Yeelirrie deposit (WMC, 1991). Figure 2.2 shows how the mineralogy varies with depth. As shown in the figure, calcrete carbonate minerals comprise calcite and dolomite, with calcite occurring predominantly nearer the surface whereas dolomite is more abundant at depth.

Calcrete formation is believed to have taken place over a long period of time, and is still taking place. Over time, carbonate minerals present in ‘upstream’ calcrete are mobilized (dissolved) and then precipitated ‘downstream’. The dissolution occurs due to the introduction of carbon dioxide (CO<sub>2</sub>)-charged rainwater to the groundwater system, thus increasing the hydrogen ion concentration which lowers the pH of the water as follows:



Pre-existing carbonate minerals dissolve when contacted by such waters. For example, calcite dissolves as follows:



The reactions are reversible and, as carbon dioxide is lost from the system, carbonate minerals precipitate again.

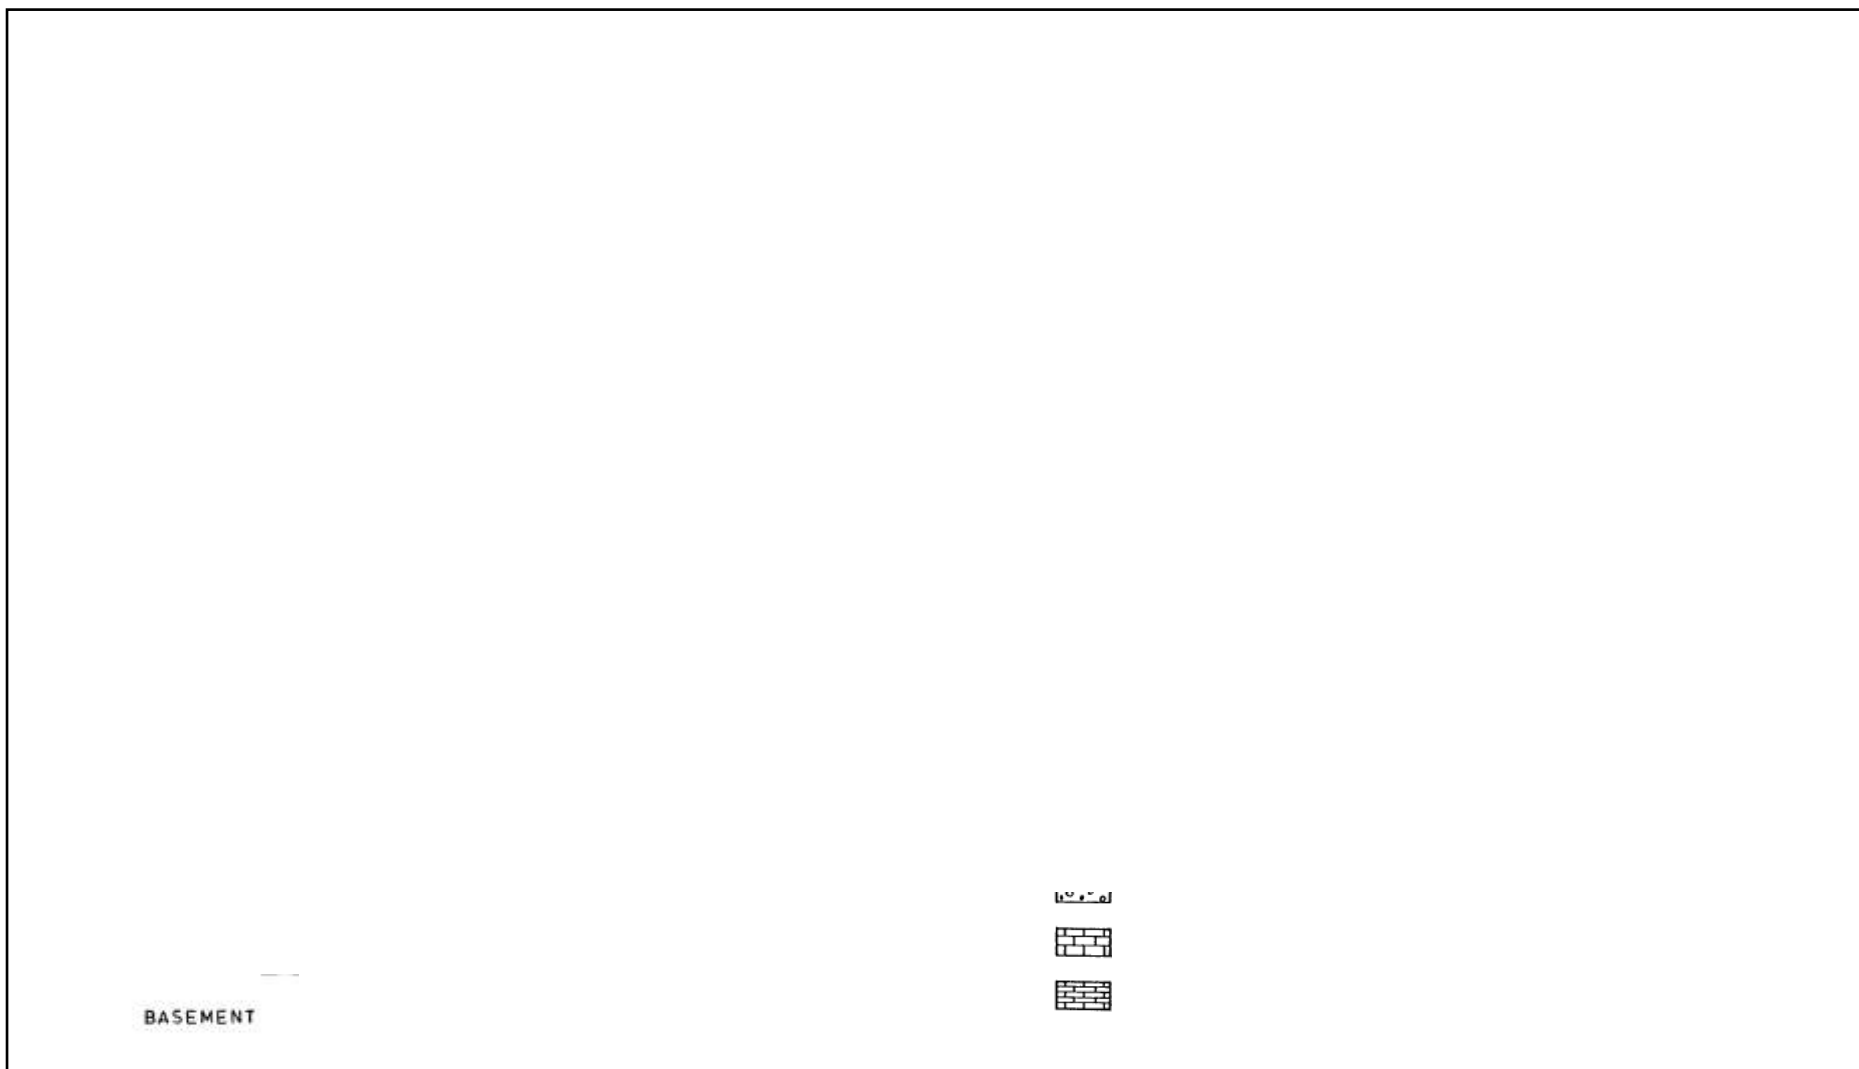


Figure 2.1: Idealised lithological profile and cross-section of the Yeelirrie deposit (WMC, 1991)



Figure 2.2: Schematic showing the mineralogical composition of the different horizons encountered at Yeelirrie (WMC, 1991)

## 2.1.1 Bulk Chemistry of Soils and Underlying Rocks

The BHP Billiton geological database<sup>†</sup> of chemical analyses for drill core from the deposit was reviewed to develop an understanding of the variability of key elements within the different lithological units. Figure 2.3 and Figure 2.4 show the calculated median uranium and vanadium concentrations in different Yeelirrie materials. As might be expected, the highest median concentrations are found in ore-bearing lithologies (LT, T and TCQ). Consistent with carnotite being the primary uranium mineral, the vanadium contents follow the same pattern.

Some general comments regarding the distribution of other element of interest are:

- Many metals, e.g. copper, nickel and lead are present at low concentrations in all materials, with median concentrations less than 50 ppm (below crustal 'averages', Bowen, 1979). Concentrations are lowest in calcrete, and highest in the deeper clay-quartz lithologies or in hardpan. There appears to be some correlation between these metals and Al and Si content, suggesting clays may be important as sorption sites (e.g. ion exchange). The hardpan concentrations may be due to evapo-concentration and the formation of evaporites of the metals.
- Median arsenic and molybdenum contents are generally less than 20 ppm and 5 ppm, respectively. Crustal 'average' values for arsenic and molybdenum are 1.5 ppm. Highest median contents are found in the deeper clay-quartz lithologies.
- Strontium contents range up to a maximum of 280,000 ppm, or 28 %, (compared to a crustal average, 370 ppm). The highest median concentrations are close to 600 ppm, for calcrete, transition calcrete and carbonated loam. The high strontium correlates with either high carbonate or high sulphate, suggesting possible control by either strontianite or celestite.

---

<sup>†</sup> The version of the database reviewed was dated 21<sup>st</sup> December 2009.

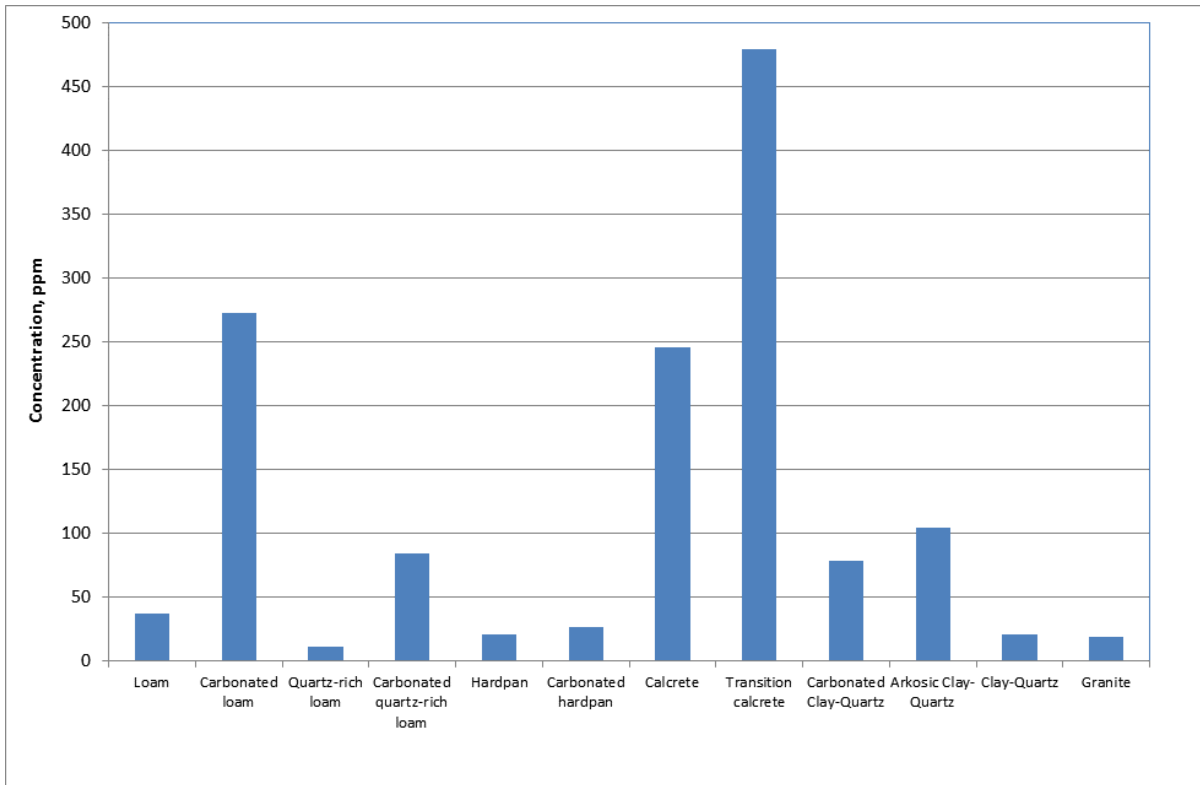


Figure 2.3: Median uranium content of different Yeelirrie materials

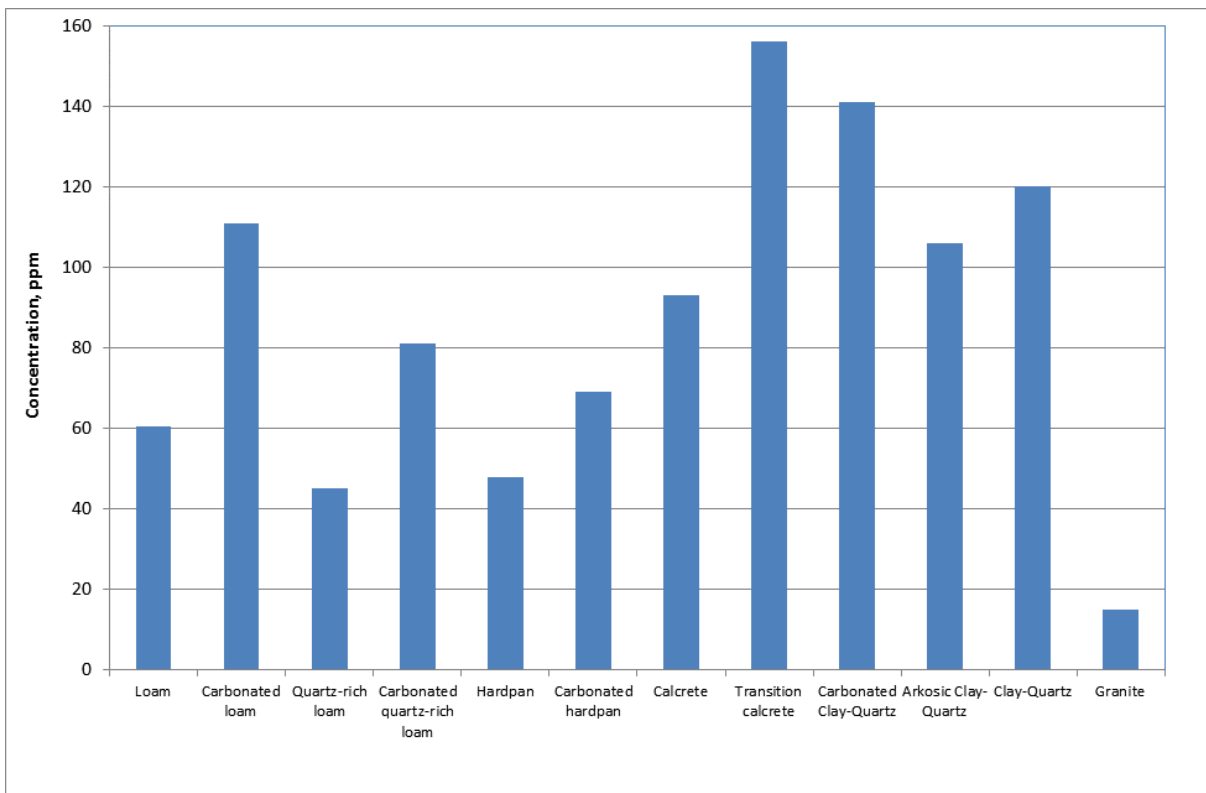


Figure 2.4: Median vanadium content of different Yeelirrie materials

## 2.1.2 Chemistry of Groundwater

Available groundwater monitoring results provided by URS (based on groundwater sampling that took place in the period from November 2009 to January 2010) represent analyses of samples collected from various boreholes and wells in the Yeelirrie area. A large proportion of these samples were collected from within depth ranges and lithologies analogous to materials that would be mined at Yeelirrie, or were obtained from within possible flow paths downstream of the deposit.

**Table 2.2: Groundwater Chemistry - Summary Statistics**

Parameter	Units	Minimum	Maximum	Median	Average
pH (field)		6.0	7.8	7.0	7.0
Eh (field)	(mV)	18	701	340	328
Alkalinity	mgCaCO <sub>3</sub> /L	41	946	205	226
Al	mg/L	0.01	2.42	0.02	0.22
Ca	mg/L	27	1020	273	361
K	mg/L	10	2100	207	460
Mg	mg/L	16	3500	434	737
Na	mg/L	113	23600	2845	5035
SiO <sub>2</sub>	mg/L	0.1	112	55	58
Br	mg/L	0.1	169	11	34
Cl	mg/L	81	43900	4985	9115
F	mg/L	0.3	3.8	1.5	1.6
N	mg/L	0.01	56.5	15.8	19.9
P	mg/L	0.01	2.7	0.1	0.2
SO <sub>4</sub>	mg/L	57	13700	1945	3155
Ag	mg/L	0.001	0.04	0.00	0.00
As	mg/L	0.001	0.05	0.00	0.02
B	mg/L	0.38	47.80	5.23	11.04
Ba	mg/L	0.01	0.53	0.05	0.07
Be	mg/L	0.001	0.05	0.00	0.00
Bi	mg/L	0.001	0.01	0.00	0.00
Cd	mg/L	0.000	0.01	0.00	0.00
Ce	mg/L	0.001	0.01	0.00	0.00
Co	mg/L	0.001	0.18	0.01	0.01
Cr	mg/L	0.001	0.04	0.00	0.01
Cu	mg/L	0.001	0.08	0.01	0.02
Fe	mg/L	0.05	5.06	0.25	0.51
Hg	mg/L	0.000	0.00	0.00	0.00
Li	mg/L	0.001	0.18	0.02	0.04
Mn	mg/L	0.001	21.50	0.17	0.77
Mo	mg/L	0.002	0.62	0.06	0.11
Ni	mg/L	0.001	0.17	0.02	0.03
Pb	mg/L	0.001	0.15	0.00	0.01
Re	mg/L	0.001	0.01	0.00	0.00
Sb	mg/L	0.001	0.01	0.00	0.00
Se	mg/L	0.01	0.23	0.03	0.05
Sn	mg/L	0.001	0.01	0.00	0.00
Sr	mg/L	0.30	25.90	5.36	8.31
Th	mg/L	0.001	0.01	0.00	0.00
Tl	mg/L	0.001	0.01	0.00	0.00
U	mg/L	0.001	2.36	0.16	0.31
V	mg/L	0.01	0.13	0.01	0.03
W	mg/L	0.001	0.20	0.01	0.01
Y	mg/L	0.001	0.01	0.00	0.00
Zn	mg/L	0.01	1.89	0.03	0.09

The results were examined using geochemical modelling techniques to identify potential solubility limits that might apply under field conditions. Using the measured groundwater chemistries as input, the saturation indices of key mineral phases were calculated. The focus of the calculations was to identify minerals close to equilibrium with the measured water chemistries (a saturation index close to zero). Such minerals, if present in the materials, may have dissolved (or precipitated) to attain equilibrium with the groundwater and therefore may be used to infer solubility limitations.


Possible solubility controls identified within the existing groundwater environments include:

- Iron and aluminium oxy-hydroxides – ferrihydrite ( $\text{Fe}(\text{OH})_3$ ), gibbsite ( $\text{Al}(\text{OH})_3$ ), boehmite ( $\text{AlOOH}$ )
- Carbonates – calcite ( $\text{CaCO}_3$ ), dolomite ( $\text{CaMg}(\text{CO}_3)_2$ ), rhodochrosite ( $\text{MnCO}_3$ ), strontianite ( $\text{SrCO}_3$ )
- Sulphates – gypsum ( $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ ), celestite ( $\text{SrSO}_4$ )
- Fluorite ( $\text{CaF}_2$ )

Carnotite ( $\text{K}_2(\text{UO}_2)_2(\text{VO}_4)_2$ ) was found to be under-saturated in most of the solutions. Given that carnotite is present at Yeelirrie, and many of the groundwaters are likely to have contacted this mineral, uranium solubility was explored further by plotting a uranyl activity diagram (Figure 2.5).


The results plot along a trend consistent with the calculated theoretical line for carnotite, but displaced toward a lower solubility. The scatter in the results may relate to the fact that activities of other relevant species, e.g.  $\text{K}^+$  and  $\text{VO}_2^+$ , vary in individual waters.

The carnotite dissociation reaction contained in the HATCHES database is as follows:



The reaction and the equilibrium constant originated from within the EQ3/6 database, parts of which were merged with the HATCHES database in the early 1990s. The original source of the data is unknown and so it is not possible to assess either the reliability of the data, or its applicability to the Yeelirrie system.

Also shown in Figure 2.5 is a calculated theoretical line for a less soluble version of the carnotite phase (based on data contained within the MINTEQ database). The plot shows that the thermodynamic data contained in the MINTEQ database reasonably reflect the observed trend for carnotite solubility under field conditions and therefore have been adopted for any further modelling.

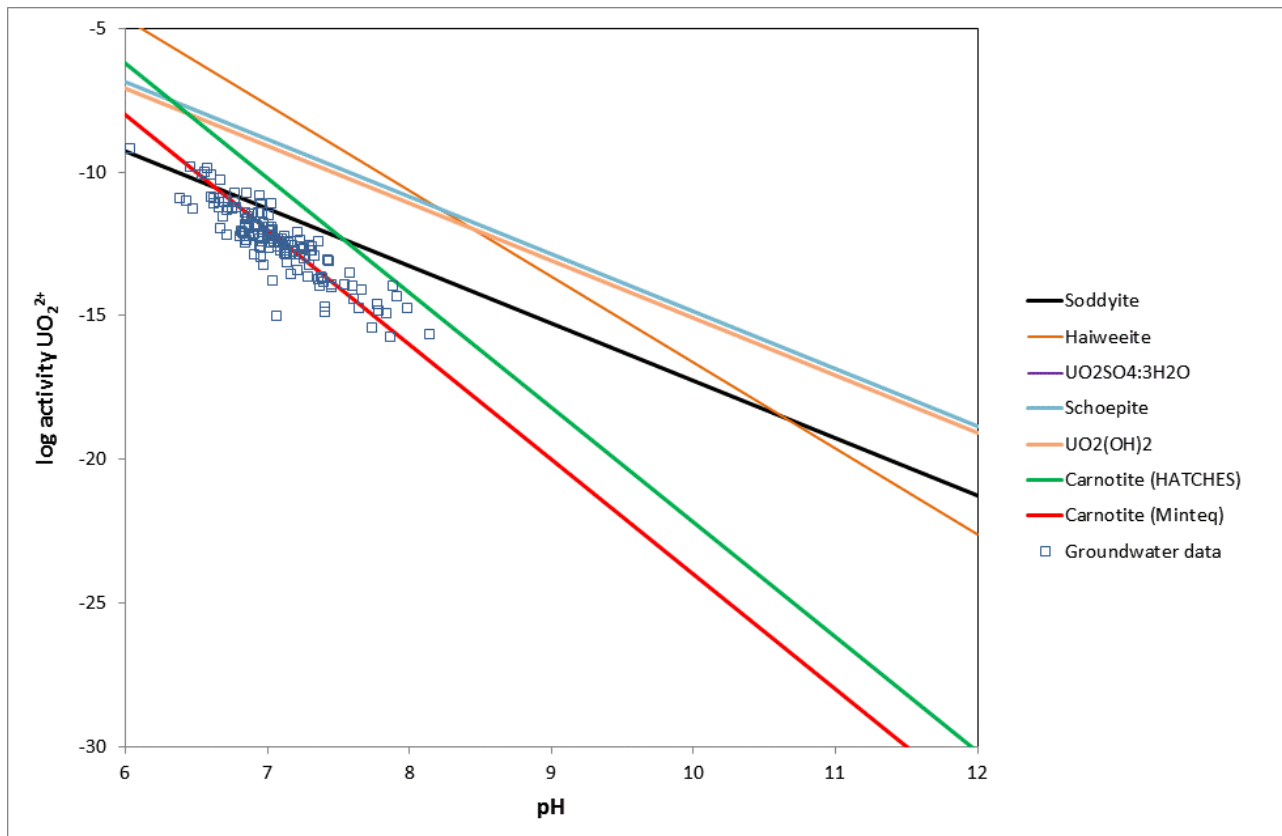

**Figure 2.5: Uranyl ( $\text{UO}_2^{2+}$ ) activity diagram showing the calculated activities of measured groundwater results**  
(Also shown are the theoretical equilibrium lines for a range of minerals)

## 2.2 Previous Mining Trials at Yeelirrie

During the 70s and 80s, various trial excavations took place at the Yeelirrie site to support investigations of possible mining strategies. The excavations provided ore material suitable for metallurgical testing. A number of stockpiles and waste piles were also constructed during this time.

In 2004, the trial sites were rehabilitated. Prior to rehabilitation activities, a series of soil pH and salinity (inferred from electrical conductivity, EC) measurements were made (Outback Ecology, 2004). Samples were obtained from pits, stockpiles, roads and undisturbed soils. Sample pH values ranged from 6.8 (alluvial plain sample) to 9.7 (calcrete sample from a road surface), with the majority of samples yielding alkaline pH values (pH greater than 8). The EC values ranged from 26 to 1913  $\mu\text{S}/\text{cm}$ . Higher EC values tended to correspond with mined materials (stockpiles and calcrete-based road surfaces) whereas lower values were recorded for natural soils from alluvial plains and calcrete platforms.

As part of the rehabilitation activities, stockpiled materials were used to backfill trial pits. Gamma radiation surveys (Fugro Spatial Solutions, 2004) took place before and after rehabilitation. Before closure, readings of up to 45  $\mu\text{S}/\text{hr}$  were obtained for stockpiled material. Surveys taken after stockpile removal typically gave readings of less than 1.5  $\mu\text{S}/\text{hr}$ . The low readings documented after removal of the stockpile suggests that there was limited or no release of radionuclides from the stockpiles during their lifetime (20 to 30 years). Soil salinity measurements however were not repeated after removal of the stockpiles. The release of other solutes from the stockpiles during this period therefore could not be determined.



## 2.3 Proposed Yeelirrie Project Development

Full details of the proposed development are given in the ERMP document (BHP, 2011). Brief summaries are given in the following sections.

### 2.3.1 Mining and Production

Tailings would be stored in mined out pits. Any residual mine waste and stockpiled materials, as well as mine infrastructure for disposal, would also be placed in mined out pits. At closure, tailings and disposal cells would be covered with mine waste and topsoil materials for final rehabilitation.

### 2.3.2 Ore Processing

Ore would be milled before subjecting it to a high temperature alkali leach using sodium carbonate/bicarbonate to dissolve the carnotite. The uranium bearing solution would be recovered in a counter current decant (CCD) system and would then be subjected to ion exchange with further processing of the concentrated solution (eluant) from the ion exchange system. Once uranium has been removed from the leachate, the final tailings could contain vanadium in excess of the stoichiometric uranium content of the source mineral (carnotite).

The barren solution discharged from the uranium ion exchange recovery circuit would be pumped to the final stage of CCD for use as wash water. The solute concentrations in this stream would also contribute to the solute loading that would be deposited with the tailings in the TSF.

### 2.3.3 Tailings Production and Storage

Tailings are expected to be produced at a solids content of about 35 % (wt). The primary disposal concept is that the tailings would be deposited sub-aerially directly in the TSF cells located in the mined out areas, utilising internal berms to contain the tailings and separate tailings deposition from mining activities.

Tailings water would be recovered from the TSF and in-pit cells throughout the life of the operation. Water recovery may occur from the tailings decant and/or an underdrainage system.

## 3. Work Programme and Methods

### 3.1 Objectives

The primary objectives of the geochemical investigation were to:

- Evaluate the chemical composition of the materials to be stockpiled on site and assess the solute loadings that may be released from these materials.
- Assess the potential for solute release from the tailings in the short and the long term.
- Determine the potential interaction between the solutes and the natural materials downstream of the mine facility.

To meet these objectives, sampling and laboratory testing programmes were developed. These programmes are described briefly in the following sections.

### 3.2 Field Programme

Samples of the mine materials were collected by others (BHPB and URS) during sonic drilling programs that took place during June and August 2009. Sonic drilling does not require use of drilling fluids or additives and so it is possible to minimise geochemical contamination during sampling.

The samples represented a range of material types from the Yeelirrie site taken at various depths (down to 30 m below ground surface) from drill cuttings for drill holes located within and downstream of the proposed mining area. A total of 199 samples were collected. Relevant drill-hole logs and field measurements are included in Appendix 1. From the 199 samples, 20 were selected for detailed geochemical characterisation and inclusion in the laboratory programme.

In addition to the site samples described above, the following samples were collected:

- Palaeochannel sand samples – two samples were collected from depths between 55 to 65 m below the Yeelirrie deposit (a reverse circulation drilling method was used).
- Pilot plant tailings and underlying sediments collected from the historic Kalgoorlie tailings storage facility - 41 samples were collected during sonic drilling of the facility).

The selected samples were submitted for testing and analysis as summarised below.

### 3.3 Laboratory Programme

A full description of the laboratory programme is given in Appendix 2. The programme was undertaken by Amdel, supported by Labmark and Minchem/Petroleum, and included the following testing procedures:

- Bottle roll tests. Tailings, soil and rock samples were contacted with solution (either de-ionised water or 'barren liquor' solution) for 72 hours. The tests were undertaken at a liquid:solid ratio of 3:1. For the majority of tests, the headspace in the bottles was occupied by air. For selected samples, tests were conducted with the bottle headspace filled by a mixture of CO<sub>2</sub> (10v%) and air.
- Column tests. Four column pairs have been set up to operate in series. The first column in each pair is open to air and operated such that the material drains down and becomes unsaturated between flushing events. The second column is not open to air and is maintained saturated with solution at all times. Effluent from the first column is used as inflow for the second column in that pair.
- Aging tests (tailings). Fresh tailings slurries were placed in open and sealed flasks, to represent atmospheric as well as anoxic conditions respectively. Series of replicate flasks were prepared so that after 1, 2, 4 and 8 months of contact time, selected flasks could be disturbed and the pore water recovered for analysis.

Changes in solution chemistry during the tests described above allow quantification of any contaminant leaching or attenuation that may have taken place.

To support the laboratory program, drill core and tailings samples were submitted for:

- Chemical assays (acid digestion followed by ICP) to determine the elemental composition of samples (conducted by Labmark).
- Mineralogical investigation (X-ray diffraction) (conducted by CSIRO, via BHP).
- Mineral surface characterisation (BET surface area, cation exchange capacity) to support the assessment of potential sorption mechanisms (conducted by Particle and Surface Sciences Pty Ltd and Australian Laboratory Services, respectively).
- Radiological investigation (analysis of radionuclide composition of solids and porewaters) to determine key radionuclide concentrations (conducted by Australian Nuclear Science and Technology Organisation).

### 3.4 Geochemical Modelling

Geochemical speciation modelling was undertaken to support interpretation of the results and observed trends on the test outcomes. All calculations were undertaken using PHREEQC Interactive, Version 2.12.5.669 (Parkhurst and Appelo, 1999). Unless otherwise indicated, the thermodynamic data used were those contained in the HATCHES thermodynamic database, NEA v18 (Bond *et al.*, 1997). As discussed before, thermodynamic data from the MINTEQ database were adopted for modelling carnotite.

## 4. Yeelirrie Rocks and Soils

### 4.1 Introduction

The sampling programme targeted material representative of all the lithological units defined at the site, distributed spatially to capture lateral variability. An assessment of the geochemical database indicated that in general the bulk chemistry of the lithological units were independent of the material classification (as ore or waste), and that the ore is distinguished primarily by uranium and vanadium content. Therefore, with the exception of uranium and vanadium, the material classified as ore would be very similar to a material classified as waste within any given lithological unit. As a result, in this section, the discussion of the geochemical properties and static leach extraction testing is arranged as follows:

- **Ore and Waste Materials** represented by samples of material from within the orebody and mining void. Sample locations were selected to be within and below the ore body. Most samples had low uranium contents and are classed as waste. Waste materials, after being stored in surface facilities, would be used to construct TSF embankments and the TSF cover. Some samples contain relatively high uranium contents and are classed as ore. Ultimately, ores would be processed, but may be subject to temporary storage on the surface. The objectives for testing these sample materials were to define their geochemical characteristics, and assess the potential for solute release during storage (by undertaking bottle roll tests involving de-ionised water).
- **Material Underlying and Adjacent to the TSF** represented by samples of materials located below the ore body and adjacent (downstream) of the TSF, i.e., materials that might lie along possible flow paths for TSF seepage. Most of the samples are from relatively deep locations (the clay-quartz unit and the palaeochannel sands), but some samples from near-surface units are included to cover the possibility that some seepage might flow away laterally from the TSF. The objectives for testing these materials were to define their geochemical characteristics, and examine potential interactions with TSF-derived seepage. TSF 'seepage' chemistry was approximated by using barren liquor solutions in the testwork (bottle roll tests). Along potential flow paths from the TSF, it would be expected that water-rock interactions would result in change to seepage chemistry. Use of unaltered barren liquor in the testwork is an approximation only, allowing examination of possible interactions that might take place.

Because the column testing included assessment of potential interaction of leachates from one type of material with another, the column testing as well as implication of solute chemistry were discussed next as follows:

- **Column Testwork** - column tests were operated as pairs, with effluent from the first column being used as influent for the other. The materials selected were representative of ore and waste (first column in the pair), and materials along possible seepage flow paths (second column in the pair). Results from the columns were used to assess leaching and attenuation behaviour under geochemical conditions that differed from those of the bottle roll tests (e.g. lower solution-to-solid ratios, longer solution contact times etc.).
- **Radionuclide Distribution and Behaviour** including analytical results for solid samples and selected solutions from testwork. Daughter/parent activity ratios in the solids were used to infer if preferential leaching or accumulation of radionuclides had taken place in situ at the Yeelirrie site.
- **Geochemical Controls** includes assessments of solubility controls and sorption using geochemical modelling techniques. Sorption was examined by processing all available results to generate sorption coefficients. The effects of geochemical conditions on sorption are discussed.

### 4.2 Ore and Waste Materials

#### 4.2.1 Mineralogy

The mineralogical compositions of the Yeelirrie ore and waste materials selected for testing are given in Table 4.1. Carbonate minerals form an important constituent of the loams, calcrete and transitional lithologies. Calcite is present in the near surface, whilst dolomite is present at greater depth.

Clays are abundant in all the samples. The clay mineralogy varies with depth. Kaolin is more abundant at greater depth (transitional and clay-quartz lithologies) and is also significant in the near surface (hardpan and some loams). Smectite is the more abundant clay in most near-surface loam samples. Other clay minerals present include palygorskite (accompanies kaolin in the clay-quartz lithology) and small quantities of illite/mica and sepiolite.

Quartz is most abundant in samples from greater depths (e.g. samples from the transitional and clay-quartz lithologies).

Minor minerals identified include oxides (goethite, anatase), sulphates (gypsum), carnotite and halite.

#### 4.2.2 Surface Characteristics

The surface areas measured for the Yeelirrie samples are shown in Table 4.2, and range from 24.6 m<sup>2</sup>/g to 114.4 m<sup>2</sup>/g. There is no obvious correlation between surface area and mineralogical composition.

The cation exchange capacity ranges from 6.4 to 53.7 meq/100g. There is a positive correlation between exchange capacity and smectite content. Smectite is a swelling clay; spacing between the aluminosilicate sheets can increase to accommodate a greater degree of exchange. In contrast, kaolin does not have swelling capacity and therefore has a more limited exchange capacity.

In most loam and carbonaceous samples, the dominant cation occupying exchange sites is Ca. However, Mg is the dominant cation in the hard pan sample.

#### 4.2.3 Particle Size Distribution

Particle size distributions are provided in Appendix 7. All samples exhibited at least a tri-modal particle size distribution. The samples showed an abundance of particles in the approximate sizes ranges, 1-5µm, 10-20µm, and 60-70µm. A fourth peak (five of the seven samples) corresponded to a coarser grain-size (200-300µm).

#### 4.2.4 Bulk Chemistry

The results for the bulk chemical analyses of the samples are contained in Appendix 3. Selected results are provided in Table 4.3. As would be anticipated, the U<sub>3</sub>O<sub>8</sub> contents were consistently elevated when compared to the mean crustal abundance. Sulphate contents also tended to be high compared to mean crustal abundance. Other elements were present at levels both above and below mean crustal abundances.

The bulk chemistry results for samples from each of the lithological units were compared to the results contained within the BHP Billiton chemical assay database (Appendix 3). In most cases, the chemistry of the samples lay within the range of values recorded in the main database for each lithological category. The samples selected for testing were therefore considered to be representative of the lithological units.

Table 4.1: Mineralogical Composition of Yeelirrie Ore and Waste (wt%)

Sample	Lithology	Carbonates		Framework and chain silicates			Sheet silicates and clays					Oxides		Other		
		Calcite	Dolomite	Quartz	Albite	Microcline	Kaolin	Smectite <sup>[1]</sup>	Illite / Mica	Sepiolite	Palygorskite	Anatase	Goethite	Gypsum	Carnotite	Halite
YYS166 0.4-0.5 m	H			57	1	11	31									
YYS165 1.5-1.6 m	HT	43		7		2	14	27	1		6					
YYS156A 3-4 m	LT	1	54	2	1	1	13	22	1	4	?1	<1		0.1		
YYS156A 1.5-2.5 m	LT	6	24	8	<1	2	6	38		7				9	<0.1	<1
YYS164 4.3-4.4 m <sup>[2]</sup>	LT	<1		34	2	7	50	5	2			<1				
YYS158 3.75-4.5 m	T	2	82	1	1			6		8						
YYS158 3.5-3.75 m	T	3	76	2	1			7		10					<1	
YYS157 3.65-4.1 m	TCQ	45	3	19		3	17	9	1	?3					<1	
YYS162 4.5-4.6 m	TCQ	1		60	3	12	6	17	1							
YYS159 4.5-5.2 m	TCQ/CQT	1	1	38	1	6	41	7	2	?3		<1				
YYS156A 12-12.75 m <sup>[2]</sup>	CQ			30	2	5	39				21	<1	2		<1	

Notes:

? denotes uncertainty in mineral identification.

- [1] Smectite includes all montmorillonite group clays (montmorillonite, beidellite, nontronite, saponite, etc). The term montmorillonite was used in earlier mineralogical studies (Section 2.1). It is not known whether the term was being used to infer the montmorillonite clay group, or a specific member within this group.
- [2] Note that these samples are also mentioned in the following section (Section 4.3 Materials Underlying and Adjacent to the TSF). Treating some samples within both categories allowed study of water -rock interactions for an individual sample under a wider range of geochemical conditions (e.g. de-ionised water and barren liquor contact tests). It also allowed for possible future change in the definition of the ore body, both in terms of lateral extent and depth.

**Table 4.2: Surface Characteristics of the Yeelirrie Ore and Waste Rock**

Sample	Lithology	BET surface area, m <sup>2</sup> /g	Cation exchange capacity, meq/100g	Exchangeable cations,(meq/100g) (grey shading = dominant cation)			
				Ca	Mg	K	Na
YYS166 0.4-0.5 m	H	24.6	6.4	1.2	3.3	1.2	0.7
YYS156A 1.5-2.5 m	LT	82.8	53.7	44.6	6	1.8	1.3
YYS158 3.75-4.5 m	T	68.5	28.4	14.7	12.4	0.7	0.6
YYS157 3.65-4.1 m	TCQ	96.1	36.5	26.2	5.4	2.7	2.2
YYS159 4.5-5.2 m	TCQ/CQT	114.4	23.4	11.1	5.7	3.3	3.3
YYS156A 12-12.75 m	CQ	41.9	18.5	10.8	3.6	2.3	1.8

Table 4.3: Bulk Chemistry of Ore and Waste Rock Samples

Major elements		Al	Ca	CO <sub>2</sub>	F	Fe	K	Mg	Mn	Na	S	Si	SO <sub>4</sub>			
Sample #	Material type	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)			
Average crustal abundance <sup>[1]</sup>		8.2	4.1			4.1	2.1	2.3	0.095	2.3			0.078			
YYS166 0.4 - 0.5 m	H	5.63	0.05	0.4	0.01	2.31	1.36	0.35	0.03	0.2	0.03	36.1	0.4			
YYS165 1.5 - 1.6 m	HT	2.54	14.3	17.4	0.33	1.11	0.59	5.85	<0.01	0.13	0.08	18	0.3			
YYS156A 3-4 m	LT (ore)	3.81	11.2	23	0.46	1.55	0.7	9.93	<0.01	0.45	<0.01	13.2	0.1			
YYS156A 1.5-2.5 m	LT (ore)	2.63	8.3	11.5	0.75	1.23	0.63	9.51	0.01	0.67	2.05	17.9	3			
YYS164 4.3-4.4 m	LT	8.44	0.17	0.2	0.1	3.38	1.53	1.08	0.02	0.54	0.1	29.3	0.1			
YYS158 3.75-4.5 m	T	0.22	17.4	37.6	0.42	0.16	0.11	12.2	<0.01	0.25	0.03	5.86	<0.05			
YYS158 3.5-3.75 m	T	0.13	16.8	34.6	0.59	0.1	0.12	12.4	<0.01	0.36	0.01	7.98	0.15			
YYS157 3.65-4.1 m	TCQ	3.6	15.6	18.5	0.17	1.67	0.65	3.01	0.02	0.21	0.03	18.1	0.15			
YYS162 4.5-4.6 m	TCQ	2.9	0.61	0.8	0.21	0.99	1.49	2.33	<0.01	0.57	0.04	37	0.15			
YYS159 4.5-5.2 m	TCQ/CQT	7.19	0.98	1.5	0.19	3.03	1.41	2.28	0.1	0.35	0.01	29.8	<0.05			
YYS156A 12-12.75 m	CQ	8.75	0.14	0.2	0.07	3.44	1.43	1.64	0.02	0.67	0.09	29.1	0.2			
Minor elements		As	Ba	Cd	Co	Cr	Cu	Mo	Ni	Pb	Sr	Th	Tl	U <sub>3</sub> O <sub>8</sub>	V	Zn
Sample #	Material type	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
Average crustal abundance <sup>[1]</sup>		1.5	500	0.11	20	100	50	1.5	80	14	370		0.6	2.8	160	75
YYS166 0.4 - 0.5 m	H	3	415	<0.1	9.5	70	20	3.4	12	9.5	50	10	<3	15	45	17.5
YYS165 1.5 - 1.6 m	HT	5	125	<0.1	3.4	40	13	0.6	13	4.5	290	5	<3	165	35	18
YYS156A 3-4 m	LT (ore)	9.5	40	<0.1	4	45	20.5	2.8	12	6.5	430	10	<3	1100	245	34.5
YYS156A 1.5-2.5 m	LT (ore)	8.5	75	<0.1	4	45	17.5	2.4	11	7	355	5	<3	700	165	700
YYS164 4.3-4.4 m	LT	3	285	<0.1	6.5	115	19.5	2.2	15	13	65	15	<3	15	60	29.5
YYS158 3.75-4.5 m	T	0.5	50	<0.1	0.6	<20	4	1.1	5	1	600	<4	<3	150	75	27
YYS158 3.5-3.75 m	T	1	20	<0.1	0.6	<20	7	1.9	5	1	550	<4	<3	55	50	265
YYS157 3.65-4.1 m	TCQ	3.5	100	<0.1	4.4	50	18.5	2	14	5.5	280	10	<3	140	60	46.5
YYS162 4.5-4.6 m	TCQ	3	315	<0.1	2.8	45	8	2.1	7	3.5	75	5	<3	45	65	14
YYS159 4.5-5.2 m	TCQ/CQT	8.5	295	<0.1	10.5	80	29.5	4.5	17	9.5	80	15	<3	10	120	85
YYS156A 12-12.75 m	CQ	13.5	220	<0.1	4.6	80	19.5	6.5	13	12.5	50	20	<3	65	145	125

Notes:

[1] Mean crustal abundances taken from Bowen 1979.



#### 4.2.5 Solute Release (De-Ionised Water Extractions)

Samples were contacted with de-ionised water in roll bottle and column tests. The bottle roll tests were undertaken at a liquid:solid ratio of 3:1. Generally, the headspace in the bottles open to the atmosphere. However, for selected samples, the headspace was purged and filled with a mixture of CO<sub>2</sub> (10v%) and air. Results from bottle roll tests are documented in Appendix 4.

A summary of the test results is provided in Table 4.4. The summary includes the results from eleven different samples (covering a range of lithological types) and the two imposed atmospheric conditions (air, and a mixture of CO<sub>2</sub> (10v%) and air). The results also include measurements made from progressive (sequential) leach tests. In these tests, following the first bottle roll test, the solution is removed and replaced with distilled water for each of a second and third stage conducted (at the same 3:1 water:rock ratio).

For some elements (silver, bismuth, cobalt, mercury, lead, antimony) the dissolved concentrations at the end of the tests were invariably below the limits of detection. Comparatively, dissolved concentrations measured for boron, strontium, uranium and vanadium were elevated, with maximum concentrations in excess of 500 µg/L. Dissolved concentrations of barium, molybdenum, thallium and zinc were generally above detection limits, with maximum concentrations in excess of 100 µg/L. For many elements, dissolved concentrations were variable. The variability reflects differences in:

- The characteristics of the solid material, e.g. lithology, mineralogy, bulk chemistry
- Solution conditions, e.g. pH, dissolved carbonate

When compared to the groundwater quality monitoring results presented in Table 2.2, the concentrations of most solutes are lower in the leach tests. These results suggest that the solute release is occurring mostly from salinity that would have been present in the porewater of the samples.

**Table 4.4: Summary of Solute Concentrations in De-ionised Water Extractions of Ore and Waste Rock Samples**

(Bottle Roll Tests at 3:1 Water:Rock Ratio)

Parameter	Units	Detection Limit <sup>[1]</sup>	Number of Assays (n)	Dissolved Concentration				
				Min	P5	Median	P95	Max
pH	pH Units	0.01	44	7.3	7.5	8.4	9.2	10.0
Eh	mV	1	44	331	348	421	486	510
EC	µS/cm	5	44	120	260	1105	7428	8890
Acidity	CaCO <sub>3</sub> (mg/L)	20	42	<20	<20	<20	<20	50
Alkalinity	CaCO <sub>3</sub> (mg/L)	1	42	24	49	174	996	1300
Br	mg/L	0.5	44	<0.5	<0.5	<0.5	5	11
Cl	mg/L	0.5	44	2	7	100	1200	1700
F	mg/L	0.5	44	<0.5	<0.5	2	4	5
TOC	mg/L	1, 5	43	1.0	1.2	5	40	200
NO <sub>2</sub>	mg N/L	0.02, 0.5	44	<0.02	<0.1	<0.5	1.7	2.2
NO <sub>3</sub>	mg N/L	0.1, 0.5	42	<0.1	<0.1	1.6	49	95
SO <sub>4</sub>	mg/L	0.5	44	2.8	5.0	63	2040	3200
Al	µg/L	5	44	<5	<5	26	95	680
Ca	µg/L	100	44	<100	500	9800	641700	694000
Fe	µg/L	50, 100	44	<50	<100	<100	109	560
Mg	µg/L	100	44	500	500	13200	170100	237000
P	µg/L	100	44	<100	<100	<100	<1000	2300
K	µg/L	1000	44	3500	12090	29950	201500	211000
Na	µg/L	100	44	13000	27750	137500	1028500	1110000
Si	µg/L	100	44	2970	3595	18000	45700	78000
As	µg/L	5	44	<5	<5	6	28	48
B	µg/L	5	44	110	186	710	4195	4900
Ba	µg/L	0.02, 5	44	<0.02	<5.0	17	74	160
Be	µg/L	1, 5	44	<1	<5	<5	<5	20
Cd	µg/L	0.2, 5	44	<0.2	<5	<5	10	27
Cr	µg/L	5	44	<5	<5	<5	15	37
Cu	µg/L	5	44	<5	<5	<5	12	20
Li	µg/L	5	44	<5	<5	<5	<5	11
Mn	µg/L	5	44	<5	<5	<5	38	53
Mo	µg/L	5	44	<5	<5	29	157	390
Ni	µg/L	1, 5	44	<1	<5	<5	15	17
Se	µg/L	1, 5	44	<1	<5	<5	23	28
Sn	µg/L	5	44	<5	<5	<5	7	24
Sr	µg/L	5	44	<5	7	195	4795	6000
Tl	µg/L	5	44	<5	<5	35	283	360
U	µg/L	5	44	<5	<5	86	1765	2100
V	µg/L	5	44	7	10	81	493	600
Zn	µg/L	5	44	47	69	115	160	200

Notes:


TOC=total organic carbon.

[1] Where more than one detection limit is given, the detection limit reported by the laboratory changed during the programme.

[2] The following constituents were consistently below detection: NH<sub>3</sub>, Ag, Bi, Co, Hg, Pb, Sb.

#### 4.2.5.1 Progressive (Sequential) Leach Tests

For most elements, concentrations in the contact solution decreased for consecutive leaching steps. The highest concentrations were observed for the first step, as shown for example by the sodium concentrations detected in the various stages. The results for sodium are shown in Figure 4.1 which show the depletion of leachable sodium from the samples. The figure also illustrates the variability between the various lithological types, but clearly also shows significant variability between the results for two samples from the same unit. For example, the first of the two TCQ samples yielded a sodium concentration in excess of 600,000 µg/L and the second less than 200,000 µg/L. This variability suggests that the wide range of solute release loadings could be expected to occur from the waste materials, even within the same lithological unit.

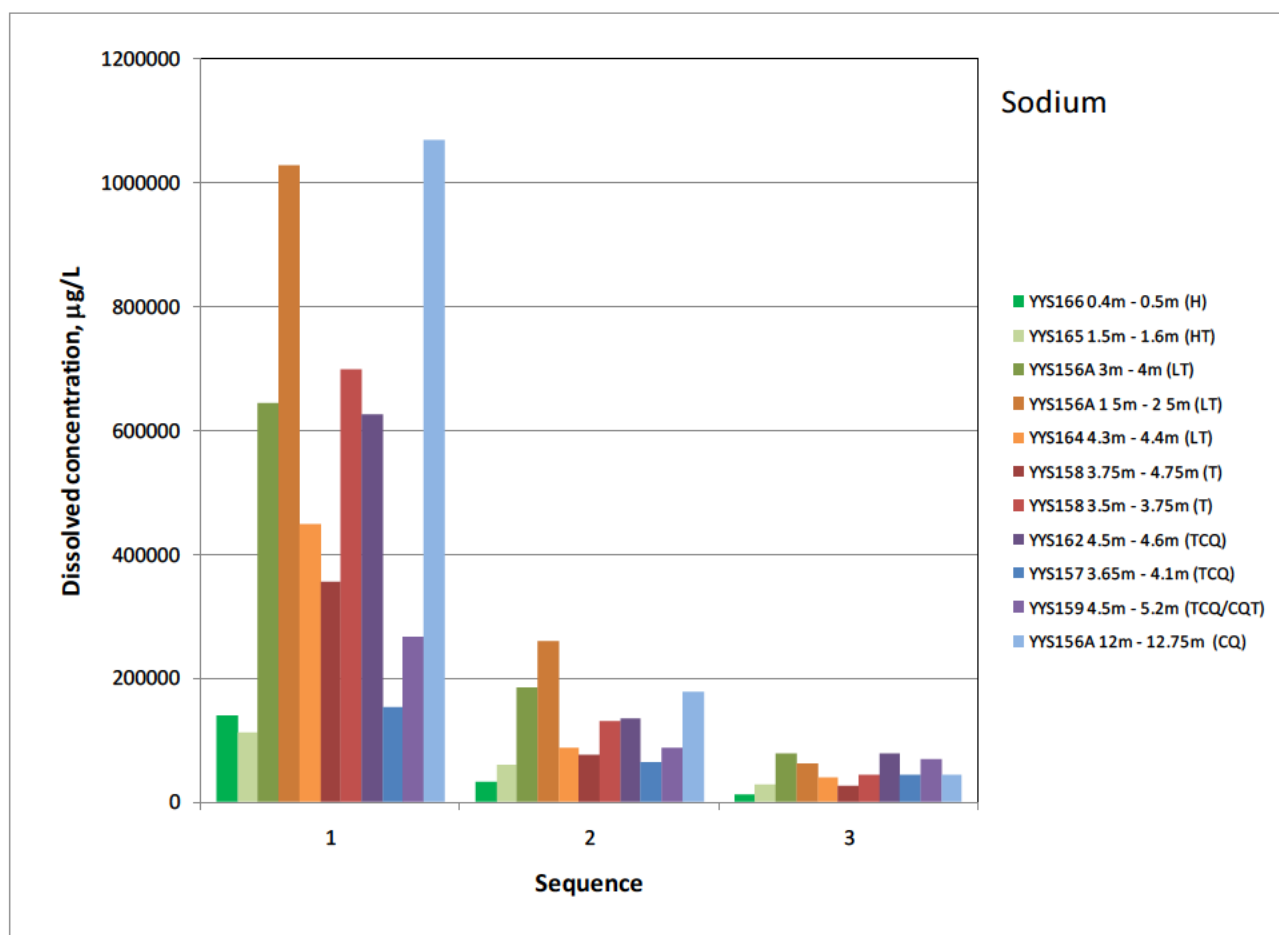

**Figure 4.1: Dissolved sodium concentrations in leachates after three consecutive leach tests (3:1 liquid:solid ratio, air atmosphere)**

In contrast to the more soluble salts, uranium, vanadium and thallium leaching do not appear to follow the general trend, as shown in Figure 4.2, Figure 4.3 and Figure 4.4, respectively. The results are variable for these elements. Dissolved uranium and vanadium concentrations often remain relatively constant for the three stages, which may suggest either a solubility constraint or that the dissolution rate is kinetically controlled.

In the case of thallium, occasionally, the concentrations in the second stage of the sequence are greater than that of the first stage, by a factor of up to 10. These results suggest that the higher concentrations of other solutes present during the first stage may limit the release of thallium, whereas in the later stages, when these solutes have largely been removed from the system, thallium leaches more readily.

Possible geochemical controls are discussed in more detail later (Section 4.5).

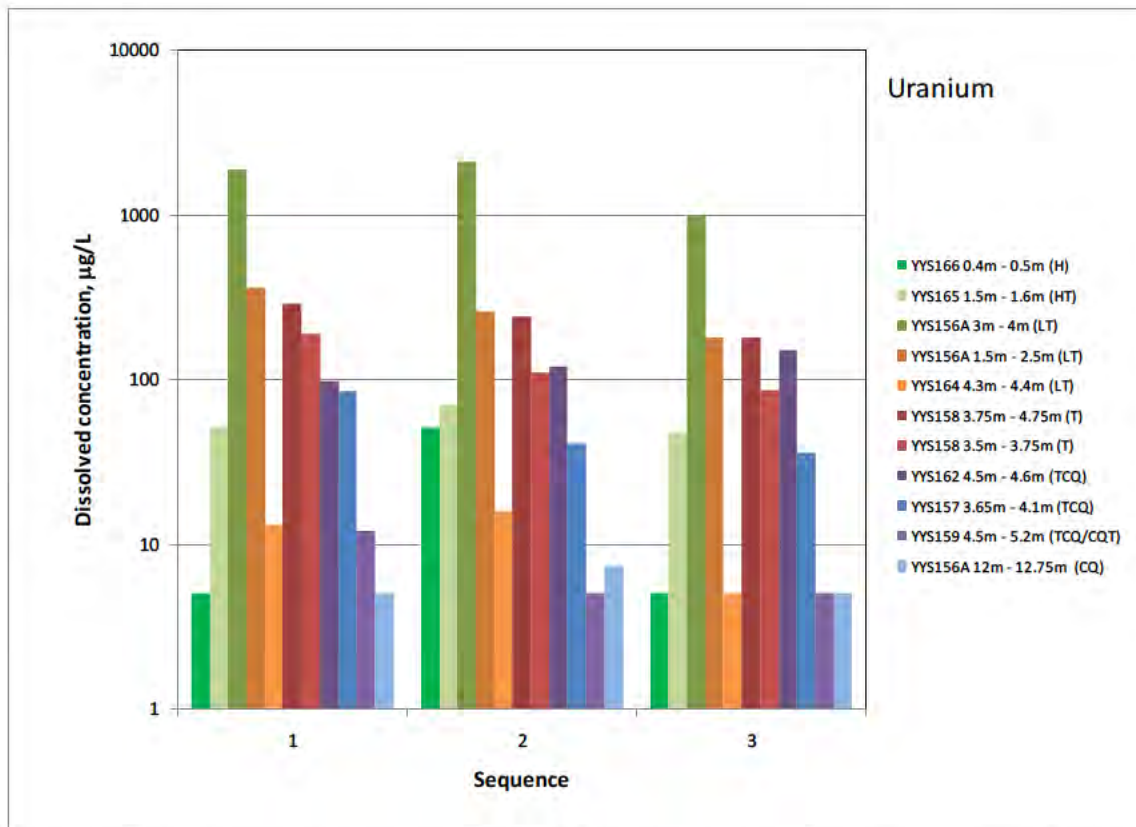


Figure 4.2: Dissolved uranium concentrations in leachates after three consecutive leach tests (3:1 liquid:solid ratio, air atmosphere)


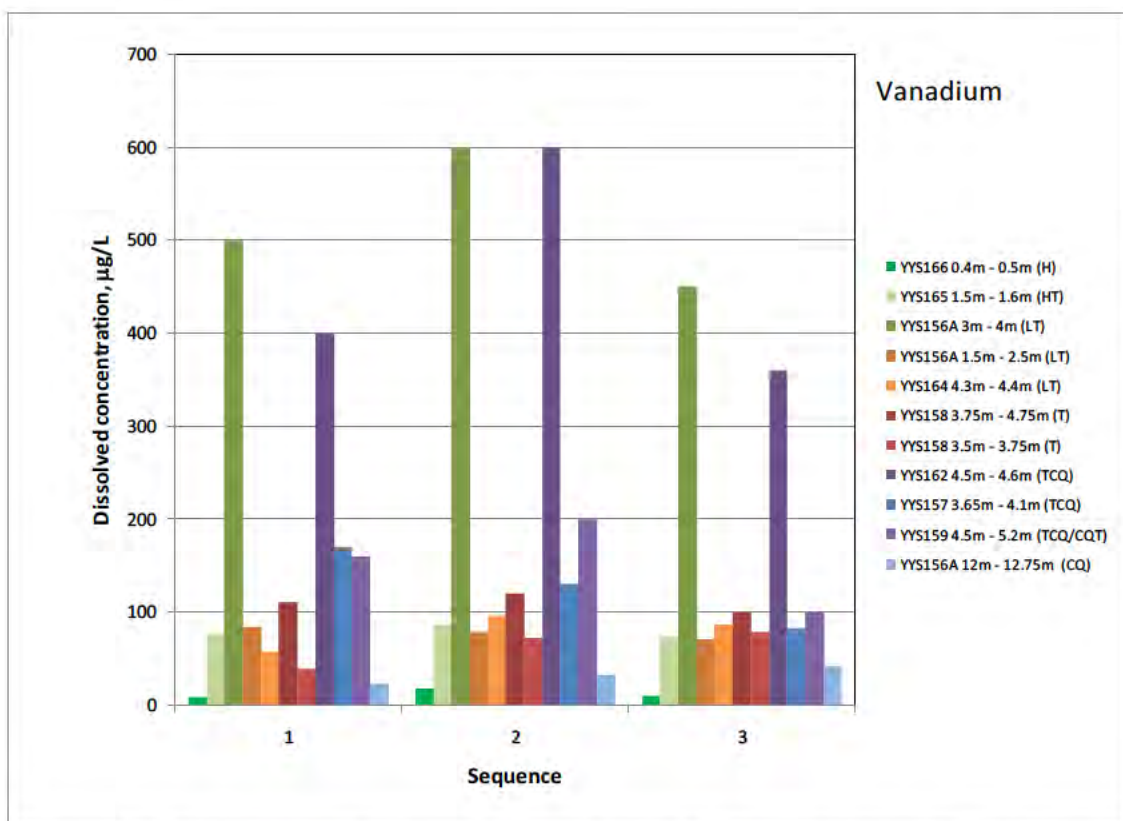


Figure 4.3: Dissolved vanadium concentrations in leachates after three consecutive leach tests (3:1 liquid:solid ratio, air atmosphere)

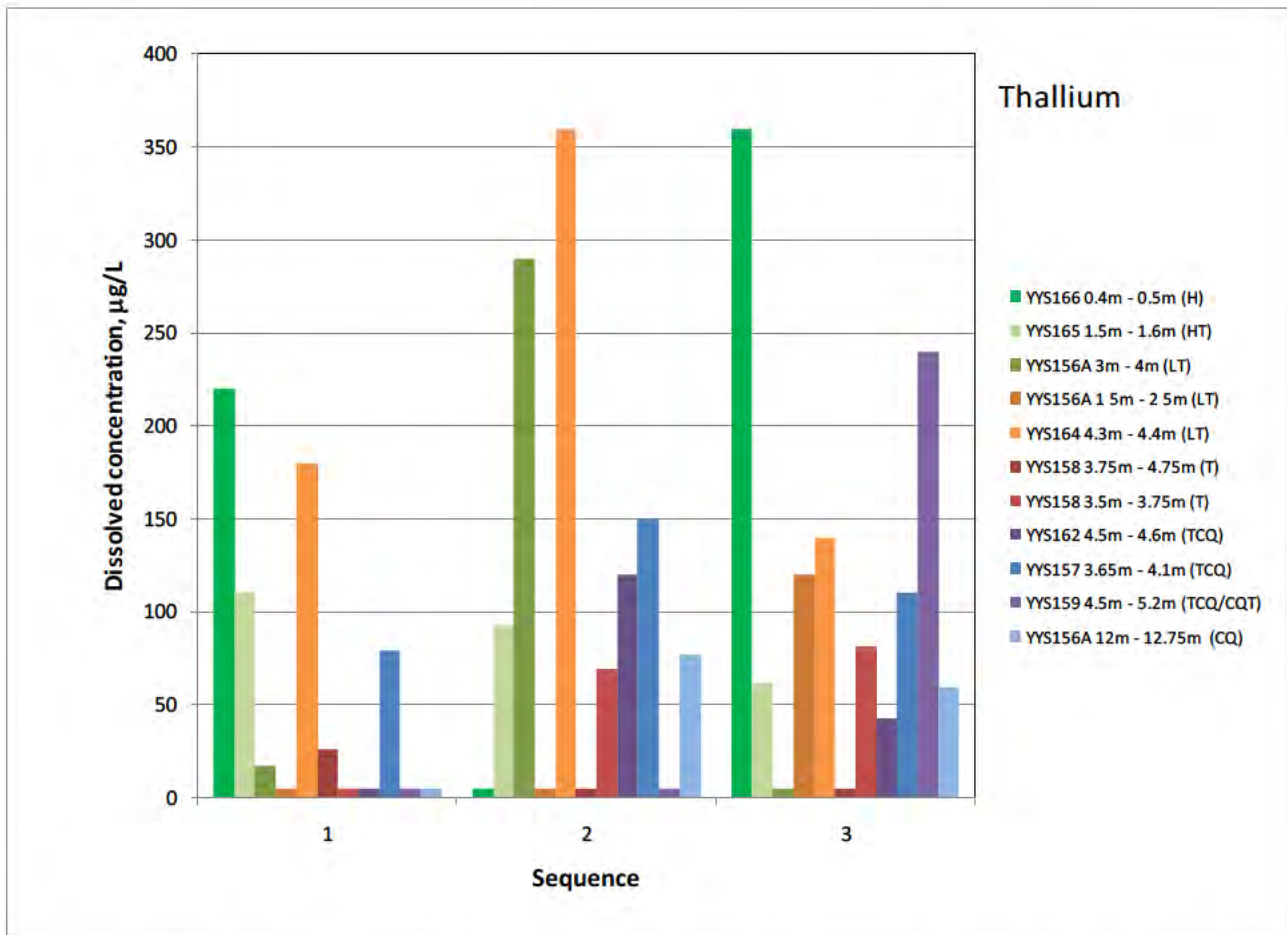


**Figure 4.4: Dissolved thallium concentrations in leachates after three consecutive leach tests (3:1 liquid:solid ratio, air atmosphere)**

4.2.5.2 Effect of Lithological Type

Figure 4.5 shows the sodium, potassium, calcium and magnesium concentrations leached from the different samples. The figure is arranged so that near-surface materials (hardpan, loams) are to the left hand side, and deeper materials (clay-quartz) are to the right. Calcrete and transitional material are in the centre.

As noted before, high concentrations of Na (more than 600,000µg/L) leached from several of the samples, indicative of residual salt present in the samples. Mineralogical characterisation recorded the presence of halite in some of these samples (Table 4.1). The calcium concentration for the loam sample, YY156A - 1.5-2.5 m, is consistent with the presence of high quantities of gypsum in this sample (9 wt%, Table 4.1). Consistent with gypsum dissolution, an elevated concentration sulphate was also recorded for this test.

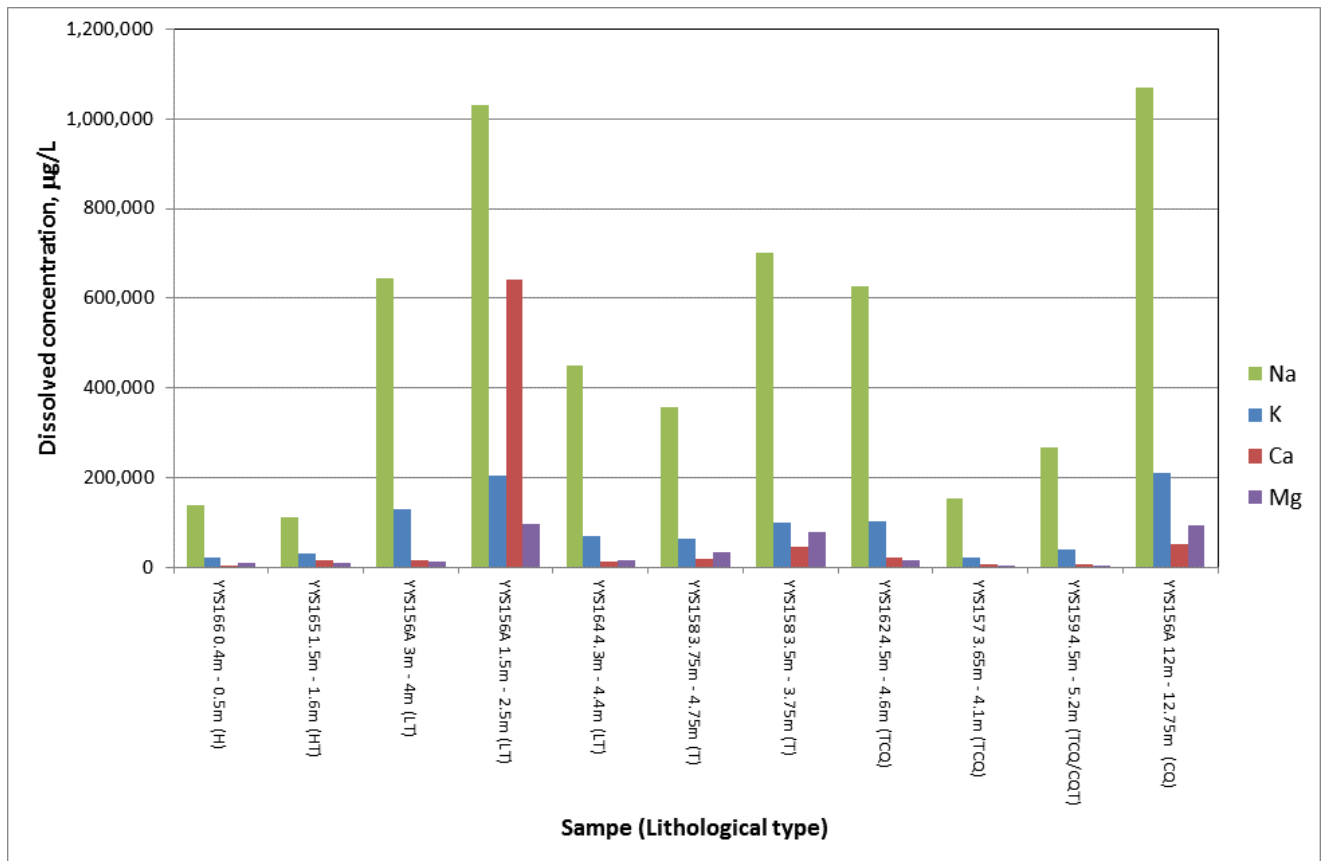

**Figure 4.5: Na, K, Ca and Mg leaching from different lithological sample types**  
(3:1 liquid:solid ratio, sequence 1 results, air atmosphere)

Figure 4.6 shows uranium, vanadium, strontium and barium leaching from the different samples. Highest uranium and vanadium concentrations were measured for the loam, calcrete and transitional samples, probably reflecting the distribution of carnotite mineralisation in the materials. The mineralogical assessment (XRD investigation) identified the presence of carnotite in two of these samples: YYS156A 1.5-2.5 m (LT) and YYS156A 3-4 m (LT).

Strontium and barium may be considered analogues for radium behaviour. Notably, the highest strontium and barium concentrations coincide with the sample that had a high calcium concentration (YY156A 1.5-2.5 m), attributed to the dissolution of gypsum. It is possible that barium and strontium are present as impurities in gypsum.

Figure 4.7 shows molybdenum, zinc, thallium and boron leaching from the different samples. The highest molybdenum and boron concentrations were observed for a clay-quartz sample (YYS156A 12-12.75 m). Otherwise, leaching of these elements is quite variable and does not appear to correlate with lithological type. The same appears to be true for thallium. Zinc leaching is relatively constant for all the samples, with a factor of approximately two between the highest and lowest dissolved zinc concentrations, as shown in the figure.

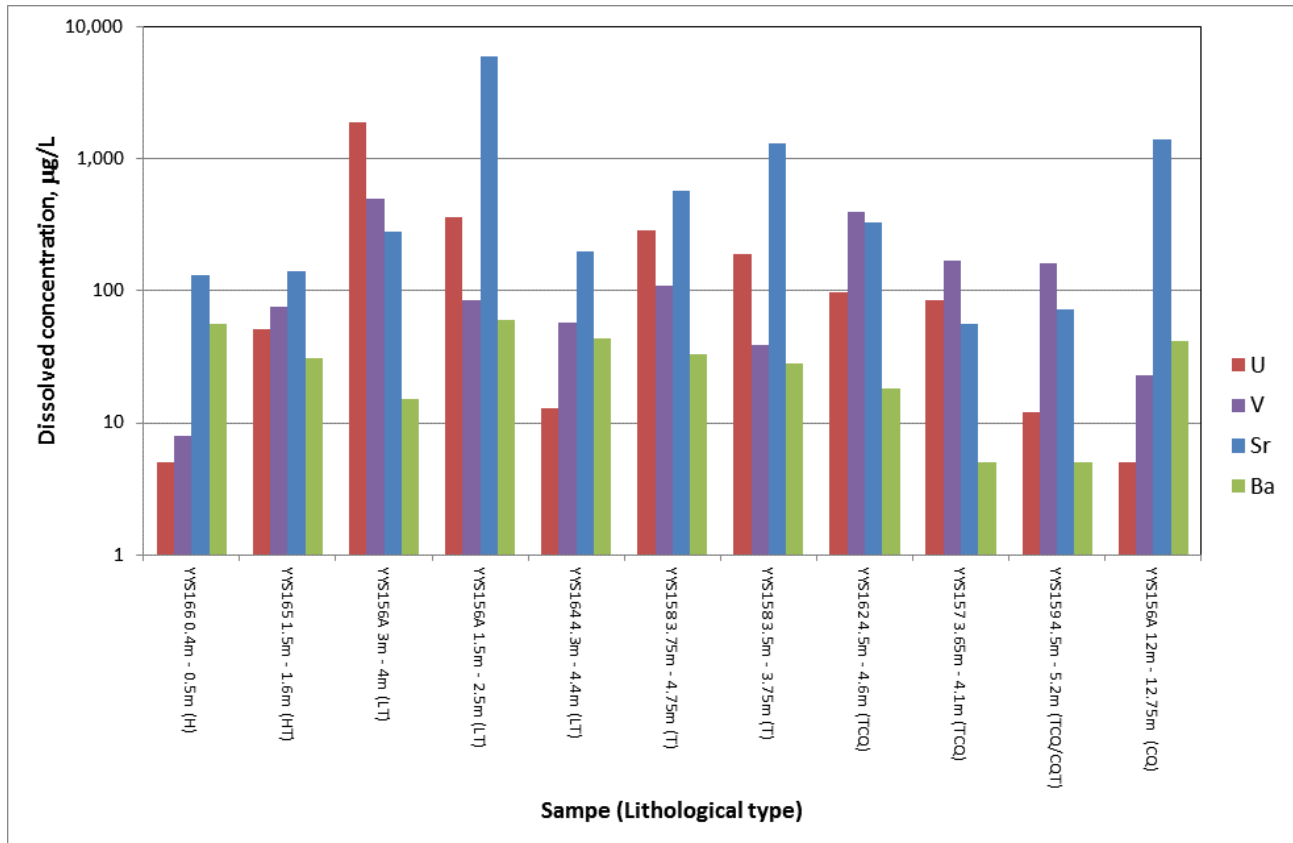


Figure 4.6: U, V, Sr and Ba leaching from different lithological sample types (3:1 liquid:solid ratio, sequence 1 results, air atmosphere)

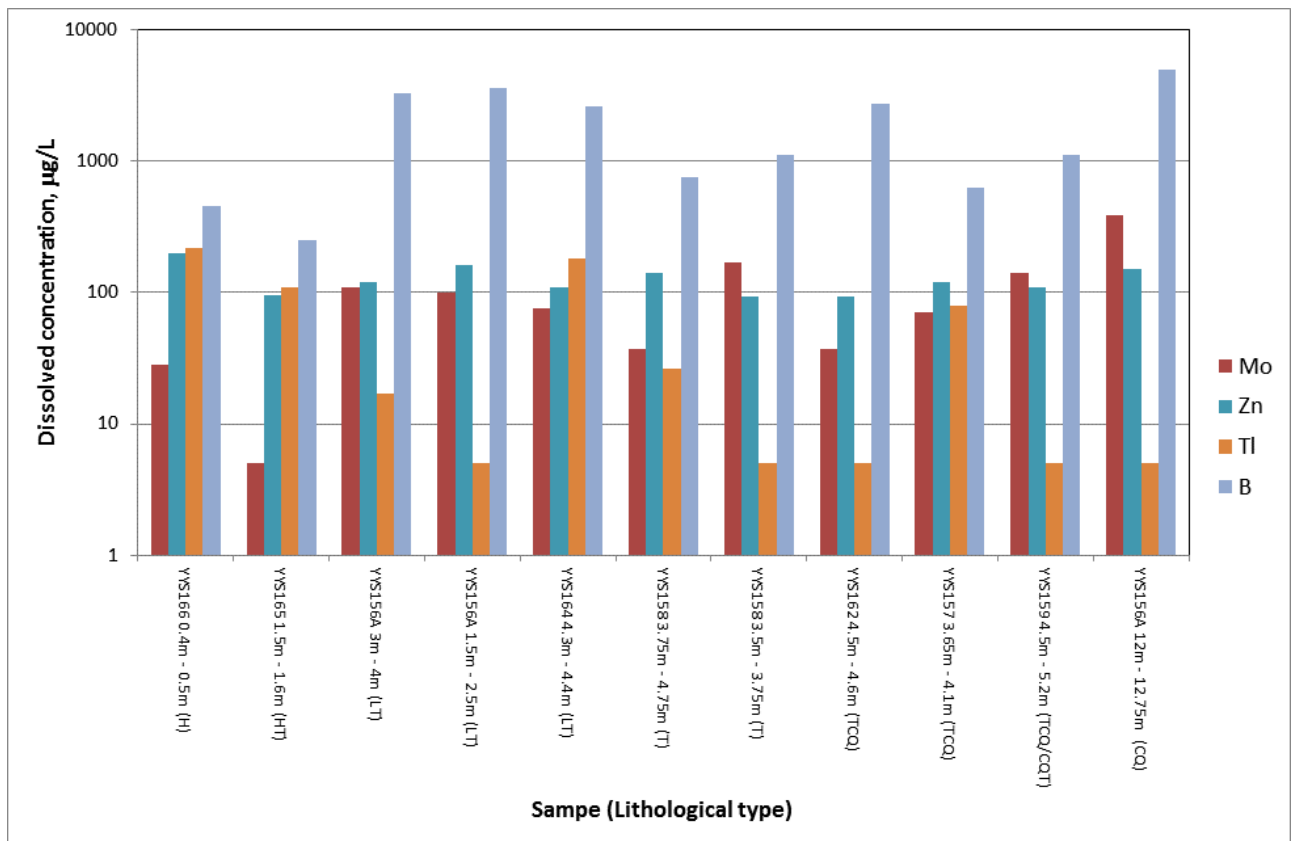


Figure 4.7: Mo, Zn, Tl and B leaching from different lithological sample types (3:1 liquid:solid ratio, sequence 1 results, air atmosphere)

4.2.5.3 Correlation Between Bulk Chemistry and Leachability

For most of the elements, the amount leached did not correlate with the mass of that element present in the sample (from bulk chemical analysis results). Exceptions were sodium (chloride by default) and uranium. Both these elements showed a positive correlation between mass leached and the bulk elemental content in the sample, Figure 4.8 and Figure 4.9, respectively.


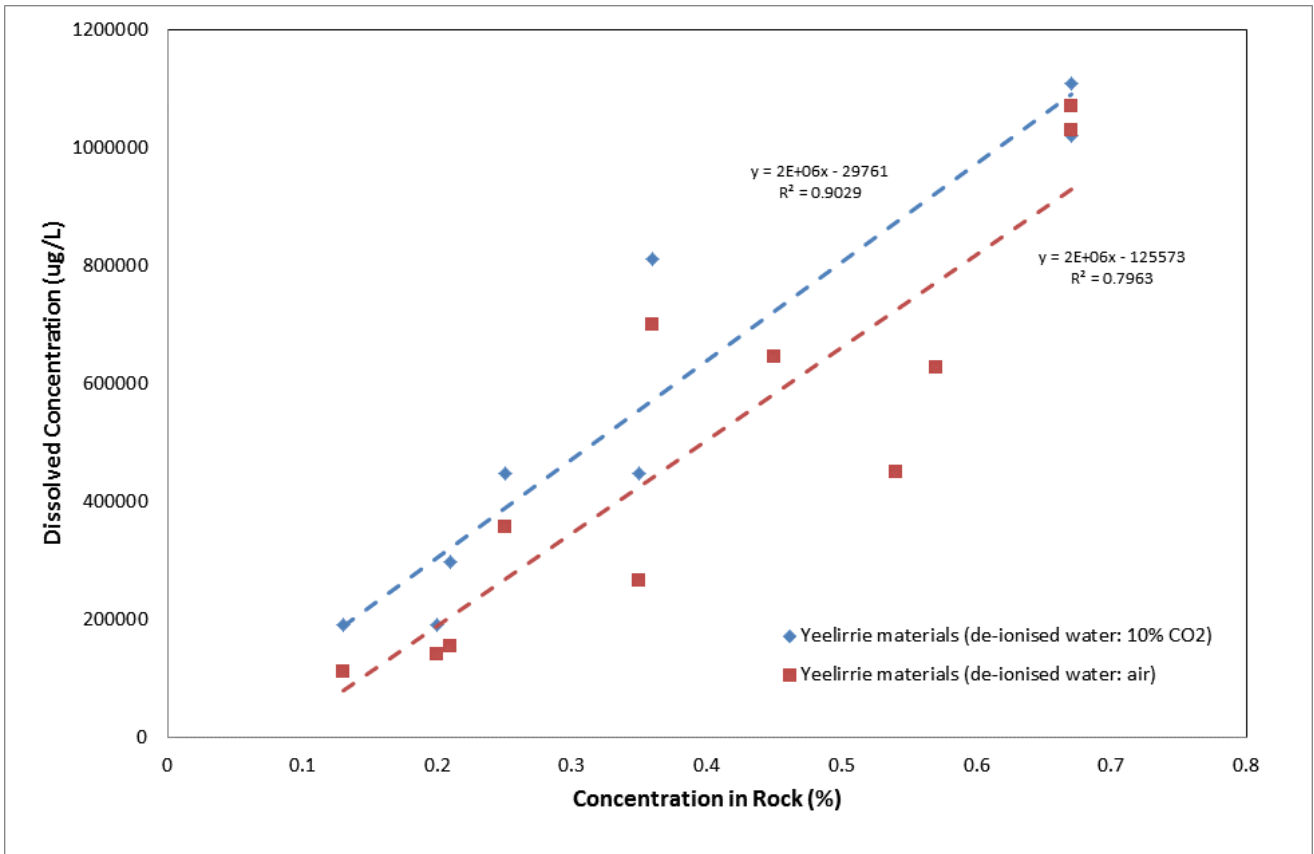


Figure 4.8: Dissolved sodium concentration plotted as a function of sodium content in the solid (3:1 liquid:solid ratio)




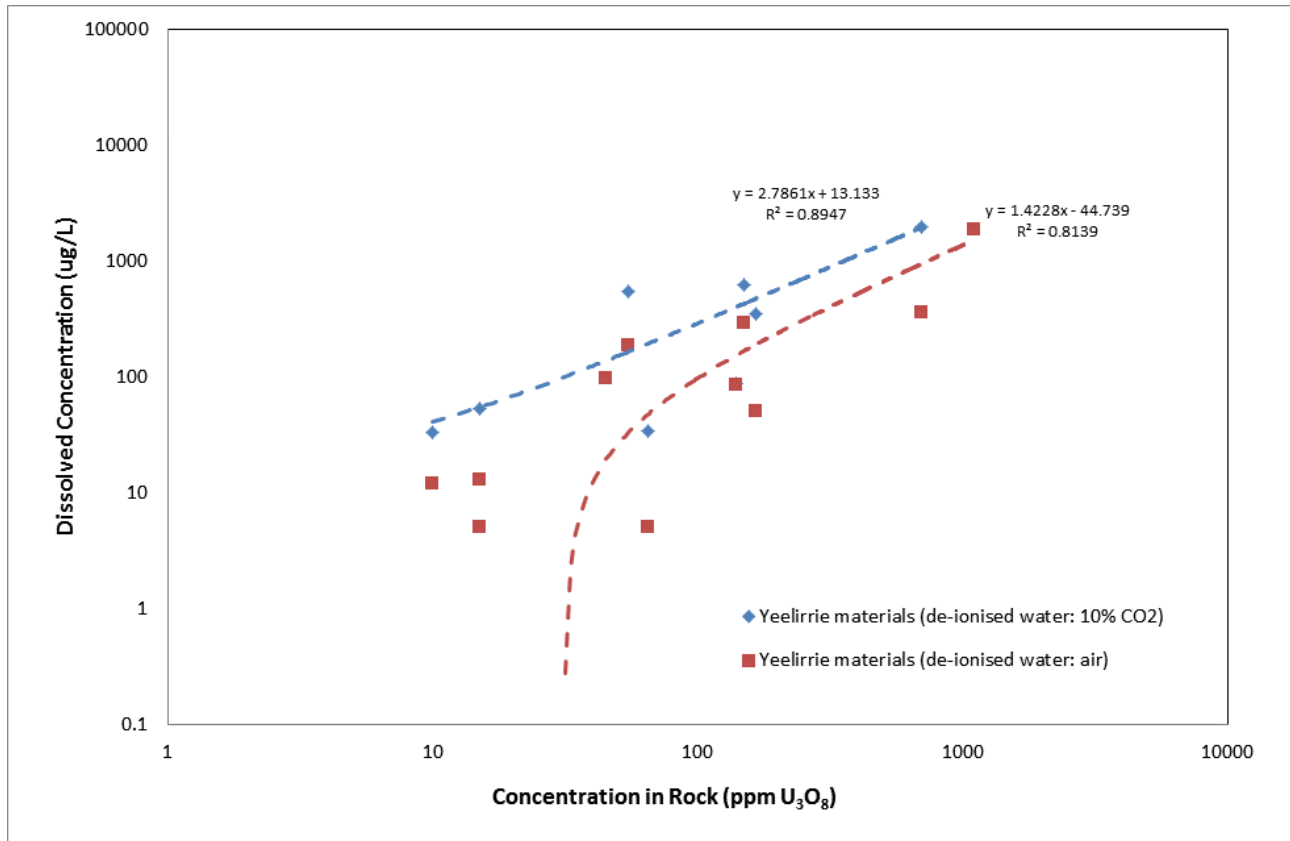


**Figure 4.9: Dissolved uranium concentration plotted as a function of uranium content in the solid**  
 (Note logarithmic scale on Y-axis; 3:1 liquid:solid ratio)

4.2.5.4 Effect of Solution Conditions

Solution pH is known to have a strong effect on the geochemical behaviour of many elements. However, because only a small range of pH values (pH 7 to 10) were observed, the effect of pH on solute concentrations was relatively small. Furthermore, pH effects were also likely masked by variability in other test parameters, e.g. lithology. As examples, Figure 4.10 and Figure 4.11 show dissolved uranium and vanadium concentrations plotted as a function of solution pH. There is a lot of scatter in the results but in general the highest solution concentrations coincide with higher pH values. This observation is discussed further in Section 4.5.

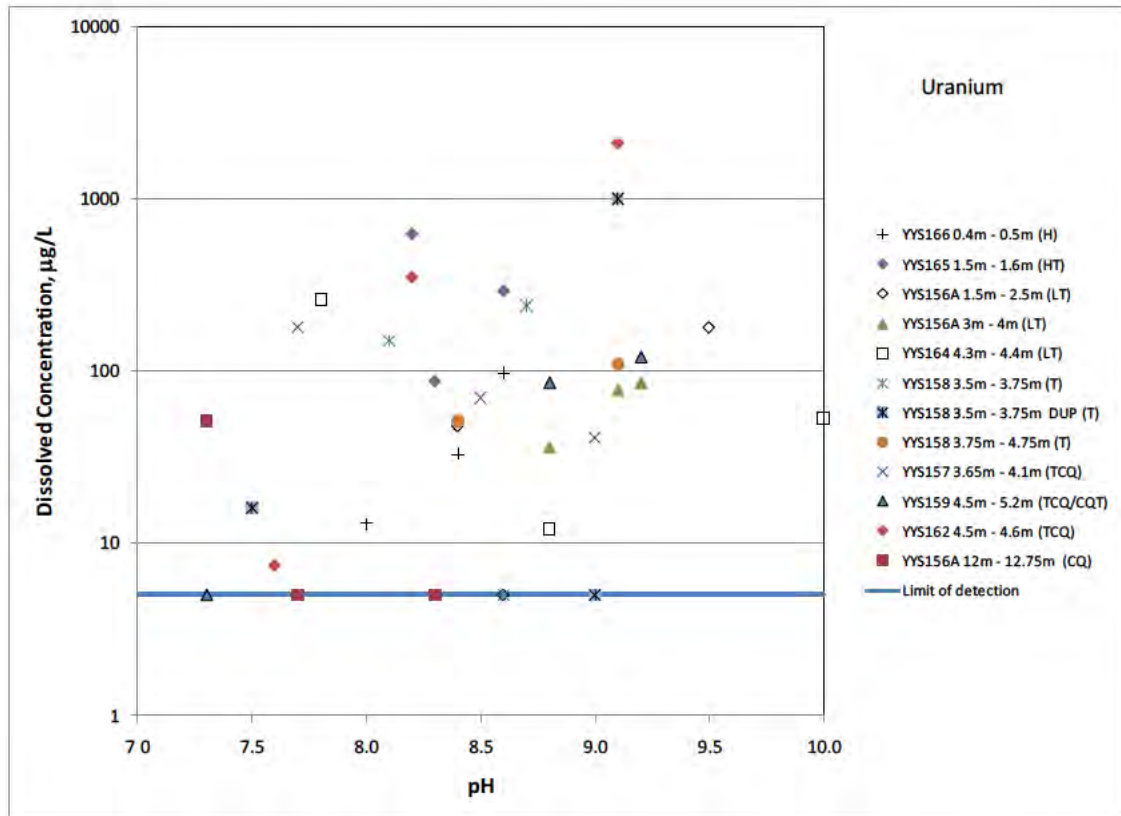


**Figure 4.10: Dissolved uranium concentration plotted as a function of solution pH (3:1 liquid:solid ratio, air atmosphere)**

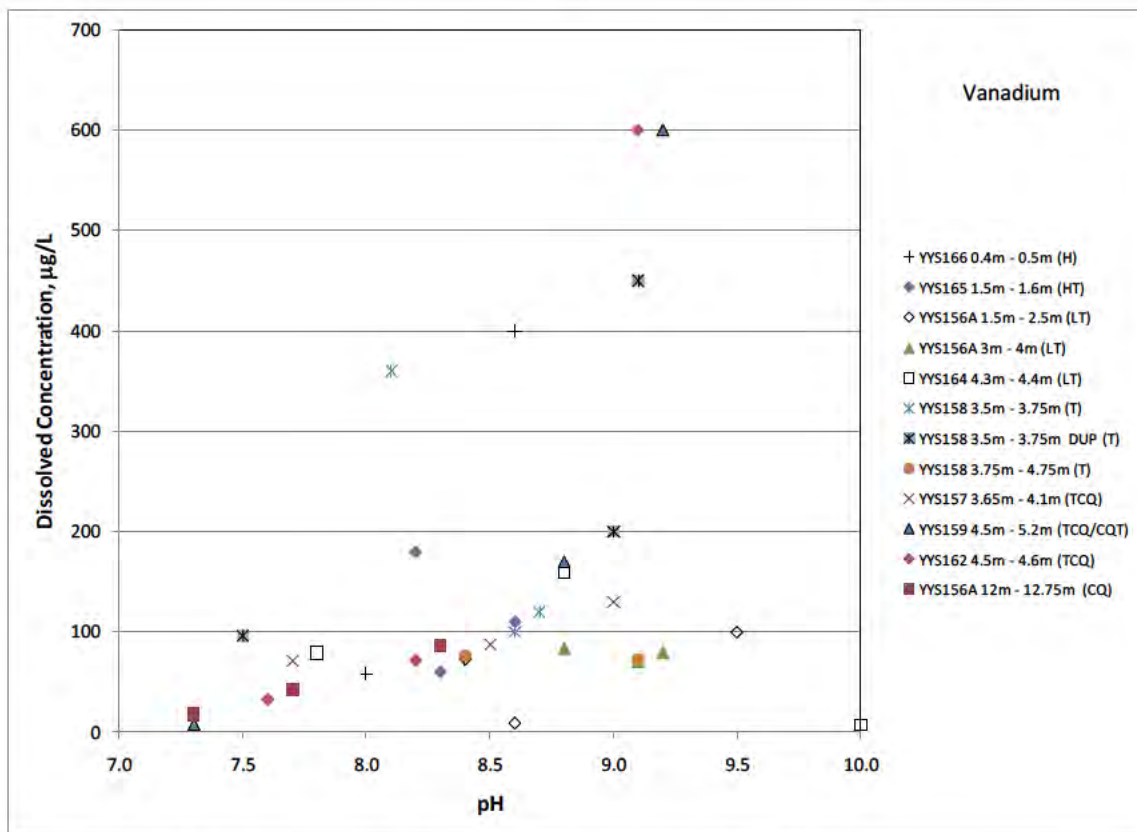

**Figure 4.11: Dissolved vanadium concentration plotted as a function of solution pH (3:1 liquid:solid ratio, air atmosphere)**

The presence of a 10% CO<sub>2</sub>:air mixture resulted in a significantly higher dissolved carbonate concentration when compared to tests in air (measured alkalinities were 3 and 50 times higher). For some elements, there is a clear trend towards higher dissolved concentrations for solutions containing higher dissolved CO<sub>2</sub>. Uranium concentrations were as much as an order of magnitude higher in the presence of higher dissolved carbonate (Figure 4.12). The concentrations of strontium, barium and some transition metals also increased in the presence of excess CO<sub>2</sub>. The higher dissolved concentrations likely reflect the role of effects such as (i) the formation of aqueous carbonate complexes and (ii) increased solubility of carbonate minerals.

Geochemical controls are discussed further in Section 4.5.

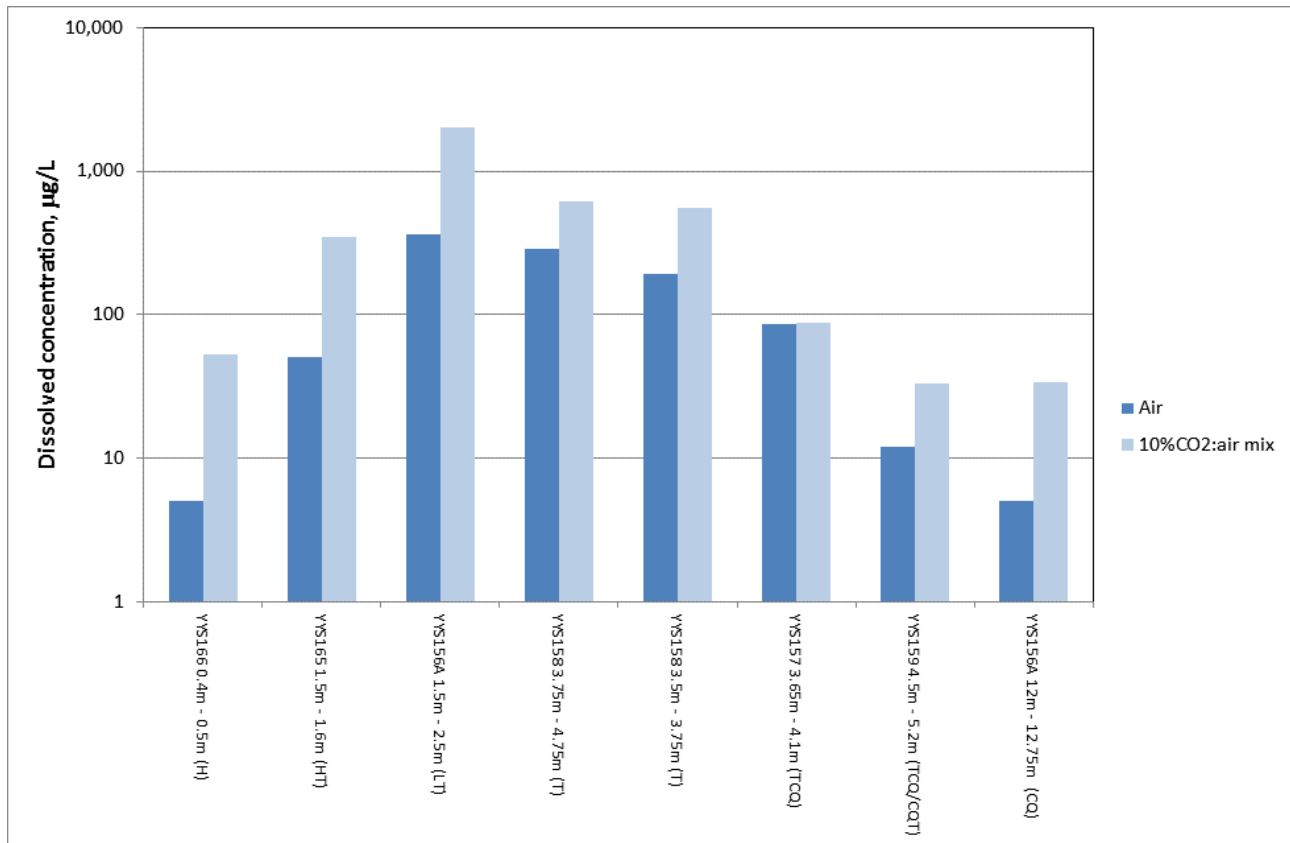

**Figure 4.12: Effect of higher dissolved carbonate on dissolved uranium concentrations**  
 (Note logarithmic scale on Y-axis; leachant is de-ionised water, 3:1 liquid:solid ratio)

## 4.3 Materials Underlying and Adjacent to the TSF

### 4.3.1 Mineralogy

The mineralogical compositions of materials underlying or adjacent to the proposed TSF are given in Table 4.5. Carbonate minerals form an important constituent of the loams. Both calcite and dolomite are present. In one loam sample, YYS167 2.3-2.4 m, Mg-rich calcite was identified.

Clays are abundant in all the samples. The clay mineralogy varies with depth. Kaolin is more abundant at greater depth (clay-quartz lithologies) and is also significant in the near surface (loams). Smectite is the more abundant clay in most near-surface loam samples. Other clay minerals present include palygorskite (accompanies kaolin in the clay-quartz lithology) and small quantities of illite/mica and sepiolite.

Quartz is most abundant in samples from greater depths (e.g. samples from the clay-quartz lithology and the palaeochannel sands).

Minor minerals identified include oxides (goethite, anatase), sulphates (gypsum) and halite. The presence of halite in the deeper clay-quartz samples may reflect a post-sampling artefact. Residual pore water in these samples may have been saline. During sample drying, it could be expected that residual salts might form.

### 4.3.2 Surface Characterisation

The surface areas measured are shown in Table 4.6, and range from 3.3 m<sup>2</sup>/g to 81.9 m<sup>2</sup>/g. There is no obvious correlation between surface area and mineralogical composition.

The cation exchange capacity ranges from 3.3 to 248 meq/100g. There is a positive correlation between exchange capacity and smectite content. Smectite is a swelling clay; spacing between the aluminosilicate sheets can increase to accommodate a greater degree of exchange. In contrast, kaolin does not have swelling capacity and therefore has a more limited exchange capacity. Kaolin is however known to be a strong adsorbent.

In loam samples and the palaeochannel sands, the dominant cation occupying exchange sites is Ca. Mg is the dominant cation for samples from the clay-quartz lithologies.

### 4.3.3 Particle Size Distribution

Particle size distributions are provided in Appendix 7. All samples exhibited at least a tri-modal particle size distribution. The samples showed an abundance of particles in the approximate sizes ranges, 1-5µm, 10-20µm, and 60-70µm. A fourth peak (five of the seven samples) corresponded to a coarser grain-size (200-300µm).

### 4.3.4 Bulk Chemistry

The results for the bulk chemical analyses of the samples are contained in Appendix 3. Selected results are provided in Table 4.7. The U<sub>3</sub>O<sub>8</sub> contents were consistently elevated when compared to the mean crustal abundance. Other constituents that tended to be high compared to mean crustal abundance were sulphate and arsenic. Remaining elements were present at levels both above and below mean crustal abundances.

The bulk chemistry results for samples from each of the lithological units were compared to the results contained within the BHP Billiton chemical assay database (Appendix 3). In most cases, the chemistry of the samples lay within the range of values recorded in the main database for each lithological category. The samples selected for testing were therefore considered to be representative of the lithological units.

Table 4.5: Mineralogical Composition of Materials Underlying and Adjacent to the TSF (wt%)

Sample	Lithology	Carbonates			Framework and chain silicates			Sheet silicates and clays					Oxides		Other		
		Calcite	Mg-Calcite	Dolomite	Quartz	Albite	Microcline	Kaolin	Smectite <sup>[1]</sup>	Illite / Mica	Sepiolite	Palygorskite	Anatase	Goethite	Gypsum	Carnotite	Halite
YYS156A 0.7-1.5 m	L/LT	39			6		2	6	28						19		<1
YYS167 2.3-2.4 m	LQT	23	8	3	23	2	5	22	12	2							
YYS158 2.5-3.5 m	LT	8		63	7	1	1		7		13						
YYS164 4.3-4.4 m <sup>[2]</sup>	LT	<1			34	2	7	50	5	2			<1				
YYS164 5.2-5.3 m	CQT	<1		<1	37	2	8	44	4	2		?3	<1				
YYS156A 12-12.75 m <sup>[2]</sup>	CQ				30	2	5	39				21	<1	2			<1
YYS156A 11.25-12 m	CQ				28	2	6	48	3	2		8	<1	2			<1
YYS163 23-23.1 m	CQ				22	1	4	61		3		9	<1				
YYS165 6.6-6.7 m	CQ				63	2	8	21	3	1		?2					
YYS167 23-23.1 m	CQ				55	1	5	31	4	2		?2	<1				
YYS164 26.2-26.3 m	CQ				61	2	12	24		1							
YYHC0059C 55-56 m	Palaeochannel Sand				91			9					<1				
YYHC0075 64-65 m	Palaeochannel Sand				91			9					<1				

## Notes:

? = denotes uncertainty in mineral identification.

[1] Smectite includes all montmorillonite group clays (montmorillonite, beidellite, nontronite, saponite, etc). The term montmorillonite was used in earlier mineralogical studies (Section 2.1). It is not known whether the term was being used to infer the montmorillonite clay group, or a specific member within this group.

[2] Note that these samples are also mentioned in the preceding section (Section 4.2, Ore and Waste Materials). Treating some samples within both categories allowed study of water-rock interactions for an individual sample under a wider range of geochemical conditions (e.g. de-ionised water and barren liquor contact tests). It also allowed for possible future change in the definition of the ore body, both in terms of lateral extent and depth.

**Table 4.6: Surface Characteristics of the Materials Underlying and Adjacent to the TSF**

Sample	Lithology	BET surface area, m <sup>2</sup> /g	Cation exchange capacity, meq/100g	Exchangeable cations, (meq/100g) (grey shading = dominant cation)			
				Ca	Mg	K	Na
YYS156A 0.7-1.5 m	L/LT	72.9	248	242	3.7	1.1	0.5
YYS158 2.5-3.5 m	LT	81.9	24.9	16.6	6	1	1.3
YYS164 5.2-5.3 m	CQT	76.0	20.6	5.2	7.5	4.1	3.8
YYS156A 12-12.75 m	CQ	41.9	18.5	10.8	3.6	2.3	1.8
YYS156A 11.25-12 m	CQ	63.0	12.6	4	4.6	2.8	1.2
YYS167 23-23.1 m	CQ	31.0	7.0	0.8	2.9	2	1.3
YYHC0059C 55-56 m	Palaeochannel Sand	3.3	3.3	1.4	0.7	0.2	0.9

Table 4.7: Bulk Chemistry of Materials Underlying and Adjacent to the TSF

Major elements		Al	Ca	CO <sub>2</sub>	F	Fe	K	Mg	Mn	Na	S	Si	SO <sub>4</sub>
Sample #	Material type	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)
Average crustal abundance <sup>[1]</sup>		8.2	4.1			4.1	2.1	2.3	0.095	2.3			0.078
YYS156A 0.7-1.5 m	L/LT	2.06	16.8	14.2	0.44	0.98	0.47	5.77	<0.01	0.49	4.49	11.6	6
YYS167 2.3 - 2.4 m	LQT	4.63	12.2	15.4	0.13	1.98	1.12	2.96	0.01	0.36	0.07	20.3	<0.05
YYS158 2.5-3.5 m	LT	0.37	15.7	31.5	0.54	0.2	0.19	11.4	<0.01	0.35	0.04	10.8	0.1
YYS164 4.3-4.4 m	LT	8.44	0.17	0.2	0.1	3.38	1.53	1.08	0.02	0.54	0.1	29.3	0.1
YYS164 5.2-5.3 m	CQT	8.39	0.24	0.5	0.05	3.22	1.71	1.29	0.03	0.4	0.03	30.7	<0.05
YYS156A 12-12.75 m	CQ	8.75	0.14	0.2	0.07	3.44	1.43	1.64	0.02	0.67	0.09	29.1	0.2
YYS156A 11.25-12 m	CQ	9.48	0.14	0.2	0.08	4.11	1.66	1	0.02	0.64	0.07	27.4	0.1
YYS163 23 -23.1 m	CQ	10.8	0.08	0.1	0.09	4.06	2.08	1.66	0.02	0.54	0.11	25.9	0.4
YYS165 6.6-6.7 m	CQ	4.32	0.09	0.1	0.13	1.93	1.19	1.16	0.03	0.32	0.03	36.8	0.05
YYS167 23 - 23.1 m	CQ	6.25	0.05	0.1	0.05	2.4	1	0.52	0.01	0.35	0.06	35.1	0.1
YYS164 26.2-26.3 m	CQ	4.88	0.04	<0.07	0.02	1.6	1.4	0.22	<0.01	0.32	0.04	37.8	<0.05
YYHC0075	Palaeo. sands	1.23	0.11	0.2	0.01	0.68	0.1	0.05	<0.01	0.16	0.06	41.8	0.05
YYHC0059C	Palaeo. sands	1.35	0.05	0.2	0.02	0.67	0.09	0.09	<0.01	0.51	0.09	41.4	0.1

Minor elements		As	Ba	Cd	Co	Cr	Cu	Mo	Ni	Pb	Sr	Th	Tl	U <sub>3</sub> O <sub>8</sub>	V	Zn
Sample #	Material type	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
Average crustal abundance <sup>[1]</sup>		1.5	500	0.11	20	100	50	1.5	80	14	370		0.6	2.8	160	75
YYS156A 0.7-1.5 m	L/LT	11.5	60	<0.1	3	30	11.5	1.4	11	5	700	5	<3	235	85	18
YYS167 2.3 - 2.4 m	LQT	5	320	<0.1	4.8	55	17	1.7	16	7.5	450	5	<3	160	60	25
YYS158 2.5-3.5 m	LT	1.5	40	<0.1	0.8	<20	10	0.9	5	1.5	500	<4	<3	195	60	145
YYS164 4.3-4.4 m	LT	3	285	<0.1	6.5	115	19.5	2.2	15	13	65	15	<3	15	60	29.5
YYS164 5.2-5.3 m	CQT	4	290	<0.1	6.5	85	22	1.9	14	10.5	60	15	<3	20	60	37.5
YYS156A 12-12.75 m	CQ	13.5	220	<0.1	4.6	80	19.5	6.5	13	12.5	50	20	<3	65	145	125
YYS156A 11.25-12 m	CQ	21.5	250	<0.1	6	95	30.5	8	15	16.5	55	25	<3	70	175	46
YYS163 23 -23.1 m	CQ	3	205	<0.1	8	100	31	1.5	20	14	1000	30	<3	15	65	38.5
YYS165 6.6-6.7 m	CQ	5	335	<0.1	7	70	14	2.2	10	7.5	45	10	<3	10	50	21
YYS167 23 - 23.1 m	CQ	2	290	<0.1	2.4	70	11	2.1	9	8	30	20	<3	15	40	15
YYS164 26.2-26.3 m	CQ	4	315	<0.1	1.8	45	15	5.5	8	15.5	40	20	<3	5	45	9.5
YYHC0075	Palaeo. sands	0.5	65	<0.1	1	105	8.5	2.1	3	31.5	10	15	<3	5	<20	17.5
YYHC0059C	Palaeo. sands	1	60	<0.1	1.8	140	20	2.3	4	23	35	15	3	5	<20	37

Notes: [1] Mean crustal abundances taken from Bowen 1979.

## 4.3.5 Interactions with Barren Liquor


### 4.3.5.1 Clay-Quartz and Near-Surface Loams

The barren solution contains high concentrations of some solutes (Appendix 4). Results from bottle roll tests contacting solids with barren tailings liquor show evidence for the attenuation of some elements onto some solids. Attenuation is discussed in more detail in Section 4.6.1.

There are numerous instances where overall net leaching is observed when materials are contacted with barren liquor. These include:

- Calcium, magnesium, barium and strontium: overall leaching occurs when in contact with the barren liquor (all lithologies). The results for the eight samples tested are illustrated in Figure 4.13 and Figure 4.14. In the case of calcium and magnesium, the dissolved concentrations are up to an order of magnitude higher in the final solutions than in the initial barren solution. For the clay-quartz sample (YYS163 23-23.1 m), the final dissolved magnesium is two orders of magnitude higher than in the barren solution. For strontium and barium the trend is similar, with the exception of the transitional TCQ sample, YYS164 5.2-5.3 m, which shows a small amount of attenuation of these elements. Barium and strontium are usually considered analogues of radium behaviour – but note that radionuclide assays (discussed in Section 4.5) suggested that radium is attenuated rather than leached in these tests.
- Uranium and vanadium leaching was observed for two of the clay-rich (CQ) samples (YYS165 6.6-6.7 m and YYS164 26.2-26.3 m) (Figure 4.15).
- Zinc was found to leach from all samples (Figure 4.16).

For most other elements, either no water-rock interaction takes place or attenuation occurs (Section 4.5).

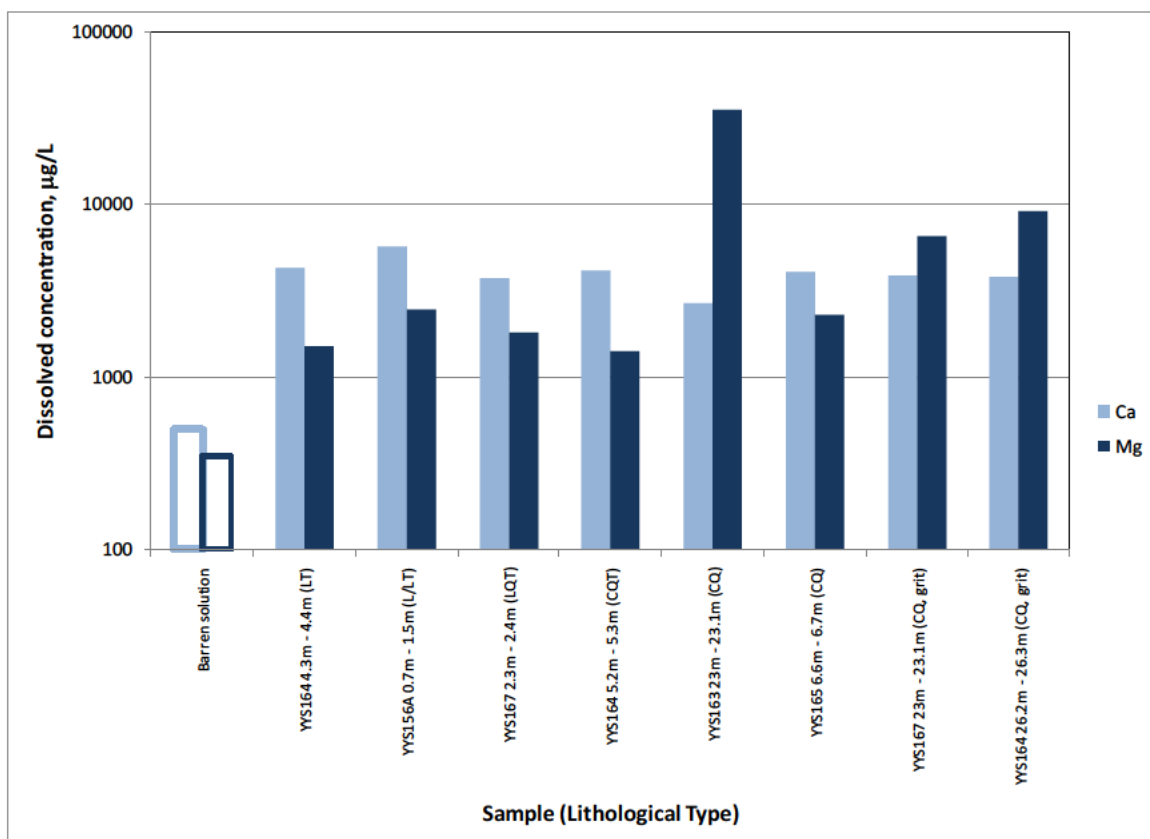

**Figure 4.13: Ca and Mg leaching in barren solution**  
(3:1 liquid:solid ratio, air atmosphere)



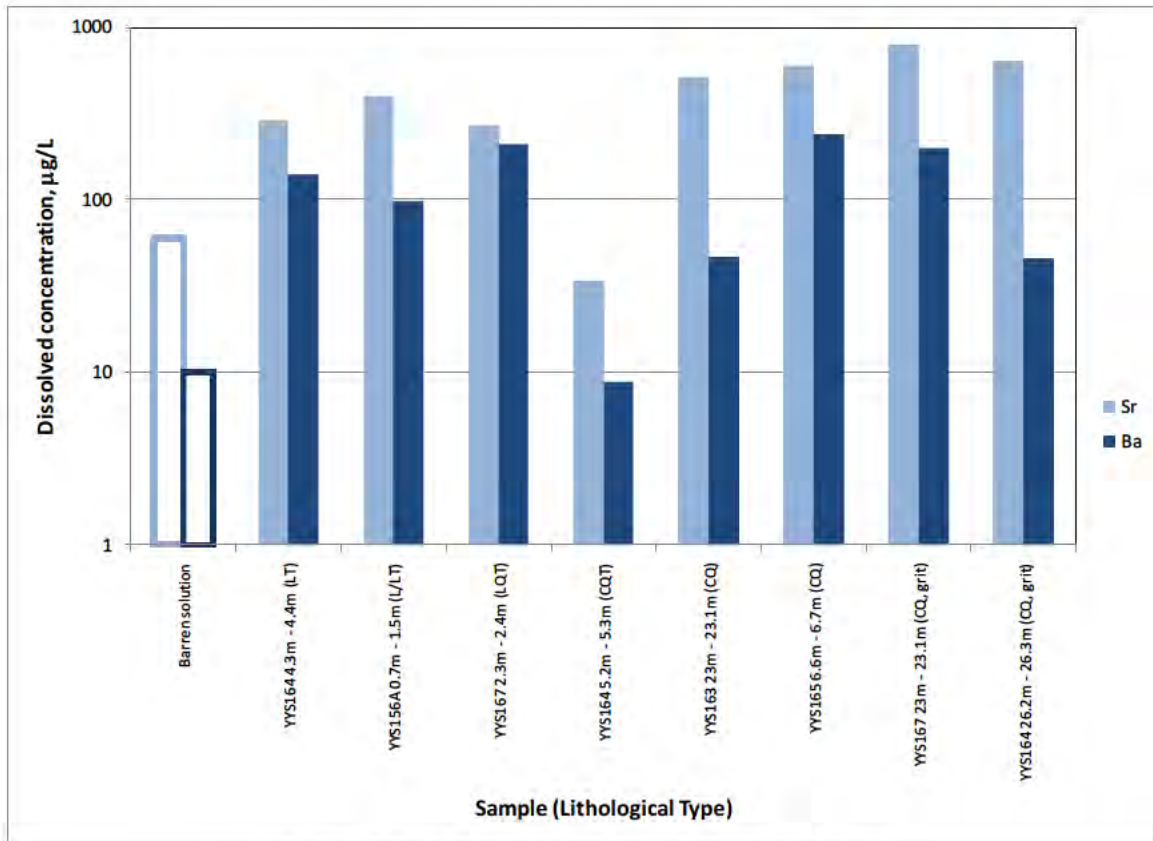


Figure 4.14: Sr and Ba leaching in barren solution (3:1 liquid:solid ratio, air atmosphere)


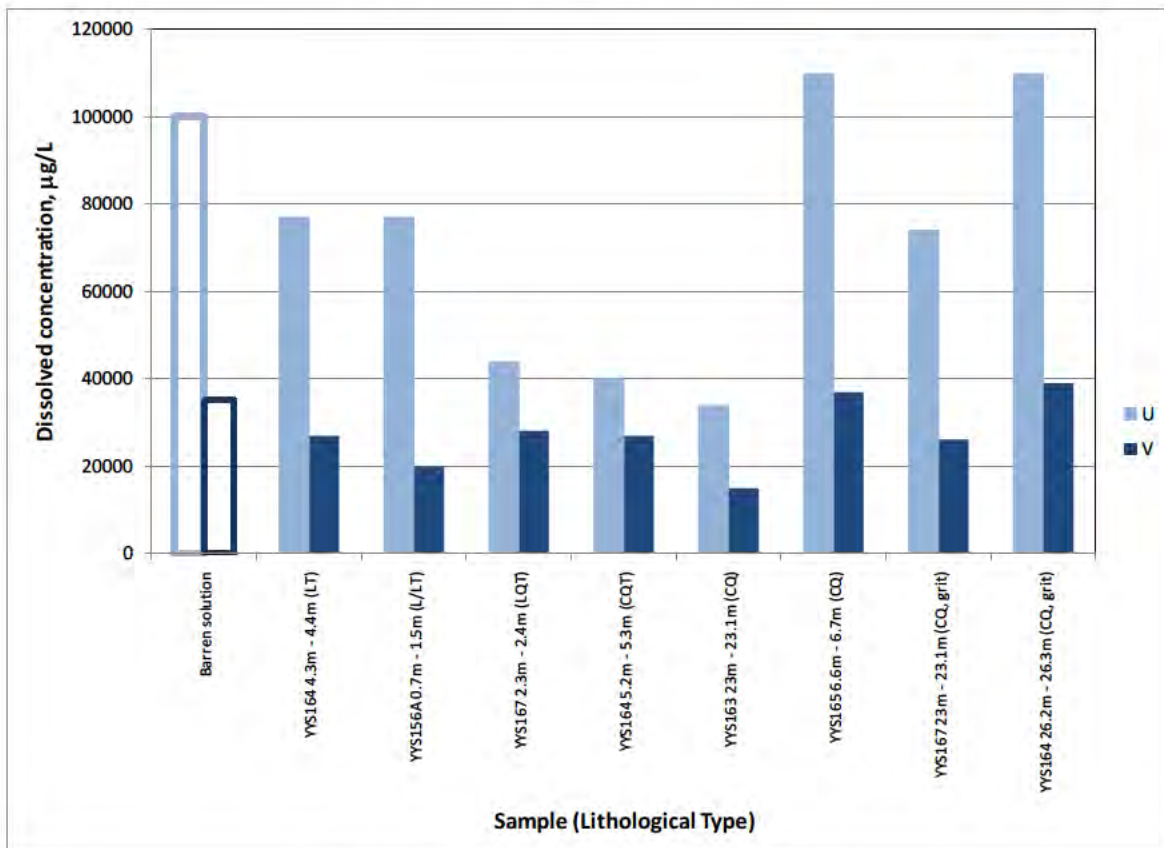


Figure 4.15: U and V leaching in barren solution (3:1 liquid:solid ratio, air atmosphere)

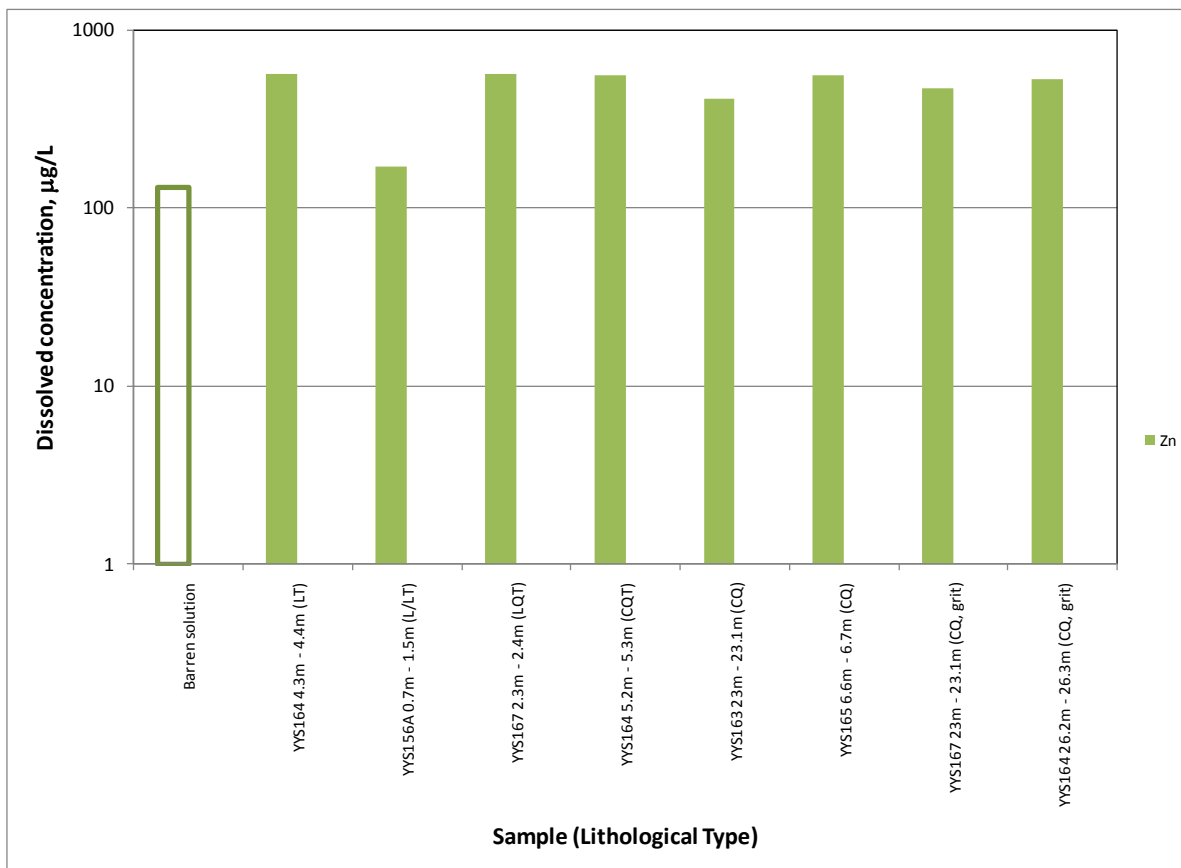

**Figure 4.16: Zn leaching in barren solution**  
(3:1 liquid:solid ratio, air atmosphere)

4.3.5.2 Palaeochannel Sands

The palaeochannel sands were subjected to sequential bottle roll tests. In the first stage, the paleochannel sand was contacted with barren liquor. On completion of the first stage, the solution was removed and replaced with de-ionised water.

Results are given in Appendix 5. Dissolved sodium, calcium, uranium and vanadium concentrations are illustrated in Figure 4.17 to Figure 4.20.

Sodium concentrations decreased slightly during the first stage indicating that the sands have capacity to exchange Na. There is a coincident increase in calcium concentrations suggesting that sodium displaces calcium from exchange sites.

Uranium concentrations in the barren liquor decrease significantly following contact with the sands, suggesting significant sorption of uranium (calculated  $R_D$  values are high,  $60,000 \text{ cm}^3 \text{ g}^{-1}$ ). See Section 4.6.1 for further discussion of sorption in Yeelirrie materials. On contact with de-ionised water in the second stage of the tests, very little of the adsorbed uranium enters solution, suggesting that sorption is irreversible under the conditions of the test.

Vanadium concentrations in the barren liquor show only a modest decrease following contact with the sands. This would suggest that vanadium sorbs only weakly. On contact with de-ionised water in the second stage of the test, the adsorbed vanadium is entirely desorbed.

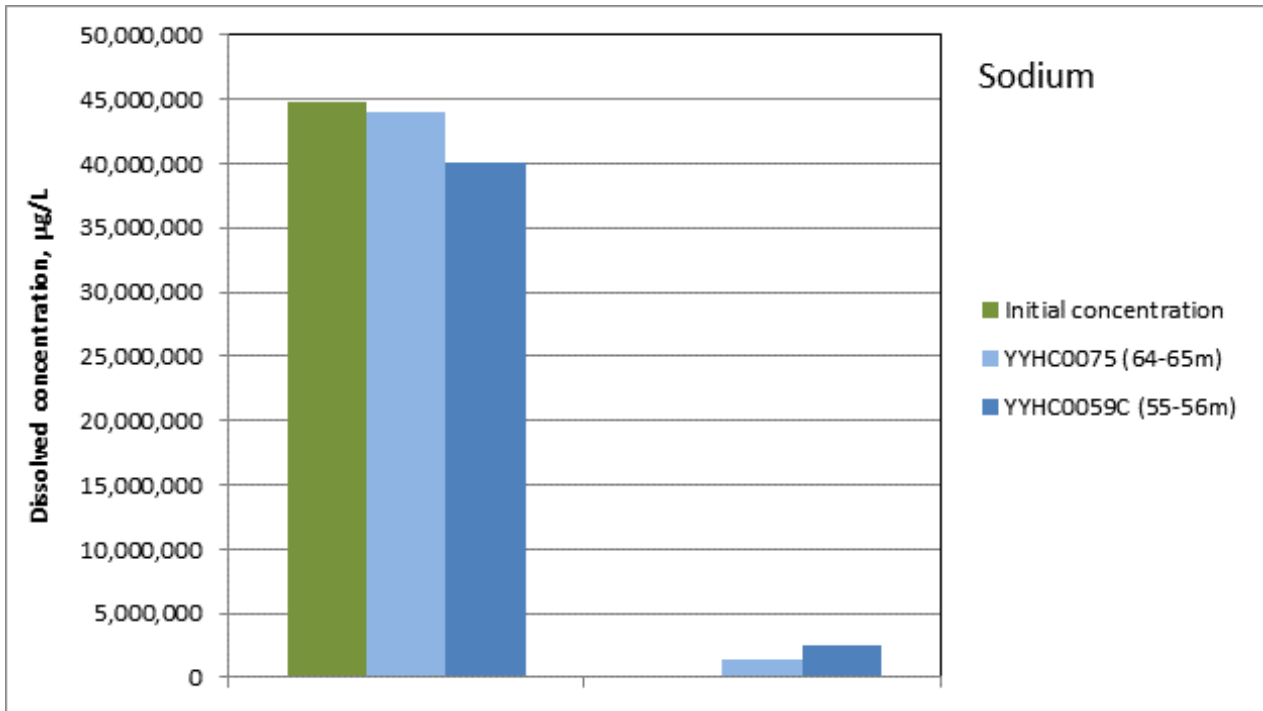


Figure 4.17: Dissolved sodium concentrations in leachates from bottle roll tests involving palaeochannel sands

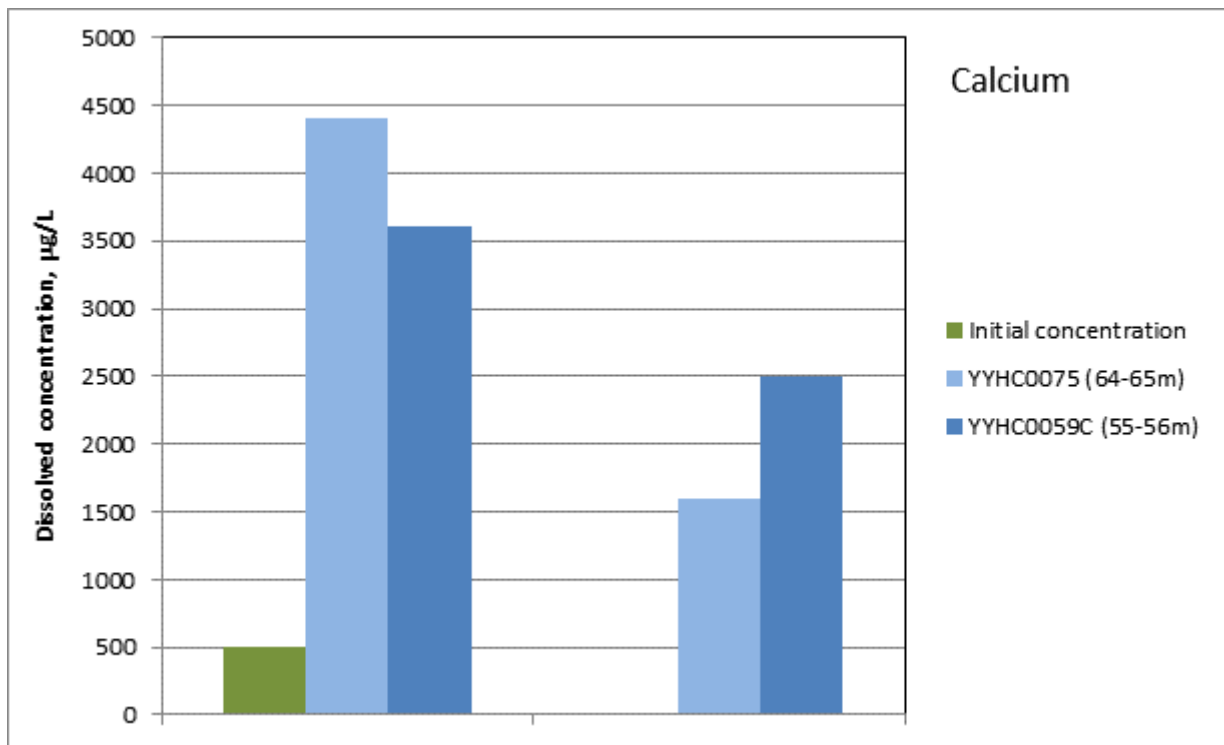


Figure 4.18: Dissolved calcium concentrations in leachates from bottle roll tests involving palaeochannel sands

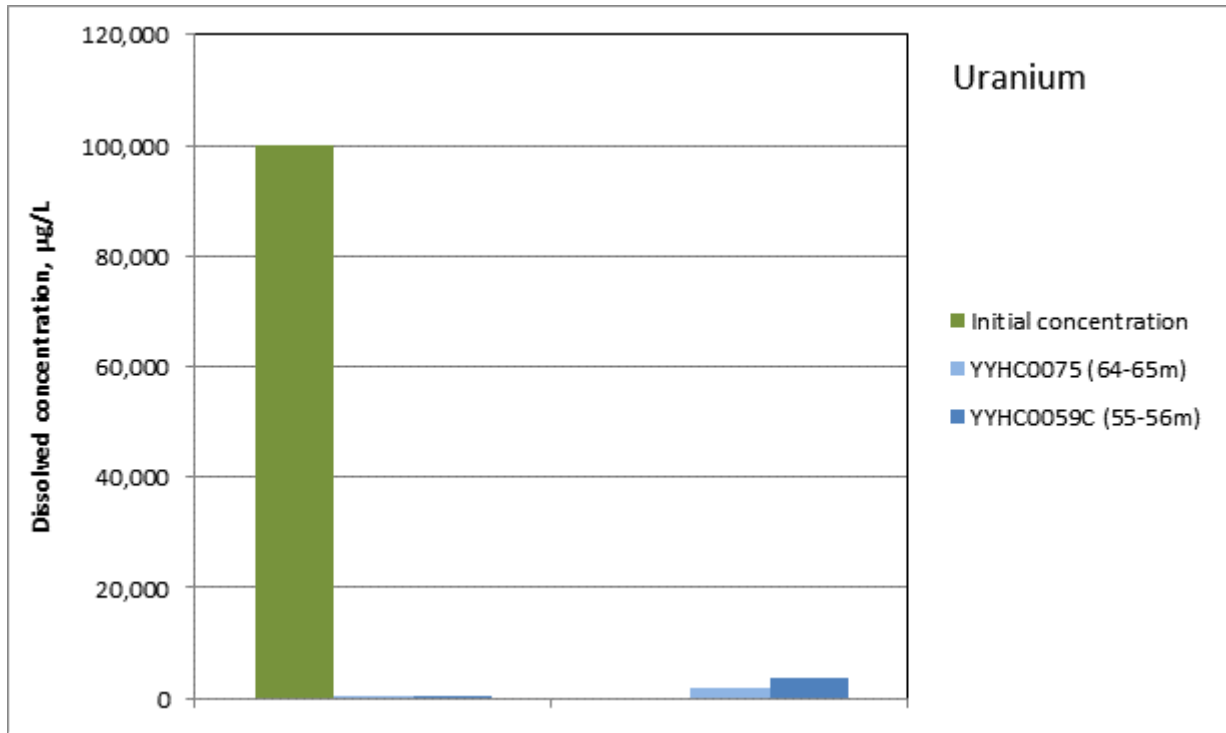


Figure 4.19: Dissolved uranium concentrations in leachates from bottle roll tests involving paleo-channel sands

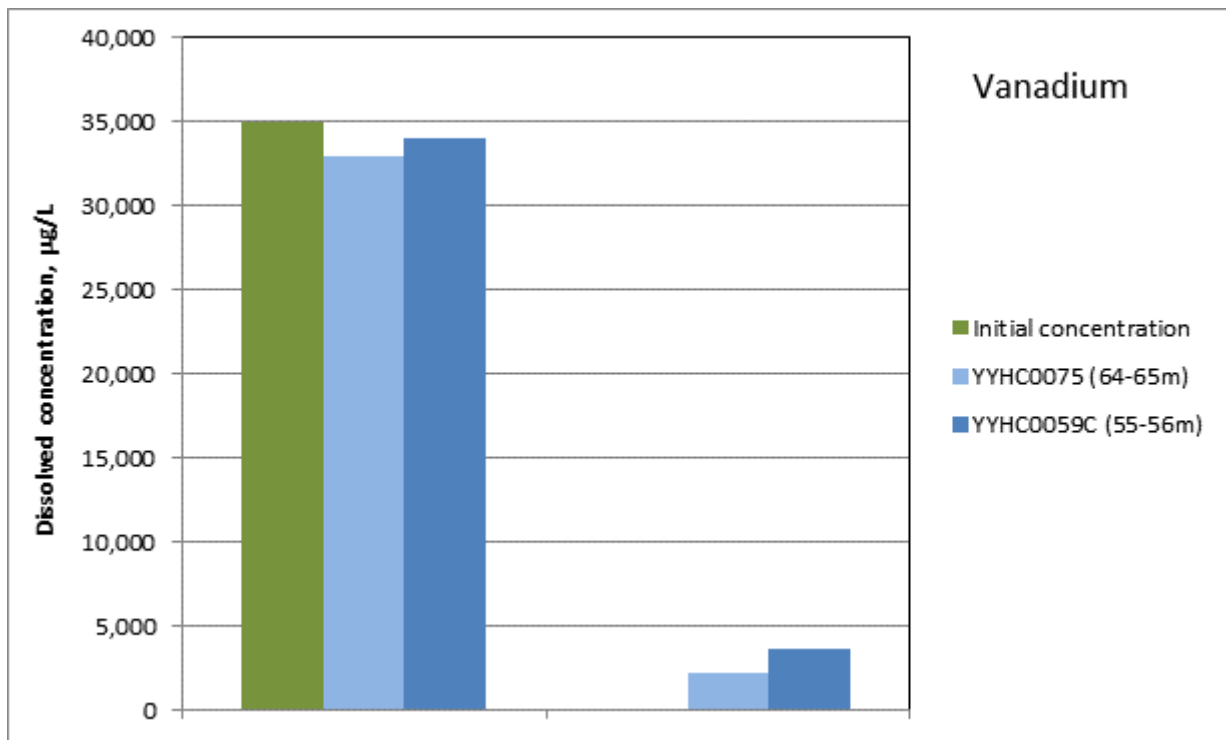


Figure 4.20: Dissolved vanadium concentrations in leachates from bottle roll tests involving palaeochannel sands

## 4.4 Column Test Results

Four sets of column pairs were set up to operate in series. The first column in each pair was open to air and operated such that the solution drains down and the sample becomes unsaturated between flushing events. The second column was not open to air and was maintained under saturated conditions (filled with solution) at all times. Effluent from the first column was used as inflow for the second column in that pair.

The column test programme is summarised in Table 4.8. Column test results are given in Appendix 5.

Table 4.8: Column Test Programme

Column #	Sample #	Lithology	Approx. W:R ratio <sup>[1]</sup>	Operating conditions	Inflow Solution
1A	YC3 tails residue	Tailings	0.2	Unsaturated	De-ionised water
1B	YYS156A 11.25-12 m	Clay-quartz (CQ)	0.5	Saturated	Sequences 1 to 5: Outflow from Column 1A; Sequences 6 to 11: De-ionised water <sup>[2]</sup>
2A	YYS158 3.75-4.5 m	Calcrete (T)	0.2	Unsaturated	De-ionised water
2B	YYS156A 0.7-1.5 m	Loam/calcareous loam (L/LT)	0.5	Saturated	Outflow from Column 2A
3A	YYS156A 1.5-2.5 m	Calcareous loam (LT)	0.3	Unsaturated	De-ionised water
3B	YYS158 2.5-3.5 m	Calcareous loam (LT)	0.5	Saturated	Outflow from Column 3A
4A	YYS159 4.5-5.2 m	Transitional between calcrete and clay-quartz (TCQ/CQT)	0.3	Unsaturated	Barren solution
4B	YYS156A 12-12.75 m	Clay-quartz (CQ)	0.5	Saturated	Outflow from Column 4A

Notes:

[1] Water:rock (W:R) ratio calculated based on the volume of inflow solution and the mass (wet) of solid in the column.

[2] Difficulties encountered with operation of Column 1A and this Column was terminated after Sequence 6. The inflow to Column 1B from Sequence 6 onward was de-ionised water – the aim being to examine whether solute attenuation during Sequences 1 to 5 would be reversible when contacted with the de-ionised water.

### 4.4.1 General Trends

The general trends are consistent with those demonstrated in the bottle roll tests. For example, for those columns rinsed with de-ionised water the earliest pore volume exchanges tend to coincide with the highest solute concentrations.

Figure 4.21 shows sodium release from loam under both saturated and unsaturated conditions (Columns 2B and 3A, respectively). The first pore volume exchange contains the highest sodium concentration. Sodium concentrations in subsequent pore volumes decrease steeply at first and then more gradually. The shape of the release curve can be approximated quite well by a power law (see Figure 4.21).

Release of minor and trace elements from the columns also tends to decrease with successive pore volume exchanges, although there are occasional deviations from this overall trend. For example, Figure 4.22 and Figure 4.23 show uranium and vanadium release from Columns 2B and 3B. As shown, the vanadium release in the second pore volume exchange (both columns) is higher than that in the first pore volume exchange. For uranium, there is evidence of a secondary leaching peak (pore volume exchanges 4 and 5). These trends are consistent with some of the trends observed in sequential leach testing, Section 4.2.5.1. The results suggest that the change in solute concentrations that occur after the first displacement (i.e. substantial decrease in the more readily soluble solutes) may affect the solubility (or rate of dissolution) of carnotite (primary source mineral for both uranium and vanadium).

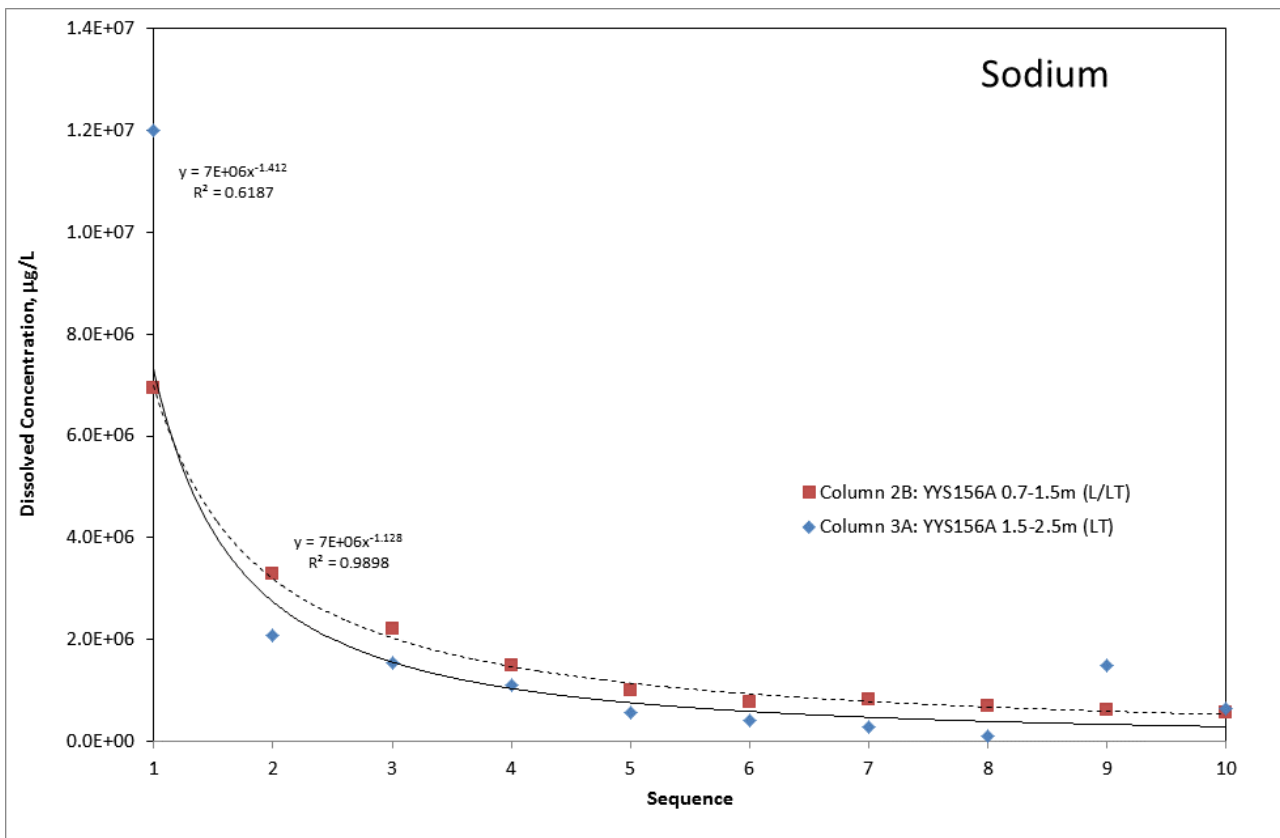


Figure 4.21: Dissolved sodium concentrations in leachates from Columns 2B and 3A

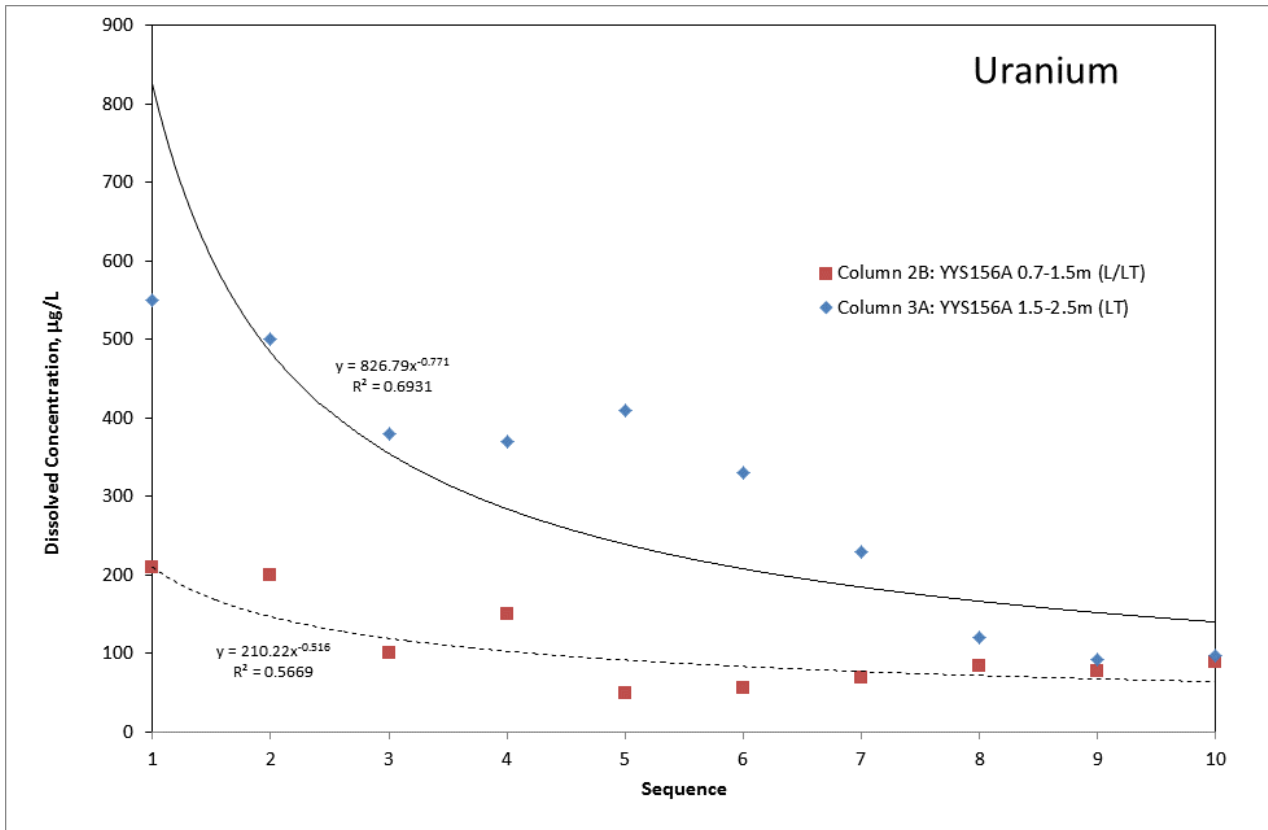


Figure 4.22: Dissolved uranium concentrations in leachates from Columns 2B and 3A

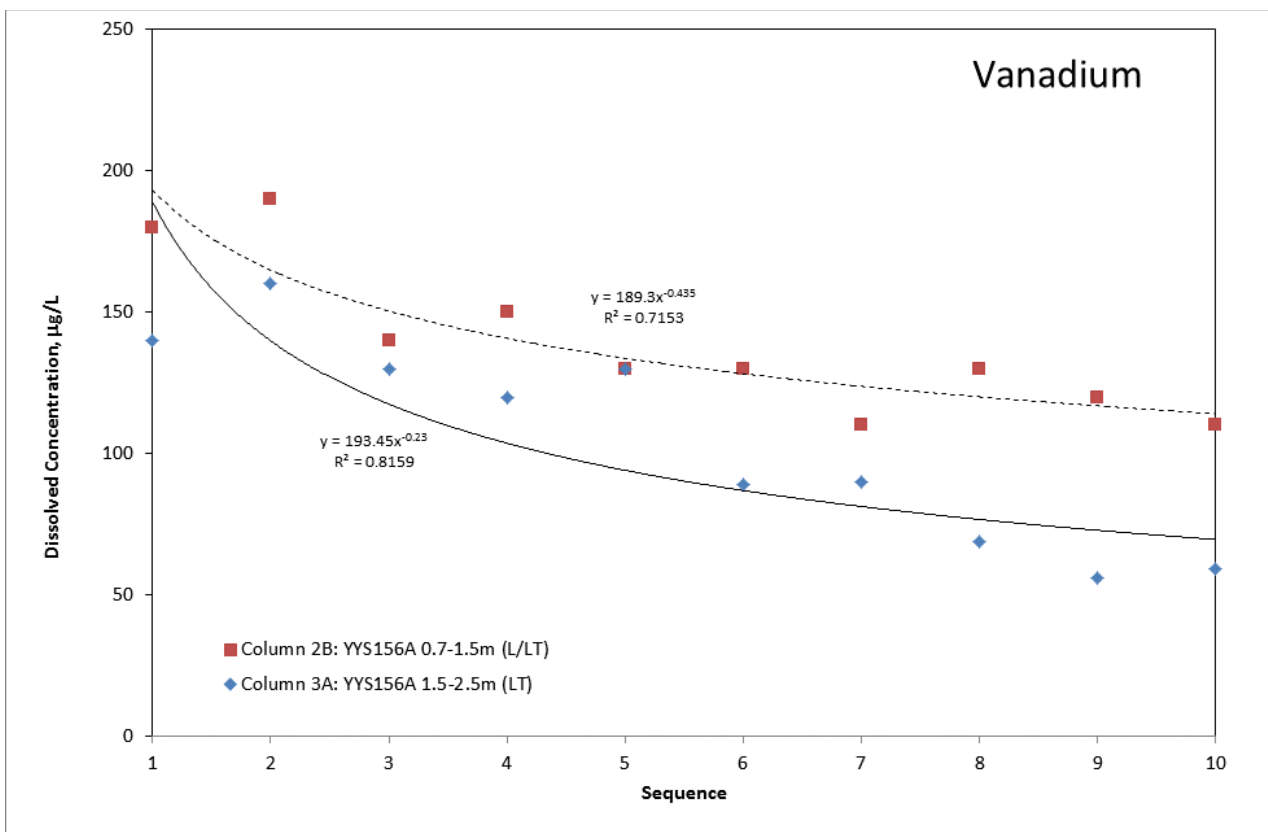


Figure 4.23: Dissolved vanadium concentrations in leachates from Columns 2B and 3A




In Column 4A (containing transitional material, TCQ/CQT), the inflow solution was barren liquor. As can be seen in Figure 4.24, the sodium concentrations in the effluent from the early pore volume exchanges from Column 4A were lower than the inflow concentrations. This reflects attenuation of sodium within the column, probably due to ion exchange (discussed further in Section 4.6.2). After four pore volume exchanges the sodium concentration in outflows are equivalent to those of the inflow suggesting that the capacity of the solid to further attenuate sodium has been exhausted (i.e. the ion exchange capacity has been depleted). In support of this conclusion, calcium was leached from Column 4A (Figure 4.25) (probably displaced by sodium in ion exchange reactions).

Column 4B contained clay-quartz (CQ). The outflow solutions from Column 4A were used as the inflow to Column 4B. The results presented in Figure 4.24 and Figure 4.25 show that trends similar to those described above were being displayed during these early pore volume exchanges (i.e. attenuation of sodium and coincident leaching of calcium).


Uranium leaching trends in Columns 4A and 4B were more complex (Figure 4.26). Attenuation appears to take place during the first pore volume exchange, and again during the fourth and fifth pore volume exchanges and the eighth exchange. Similar trends were observed for chromium and selenium. One possible explanation for this trend relates to iron behaviour in the column. There is some evidence for iron leaching in the early pore volume exchanges (see Appendix 5). The iron may have been displaced from exchange sites (as is the case for calcium) in exchange for the other metals. The displaced iron could re-precipitate in the form of oxy-hydroxides, generating new sorptive capacity to the material and explaining the renewed attenuation.

Figure 4.27 shows vanadium release from Columns 4A and 4B. In Column 4A, vanadium concentration in leachate is gradually increasing, and by the tenth pore volume exchange returned to the initial concentration found in the barren liquor. This suggests that the capacity of the material to attenuate vanadium has been exhausted. The limited results from Column 4B suggests ongoing attenuation of vanadium is likely to occur.

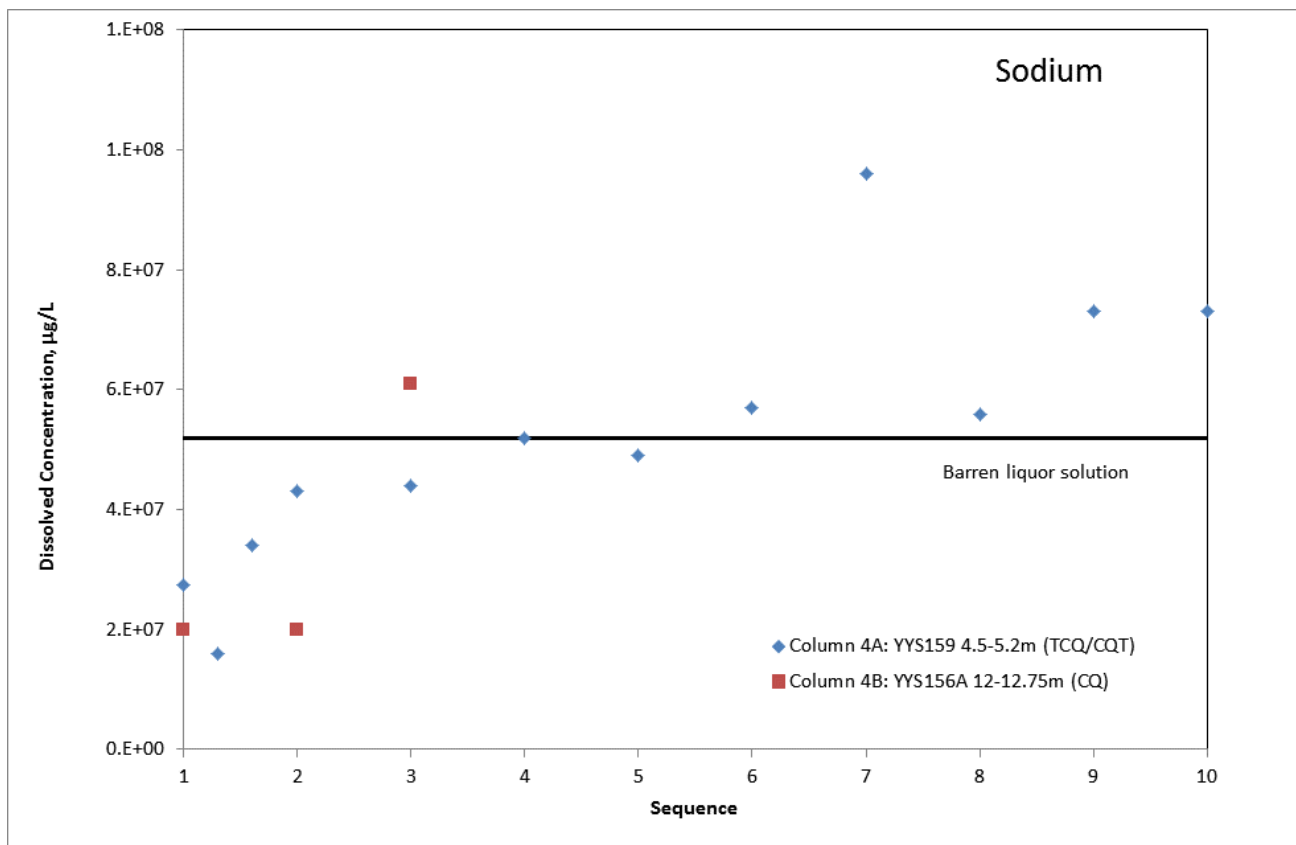


**Figure 4.24: Dissolved sodium concentrations in leachates from Columns 4A and 4B**

Due to operational difficulties, Column 4B was terminated after three pore volume exchanges.

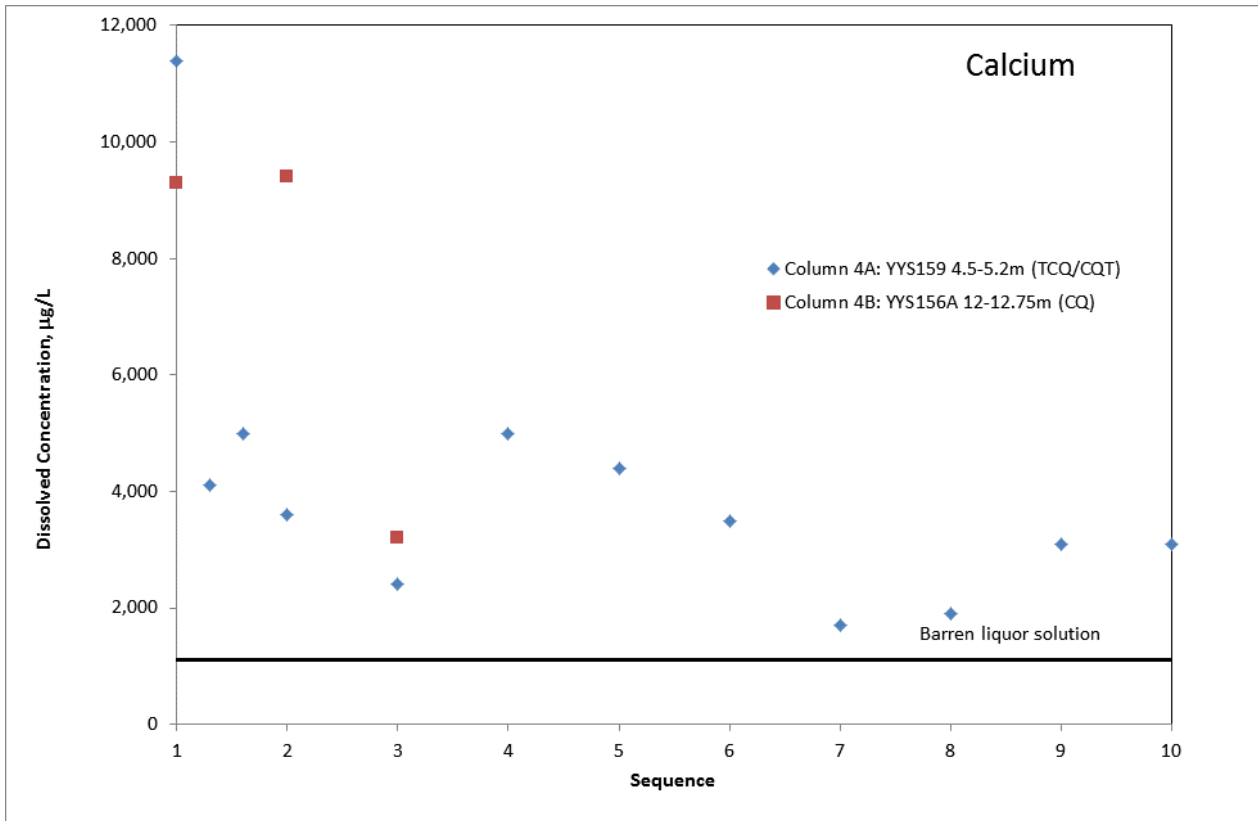


**Figure 4.25: Dissolved calcium concentrations in leachates from Columns 4A and 4B**

Due to operational difficulties, Column 4B was terminated after three pore volume exchanges.

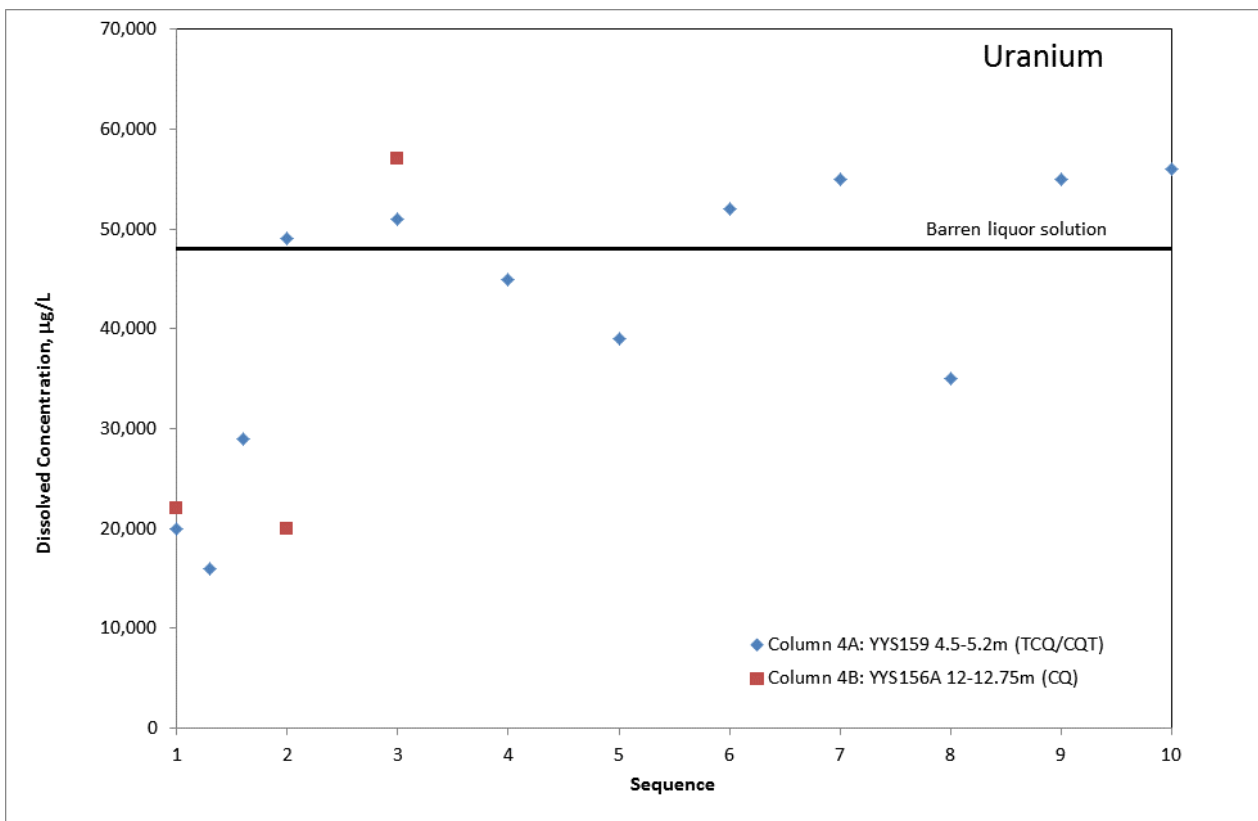

**Figure 4.26: Dissolved uranium concentrations in leachates from Columns 4A and 4B**

Due to operational difficulties, Column 4B was terminated after three pore volume exchanges.

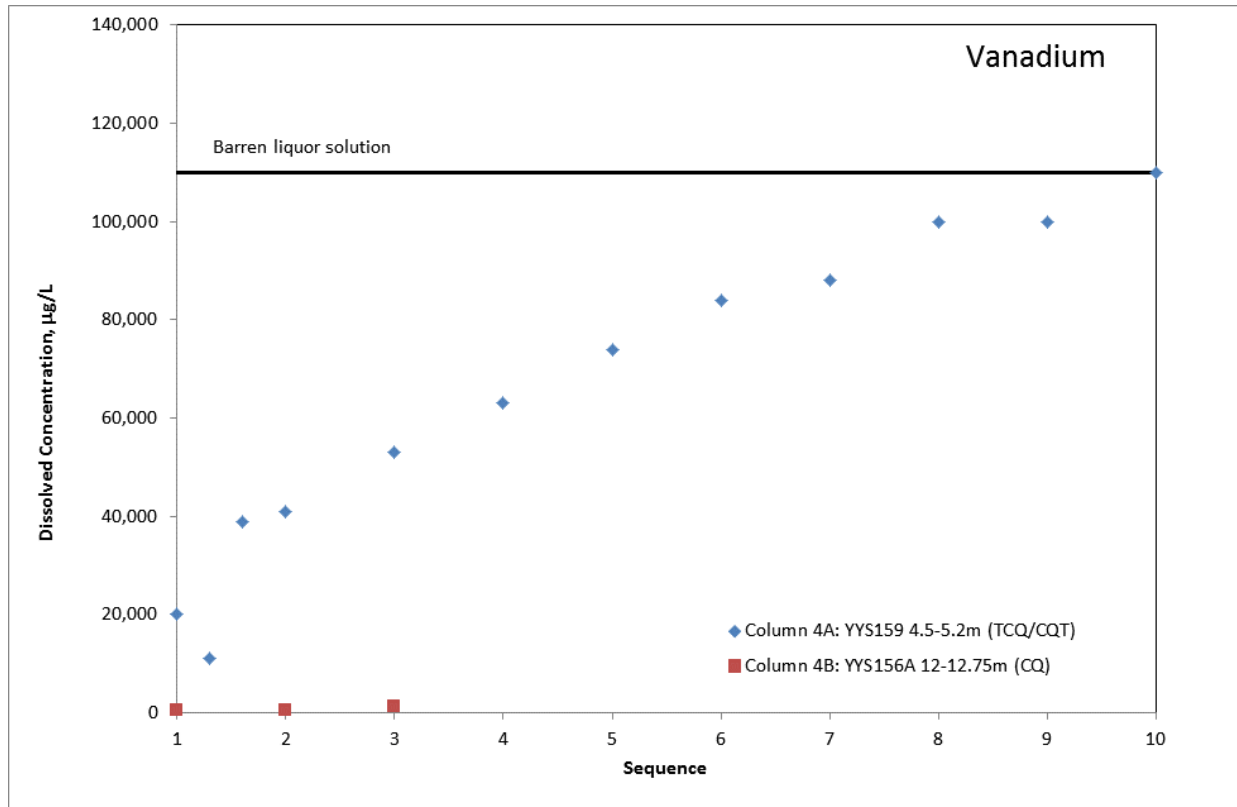

**Figure 4.27: Dissolved vanadium concentrations in leachates from Columns 4A and 4B**

Due to operational difficulties, Column 4B was terminated after three pore volume exchanges.

#### 4.4.2 Quantitative Comparisons between Column and Bottle Roll Test Results

The column tests involve solid:solution ratios much higher than those of bottle roll tests. Unless solubility limits apply, the higher mass of solid may result in higher solute concentrations in leachates. Table 4.9 summarises the maximum dissolved concentrations observed in the column programme (to-date) and those observed in the bottle roll tests.

Looking first at the de-ionised water results, higher dissolved concentrations were observed in the column effluent (when compared to the roll bottle tests) for most elements. However, the maximum concentrations of thallium, uranium and vanadium were higher in the bottle roll tests. Uranium and vanadium are believed to be solubility limited in the columns, which may explain the limited dissolved concentrations of these elements in column leachates. The same may apply to thallium, however, no thermodynamic data are available with which to assess potential solubility controls for this element.

In the case of the barren liquor leach results, attenuation as well as leaching takes place. For attenuated elements, the higher solid:solution ratio in the columns offers additional sorptive capacity, and so it would be expected that maximum dissolved concentration be less in the column dataset than in the bottle roll dataset. The comparisons within the barren liquor dataset are therefore more complex. Nevertheless, uranium concentrations were elevated in the column and roll bottle tests, suggesting that the uranium contained in the barren solution dominates the solution chemistry after contact with the materials tested.

**Table 4.9: Summary of Maximum Solute Concentrations in Column Tests Compared to Outcomes from Bottle Roll Tests**

Parameter	Units	Detection Limit <sup>[1]</sup>	Maximum value			
			De-ionised water		Barren Liquor	
			Columns (2,3)	Bottle Rolls	Columns (1B, 4)	Bottle Rolls
pH	pH Units	0.01	9.1	10.0	11.0	11.0
Eh	mV	1	516	510	426	383
EC	µS/cm	5	57900	8890	275000	258000
Acidity	as CaCO <sub>3</sub> (mg/L)	20	890	50	<20	<20
Alkalinity	as CaCO <sub>3</sub> (mg/L)	1	1100	1300	124000	81000
Br	mg/L	0.5	48	11	240	92
Cl	mg/L	0.5	18000	1700	22000	23000
F	mg/L	0.5	10	5	42	27
TOC	mg/L	1, 5	80	200	89	2900
NO <sub>2</sub>	mg/L	0.02, 0.5	2.2	2.2	1.8	0.63
NO <sub>3</sub>	mg/L	0.1, 0.5	840	95	960	740
SO <sub>4</sub>	mg/L	0.5	9100	3200	13000	54000
Al	µg/L	5	120	680	88	150
Ca	µg/L	100	2010000	694000	11400	6060
Fe	µg/L	100	<100	560	300	300
Mg	µg/L	100	1470000	237000	490000	88000
P	µg/L	100	5000	2300	6100	1800
K	µg/L	1000	1250000	211000	2100000	1900000
Na	µg/L	100	12000000	1110000	57000000	53000000
Si	µg/L	100	24000	78000	180000	76000
Ag	µg/L	5	6.3	<5	9	5.4
As	µg/L	5	46	48	12000	7800
B	µg/L	5	47000	4900	60000	38000
Ba	µg/L	0.02, 5	530	160	28	550
Cd	µg/L	0.2, 5	19	27	18	31
Co	µg/L	1, 5	9.7	<5	6	<5
Cr	µg/L	5	8.1	37	3400	3500
Cu	µg/L	5	36	20	1400	140
Li	µg/L	5	<5	11	350	15
Mn	µg/L	5	110	53	6.1	15
Mo	µg/L	5	900	390	4500	3100
Ni	µg/L	1, 5	31	17	30	34
Pb	µg/L	1, 5	<5	<5	120	45
Sb	µg/L	5	<5	<5	<5	8
Se	µg/L	1, 5	330	28	650	560
Sn	µg/L	5	660	24	700	27
Sr	µg/L	5	36000	6000	1600	1900
Tl	µg/L	5	10	360	11	180
U	µg/L	5	550	2100	64000	110000
V	µg/L	5	190	600	84000	39000
Zn	µg/L	5	270	200	2200	680

## 4.5 Radionuclide Distribution and Behaviour

Results from the radionuclide assays of Yeelirrie rock and soils are summarised in Table 4.10. Daughter/parent activity ratios that differ from unity indicate secular disequilibrium.

Notably, in many of the near-surface lithologies (loams, calcrete and transitional calcrete), the activity of  $^{238}\text{U}$  is less than the activities of isotopes further down the  $^{238}\text{U}$  decay chain, suggesting isotopic disequilibrium within this decay chain. Daughter/parent activity ratios would suggest that whilst thorium, radium and lead isotopes are behaving similarly, uranium isotopes are not. Leaching and preferential removal of uranium would explain the observed disequilibrium relationships. Isotopes within the  $^{232}\text{Th}$  decay chain give comparable activities suggesting isotopic equilibrium and suggesting that no preferential leaching or accumulation of thorium or radium isotopes.

In the deeper lithologies (clay-quartz and the palaeochannel sands) isotopes within the  $^{232}\text{Th}$  and  $^{238}\text{U}$  decay chains generally give comparable activities, suggesting secular equilibrium. This would suggest that within the last several million years, no geochemical processes have resulted in either preferential leaching or accumulation of individual radionuclides within the decay chains.

For many samples, isotopes within the  $^{235}\text{U}$  decay chain are present at activities that are below detection. In the six samples, mostly loams, where  $^{235}\text{U}$  and  $^{227}\text{Ac}$  activities were detectable, the  $^{227}\text{Ac}$  activities tend to be slightly less than the  $^{235}\text{U}$  activities. This would suggest either accumulation of uranium in the loams, or conversely, leaching of actinium. Leaching of actinium is contrary to expectation. Actinium sorbs very strongly and would be expected to be relatively immobile (Baston et al, 1997). However, data from the  $^{238}\text{U}$  decay chain generally suggested uranium leaching rather than accumulation. An exception to this rule was one of the loam samples (YYS156A 0.7-1.5 m), which gave high  $^{238}\text{U}$  activities relative to isotopes further down the decay chain, possibly consistent with accumulation of uranium in this sample. Accumulation of uranium in loam could be explained by high sorption within this material type. Sorption is discussed further in Section 4.6.2.

Results from radionuclide assays of leachate solutions are summarised in Table 4.11.

In leach tests involving de-ionised water, the radionuclide concentrations were often below limits of detection. Detectable uranium ( $^{238}\text{U}$ ) was only recorded in one test, leaching from the sample (loam, YYS156A 1.5-2.5 m) under conditions of high dissolved  $\text{CO}_2$ .

The detection limit for  $^{226}\text{Ra}$  was lower, and thus  $^{226}\text{Ra}$  concentration were quantified for most samples. In the de-ionised water tests, the measured radium concentration correlates well with that of strontium and barium (dissolved barium and strontium concentrations are also shown in Table 4.11). However, this is not the case for tests involving leaching with barren liquor solution. As noted in Section 4.3.5, calcium, magnesium, barium and strontium leached from solids contacted with barren liquor. An exception is barium behaviour in Column 4A; barium concentrations in leachates from this column are lower than measured in the initial barren liquor suggesting barium attenuation in this column. In all but one test, the  $^{226}\text{Ra}$  concentration in the final leachate was lower than that of the starting barren liquor solution, suggesting attenuation rather than leaching was occurring in the majority of tests. It would appear therefore that, in tests involving barren liquor solution,  $^{226}\text{Ra}$  behaviour is distinct from that of strontium and barium.

Table 4.10: Radionuclide Assay Results for Yeelirrie Solids

Sample #	Depth range (m)	Material	Concentration (Bq/g)									
			<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain				<sup>235</sup> U Decay Chain		<sup>40</sup> K
			<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>235</sup> U	<sup>227</sup> Ac	
YYS166	0.4-0.5	H	0.044	0.048	0.044	0.17	<0.2	0.13	0.11	<0.02	<0.01	0.46
YYS165	1.5-1.6	HT	0.019	<0.02	0.019	1.5	2.4	2.0	2.2	0.074	0.079	0.23
YYS156A	0.7-1.5	L/LT	0.019	<0.04	0.018	2.3	1.5	1.4	1.5	0.10	0.067	<0.2
YYS167	2.3-2.4	LQT	0.033	<0.02	0.033	1.5	2.0	2.1	2.2	<0.04	0.064	0.37
YYS156A	1.5-2.5	LT	0.022	<0.03	0.021	6.0	6.6	5.6	5.5	0.30	0.23	<0.3
YYS158	2.5-3.5	LT	0.0044	<0.02	<0.01	2.0	2.6	2.4	2.7	0.10	0.078	<0.08
YYS156A	3-4	LT	0.024	<0.05	0.024	12	13	11	12	0.55	0.49	0.32
YYS164	4.3-4.4	LT	0.072	0.077	0.077	0.12	<0.2	0.070	0.072	<0.02	<0.01	0.39
YYS158	3.5-3.75	T	0.0014	<0.02	<0.01	0.69	0.98	0.95	1.1	<0.03	0.028	<0.05
YYS158	3.75-4.5	T	0.0016	<0.03	<0.01	1.5	2.0	1.8	1.9	<0.07	0.057	<0.08
YYS157	3.65-4.1	TCQ	0.028	0.032	0.023	1.3	1.5	1.3	1.4	<0.03	0.057	0.20
YYS162	4.5-4.6	TCQ	0.027	<0.04	0.025	0.46	0.79	0.63	0.79	<0.02	0.022	0.47
YYS159	4.5-5.2	TCQ/CQT	0.056	0.061	0.058	0.15	<0.3	0.19	0.21	<0.03	<0.01	0.46
YYS164	5.2-5.3	CQT	0.062	0.053	0.048	0.17	<0.1	0.089	0.11	<0.01	<0.01	0.46
YYS156A	11.25-12	CQ	0.11	0.11	0.11	0.82	0.95	0.82	0.79	<0.03	0.036	0.53
YYS156A	12-12.75	CQ	0.083	0.091	0.076	0.81	1.0	0.81	0.82	0.039	0.032	0.44
YYS163	23-23.1	CQ	0.12	0.13	0.11	0.13	<0.3	0.15	0.16	<0.03	<0.02	0.65
YYS167	23-23.1	CQ	0.068	0.072	0.073	0.11	<0.3	0.14	0.16	<0.03	<0.02	0.33
YYS164	26.2-26.3	CQ	0.074	0.089	0.078	0.071	<0.2	0.087	0.10	<0.02	<0.01	0.45
YYS165	6.6-6.7	CQ	0.042	0.042	0.044	0.15	<0.2	0.17	0.20	<0.02	<0.01	0.37
YYHC0059C	55-56	Palaeochannel sand	0.073	0.076	0.067	0.077	<0.2	0.063	0.083	<0.02	<0.01	0.043
YYHC0075	64-65	Palaeochannel sand	0.058	0.056	0.055	0.063	<0.1	0.062	0.071	<0.01	<0.01	0.037

**Table 4.11: Radionuclide Assay Results for Leachate Solutions**

Test	Sample	Material type	Leach solution	Concentration (Bq/L)										Concentration (µg/L)	
				<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain				<sup>235</sup> U Decay Chain		<sup>40</sup> K	Ba	Sr
				<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>235</sup> U	<sup>227</sup> Ac			
Sequential 3 - Sequence 1	YYS162 4.5-4.6 m	TCQ	DI water	<4	<1	<0.5	<12	<30	<0.6	<5	<3	<2	<6	18	330
Sequential 9 - Sequence 1	YYS156A 1.5-2.5 m	LT	DI water	<4	<0.8	<0.3	<12	<20	4.4	<4	<2	<0.8	<7	60	6000
Sequential 11 - Sequence 1	YYS158 3.5-3.75 m	T	DI water	<4	<1	<0.3	<12	<30	0.57	<4	<2	<1	<8	28	1300
Leach Extraction 19	YYS156A 1.5-2.5 m	LT	DI water (high CO <sub>2</sub> )	<4	<0.9	<0.4	26	<20	6.1	<4	<1	<1	<5	82	5400
Leach Extraction 21	YYS158 3.5-3.75 m	T	DI water (high CO <sub>2</sub> )	<4	<1	<0.4	<12	<20	3.1	<5	<3	<2	<10	51	2600
Column 2A Sequence 1	YYS158 3.75-4.5 m	T	DI water	<4	<0.9	<0.5	<12	<20	1.6	<5	<2	<2	<7	15	1500
Column 2B Sequence 1	YYS156A 0.7-1.5 m	L/LT	Effluent from column 2A	<4	<1	<0.5	<12	<40	7.1	<5	<2	<2	30	58	21000
Column 3A Sequence 1	YYS156A 1.5-2.5 m	LT	DI water	<4	<10	<6	<12	<260	340	<60	<20	<20	450	530	36000
Column 3A Sequence 3	YYS156A 1.5-2.5 m	LT	DI water	<0.4	< 0.4	< 0.2	3.9	< 5	3.8	< 2	< 0.3	< 0.4	10	46	3900
Column 3B Sequence 1	YYS158 2.5-3.5 m	LT	Effluent from column 3A	<4	<2	<0.4	<12	<50	5.9	<20	<2	<2	<10	42	8100
Column 3B Sequence 3	YYS158 2.5-3.5 m	LT	Effluent from column 3A	<0.4	< 0.5	< 0.3	3.4	< 7	3.9	< 2	< 0.4	< 0.6	10	38	5200
Barren Liquor		-	Barren liquor	<4	<2	<0.5	1160	<110	5	<20	68	<2	28	10	60
Leach Extraction 24	YYS156A 0.7-1.5 m	L/LT	Barren liquor	<4	<0.9	<0.4	1150	<80	4.6	<10	63	<2	43	98	400
Leach Extraction 27	YYS163 23-23.1 m	CQ	Barren liquor	<4	<1	<0.6	1090	<90	2.6	<10	62	<2	49	47	510
Leach Extraction 38	YYS167 2.3-2.4 m	LQT	Barren liquor	<4	<2	<0.6	1150	<100	6.2	<20	71	<2	39	550	1200
Column 4A Sequence 1	YYS159 4.5-5.2 m	TCQ/CQT	Barren liquor	<4	<2	<0.6	320	<60	<0.7	<20	20	<2	15	<5	1400
Column 4A Sequence 3	YYS159 4.5-5.2 m	TCQ/CQT	Barren liquor	<0.4	< 0.4	0.36	292	< 22	< 0.3	< 3	22	< 0.5	60	<5	200
Column 4B Sequence 1	YYS156A 12-12.75 m	CQ	Effluent from column 4A	<4	<1	0.52	200	<30	<0.5	<7	12	<2	28	11	1600
Column 4B Sequence 3	YYS156A 12-12.75 m	CQ	Effluent from column 4A	<0.4	< 0.6	4.1	378	< 33	2.3	< 4	30	< 0.8	54	61	500

## 4.6 Geochemical Controls

### 4.6.1 Mineral Solubility

Geochemical modelling techniques have been used to identify potential solubility limits. Using measured leachate chemistries as input, the saturation indices of key mineral phases were calculated. The focus of the calculations was to identify minerals close to equilibrium with the measured leachate water chemistries (a saturation index close to zero). Such minerals, if present in the materials, may have dissolved (or precipitated) to attain equilibrium with the leachate and therefore may be used to infer solubility limitations.

Possible solubility controls identified were:

- Iron and aluminium oxy-hydroxides – ferrihydrite ( $\text{Fe}(\text{OH})_3$ ), gibbsite ( $\text{Al}(\text{OH})_3$ ), boehmite ( $\text{AlOOH}$ )
- Carbonates – calcite ( $\text{CaCO}_3$ ), dolomite ( $\text{CaMg}(\text{CO}_3)_2$ ), rhodochrosite ( $\text{MnCO}_3$ ), strontianite ( $\text{SrCO}_3$ )
- Sulphates – gypsum ( $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ ), celestite ( $\text{SrSO}_4$ )

Carnotite ( $\text{K}_2(\text{UO}_2)_2(\text{VO}_4)_2$ ) solubility was modelled using the Minteq carnotite data as previously discussed in Section 2.1.2. In most of the bottle roll tests involving de-ionised water solutions, carnotite was found to be under-saturated, suggesting that carnotite would leach rather than precipitate in the tests. Test involving barren liquor solutions gave saturation indices closer to equilibrium with carnotite.

Figure 4.28 and Figure 4.29 show uranyl activity diagrams calculated for leachate results plotted as a function of pH. The results that plot closest to the theoretical carnotite line tend to be for barren liquor leachates.


In general, column test leachates were closer to equilibrium with carnotite (Figure 4.30). There is however, a significant degree of scatter, and a significant number of the solutions were found to be oversaturated with respect to carnotite.

Results from the current programme suggests that in most of the de-ionised water bottle roll tests, although carnotite may be dissolving from the solids, equilibrium conditions with the solution were not achieved. Possibly insufficient carnotite mass is available within the samples to attain equilibrium with the contacting solution. It is also possible that (i) in many of these tests the concentration of the key solute, K, remains below the threshold levels required to exceed carnotite solubility or (ii) that carnotite dissolution is subject to kinetic controls and longer contact times are required to reach equilibrium.


In the column tests, the water-to-rock ratios were lower (i.e. more carnotite mass per unit volume water), solute concentrations are higher, and contact time between the solids and the leachate solutions were longer, sometimes up to weeks. All these conditions are more likely to result in equilibration of carnotite with the contacting solution.

Another observation that can be made from the current results is that release of uranium to solution is disproportionate to the vanadium release. The uranium:vanadium molar ratio in carnotite is unity (1.0); therefore congruent dissolution of carnotite would result in a uranium:vanadium molar ratio of 1.0. However, in most of the leachate solutions the uranium:vanadium molar ratio is less than 1.0. The low ratios suggest that uranium is preferentially held within the solid phase, possibly due to a change in the composition of the dissolving phase, or preferential sorption.




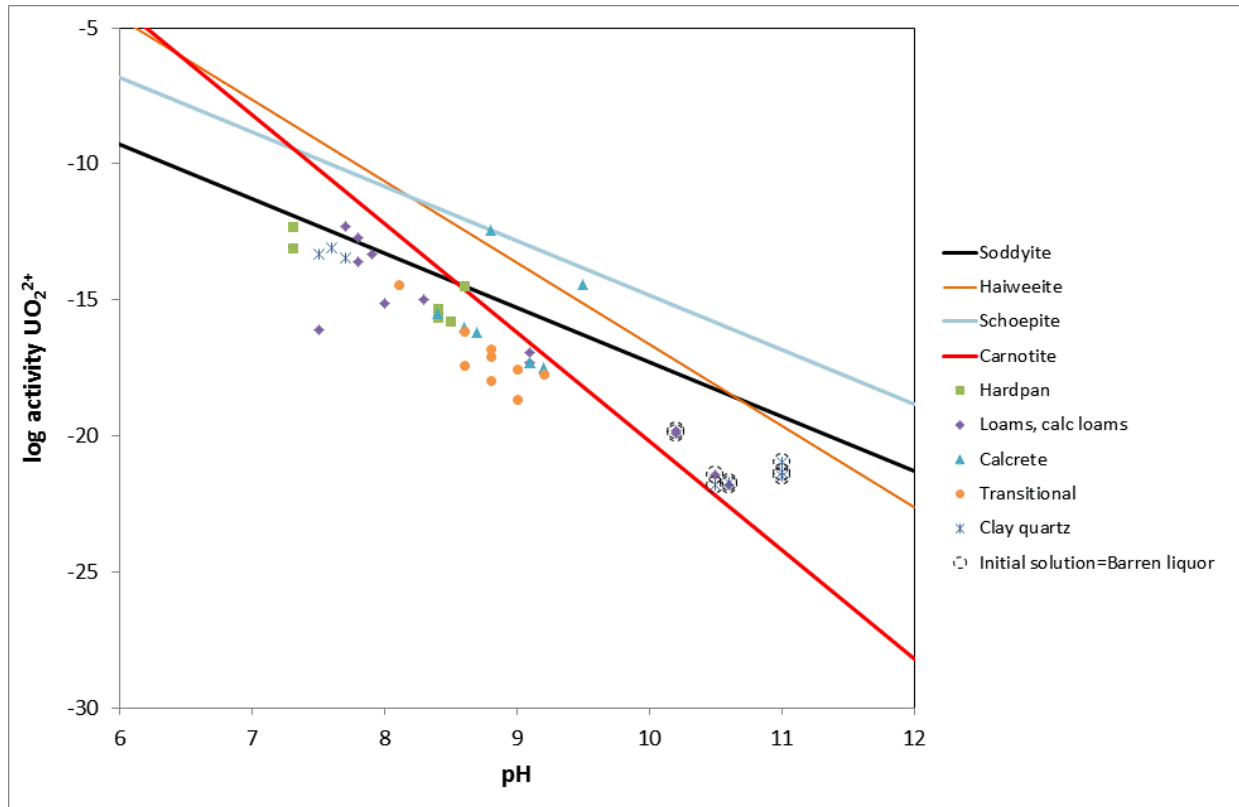

**Figure 4.28: Uranyl ( $UO_2^{2+}$ ) activity diagram showing the calculated activities of bottle roll leach solutions (3:1 liquid:solid ratio, air atmosphere)**  
 (Also shown are the theoretical equilibrium lines for a range of minerals)

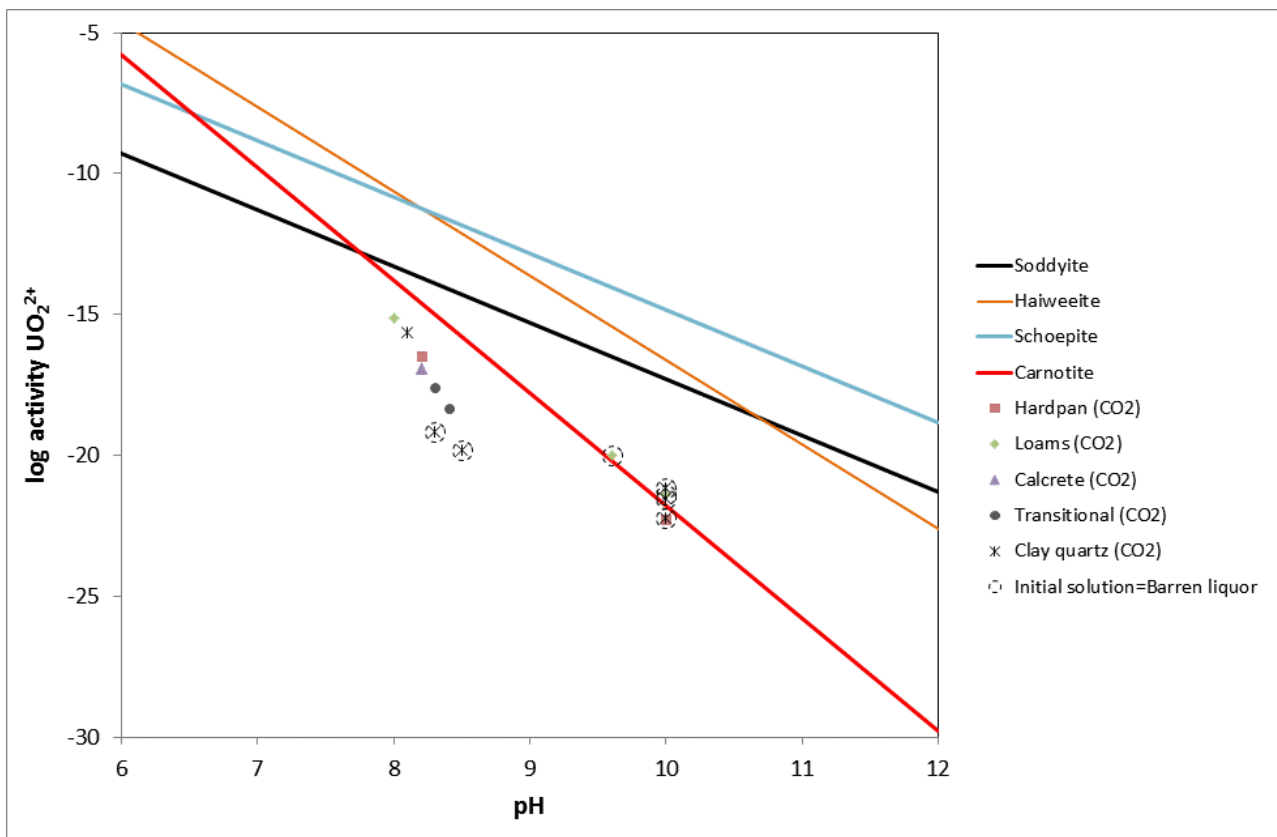

**Figure 4.29: Uranyl ( $UO_2^{2+}$ ) activity diagram showing the calculated activities of bottle roll leach solutions (3:1 liquid:solid ratio, 10%  $CO_2$  air mixture)**  
 (Also shown are the theoretical equilibrium lines for a range of minerals)

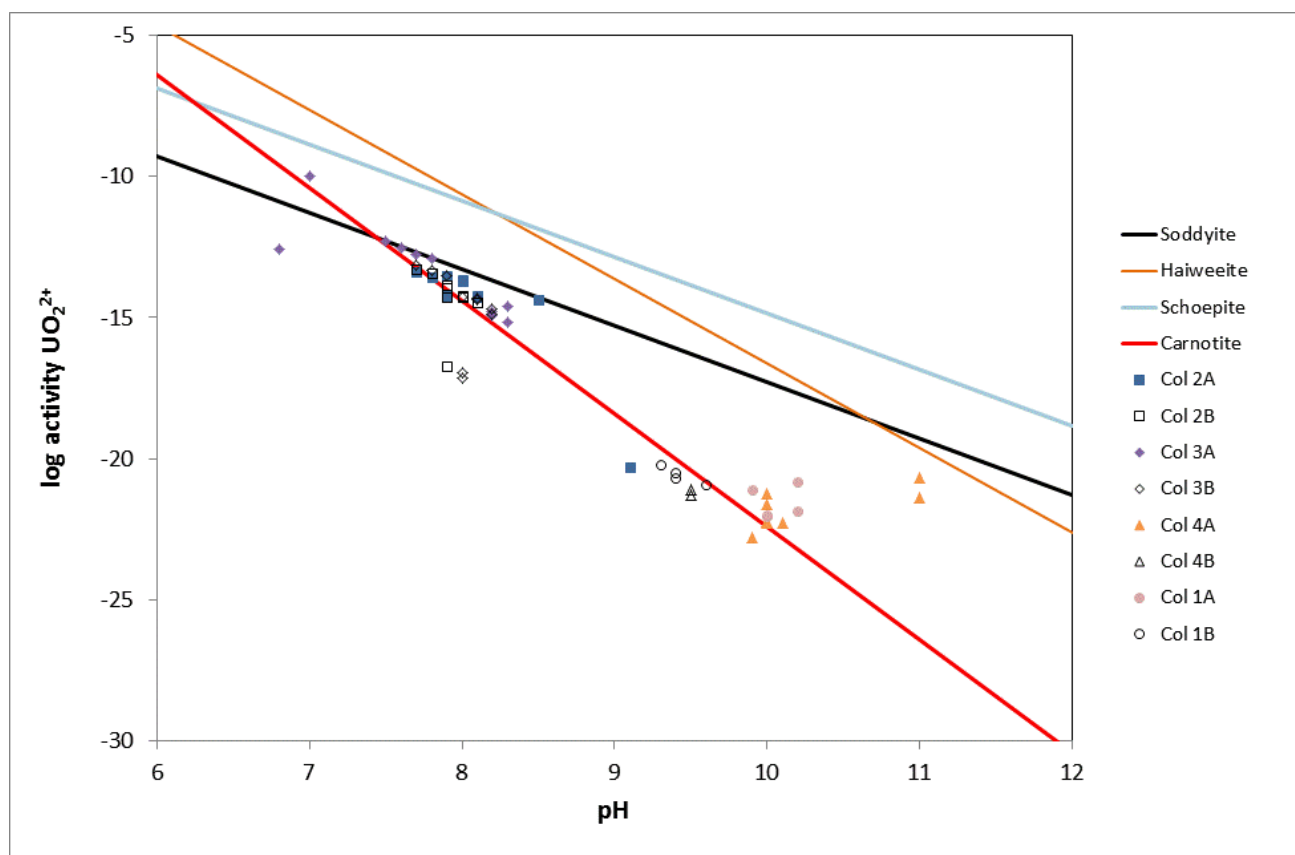

**Figure 4.30: Uranyl ( $\text{UO}_2^{2+}$ ) activity diagram showing the calculated activities of column leachates**  
(Also shown are the theoretical equilibrium lines for a range of minerals)

#### 4.6.2 Sorption

Sorption may be an important attenuation mechanism for metals and radionuclides. It can occur via a number of mechanisms, the most important being surface complexation and ion exchange.

Surface complexation is a pH-dependent process. The outer surfaces of most minerals hydrate when in contact with water. Loss or gain of protons from this hydrated surface layer results in development of surface charge. At acidic pH values, surfaces are predominantly positively charged (protonated), whereas at alkaline pH values the surface charge is predominantly negative (de-protonated). Ideal circumstances for sorption exist when the aqueous species and the surface are of opposite charge. Oxides/hydroxides are known to interact strongly with solution species via surface complexation. However, most minerals have some component of pH-dependent charge. For example, exposed aluminol ( $\text{Al-OH}$ ) and silanol ( $\text{Si-OH}$ ) sites on the surfaces and edges of silicate minerals may hydrate and interact with solution species in a similar manner.

Ion exchange is a process where solution ions exchange for ions that are present in the mineral lattice. For ion exchange to take place, the ions involved must be of similar charge and ionic radius. Ion exchange is largely independent of solution pH; the exchange sites are associated with a permanent charge. Clays and zeolites are known to have a high cation exchange capacity; exchange reactions involve cations that occupy interlayer or inter-framework positions, respectively. Oxides/hydroxides are not normally associated with a high exchange capacity, although impurities within the mineral lattice may result in some component of permanent charge.

The mineralogical investigation (Section 4.1) has identified the presence of iron oxides, e.g. goethite and hematite, in some of the Yeelirrie samples. Solubility modelling indicates that iron and aluminium concentrations in most leachates are consistent with control by iron and aluminium hydroxides. Most of the materials contain some quantity of such minerals, even if present at concentrations below the detection limits of XRD. Even a very small quantity by mass can represent a significant sorptive capacity due to the tendency of such minerals to form surface coatings on other mineral grains.

Clay minerals have been identified as important mineral constituents in all samples. The clay minerals are predominantly kaolin and smectite. The smectite-rich samples in particular were found to have significant cation exchange capacity.

Sorption is often represented by a distribution coefficient,  $K_D$ , as follows:

$$K_D = C_{ads}/C_{aq}$$

Where  $C_{ads}$  is the concentration of element adsorbed to the solid phase and  $C_{aq}$  is the concentration remaining in solution. In the current work,  $K_D$  values were calculated in two ways:

- Accounting for element 'already present' in the solid, i.e. assuming that it could participate in desorption/sorption during test; and
- Excluding element already present, i.e. assuming the element is present in an insoluble mineral form unlikely to participate in reaction during the test. Significant proportions of many elements may be associated with phases that do not interact with solutions under test conditions, or test timescales.

Distribution coefficients calculated without accounting for element already present are denoted as  $R_D$  values as follows:

$$R_D = (C_i - C_f)/C_i \times V/m$$

Where  $C_i$  and  $C_f$  are the initial and final solution concentrations of the element, and  $V/m$  is the volume to mass ratio that applied in the test.  $R_D$  values can only be calculated for those tests where the initial solutions contain dissolved solute (e.g. barren liquor solutions).

Ranges of calculated sorption coefficients for selected elements are shown in Table 4.12 (based on all lithologies except the palaeochannel sands). The negative  $R_D$  values calculated for some tests suggest leaching rather than sorption.

Sorption coefficients for palaeochannel sands are shown in Table 4.13. Palaeochannel sands have been treated separately because the extremely strong uranium sorption onto the sands appears to be at odds with trends shown elsewhere. Based on the high dissolved carbonate levels during the first stage of the barren liquor contact test (Section 4.3.5.2), weak sorption was expected. No explanation has yet been found for this unexpected result. For example, the mineralogical composition of the sands is dominated by quartz (91 wt%, Table 4.5). Quartz is not expected to be a strong adsorbent. The other mineral present is kaolin (9 wt%). Kaolin is known to be a strong adsorbent and could explain the strong sorption. However, other samples contained similar or higher quantities of kaolin, and were not associated with strong uranium sorption.

Within the barren liquor results, for some elements there was good agreement between the calculated  $K_D$  and  $R_D$  values— for example, sodium, arsenic, molybdenum, selenium, uranium and vanadium. For these elements, the  $K_D$  approach can be considered a good estimate of sorption. However,  $K_D$  values should still be used with caution as there remains a possibility that sorption is overestimated.

For many elements, the  $K_D$  values were significantly higher than the  $R_D$  values – for example, barium, chromium, radium and zinc. For these elements a major proportion of element present is likely to be in a form that does not readily interact with solutions under the conditions of the tests. The  $K_D$  value is therefore an overestimate of sorption and would be considered unreliable. Values believed to be unreliable are shaded in Table 4.12.

The ranges of sorption coefficients calculated from column test results are often very similar to those calculated from the bottle roll test results. However, for a number of elements including arsenic, boron, molybdenum, selenium, uranium and vanadium the column sorption coefficients ranged values higher than determined for the bottle roll tests. This may reflect a number of factors, such as slightly different chemical conditions in the columns, or the possibility that site saturation had occurred in the bottle rolls. It should also be noted that different ranges of sample types/numbers are represented in each set of results.

**Table 4.12: Calculated  $K_D$  and  $R_D$  values (in units of  $\text{cm}^3\text{g}^{-1}$ ) for Yeelirrie Materials (Excepting Palaeochannel Sands): Summary statistics**

Parameter		Bottle Rolls (De-ionised Water) <sup>[1,2]</sup>					Bottle Rolls (Barren Liquor) <sup>[1]</sup>					Columns (Range of Solution Types) <sup>[3]</sup>				
		Number of samples = 11; Water:solid ratio 3:1					Number of samples = 8; Water:solid ratio 3:1					Number of samples = 7; Water:solid ratio: 0.2-0.5:1				
		n	Minimum	Maximum	Median	Average	n	Minimum	Maximum	Median	Average	n	Minimum	Maximum	Median	Average
	pH	44	7.3	10.0	8.4	8.4	15	8.3	11	10.2	10.12	57	6.8	11.0	8.1	8.5
As	$K_D$	44	55	2700	420	620	15	0.55	22	1.3	5.9	56	0.73	1700	99	280
	$R_D$						15	0.038	19	0.82	4.3	36	-0.3	4.7	0.026	0.48
B <sup>[4]</sup>	$K_D$	44	17	890	130	180	15	2	5.3	3.8	3.7	56	1.7	240	16	51
	$R_D$						15	-0.6	0.91	0.21	0.19	36	-0.3	2.2	-0.04	0.062
Ba	$K_D$	44	390	14000000	5100	340000	15	580	33000	2000	4500	56	140	59000	3200	15000
	$R_D$						15	-3	0.41	-3	-2	36	-0.4	6.2	0.032	0.35
Cd <sup>[4]</sup>	$K_D$	44	-0.4	500	14	41	15	0.71	570	20	110	56	4.6	510	460	310
	$R_D$						15	-3	72	0	11	36	-0.4	8.2	0	1.2
Cr	$K_D$	44	2200	23000	9000	9200	15	10	21000	360	1900	56	24	20000	4000	4700
	$R_D$						15	-3	310	7.5	25	36	-0.2	29	0	2.4
Cu	$K_D$	44	440	5900	2600	2600	15	81	760	320	340	56	14	6100	1500	1700
	$R_D$						15	-1	8.4	1.1	1.7	36	-0.4	1.4	0	0.14
K	$K_D$	44	5.7	3800	160	380	15	2.7	12	7.6	7.8	56	3.7	69	13	18
	$R_D$						15	-0.5	0.67	-0.1	-0.07	36	-0.3	1.1	-0.05	-0.04
Mn	$K_D$	44	0.3	20	2	4	15	-1	6	2	3.1	56	0.1	20	2	4.7
	$R_D$						15	-2	0	0	-0.2	36	-0.2	5.5	0	0.15
Mo	$K_D$	44	8.2	520	100	130	15	0.62	2.4	1.4	1.4	56	1.3	410	16	49
	$R_D$						15	-0.7	1.5	0.43	0.35	36	-0.3	1.1	-0.2	-0.09
Na	$K_D$	44	1.4	110	11	21	15	-0.4	0.51	0.18	0.19	56	-2	25	0.37	2.3
	$R_D$						15	-0.5	0.39	0.062	0.095	36	-0.3	11	-0.06	0.28
Ni	$K_D$	44	640	15000	2400	2500	15	260	4000	2000	2000	56	350	5000	1000	1400
	$R_D$						15	-3	0	0	-0.7	36	-0.3	1.1	0	0.041
Ra-226	$K_D$	5	300	1700	1000	1000	3	60	340	300	230	7	16	5200	420	1400
	$R_D$						3	-0.6	2.8	0.26	0.82	4	-0.3	15	6.8	7
Se <sup>[4]</sup>	$K_D$	44	15.0	440	91	91	15	0.52	24	1.7	5.5	56	0.75	490	19	37

Parameter		Bottle Rolls (De-ionised Water) <sup>[1,2]</sup>					Bottle Rolls (Barren Liquor) <sup>[1]</sup>					Columns (Range of Solution Types) <sup>[3]</sup>				
		Number of samples = 11; Water:solid ratio 3:1					Number of samples = 8; Water:solid ratio 3:1					Number of samples = 7; Water:solid ratio: 0.2-0.5:1				
		n	Minimum	Maximum	Median	Average	n	Minimum	Maximum	Median	Average	n	Minimum	Maximum	Median	Average
	pH	44	7.3	10.0	8.4	8.4	15	8.3	11	10.2	10.12	57	6.8	11.0	8.1	8.5
	R <sub>D</sub>						15	-0.4	17	0.5	3.3	36	-0.3	2	-0.2	-0.01
Sn <sup>[4]</sup>	K <sub>D</sub>	44	410	2000	2000	1900	15	370	2000	1500	1400	56	5.2	2000	190	910
	R <sub>D</sub>						15	-2	3	1.3	1.1	36	-0.4	0.054	-0.3	-0.2
Sr	K <sub>D</sub>	44	33	13000	1600	2900	15	17	19000	220	1900	56	9.6	2900	120	430
	R <sub>D</sub>						15	-3	2.3	-3	-2	36	-0.3	0.9	-0.2	-0.1
Tl <sup>[4]</sup>	K <sub>D</sub>	44	3.5	600	85	280	15	14	600	370	340	56	270	3000	600	670
	R <sub>D</sub>						15	-3	0	-1	-1	36	-0.2	1.9	0	0.072
U	K <sub>D</sub>	44	82	11000	750	1700	15	-0.2	16	1.3	3.3	56	-0.4	9800	1100	1700
	R <sub>D</sub>						15	-0.3	16	0.9	2.4	36	-0.3	0.62	-0.02	0.0011
V	K <sub>D</sub>	44	100	6400	700	1500	15	0.85	8.9	2.9	4	56	1.5	2900	650	870
	R <sub>D</sub>						15	-0.3	4	0.89	1.4	36	-0.3	26	0.047	1.9
Zn	K <sub>D</sub>	44	85	5000	380	1200	15	16	280	63	75	56	39	7000	320	1300
	R <sub>D</sub>						15	-2	1.3	-2	-2	36	-0.06	2.6	0.26	0.43

Notes:

- [1] Each dataset includes a range of atmospheric conditions: air, air:10%CO<sub>2</sub> mixture.
- [2] Results from progressive leach testing have been included – i.e. from the second and third leach cycles. For some elements, the second and third leach tests may give better indicators of sorption because the influence of readily soluble salts is less in these later sequences.
- [3] Column inflow solutions included de-ionised water, barren liquor and, in the case of the 'B' columns, effluent from the paired 'A' column (Table 4.8). Data from Column 1A (tails) was excluded.
- [4] These elements were present in the solids at levels close to or below the limits of detection. Where values were below the detection limit, the detection limit itself was used in the K<sub>D</sub> calculation. Thus, the calculated K<sub>D</sub> value is the maximum that could apply.

Values shaded grey are considered unreliable as most of the element mass present in the solid may not have interacted with the solution phase during the test.

**Table 4.13: Sorption Coefficients Calculated for the Paleochannel Sand Samples**



Parameter	$R_D$ values, $\text{cm}^3\text{g}^{-1}$	
	YYHC0075 64 m – 65 m	YYHC0059C 55 m – 56 m
pH	11	11
K	0.2	0.7
Na	0.1	0.4
As	81.6	53.4
B	0.2	0.3
Cr	10.6	11.0
Cu	45.0	45.0
Mo	0.6	1.0
Se	13.5	17.4
Sn	3.0	3.0
Tl	-2.5	0.0
U	60,000	60,000
V	0.2	0.1
Zn	0.3	1.1

Sorption coefficients calculated for barren liquor conditions were typically less than  $10 \text{ cm}^3\text{g}^{-1}$ . Low sorption is expected under the geochemical conditions in question. The barren liquor contains high dissolved carbonate. Many elements form aqueous complexes with carbonate and carbonate complexation reactions can compete with surface sorption reactions, causing reduced sorption. As well, the solution pH is quite alkaline, ranging up to pH 11. At alkaline pH values the surface charge on most minerals is predominantly negative (de-protonated). Negatively charged aqueous species will be repelled from such surfaces. Under the alkaline, carbonate-rich geochemical conditions of these solutions, many elements form either negatively charged carbonate species (e.g.  $\text{UO}_2(\text{CO}_3)_2^{-2}$ ,  $\text{Cu}(\text{CO}_3)_2^{-2}$ ) or negatively charged hydroxyl species (e.g.  $\text{Ni}(\text{OH})_3^-$ ). Such an effect may also explain the observation in Section 4.2.5.4 that uranium and vanadium leachate concentrations tend to be higher at more alkaline pH (i.e. reduced sorption under these conditions). The effect of dissolved carbonate on uranium sorption is also illustrated in Figure 4.31, which compares results for equivalent tests in contact with air and tests in contact with an mixture of air and 10%  $\text{CO}_2$ .



Sorption coefficients calculated for de-ionised water tests were up to three orders of magnitude higher than those for barren liquor tests, reflecting stronger sorption when dissolved carbonate and solution pH are lower.

Figure 4.31 to Figure 4.35 show sorption of uranium, vanadium, arsenic, selenium and zinc onto a range of sample types. Although the lowest sorption coefficients were found for tests involving calcrete, there does not appear to be a strong correlation between sorption and lithological type. Possibly the lower sorption onto calcrete is related to presence of relatively low clay contents in this lithology (Table 4.1). Clays, and in particular kaolin, are known to be a strong sorbents for many elements; the presence of these clays are likely to explain the higher sorption coefficients measured in loams and clay-quartz lithologies.

The high smectite clay content of some samples explains the measurable sorption of sodium (and sometimes potassium) onto the materials. Given the very high concentrations of sodium and potassium in the initial barren liquor solution, the fact that measurable sorption takes place indicates that the smectite clay material has a high capacity to adsorb these elements. This is likely attributable to ion exchange as it also explains the observed calcium, magnesium, strontium and barium leaching (Section 4.3.5). Alkaline earths and alkali metals (e.g. sodium, potassium, calcium and magnesium) are known to participate strongly in ion exchange reactions, in part because they remain in the form of monovalent or divalent cations over a wide pH range. Strongest sodium sorption, and higher degrees of calcium and magnesium leaching coincide with the distribution of smectite (and higher cation exchange capacity) samples.

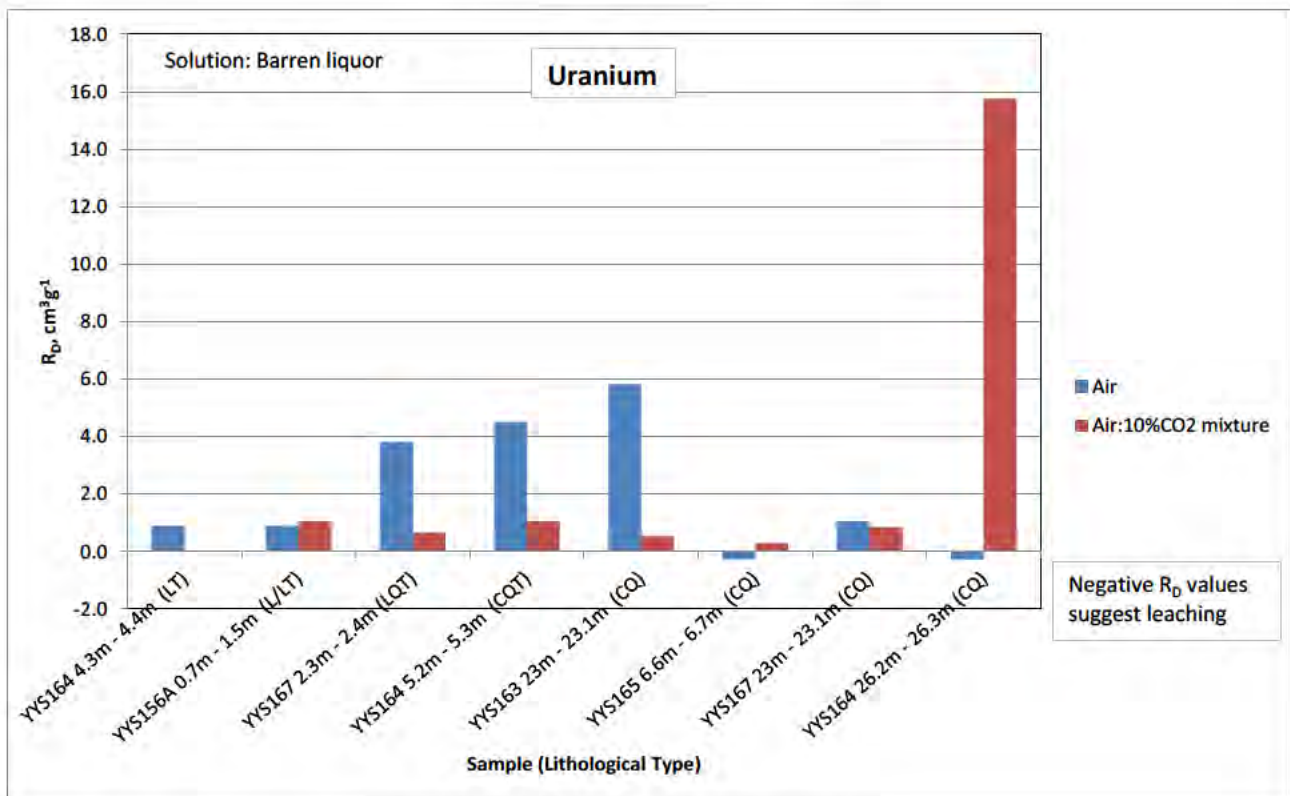
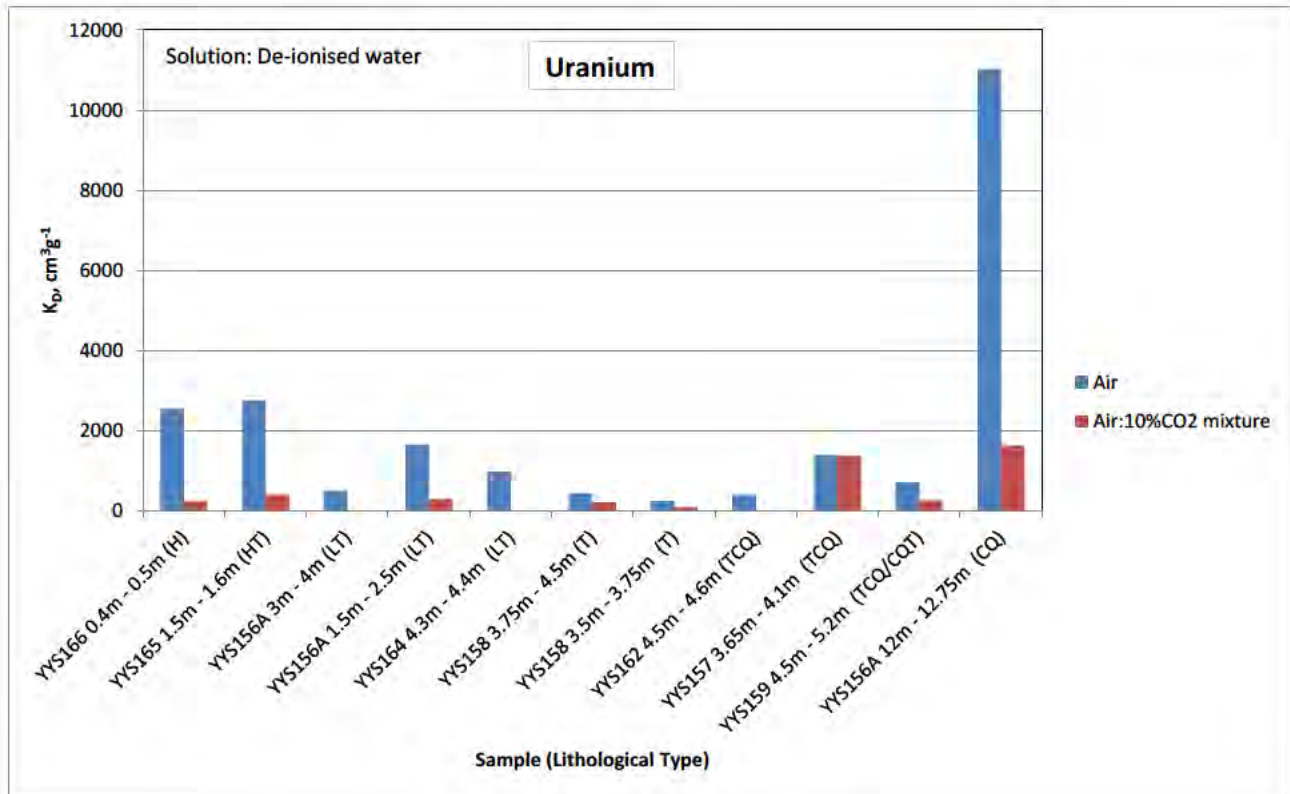


**Figure 4.31: Sorption coefficients for uranium**  
 [Note the different scales on the y-axes of the two diagrams]

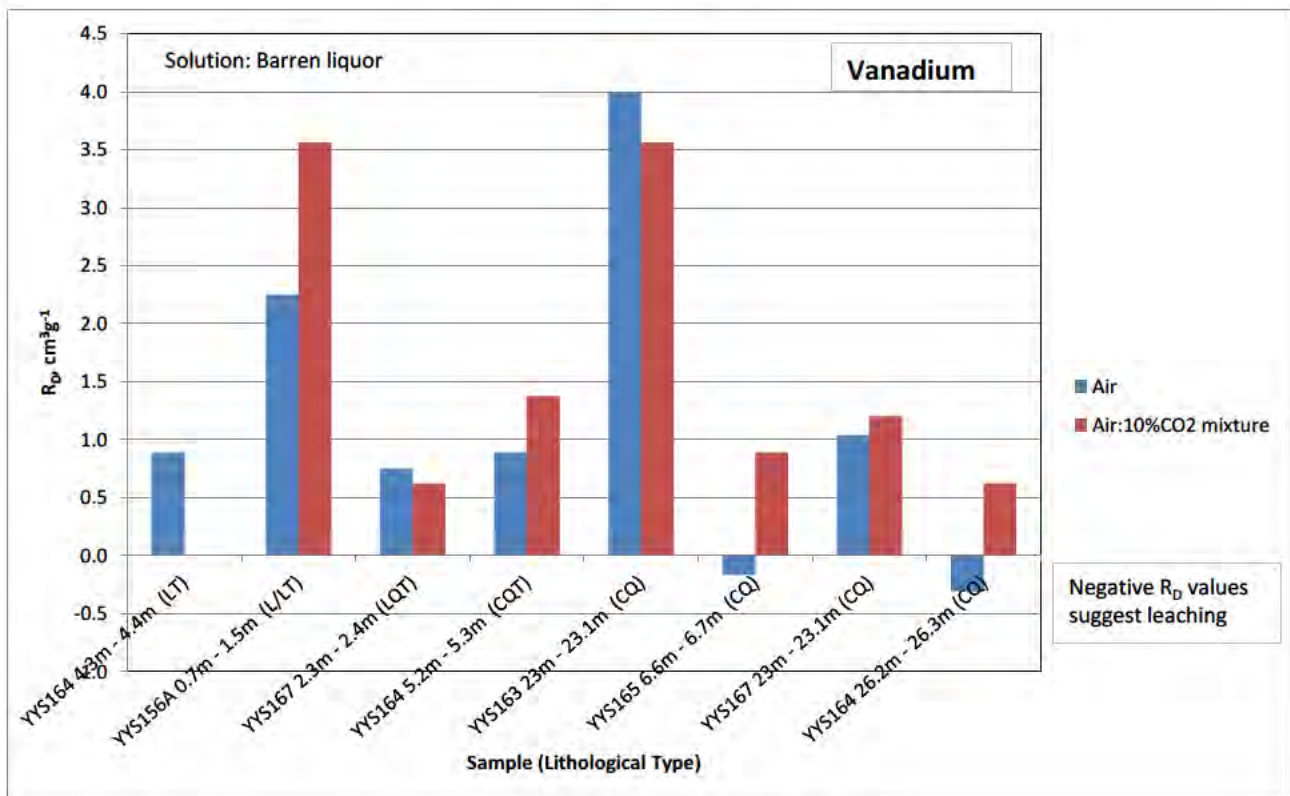
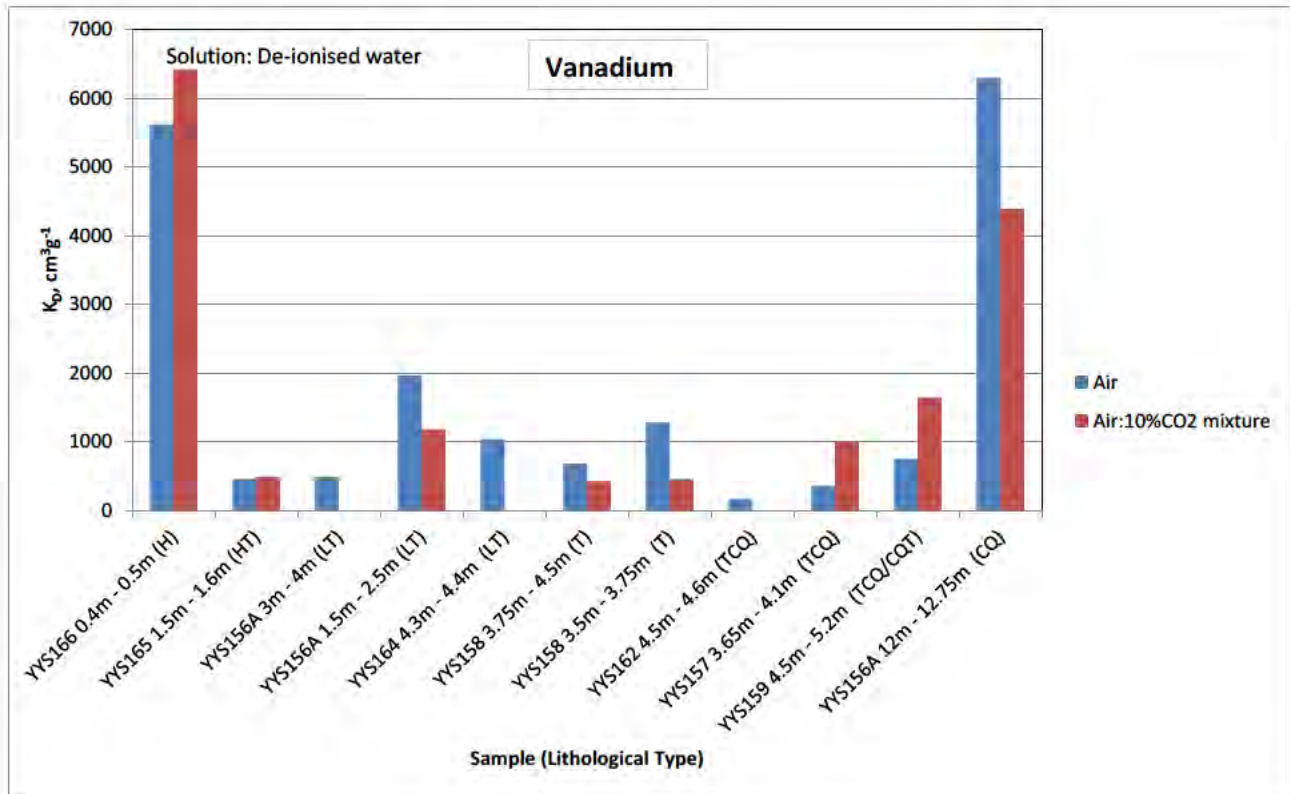


**Figure 4.32: Sorption coefficients for vanadium**  
 [Note the different scales on the y-axes of the two diagrams]





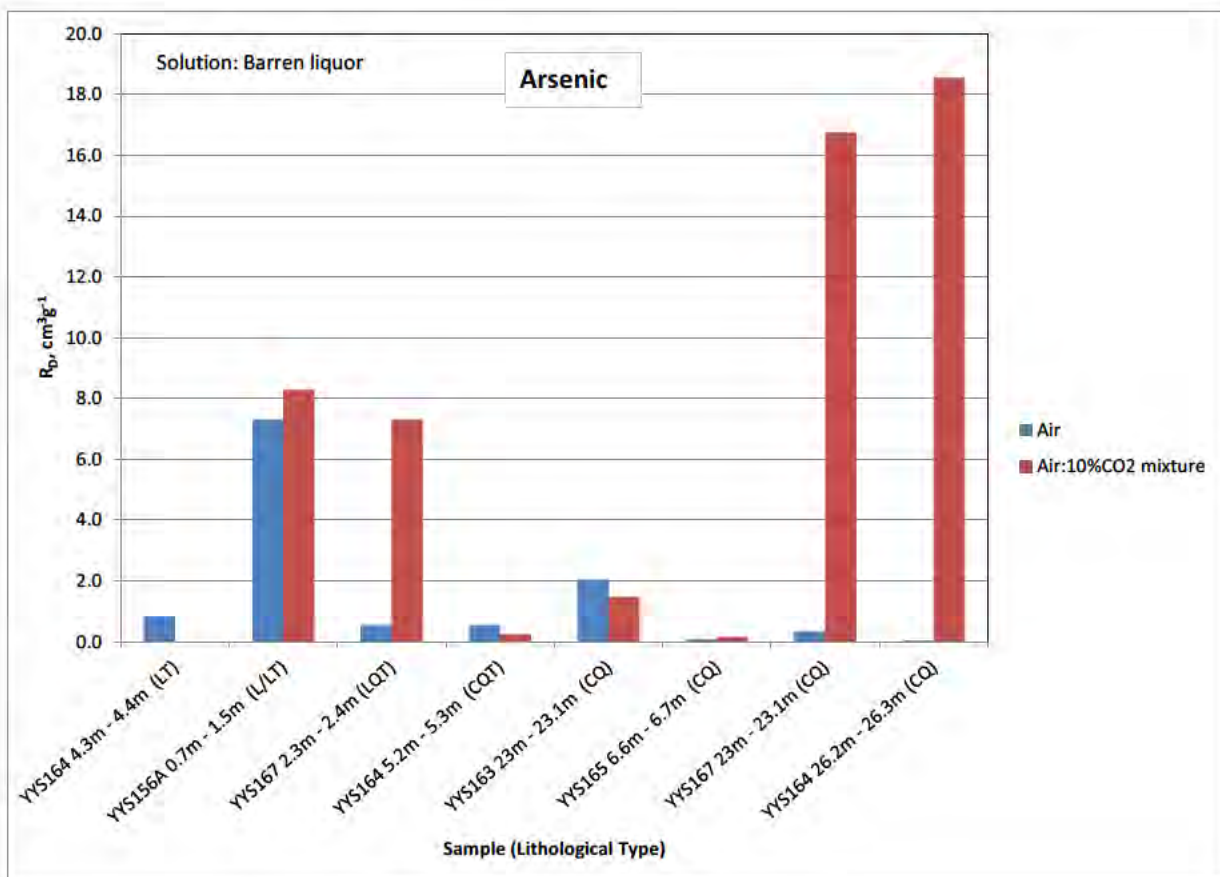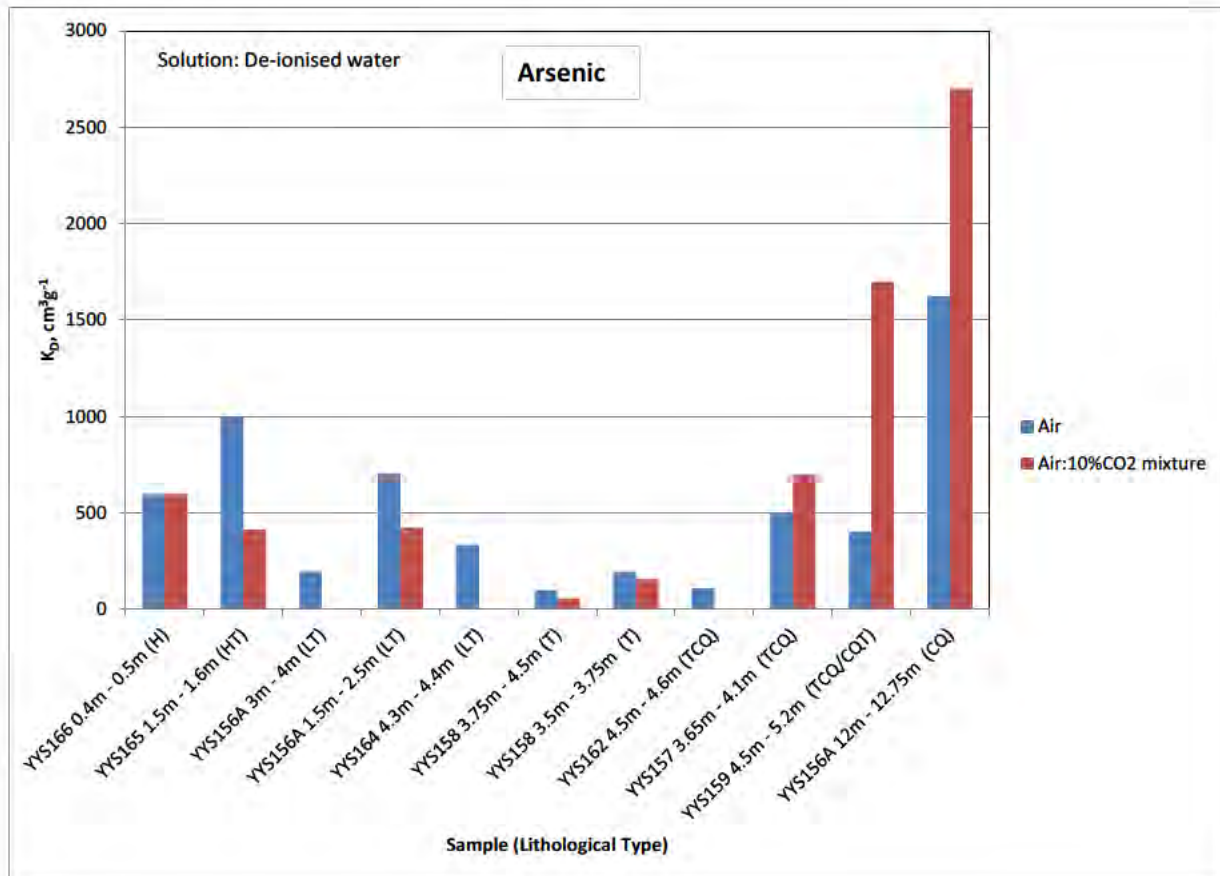

**Figure 4.33: Sorption coefficients for arsenic**  
 [Note the different scales on the y-axes of the two diagrams]

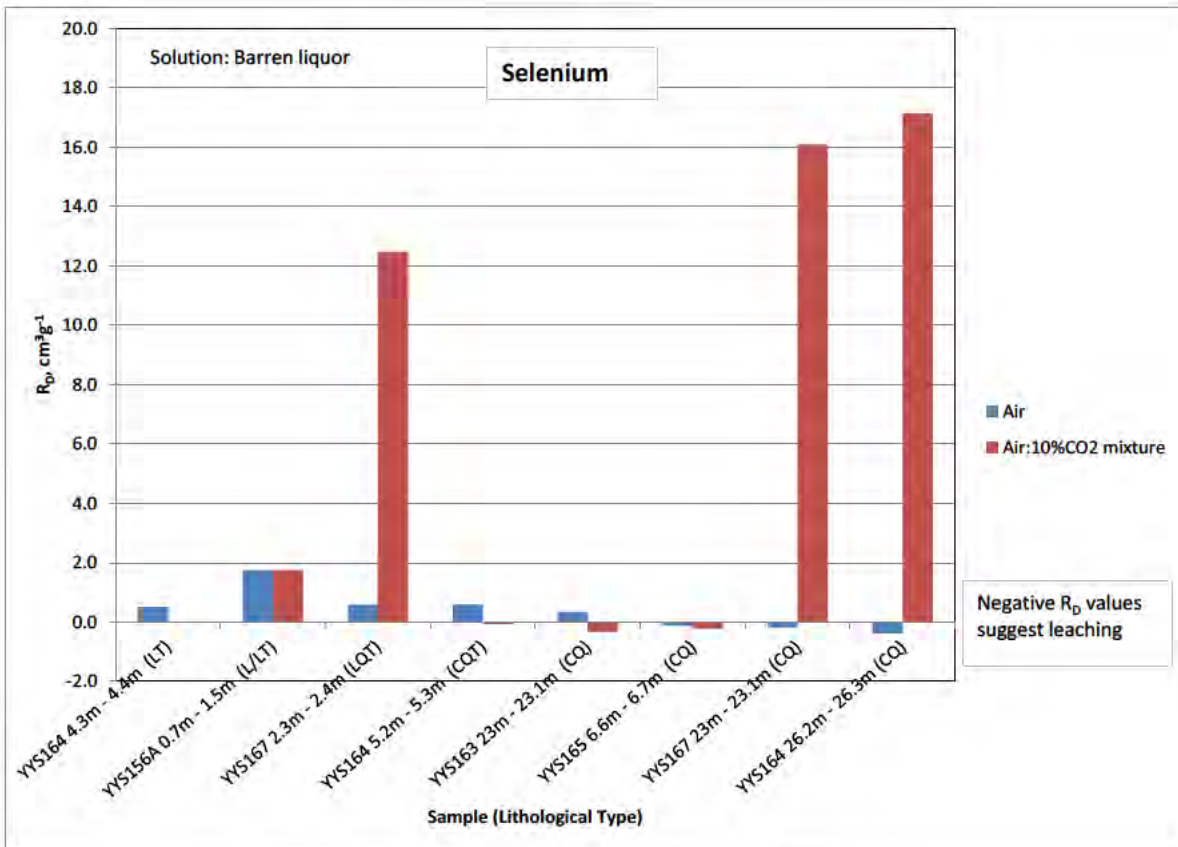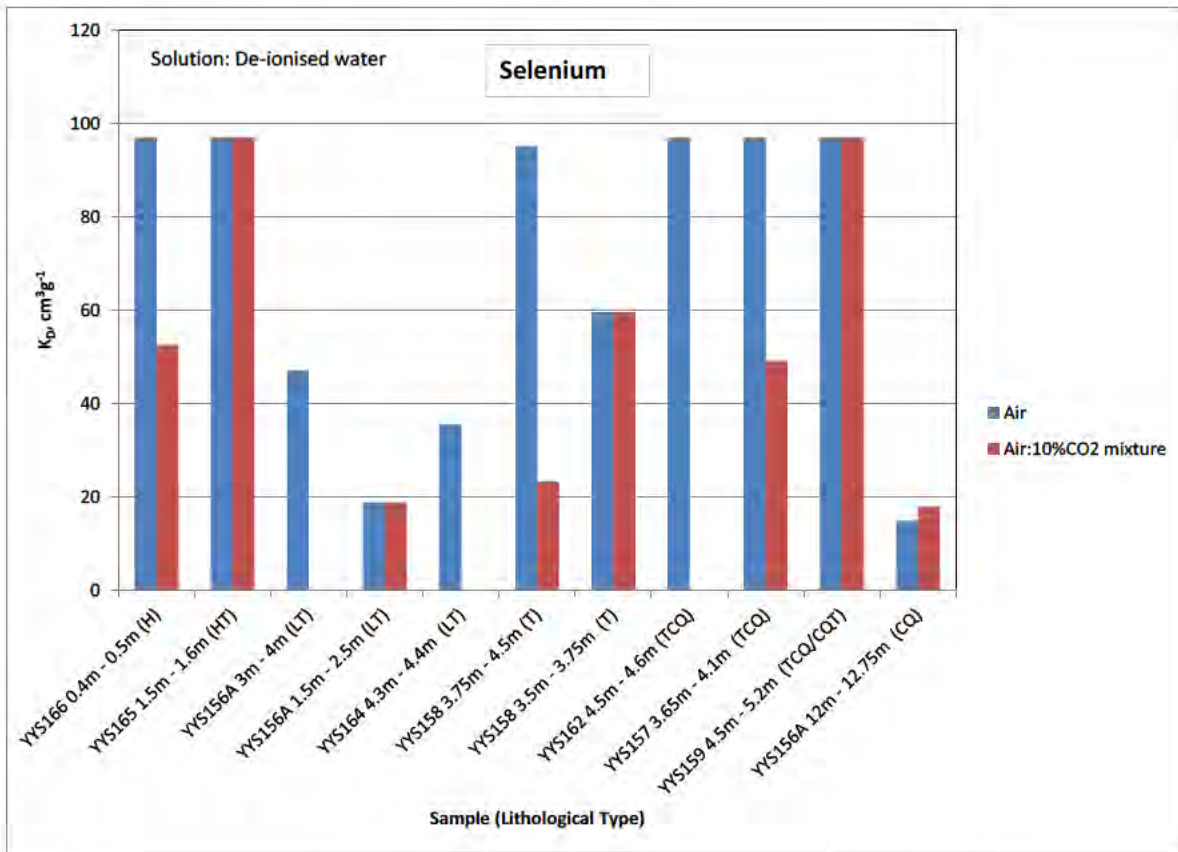

**Figure 4.34: Sorption coefficients for selenium**  
[Note the different scales on the y-axes of the two diagrams]

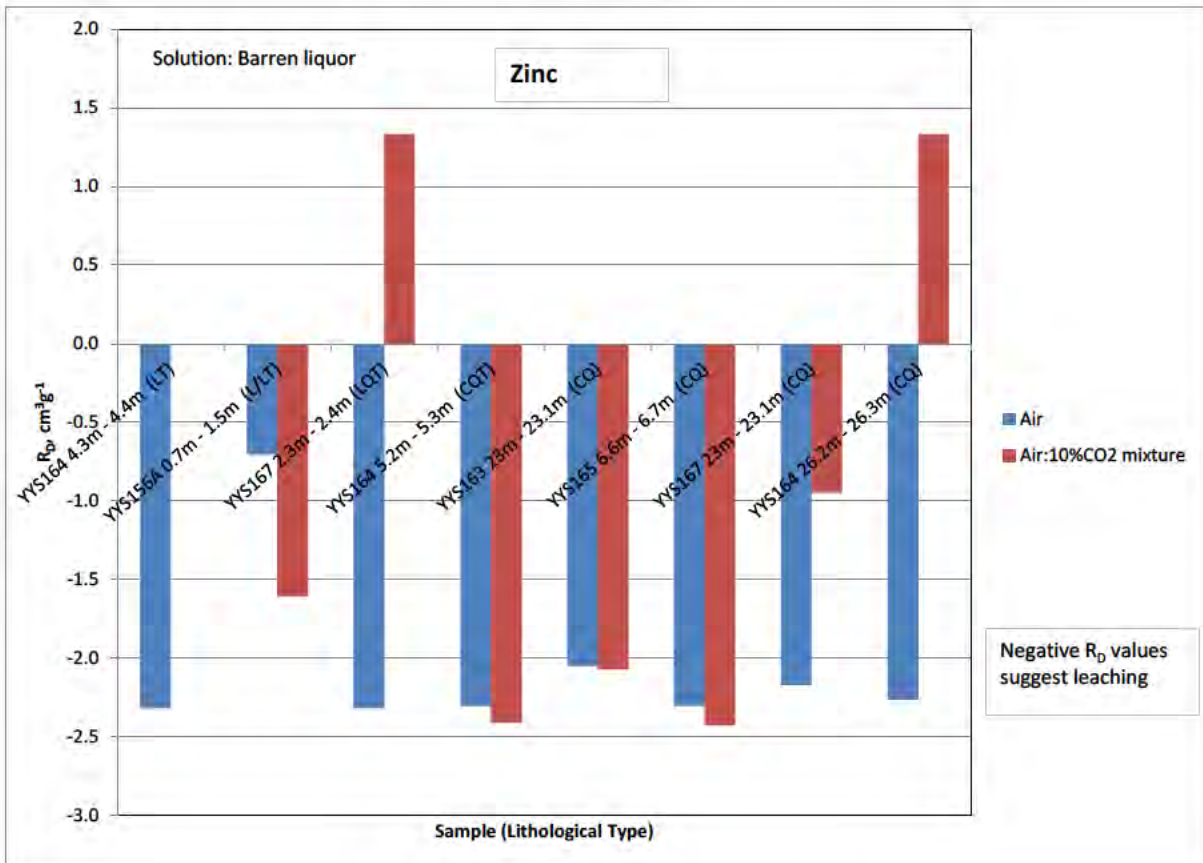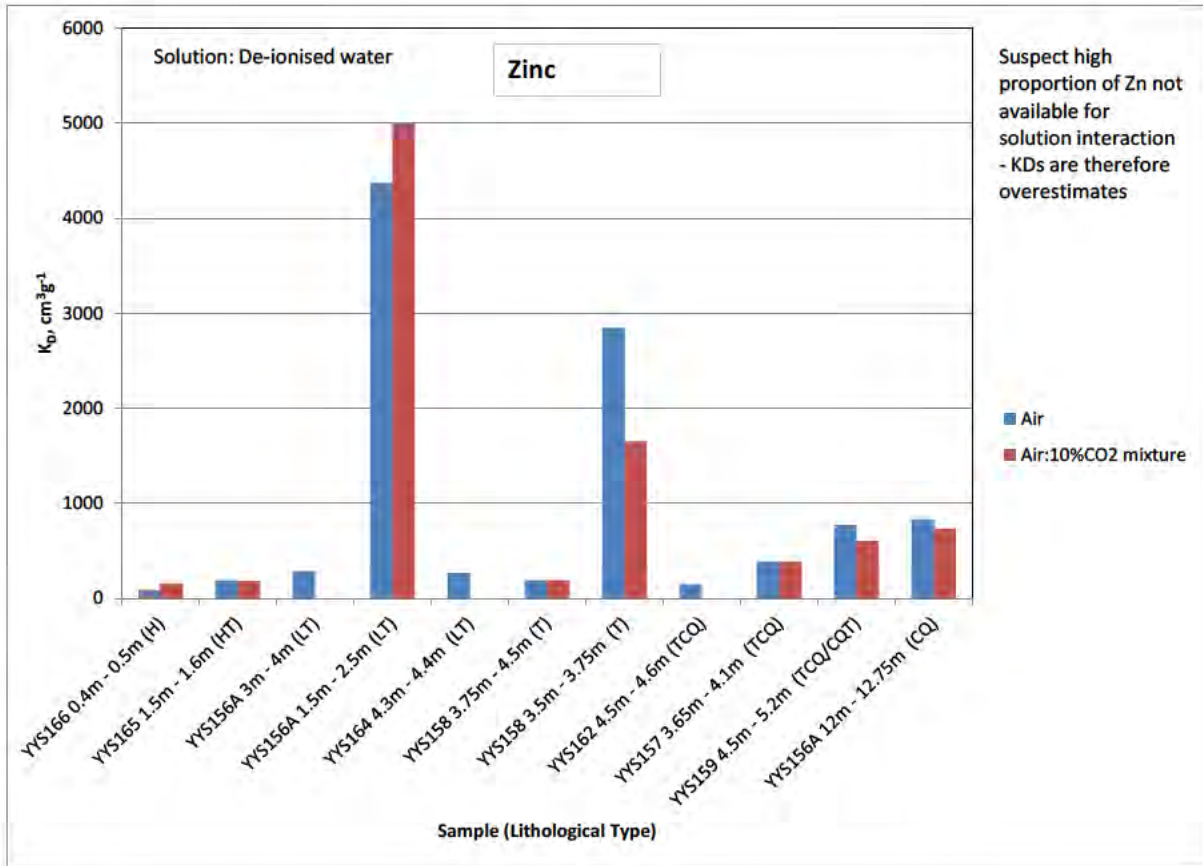

**Figure 4.35: Sorption coefficients for zinc**  
[Note the different scales on the y-axes of the two diagrams]

### 4.6.3 Summary

Results collected for a range of material types, and under a range of geochemical conditions, have been interpreted to gain insight to geochemical controls on contaminant mobility.

With respect to uranium and vanadium, the main control on mobility is considered to be carnotite solubility. In ore and waste rock stockpiles, uranium and vanadium will leach as the carnotite dissolves. Where the mass of carnotite in the material is low, the dissolved uranium and vanadium may remain under-saturated with respect to carnotite because there is insufficient mass of carnotite present to attain equilibrium with the contacting solution. However, in cases where the mass of carnotite is high, or where the volume of contacting water is low, saturation with respect to carnotite is more likely to occur. Carnotite solubility will define an upper limit on dissolved uranium and vanadium concentrations. Amongst other parameters, carnotite solubility is sensitive to solution pH, dissolved carbonate, potassium concentrations and redox.

Carnotite solubility controls will play an important role in limiting the amount of uranium and vanadium leaching from mine waste rock and tailings materials, and could limit their mobility along flow paths within the groundwater system.

The uranium:vanadium molar ratio in carnotite is unity (1.0). However, solution uranium:vanadium ratios are often less than 1.0, indicating that uranium may be preferentially held within the solid phase, possibly indicative of the influence of sorption. The laboratory results have been assessed to derive estimates of sorption coefficients, for uranium, vanadium and other potential contaminants. Table 4.14 is a summary of sorption coefficients that could apply to loams and clay-quartz materials. These are based on median values calculated from the combined set of calculated  $R_D$  and  $K_D$  values.

**Table 4.14: Recommended Sorption coefficients for Yeelirrie Materials**

	Sorption coefficient, $\text{cm}^3\text{g}^{-1}$	
	Loams	Clay-Quartz
<b>As</b>	350	1.3
<b>Ba</b>	0	0
<b>B</b>	51	3
<b>Cd</b>	0	5.3
<b>Cr</b>	4	10
<b>Cu</b>	0.93	1.1
<b>Mn</b>	2	2
<b>Mo</b>	47	0.67
<b>Ni</b>	0	0
<b>Se</b>	50	0.83
<b>Sr</b>	0	0
<b>Tl</b>	0	0
<b>Sn</b>	0.7	1.9
<b>U</b>	420	1.1
<b>V</b>	480	2.7
<b>Zn</b>	0	0
<b>Ra-226</b>	0	2.8

The highest sorption is expected for loams. Strong U sorption onto loams is consistent with outcomes of the radionuclide assessment (Section 4.5). Lower sorption is expected in the case of the clay-quartz lithology. In the case of calcrete, little or no sorption is expected to occur.

Sorption is dependent upon geochemical conditions, e.g. solution pH, dissolved carbonate and alkalinity. Under the highly alkaline conditions of the TSF porewater sorption will be weak. However, along potential groundwater flow paths away from the TSF, conditions will become less alkaline, and sorption would become a more significant mechanism contributing to the attenuation of solutes.

## 5. Tailings

### 5.1 Introduction

Tailings solids and liquors were prepared by the BHP Billiton metallurgical testwork programme:

- YC3 – bulk leach residue, provided during December 2009
- Barren liquor – solution resulting from the bulk leach, following precipitation of uranium and re-carbonation (also provided during December 2009)
- YM0015, YM0046, YM0074, YM0076 – bulk leach residues, provided during March 2010.

### 5.2 Mineralogy

The mineralogical compositions of the tailings samples are given in Table 5.1. The dominant minerals are carbonates in the case of tailings generated from the processing of calcrete ore, and silicates in the case of tailings generated from clay-quartz ore.

### 5.3 Surface Characteristics

One sample was submitted for surface area and ion exchange capacity measurements, Sample YC3. The surface area of the sample was 46.2 m<sup>2</sup>/g and the cation exchange capacity was 45.2 meq/100g. The dominant cation occupying the sites was Ca.

### 5.4 Particle Size Distribution

The particle size distribution for sample YC3 is given in Figure 5.1.



Figure 5.1: Particle size distribution for tailings sample, YC3

### 5.5 Bulk Chemistry

The results of the bulk chemical analyses of the tailings samples are provided in Appendix 3, and summarised in Table 6.2.

**Table 5.1: Mineralogical Composition of Yeelirrie Tailings Samples**

Sample	Description	Carbonates			Framework and chain silicates			Sheet silicates and clays					Oxides		Sulphates		Other	
		Calcite	Mg-Calcite	Dolomite	Quartz	Albite	Microcline	Kaolin	Smectite	Illite / Mica	Sepiolite	Palygorskite	Anatase	Goethite	Gypsum	Celestine	Halite	Carnotite
YC3		10		24	23	1	3	22	10	1	2	3	<1					
YM0015	High U grade, clay/quartz			1	34	1	5	45	5	6			<1	2		1	<1	0.4
YM0074	low U grade, clay/quartz			1	23	1	4	53	4	3		7	<1	2		1	1	0.2
YM0076	high U grade, calcrete	3		78	3	1	1	7	4						1	2	<1	0.3
YM0046	low U grade, calcrete	13		38	5	1	2	6	22	1	8				3		1	

**Table 5.2: Chemical Composition of Yeelirrie Tailings Samples**

Element	Units	YC0076	YM0015	YM0046	YM0074	YC3	Mean Crustal Abundance <sup>[1]</sup>
Al	%	1.61	8.99	1.61	10.64	5.48	8.2
Ca	%	17.69	0.42	13.77	0.35	6.85	4.1
CO <sub>2</sub>	%	35.98	1.41	24.09	1.16	12.3	
F	%					0.26	
Fe	%	0.73	3.53	0.72	4.31	2.4	4.1
K	%	0.31	1.58	0.4	1.69	1.04	2.1
Mg	%	10.83	1.72	9.37	1.66	5.17	2.3
Mn	%	0.03	0.02	<0.01	0.02	0.03	0.095
Na	%	0.37	1.24	1.12	1.2	1.45	2.3
P	%	0.01	<0.01	<0.01	0.01	0.02	0.1
S	%	0.03	0.05	0.08	0.05	0.04	
Si	%	6.64	28.36	13.28	27.05	20.3	
SO <sub>4</sub>	%					0.15	0.078
TOC	%					0.05	
Ag	ppm	<0.05	<0.05	0.05	<0.05	0.1	0.07
As	ppm	2.42	15.16	2.98	21.21	15.5	1.5
B	ppm					100	10
Ba	ppm	<200	400	<200	400	230	500
Be	ppm					1	2.6
Bi	ppm	<0.1	0.22	<0.1	0.27	0.2	0.048
Cd	ppm	<0.1	<0.1	<0.1	<0.1	0.1	0.11
Ce	ppm	<100	<100	<100	<100	32	
Co	ppm	3.67	7.07	2.86	7.47	6	20
Cr	ppm	76	137	52	128	130	100
Cu	ppm	17.2	23.24	18.76	27.98	23.5	50
Hg	ppm					0.05	0.05
Li	ppm					15	20
Mo	ppm	5.4	5.34	3.43	5.58	13	1.5
Ni	ppm	36	45	28	46	60	80
Pb	ppm	4.79	15.81	5.07	17.18	9	14
Sb	ppm	<0.1	0.1	<0.1	<0.1	0.1	0.2
Sc	ppm	<5	11	<5	14	10	
Se	ppm	<0.5	<0.5	<0.5	<0.5	0.5	0.05
Sn	ppm					10	2.2
Sr	ppm	8184	5560	928	4713	2100	370
Th	ppm	3.14	19.61	3.07	20.22	15	
Tl	ppm					3	0.6
U <sub>3</sub> O <sub>8</sub>	ppm	95	229	63	66	180	2.8
V	ppm	49	222	84	177	230	160
W	ppm					3	
Y	ppm	<10	11	<10	13	9	
Zn	ppm	12.68	40.9	19.26	45.53	37	75

[1] Mean crustal abundances taken from Bowen 1979

[2] Results for samples as tested for current programme; note however that the average U<sub>3</sub>O<sub>8</sub> from 56 samples was = 84.6 ppm.

## 5.6 Metal Leaching

Metal leaching was assessed by column testing (Column 1A). Results are shown in Figure 5.2 to Figure 5.5. As described elsewhere, the leachate from the tailings column was transferred to a second column, which was operated in series to assess the interaction with native materials. The results for the second column, Column 1B, which contained clay-quartz material, are also shown in the figures.

Trends shown in Column 1A results are as follows:

- The shape of the sodium release curve can be approximated quite well by a power law (see Figure 5.2), as can the uranium release (Figure 5.4).
- Calcium release increases during the first four pore volumes displaced, but decreased in the fifth displacement.
- Vanadium concentrations appear to oscillate between 15 and 19 mg/L (if the result for the third pore volume displacement is disregarded).

The results for Column 1B are consistent with some of the geochemical controls discussed in previous sections. For example, attenuation of sodium in the first pore volume displaced. The coincident leaching of calcium is indicative of ion exchange. In later pore volumes sodium concentrations in the outflow are greater than the inflow, suggesting that Na leaching takes place in Column 1B. One possible explanation is that some previously exchanged sodium is displaced by other solutes. From the sixth pore volume exchange onward, the inflow to Column 1B was de-ionised water. Since sodium leached during the sixth pore volume exchange, the attenuation that took place during the first five pore volume exchanges is shown to be reversible.

Both uranium and vanadium are attenuated in Column 1B. In the case of uranium, it appears that the attenuation is exhausted after the second pore volume was displaced, and uranium leaches during the third exchange. In contrast, vanadium continues to be attenuated through to the fourth pore volume displacement. Similar trends in uranium and vanadium attenuation behaviour were observed in the Column 4A and 4B pair (Section 4.4.1). There is evidence of desorption of uranium during the sixth pore volume exchange, when the inflow water becomes de-ionised water instead of the outflow from Column 1A.



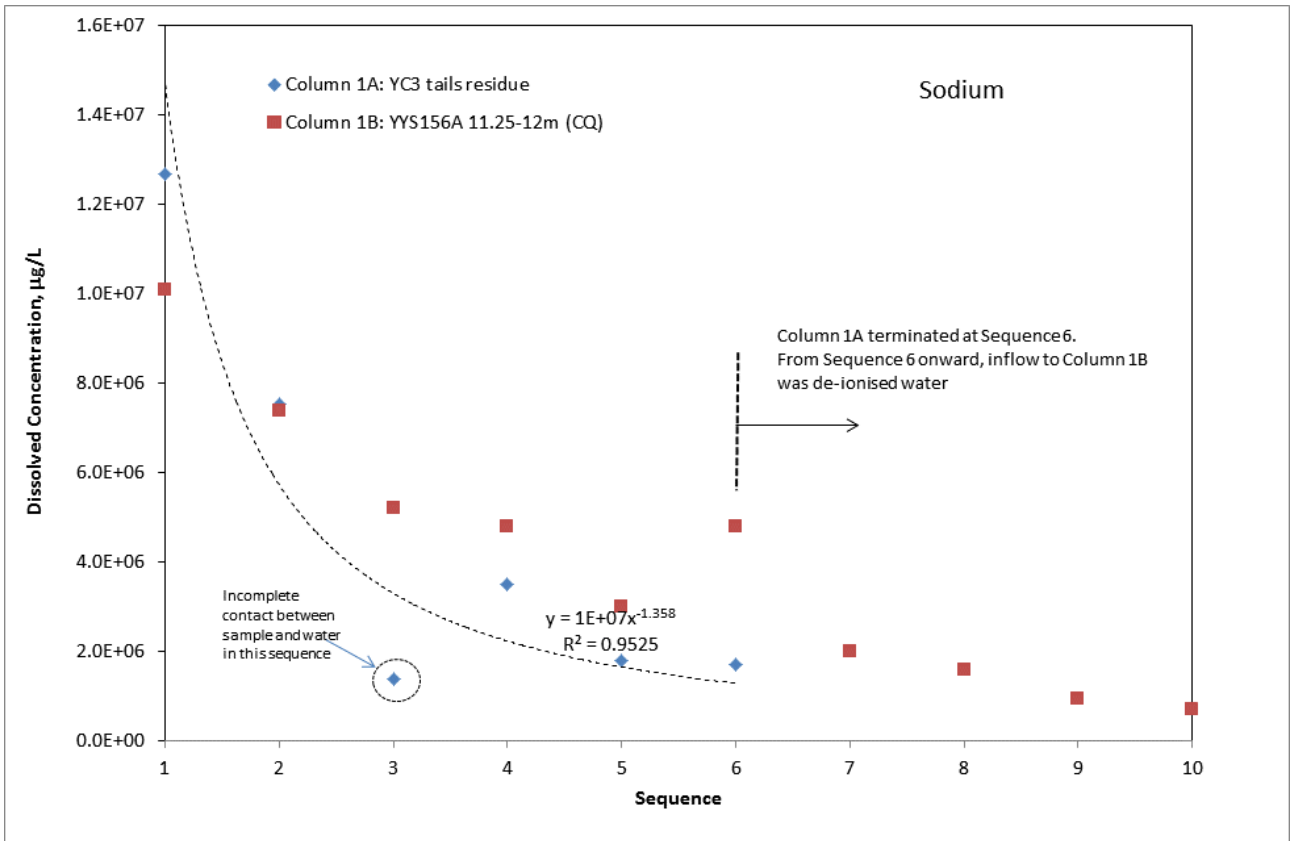


Figure 5.2: Dissolved sodium concentrations in leachates from Columns 1A and 1B

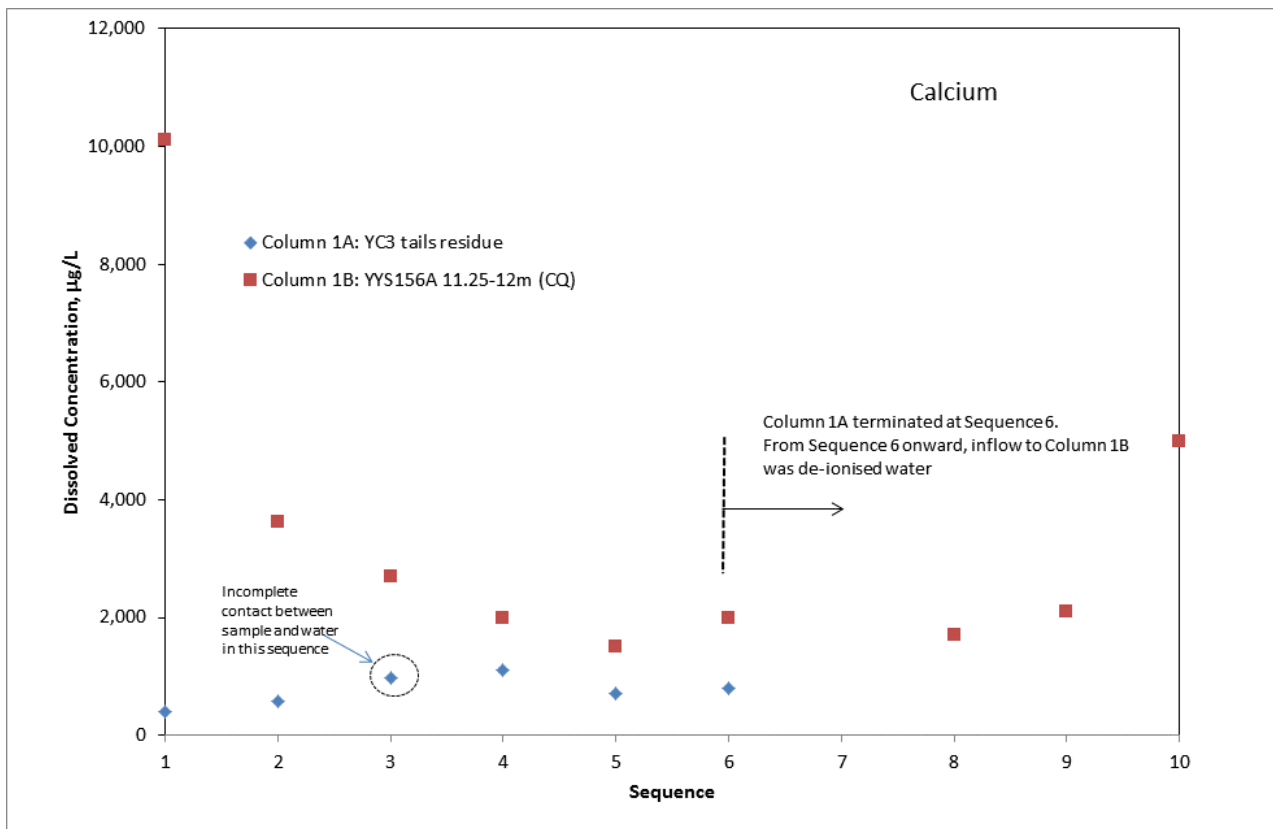


Figure 5.3: Dissolved calcium concentrations in leachates from Columns 1A and 1B

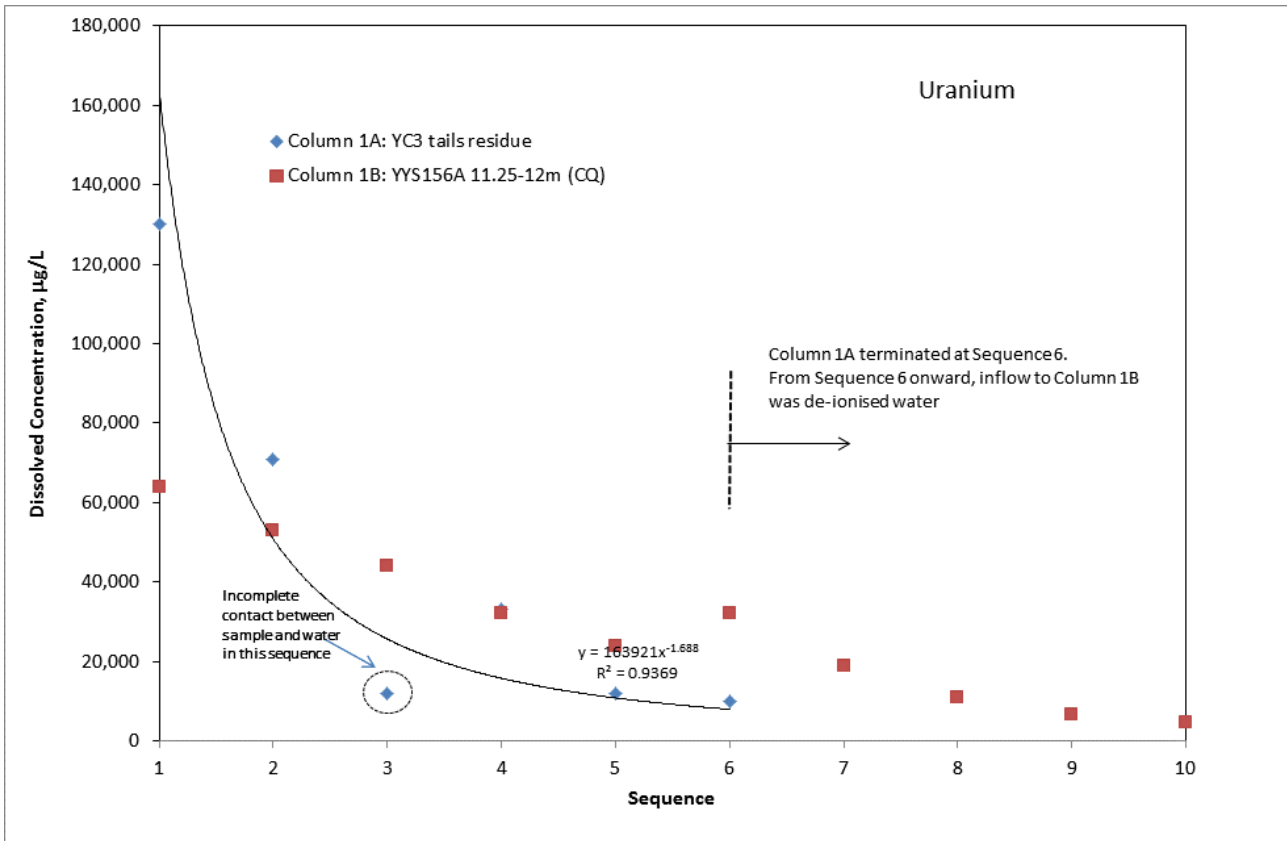


Figure 5.4: Dissolved uranium concentrations in leachates from Columns 1A and 1B

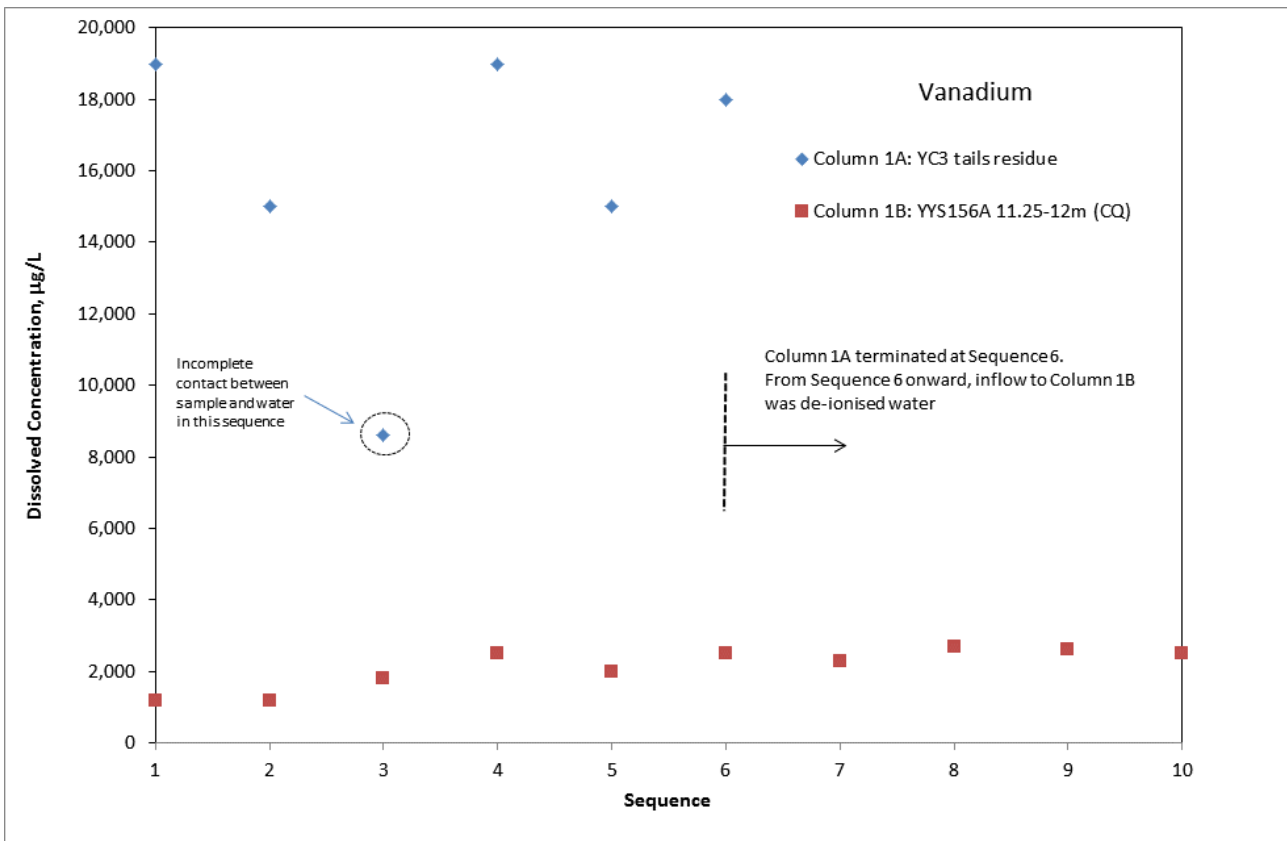


Figure 5.5: Dissolved vanadium concentrations in leachates from Columns 1A and 1B

## 5.7 Radionuclide Behaviour

Results from radionuclide assays of Yeelirrie tailings are shown in Table 5.3.

All the samples are depleted with respect to uranium isotopes. This is consistent with removal of uranium during processing. Some of the radionuclides further down the decay chain appear to be close to secular equilibrium, except for  $^{210}\text{Pb}$ , which gives activities consistently higher than those of  $^{230}\text{Th}$  and  $^{226}\text{Ra}$ . It would appear therefore that processing has resulted in some preferential fractionation of radionuclides other than uranium.

Table 5.4 shows the results of radionuclides assays of barren liquor solution and leachates from Columns 1A and 1B. Column 1A involved YC3 tailings residue, and the effluent from Column 1A was used as inflow to Column 1B. The solutions contain significant  $^{238}\text{U}$  and  $^{235}\text{U}$  activities, and detectable  $^{226}\text{Ra}$ . Other radionuclides were below detection limits.

Table 5.3: Radionuclide Assay Results for Yeelirrie Tailings

Sample	Concentration (Bq/g)									
	<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain				<sup>235</sup> U Decay Chain		<sup>40</sup> K
	<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>235</sup> U	<sup>227</sup> Ac	
YC3 Sample	0.043	<0.09	0.049	1.6	13	10	14	<0.1	0.56	0.36
YM0076	0.013	<0.06	0.021	1.1	21	18	24	<0.2	0.91	<0.2
YM0015	0.069	<0.04	0.077	0.78	15	17	22	<0.02	0.86	0.49
YM0046	0.012	<0.03	<0.02	0.74	6.9	6.7	7.4	<0.06	0.25	0.18
YM0074	0.074	0.11	0.075	0.35	5.7	6.5	8.4	<0.07	0.33	0.52

Table 5.4: Radionuclide Assay Results for Barren Liquor, and the First Leachate Cycles from Columns 1A and 1B

Test	Sample	Description	Leachant	Concentration (Bq/L)									
				<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain				<sup>235</sup> U Decay Chain		<sup>40</sup> K
				<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>235</sup> U	<sup>227</sup> Ac	
Barren liquor	-	-	Barren liquor	<4	<2	<0.5	1160	<110	5	<20	68	<2	28
Column 1A Sequence 1	YC3 tails residue	YC3 tails	DI water	<4	<2	<0.6	1520	<130	17	<20	90	<2	<20
Column 1A Sequence 3	YC3 tails residue	YC3 tails	DI water	<0.4	< 0.4	< 0.2	76	< 16	1.9	< 2	7.3	< 0.6	5.8
Column 1B Sequence 1	YYS156A 11.25-12 m	CQ	Effluent from column 1A	<4	<0.7	<0.3	840	<40	<0.4	<5	42	<0.9	29
Column 1B Sequence 3	YYS156A 11.25-12 m	CQ	Effluent from column 1A	<0.4	< 0.4	< 0.2	583	< 25	< 0.2	< 3	31	< 0.5	14
Column 1B Sequence 5	YYS156A 11.25-12 m	CQ	Effluent from column 1A	<0.4	< 0.4	< 0.3	211	< 23	< 0.3	< 3	19	< 0.7	11

## 5.8 Process Tailings Ageing

Not all chemical reactions occur instantaneously nor is equilibrium always reached in a short time. Therefore, reactions may take place between tails and contacting solutions overtime which could result in changes to the porewater composition in the TSF. To examine the nature and rate of such changes, aging tests were undertaken. Tailings slurries were allowed to contact for a period of up to 8 months, in both sealed (closed) and open flasks. The solution compositions were monitored over time and results are documented in Appendix 6.

The initial solution composition is essentially dominated by sodium carbonate, due to the high reagent addition during processing. In two of the aging tests, the dissolved Na concentration decreased. In Month 8, the sodium concentration was around 80 to 90% of the concentration measured in the first month. A similar trend was observed for potassium in one of the tests. The decreasing concentrations are interpreted as sodium and potassium exchange for calcium and magnesium on clays, possibly combined with precipitation of sodium/potassium-bearing salts. Ion exchange reactions are consistent with:

- Swelling of solids observed in some flasks. This observation was made for some of the flasks containing samples YM0046 and YM0015. These were the samples with the highest swelling clay content (e.g. smectite, illite - Table 5.1).
- Measured increases in dissolved calcium – although it is noted that in terms of milli-equivalents, the calcium increase is less than 1% of the sodium decrease. It is possible that calcium and magnesium released during the exchange reactions do not remain dissolved, but instead precipitate as secondary minerals (see below).

Precipitation of Na/K and Ca/Mg carbonates could explain coincident decreases in alkalinity, and precipitation of Na/K salts (chloride or sulphate phases) could explain the decrease in chlorine and sulphate in the majority of the tests. The XRD results (Appendix 6) show that, with the exception of YM0076, the Month 8 residues contain more calcite than the initial solid, by between 1 and 4 wt%. Geochemical modelling (PHREEQC) suggests that the solution compositions could be consistent with precipitation of phases such as dawsonite ( $\text{NaAlCO}_3(\text{OH})_2$ ) or gaylussite ( $\text{CaNa}_2(\text{CO}_3)_2 \cdot 5\text{H}_2\text{O}$ ). Most sulphate and chloride phases were under-saturated, and would therefore dissolve rather than precipitate. However, it is possible that phases may have formed in the tests that are not represented in the thermodynamic database used. *[Also note that the high ionic strength of the solutions introduce uncertainty to the solubility calculations.]*

The aging tests included tailings from both high and low-grade calcrete and clay-quartz ores. Major element aging trends appeared unaffected by ore type. However, different trends are observed for some minor elements.

Dissolved uranium and vanadium concentrations were variable among tests and also showed variable trends with time. Figure 5.6 shows the uranium concentrations with time. The samples with little or no carbonate content (YM0015 and YM0074) continued to leach U. Since the residual uranium content of sample YM0015 was well above the average for all tailings samples (see Table 5.2), it could be expected that it would continue to leach uranium; however the results for sample YM0074 indicates that ongoing leaching could be expected even for a below average uranium content. The results for YC0076 showed little or no additional uranium leaching, whereas the uranium concentration of sample YM0046 commenced at a higher initial concentration than the other tests, but then decreased over time.

Geochemical calculations suggest that the uranium concentrations are consistent with a carnotite solubility control. For example, Figure 5.7 shows that at early times, the solutions are close to equilibrium with carnotite (saturation index close to zero). The variable concentrations between tests reflect differences in geochemical conditions between tests, e.g. dissolved K and alkalinity. In month 2 and 4, the solutions start to become under-saturated with respect to carnotite, possibly reflecting the general trend toward reduced K concentrations in solution. This would mean that residual carnotite present in the tailings would start to dissolve over time. The XRD results (Appendix 6) show that whilst detectable in three of the four initial solid samples, carnotite is invariably below detection in the Month 8 residues.

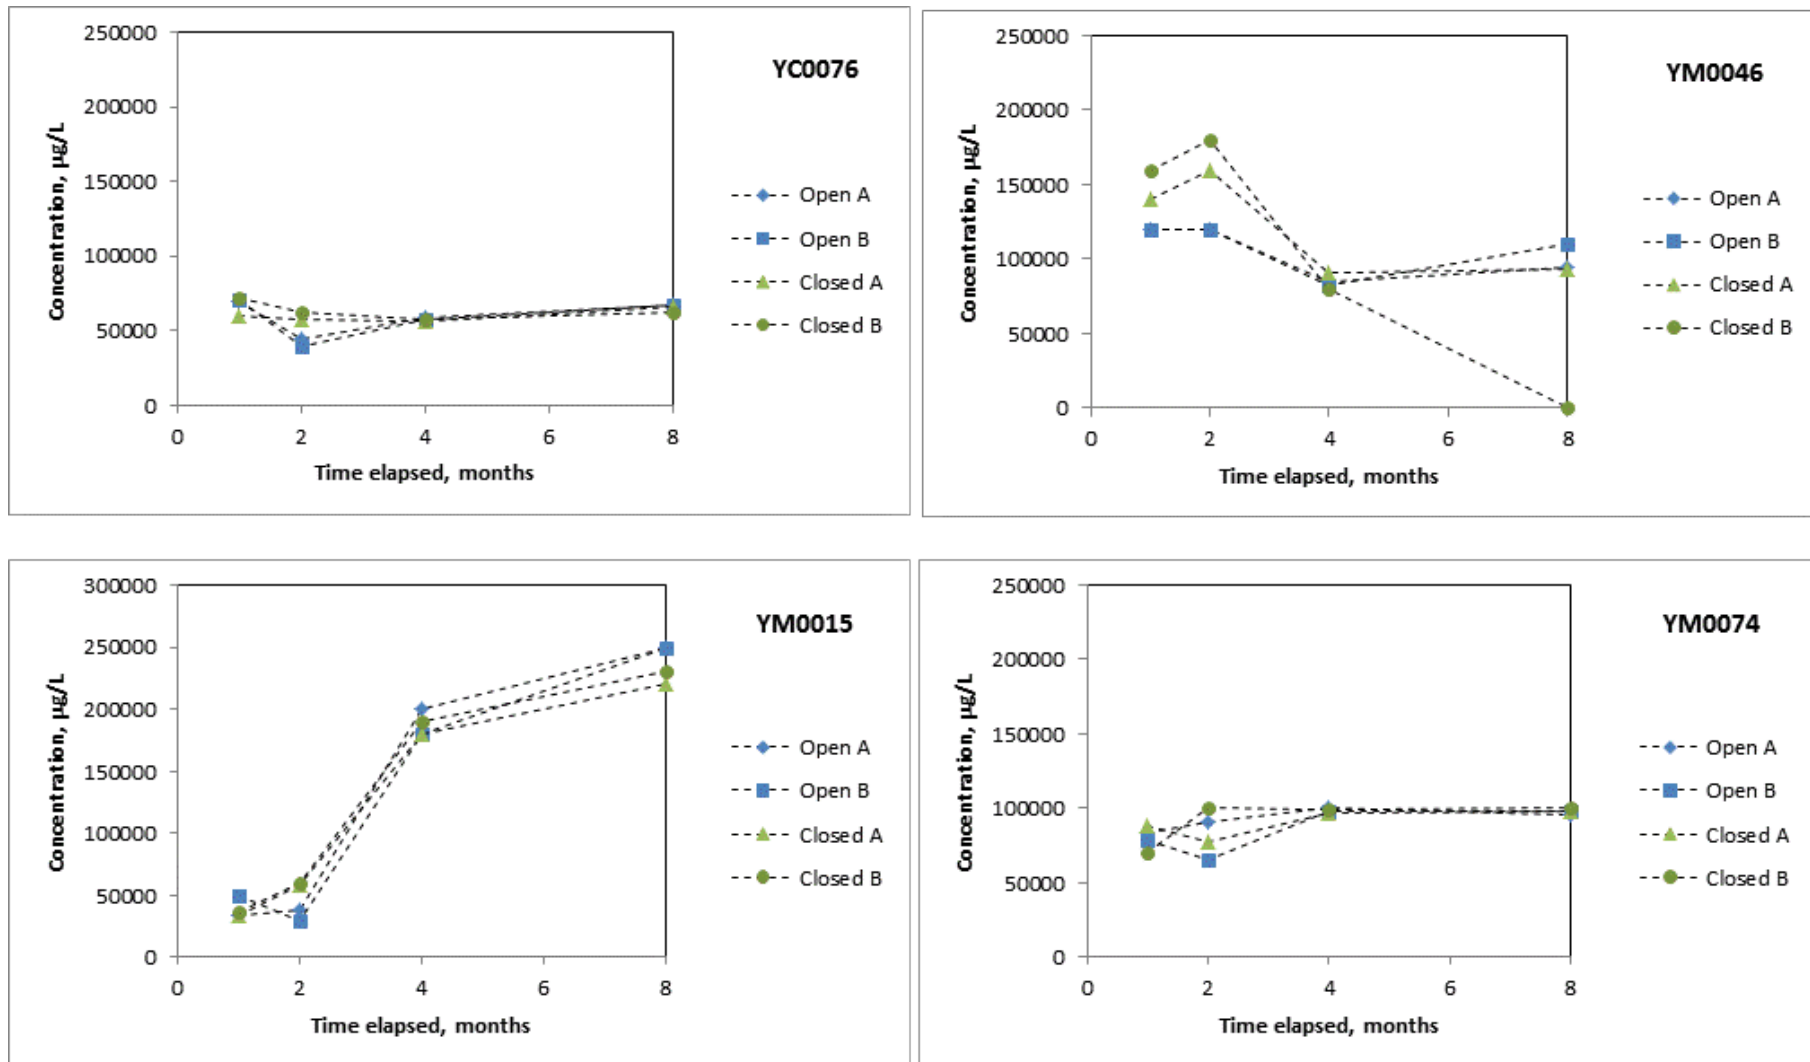


Figure 5.6: Dissolved uranium concentrations in the aging tests as a function of time

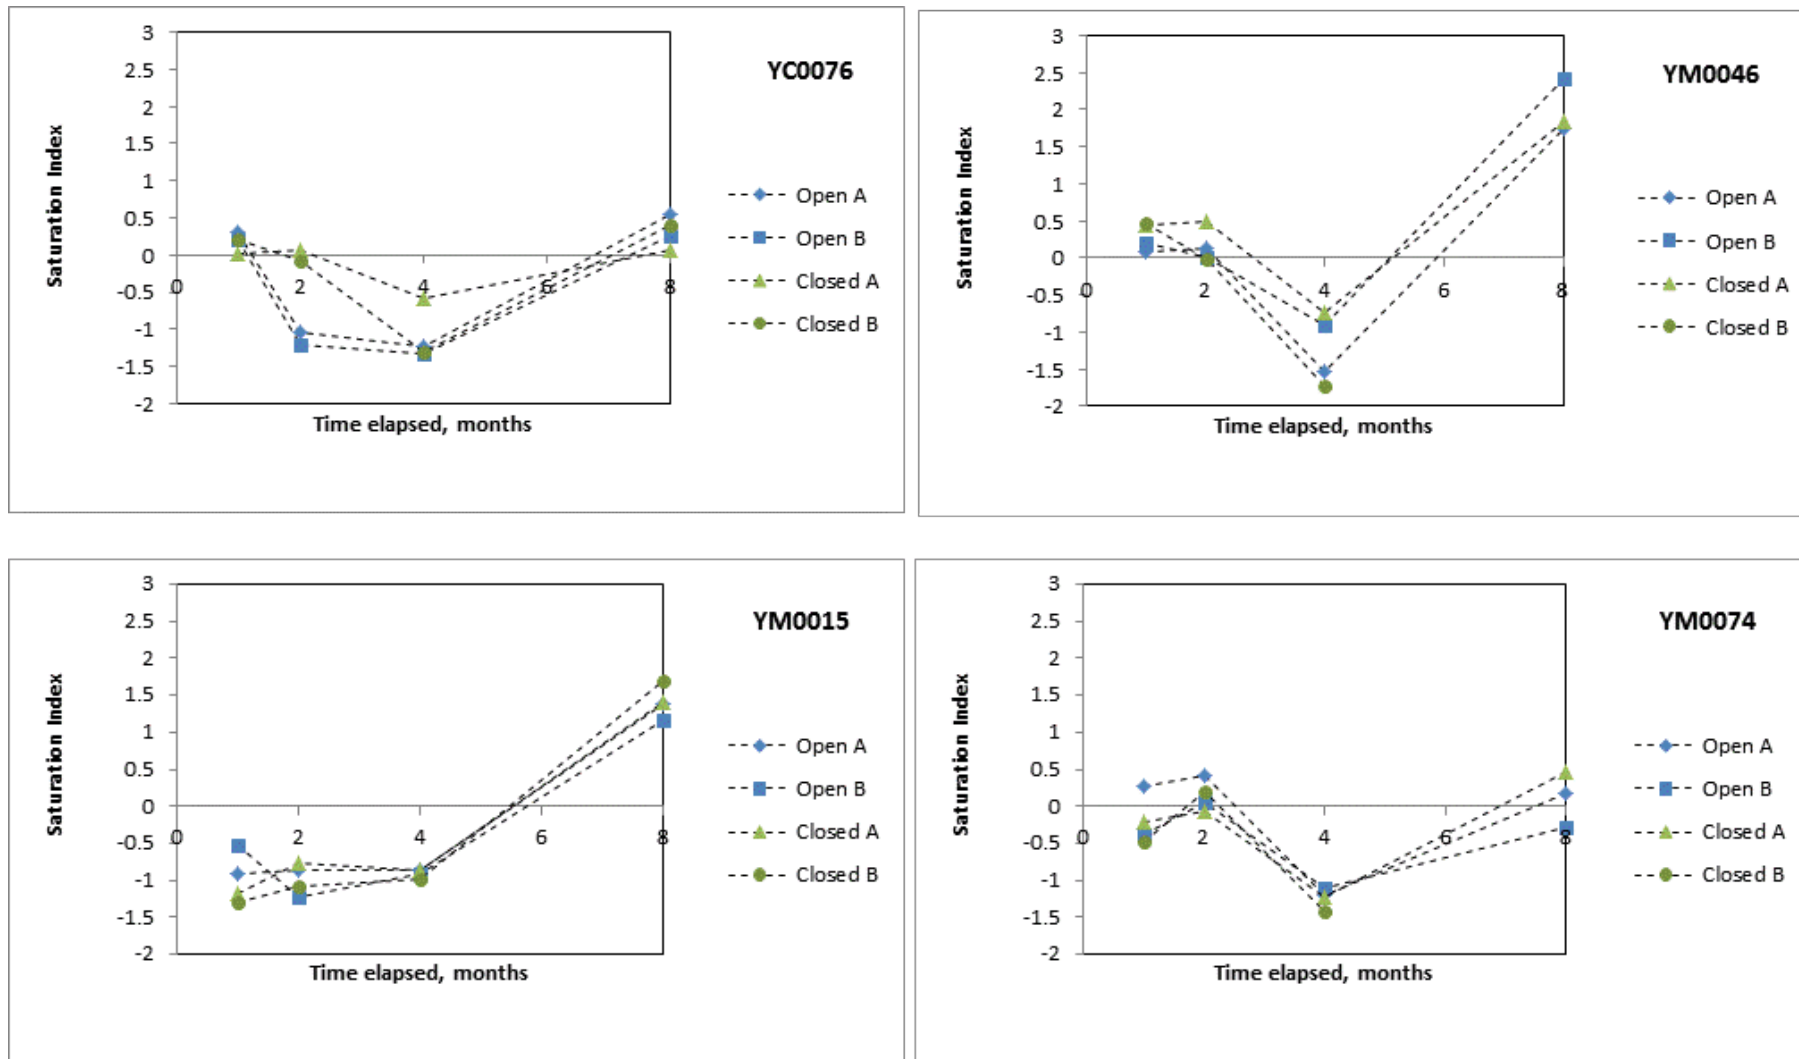


Figure 5.7: Calculated carnotite saturation index as a function of time

In month 8, the calculated carnotite saturation indices suggest over-saturation. These calculations have been influenced by much lower alkalinity values measured for the month 8 tests. (Note that results for month 8 were in fact provided by a different laboratory. A limited comparison of results from the two laboratories suggests that the second laboratory consistently reported alkalinity values around half of those reported by first laboratory. The charge balance was found to be poor; a deficiency in anions suggested that the alkalinity results could be erroneously low. Consequently, the saturation indices for the month 8 results are likely incorrect.

For some elements (barium, strontium, arsenic and molybdenum), there are systematic differences in behaviour depending on the ore-type, suggesting different mineralogical controls could be in operation. In the calcrete tailings, the dissolved concentrations of these elements decrease with time. A possible interpretation of this trend could be gradual incorporation of these elements in carbonate minerals as they recrystallise and age.

In the case of the clay-quartz tailings, the dissolved concentrations of these elements are either constant with time (strontium), increase (barium, arsenic) or both (molybdenum). The clay-quartz samples contain goethite and kaolin, both of which contribute significant sorptive capacity and would be expected to influence trace element behaviour. Aluminium concentrations increased during the tests possibly indicative of kaolin dissolution, although this is inconclusive as there are other aluminium phases present. Kaolin dissolution would reduce sorptive capacity and could cause an increase in solution concentrations as a result of release of sorbed solutes.

In general, only a few elements show major differences in behaviour between open and closed flasks. Most significant was the calcium for calcrete tails (sample YM0076) whereas calcium trends in other flasks showed a minor trend only. Other elements that show a significant response include chromium and zinc. Results for sodium, magnesium, uranium, and vanadium in some of the tests show evidence of a systematic effect – generally minor. The effects are probably linked to carbonate geochemistry, i.e. exchange with atmospheric CO<sub>2</sub> leading to changes in dissolved carbonate.

Other general comments about the tailings test results include:

- Oxy-anion elements like selenium, chromium decrease with time in all tests.
- Metals such as copper, lead increased sharply in month 4 leachates, but decreased in the month 8 test results.
- Clays present in the tailings lead to ion exchange which affects the sodium/potassium ratio (exchanges with calcium/magnesium) and influences the solubility of carnotite due to the loss of potassium from solution.
- Gypsum dissolution and ion exchange reactions increase dissolved calcium which leads to calcite precipitation.
- Dissolved alkalinity is lost from solution due to the formation of calcite and other carbonate minerals.
- Loss of alkalinity reduces carnotite solubility and will result in lower uranium and vanadium equilibrium concentrations.



## 6. Tailings (Kalgoorlie Storage Facility)

Although the Kalgoorlie tailings may not have been processed in strict accordance with the method that will be used for uranium recovery as proposed for the Yeelirrie Development, the results may be used as an analogue to the proposed TSF facility.

### 6.1 Mineralogy

The mineralogical composition of Kalgoorlie samples is given in Table 6.1. The main minerals are carbonates (calcite and dolomite), quartz, kaolin and iron oxide (hematite).

The mineralogical differences between the tails and the underlying sediments are slight. The sediments contain higher quantities of kaolin and iron oxide. In Borehole #2 and #3, there is a decrease in calcite and dolomite content across the tails/sediment interface.

### 6.2 Surface Characteristics

The surface characteristics of Kalgoorlie materials are given in Table 6.2. In the case of samples S2.9 and S3.7, there were distinct colour changes along the length of the core. Two sub-samples were obtained to determine if there were coincident differences in surface characteristics.

The surface area ranges from 18.9 m<sup>2</sup>/g to 80.9 m<sup>2</sup>/g. There is no obvious correlation between surface area and mineralogy or colour.

The cation exchange capacity shows a small range, from 17 to 36.8 meq/100g. The dominant cation occupying exchange sites is calcium. Note that the tailings cation exchange capacity is about half that measured for the fresh tailings reported herein (Section 5.3).

### 6.3 Bulk Chemistry

The bulk chemistry analytical results are provided in Appendix 3, and selected results are shown in Table 6.3.

The samples collected from the Kalgoorlie facility span the tailing/sediment interface. Solid assay results plotted as a function of depth indicated:

- Elevated carbonate within the tailings materials (Figure 6.1).
- Variability in the minor element composition of the tailings, over depth scales of less than a metre (Figure 6.2).

**Table 6.1: Mineralogical Composition of Kalgoorlie Samples (wt%)**

Sample	Borehole	Depth range	Material type	Carbonates		Framework and chain silicates				Sheet silicates and clays					Oxides		
				Calcite	Dolomite	Quartz	Albite	Microcline	Amphibole	Kaolin	Smectite	Illite / Mica	Sepiolite	Chlorite	Hematite	Anatase	Rutile
S1.9	1	4-4.5 m	Tailings	8	26	35	1	4		16	8	1	?1			<1	
S2.14	2	4-4.5 m	Tailings	12	23	15	<1	1		23	21	1			4	<1	
S2.9	2	5.25-6 m	Sediment	10	24	14	<1	2		22	21	1			6	<1	
S3.7	3	5.3-5.75 m	Tailings	3	6	75	3	2	<1	7					4		
S3.8	3	6-7 m	Sediment	<1	2	12				67				<1	15	2	1

Notes:

?=denotes uncertainty in mineral identification


**Table 6.2: Surface Characteristics of the Kalgoorlie Tailings and Underlying Soils**

Sample	Borehole #	Depth interval, m	Lithology	BET Surface area, m <sup>2</sup> /g	Cation exchange capacity, meq/100g	Site Occupancy: exchangeable cations, meq/100g (grey shading indicates dominant cation)			
						Ca	Mg	K	Na
S1.9	1	4-4.5	Tailings	46.6	31.2	21.5	3.1	1.7	4.9
S2.14	2	4-4.5	Tailings	61.2	36.8	21.4	1.1	2.3	12
S2.9A (red)	2	5.25-6	Underlying soil	73.9	19.5	8.3	0.5	1.8	8.9
S2.9B (pale brown)	2	5.25-6	Underlying soil	30.5	35.2	24.5	1.1	1.8	7.8
S3.7A (red)	3	5.3-5.75	Tailings	18.9	30	23.4	3.3	1.1	2.2
S3.7B (pale brown)	3	5.3-5.75	Tailings	27.2	32	24	2.4	1.4	4.1
S3.8	3	6-7	Underlying soil	80.9	17	12.4	1.4	0.2	3

Table 6.3: Bulk Chemistry of Kalgoorlie Tailings and Sediments


Major elements		Al	Ca	CO <sub>2</sub>	F	Fe	K	Mg	Mn	Na	S	Si	SO <sub>4</sub>			
Sample #	Material type	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)	(%)			
Average crustal abundance		8.2	4.1			4.1	2.1	2.3	0.095	2.3			0.078			
S1.8 (4 m)	Tailings	4.28	8.27	15.4	0.312	1.89	0.84	4.88	0.01	0.69	<0.01	20.1	0.55			
S1.9 (4-4.5 m)	Tailings	3.78	8.32	14.3	0.218	2.02	0.86	4.74	0.01	0.55	0.07	22.6	0.1			
S2.14 (4-4.5 m)	Tailings	5.57	8.41	14.1	0.254	5.29	0.81	5.54	0.02	1.1	0.07	17.3	0.1			
S2.8 (4.5-5.25 m)	Tailings	4.18	8.46	16	0.25	1.84	0.9	5.22	0.02	0.76	0.02	20.4	0.2			
S2.9 (5.25-6 m)	Underlying soil	6.31	7.57	13	0.226	7	0.62	4.97	0.01	1.2	0.07	16	0.7			
S2.10 (6 m)	Underlying soil	9.59	0.31	0.9	0.05	20	0.32	0.39	0.01	0.64	0.06	17.7	0.1			
S2.11 (6-6.75 m)	Underlying soil	10.5	0.21	0.8	0.042	16.7	0.25	0.31	<0.01	0.59	0.05	19	0.1			
S3.11 (3.75 m)	Tailings	3	6.92	13.1	0.254	1.37	0.86	3.86	0.01	0.37	0.02	25.9	0.1			
S3.6 (4.5-5.25 m)	Tailings	5.44	4.66	4.5	0.034	16	0.12	1.82	0.17	1.22	0.27	20.6	<0.05			
S3.7 (5.3-5.75 m)	Tailings	2.99	7.98	15.2	0.202	2.58	0.69	4.32	0.02	0.41	0.02	23	0.15			
S3.10 (5.75-6 m)	Underlying soil	5.81	5.77	6.1	0.034	14	0.16	2.21	0.15	1.02	0.3	20.5	<0.05			
S3.8 (6-7 m)	Underlying soil	11.4	0.47	1	0.018	14.5	0.17	0.34	0.01	0.48	0.06	18.8	<0.05			
S3.9 (8 m)	Underlying soil	16.4	0.08	0.5	0.01	4.11	0.08	0.22	<0.01	0.35	0.16	21.3	0.15			
Minor elements		As	Ba	Cd	Co	Cr	Cu	Mo	Ni	Pb	Sr	Th	Tl	U <sub>3</sub> O <sub>8</sub>	V	Zn
Sample #	Material type	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
Average crustal abundance		1.5	500	0.11	20	100	50	1.5	80	14	370		0.6	2.8	160	75
S1.8 (4 m)	Tailings	13.5	210	<0.1	4.4	60	21.5	1.8	4.4	60	2300	10	<3	230	375	45
S1.9 (4-4.5 m)	Tailings	11	235	<0.1	3.8	55	16	2.3	3.8	55	1800	10	<3	180	210	180
S2.14 (4-4.5 m)	Tailings	16	205	<0.1	8	130	25	2.1	8	130	1800	15	<3	360	420	120
S2.8 (4.5-5.25 m)	Tailings	10.5	250	<0.1	4.4	50	23.5	1.7	4.4	50	2900	10	<3	160	195	70
S2.9 (5.25-6 m)	Underlying soil	10.5	165	<0.1	7.5	190	18.5	1.6	7.5	190	900	10	<3	450	340	34
S2.10 (6 m)	Underlying soil	15	175	<0.1	5.5	495	22.5	2.6	5.5	495	105	10	<3	215	550	185
S2.11 (6-6.75 m)	Underlying soil	12	125	<0.1	6	440	25	3	6	440	95	5	<3	185	475	30
S3.11 (3.75 m)	Tailings	13.5	230	<0.1	2.8	40	19	1.8	2.8	40	1200	10	<3	250	210	23.5
S3.6 (4.5-5.25 m)	Tailings	11.5	60	<0.1	47	130	41.5	1.4	47	130	135	<4	<3	15	280	130
S3.7 (5.3-5.75 m)	Tailings	10.5	240	<0.1	5.5	70	18	1.8	5.5	70	1300	5	<3	205	185	41.5
S3.10 (5.75-6 m)	Underlying soil	10.5	65	<0.1	47.5	135	55	1.9	47.5	135	150	<4	<3	15	290	280
S3.8 (6-7 m)	Underlying soil	8.5	130	<0.1	10.5	365	20	1.8	10.5	365	20	15	<3	125	410	30.5
S3.9 (8 m)	Underlying soil	1	100	<0.1	7.5	215	9.5	0.5	7.5	215	15	10	<3	5	175	70

Note: [1] Mean crustal abundances taken from Bowen 1979

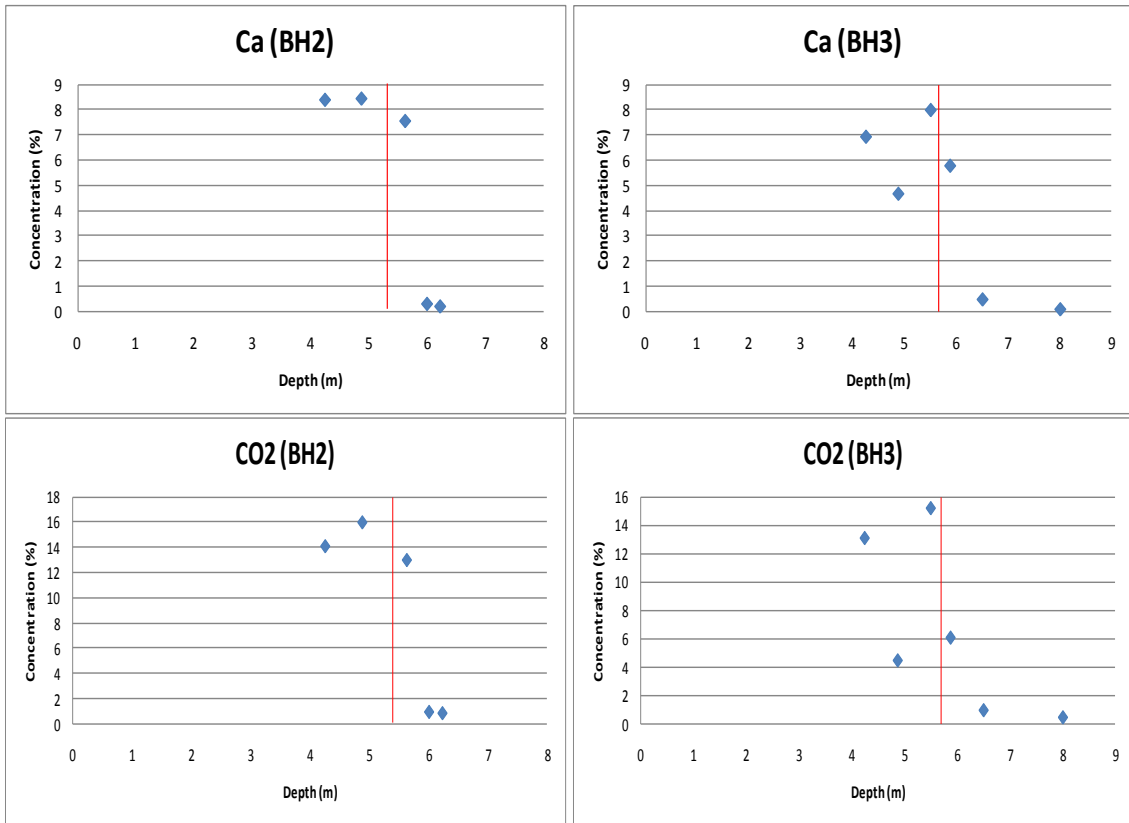

**Figure 6.1: Profiles of Ca and inorganic carbon (as CO<sub>2</sub>) content in solids as a function of depth, BH2 and BH3 (Kalgoorlie TSF)**

Red line indicates the approximate position of the tailings/sediment interface.

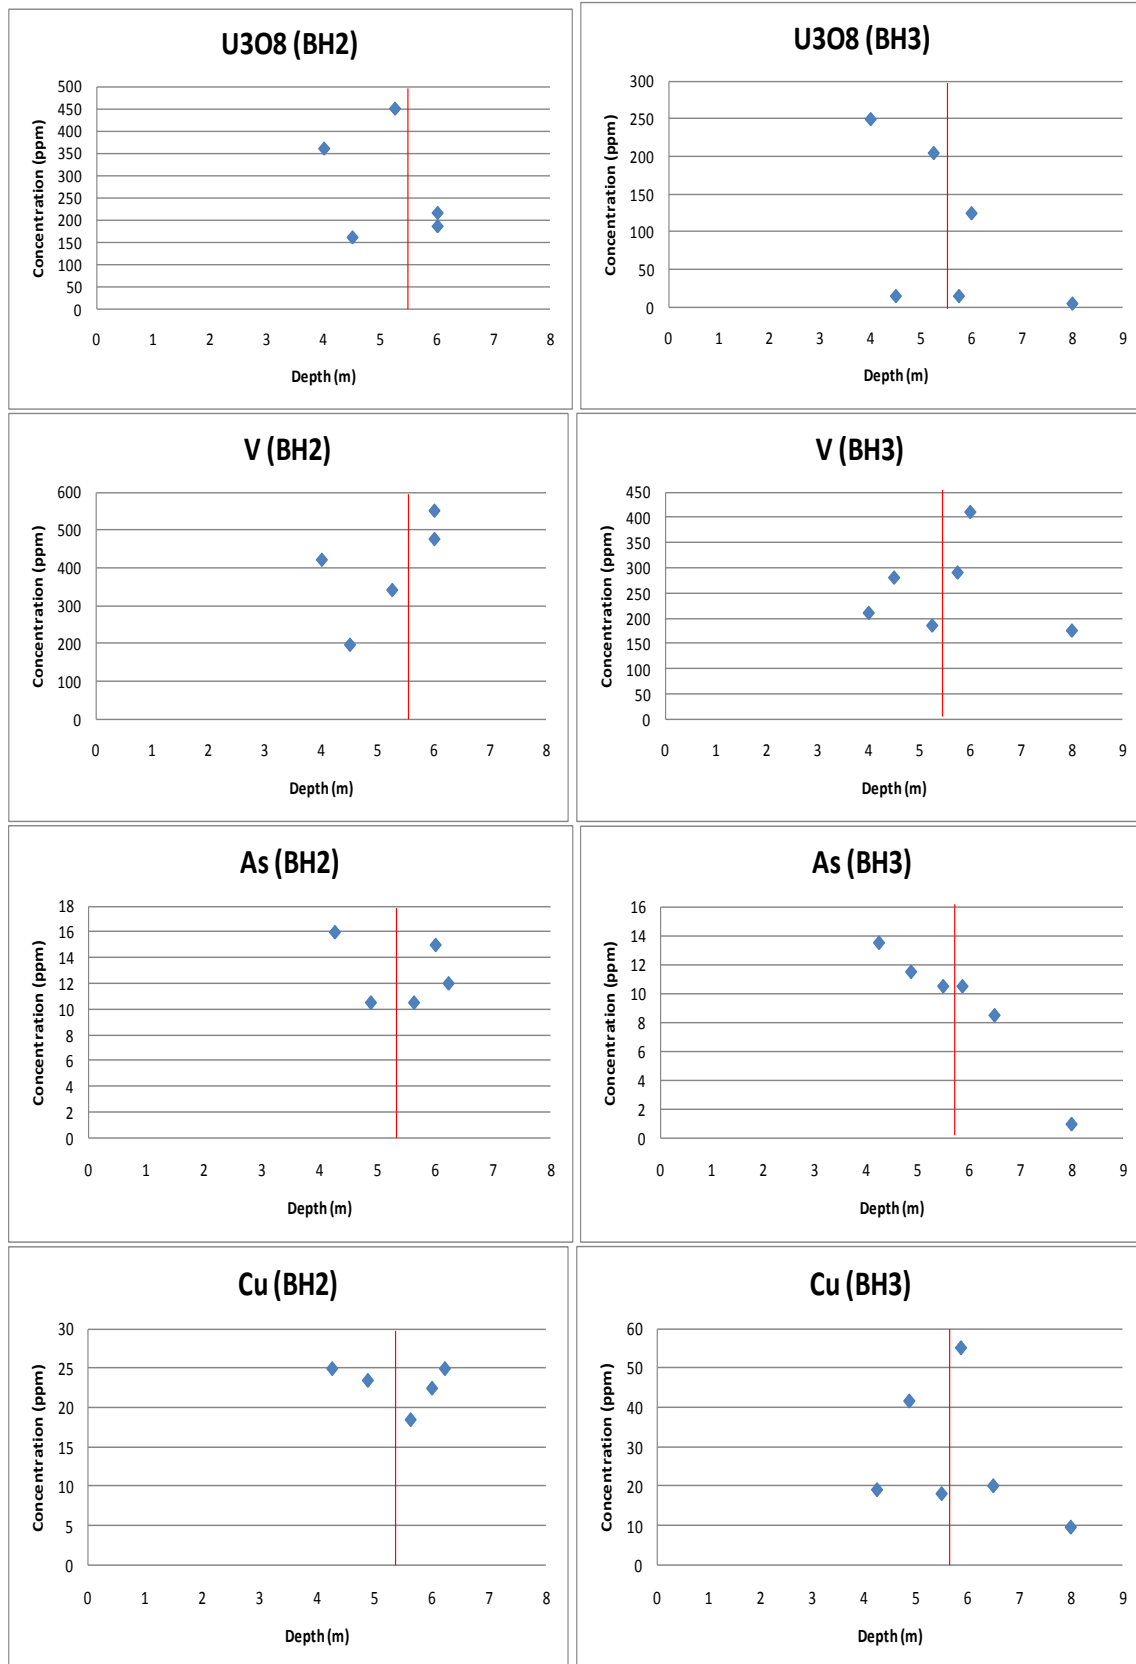

**Figure 6.2: Profiles of uranium, vanadium, arsenic and copper content in solids as a function of depth, BH2 and BH3 (Kalgoorlie TSF)**

Red line indicates the approximate position of the tailings/sediment interface

## 6.4 Metal Leaching

Samples were contacted with de-ionised water in bottle tests. The bottle roll tests were undertaken at a liquid:solid ratio of 3:1 and the headspace in the bottles was occupied by air. Results from bottle roll tests are documented in Appendix 4.

Table 6.4 summarises solute concentrations measured in the bottle roll tests. The summary includes results from both tailings and sediment samples, and uses results from progressive (sequential) leach tests. In these tests, following the first bottle roll test, the solution is removed and a second and third test conducted (at the same 3:1 water:rock ratio).

For some elements (silver, beryllium, bismuth, cobalt, lithium, lead, antimony) the dissolved concentrations at the end of the tests were invariably below the limits of detection. Comparatively, dissolved concentrations measured for boron, strontium, thallium, uranium and vanadium were elevated, with maximum concentrations in excess of 500 µg/L. Dissolved concentrations of arsenic and tin were generally above detection limits, with maximum concentrations in excess of 100 µg/L.

With the exception of arsenic and tin, the suite of leachable elements is similar to that observed for the Yeelirrie materials.

As with Yeelirrie materials, the highest concentrations generally were observed for the first stage of the progressive leach tests. Exceptions included tin and zinc where the highest concentrations occurred in the second and third stages of the leaching sequence.

There were no significant differences in leaching behaviour between the tails and sediments samples.

**Table 6.4: Summary of Solute Concentrations in De-ionised Water Extractions of Kalgoorlie Materials**

(Bottle Roll Tests at 3:1 Water:Rock Ratio)

Parameter	Units	Detection Limit	Underlying Soils (Two samples, six solutions)			Tailings (Three samples, nine solutions)		
			Minimum	Median	Maximum	Minimum	Median	Maximum
pH	pH Units	0.0	8.4	8.6	9.4	8.3	9.1	9.4
Eh	mV	1.0	410	432	453	401	423	443
EC	µS/cm	5.0	351	982	5240	385	1200	5530
Alkalinity	CaCO <sub>3</sub> (mg/L)	1.0	229	297	1190	322	443	680
Br	mg/L	0.5	<0.5	<0.5	3.1	<0.5	1.6	3.6
Cl	mg/L	0.5	5.1	51	750	3.2	76	860
F	mg/L	0.5	1.1	2.65	7.2	1.5	3.8	6.1
TOC	mg/L	1	4.2	7.85	28	2.9	6.1	45
NO <sub>2</sub> -N	mg/L	0.5	<0.5	<0.5	1.6	<0.5	<0.5	0.6
NO <sub>3</sub> -N	mg/L	0.5	<0.5	0.85	51	<0.5	2.25	58
SO <sub>4</sub>	mg/L	0.5	7.1	48	480	5.9	87	590
Al	µg/L	5	15	123.5	310	76	190	1100
Ca	µg/L	100	1010	2710	5700	1390	2560	4620
Fe	µg/L	100	<100	<100	<100	<100	<100	120
Mg	µg/L	100	202	491	1740	328	636	1520
P	µg/L	100	<100	220	510	<100	<100	650
K	µg/L	1000	1500	6795	48600	7660	14500	57600
Na	µg/L	100	83500	207000	1080000	87200	312000	1110000
Si	µg/L	100	2980	17500	180000	2500	5180	240000
As	µg/L	5	<5	42	210	52	130	340
B	µg/L	5	370	530	1700	310	1200	2400
Ba	µg/L	5	8.6	12.5	45	<5	8.5	19
Cd	µg/L	5	<5	<5	<5	<5	<5	11
Cr	µg/L	5	<5	<5	6.9	<5	5.3	9.5
Cu	µg/L	5	5.8	19	25	<5	7.8	32
Hg	µg/L	0.1	<0.1	<0.1	<0.1	<0.1	<0.1	0.2
Mn	µg/L	5	<5	<5	7.4	<5	<5	<5
Mo	µg/L	5	9.7	32	68	<5	15	93
Ni	µg/L	5	<5	<5	7.5	<5	<5	<5
Se	µg/L	5	<5	6	42	<5	<5	27
Sn	µg/L	5	<5	42	240	<5	6	61
Sr	µg/L	5	6.3	61.5	280	110	210	1200
Tl	µg/L	5	<5	<5	<5	<5	<5	3600
U	µg/L	5	280	2450	56000	180	2200	21000
V	µg/L	5	5	704	3100	2200	3700	12000
Zn	µg/L	5	<5	8.1	18	<5	11	93

## Notes:

[1] Where more than one detection limit is given, the detection limit reported by the laboratory changed during the programme.

[2] The following constituents were consistently below detection: acidity, NH<sub>3</sub>, Ag, Be, Bi, Co, Hg, Li, Pb, Sb.

## 6.5 Radionuclide Distribution and Behaviour

Results from radionuclide assays of Kalgoorlie solids are shown in Table 6.5.

Daughter/parent activity ratios that differ from unity indicate secular disequilibrium. All three tails samples are depleted with respect to uranium isotopes, consistent with removal of this element during processing. Radionuclides further down the decay chain appear to be in equilibrium. In the case of the longer lived nuclides, e.g.  $^{230}\text{Th}$ ,  $^{226}\text{Ra}$ , this suggests that processing did not disturb pre-existing equilibrium relationships. In the case of shorter lived nuclides, e.g.  $^{210}\text{Pb}$ ,  $^{210}\text{Po}$ , the same could be true.

One of the soils, S2.9, is enriched with respect to uranium. The sample was located immediately below the tails. It is possible that the radionuclide content of this soil is sourced from overlying tails, i.e. represents an attenuation front. This could explain why the sediment reflects the same radionuclide disequilibrium as the overlying tails.

Table 6.6 shows leachate concentrations from the first stage of the progressive leach tests. Most radionuclides are below detection limits suggesting no significant leaching of these nuclides from the solids. However,  $^{238}\text{U}$ ,  $^{235}\text{U}$  and  $^{226}\text{Ra}$  were detectable. The  $^{226}\text{Ra}$  trends correlate with strontium behaviour providing some confidence in the use of strontium as a chemical analogue for radium.



**Table 6.5: Radionuclide Assay Results for Kalgoorlie Tailings and Underlying Sediments**

Sample	Concentration (Bq/g)										
	<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain					<sup>235</sup> U Decay Chain		<sup>40</sup> K
	<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>210</sup> Po	<sup>235</sup> U	<sup>227</sup> Ac	
S1.9 (tails)	0.032	0.049	0.034	1.8	8.7	12	13	13	0.14	0.41	0.34
S2.14 (tails)	0.040	<0.05	0.045	3.8	23	18	19	20	0.29	0.84	0.27
S2.9 (underlying soil)	0.036	<0.05	0.045	4.7	23	18	21	17	0.27	0.91	<0.1
S3.7 (tails)	0.028	<0.03	0.031	1.8	8.6	9.9	11	10	<0.08	0.38	0.24
S3.8 (underlying soil)	0.029	0.029	0.027	1.3	<0.2	0.026	<0.03	0.035	0.050	<0.006	<0.05

**Table 6.6: Radionuclide Assay Results for De-ionised Water Extraction of Kalgoorlie Tailings and Underlying Sediments**

(Sequence 1, Bottle Roll Tests at 3:1 Water:Rock Ratio)

Sample	Concentration (Bq/L)									Concentration (µg/L)		
	<sup>232</sup> Th Decay Chain			<sup>238</sup> U Decay Chain				<sup>235</sup> U Decay Chain		<sup>40</sup> K	Ba	Sr
	<sup>232</sup> Th	<sup>228</sup> Ra	<sup>228</sup> Th	<sup>238</sup> U	<sup>230</sup> Th	<sup>226</sup> Ra	<sup>210</sup> Pb	<sup>235</sup> U	<sup>227</sup> Ac			
S1.9 (tails)	<4	<0.3	<0.1	<12	<4	0.5	<2	<1	<0.4	<2	8.5	710
S2.14 (tails)	<4	<0.3	<0.2	293	<20	<0.2	<2	8.6	<0.5	<2	10	600
S2.9 (underlying soil)	<4	<0.4	<0.2	755	<30	<0.6	<3	39	<0.6	<2	8.6	280
S3.7 (tails)	<4	<0.5	<0.2	92	<20	0.8	<4	4.3	<0.5	<4	19	1200
S3.8 (underlying soil)	<4	<0.4	<0.1	18	<9	<0.2	<3	<1	<0.4	<4	45	51


## 6.6 Geochemical Controls

### 6.6.1 Attenuation

Minor element enrichment is observed at and below the tailings/sediment contact (Figure 6.2). This enrichment is taken as evidence of attenuation at this interface.

### 6.6.2 Solubility Controls

Figure 6.3 is uranyl activity diagram showing uranyl activities for the Kalgoorlie leachate results plotted as a function of pH. Many of the solutions were under-saturated with respect to carnotite solubility, and the results plot below the theoretical carnotite line. However, there were several solutions that were over-saturated with respect to carnotite. These results actually plot along a trend parallel to the solubility of uranium hydroxide minerals, e.g. schoepite. This introduces the possibility that in tailings-related materials, uranium solubility could be controlled by minerals other than carnotite in the longer term after deposition. However this may depend on the processing route and the physico-chemical conditions that develop after deposition.

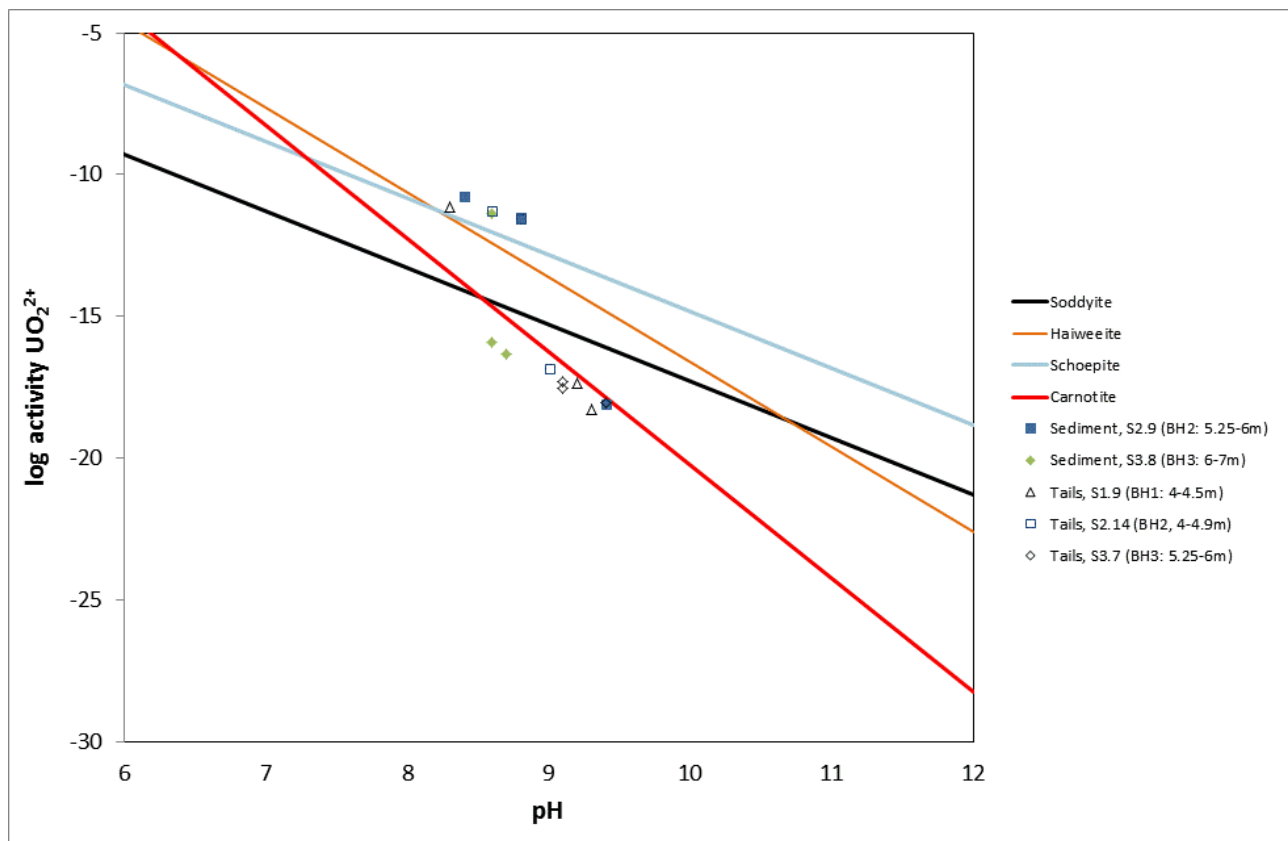

**Figure 6.3: Uranyl (UO<sub>2</sub><sup>2+</sup>) activity diagram showing the calculated activities of bottle roll leach solutions**

(3:1 liquid:solid ratio, air)

(Also shown are the theoretical equilibrium lines for a range of minerals)

## 6.7 Kalgoorlie TSF as an Analogue for the Proposed Yeelirrie TSF

Despite possible differences in processing methodologies, the geochemical characteristics of the Kalgoorlie tailing materials are similar to the more recently produced tailings samples. It might be expected therefore that similar processes would control contaminant mobility within the tails and that the Kalgoorlie system be regarded as an analogue of the Yeelirrie system.

There are parallels observed between the results from the Kalgoorlie programme and those from both the Yeelirrie rocks and soils, and the more recently produced tailings materials. For example, the importance of carnotite as a possible solubility control on uranium and vanadium behaviour. There is additional evidence of an alternative solubility control within the Kalgoorlie results (i.e. schoepite). These observations are valid for an unsaturated system that likely has been affected by evaporation. A significant difference between the Kalgoorlie facility and the proposed Yeelirrie TSF is that in the proposed TSF the tailings will largely be below the groundwater table and will remain saturated. This may influence the suite of secondary mineral phases that may form.

Of particular interest is the possible evidence of attenuation at the base of the Kalgoorlie TSF. The Kalgoorlie TSF has been in place for more than 30 years. It would appear that during this time, contaminants in seepage from the TSF have been attenuated at the tails/sediment interface. Soils underly the Kalgoorlie TSF and would be expected to present a significant sorptive capacity (e.g. due to high iron oxide and clay content). However, it should be noted that clay-quartz would underly the Yeelirrie TSF and may not present such a high sorptive capacity.

## 7. Conclusions

This report provides a summary of the field and laboratory investigations completed in support of the source term development for the temporary stockpiles and the tailings area. Outcomes from the programme are summarised below.

### **Stockpiled Materials**

Leaching behaviour is dominated by flushing of readily soluble phases on contact with water, e.g. halite, sulphates, carnotite. The main contaminants correlated with such flushing are: boron, barium, molybdenum, strontium, thallium, uranium, vanadium and zinc. Radionuclide assays of leachate solutions showed that  $^{226}\text{Ra}$  would also be released during flushing. The earliest pore volume exchanges tend to coincide with the highest solute concentrations. Concentrations are much reduced in subsequent pore volume exchanges. The shape of release curves generated from column testwork can be approximated quite well by a power law.

Carnotite solubility is expected to place an upper limit on uranium and vanadium in leach solutions. In many cases, the mass of available carnotite may be limited and the solutions could remain under-saturated with respect to this mineral. There is a greater likelihood that carnotite saturation would occur where water-to-rock ratios are lower (i.e. more carnotite mass per unit volume water), solute concentrations are higher and contact times are longer. Amongst other parameters, carnotite solubility is sensitive to solution pH, dissolved carbonate, potassium concentrations and redox.

Sorption onto iron and aluminium oxyhydroxides and clays may further limit release of some elements.

Based on outcomes for the leach testwork, tables of leachable solute mass (per kg of material) have been prepared for use as input to the source term modelling.

### **Tailings**

In the short-term, tailings porewater quality is dominated by process water (barren liquor). Barren liquor is highly alkaline and contains relatively high dissolved uranium and vanadium concentrations. Over the longer-term, it is expected that ion exchange processes could result in decreases in dissolved sodium and potassium concentrations in porewater. It is also possible that alkalinity will decrease (although available results are ambiguous with respect to trends in alkalinity) due to the formation of carbonate minerals. Reduced concentrations of potassium in solution will result in increased carnotite solubility; however this could be offset by reduced solubility should alkalinity decrease. The net effect may be that dissolved uranium and vanadium remain constant.

Results from the Kalgoorlie programme suggested that in the long term, in addition to carnotite, alternative solubility controls such as uranium hydroxide minerals (e.g. schoepite) may come into play.

Ion exchange reactions involving clay minerals may have a secondary outcome with respect to changing the physical characteristics of the materials. There is a correlation between exchange site occupancy and the swelling capacity of the clay. Replacing calcium with sodium will result in clay swelling, and consequently may reduce the permeability of the material. [This was observed in the column testwork where permeability decreased progressively in some materials and made it difficult to continue operating the columns in later cycles of testing.] In the field, for example, within and downstream of the tailings storage areas, this effect could reduce the potential for percolate to be released to the surrounding ground and act as a possible physical barrier to contaminant migration.

### **Downstream Interactions**

Initial percolate from the TSF could contain high dissolved sodium. Such high sodium concentrations are likely to result in displacement of ions from exchange sites on contacting clays, and result in leaching of calcium, magnesium, barium and strontium. Notably,  $^{226}\text{Ra}$ , rather than being displaced, appears to be attenuated from this percolate. Thus, under these particular geochemical conditions, radium does not behave as other analogous elements such as barium and strontium. [Under less alkaline, more dilute chemical conditions trends in  $^{226}\text{Ra}$  behaviour were analogous with trends in calcium, magnesium, barium and strontium behaviour.]

Carnotite solubility controls are expected to play an important role in controlling uranium and vanadium mobility along potential flow paths downstream of the facility. Geochemical conditions are expected to result in reduced carnotite solubility, principally due to the much lower alkalinities expected downstream. Solubility controls that could apply to other elements are co-precipitation in sulphate or carbonate phases.

Contaminant mobility may also be limited due to sorption onto mineral surfaces (e.g. iron and aluminium oxyhydroxides and clays). Sorption is not strong under the relatively carbonate-rich conditions expected in Yeelirrie groundwaters. However, moderate sorption is expected for many elements, except for the very elevated dissolved carbonate levels expected in early tailings seepage. Highest sorption is expected for loams; sorption coefficients in excess of  $100 \text{ cm}^3 \text{ g}^{-1}$  were calculated for arsenic, uranium and vanadium sorption. Lower sorption is expected in the case of the clay-quartz lithology (sorption coefficients for most elements were less than  $10 \text{ cm}^3 \text{ g}^{-1}$ ). In the case of calcrete, little or no sorption is expected to occur.

Potential attenuation of contaminants at the tailings/sediment interface is supported by observations within the Kalgoorlie programme. However, the Kalgoorlie TSF is underlain by soils that are expected to have a strong sorptive capacity. In contrast, clay-quartz will underly the Yeelirrie TSF and may not present such a high sorptive capacity. The clay quartz may also contain low levels of uranium that could be leached by the process water when first contacted.

## 8. References

- Baston, G.M.N., Berry, J.A., Brownsword, M., Heath, T.G., McCrohon, R., Tweed, C.J. and Yui, M. *The Effect of Temperature on the Sorption of Actinium and Protactinium on Geological Materials*, Presented at Migration 97, Sendai, September 1997.
- BHP, 2011, Proposed Yeelirrie Development: Environmental Review and Management Program.
- Bond, K.A., Heath T.G., Tweed, C.J., 1997. *HATCHES: A Referenced Thermodynamic Database for Chemical Equilibrium Studies*, Nirex Report NSS/R379.
- Bowen, H.J.M. 1979. *Environmental Chemistry of the Elements*, Academic Press, London, (1979).
- Outback Ecology, Yeelirrie Rehabilitation Report, July 2004.
- Parkhurst, D.L. and Appelo, C.A.J. User's guide to PHREEQC (Version 2) – A computer program for speciation, batch-reaction, one-dimensional transport, and inverse geochemical calculations. Water-Resources Investigations Report 99-4259, 1999.
- SRK, 2009. Proposed Yeelirrie Project: Geochemical Assessment of Tailings and Waste rock, SRK Report BHP040, August 2009.
- WMC, 1991. Yeelirrie Uranium Project 1991 Study Update.

# Appendices

## Appendix 1: Field Programme



The following appendix comprises:

- A map showing the locations of drill-holes at the Yeelirrie site.
- A sample log summarising characteristics of samples collected from drilling at the Yeelirrie site.
- Some figures illustrating trends in paste pH, EC and redox as a function of depth at the Yeelirrie site (data based on field measurements undertaken by URS). Also shown on the figures are results from the BHP assay database for CO<sub>2</sub>(%), S(%), U<sub>3</sub>O<sub>8</sub>(ppm) and V(ppm). These latter data are only shown for those cases where the database contained data collected from a drill-hole within 5 m of the current drill-hole.
- Drill logs for boreholes at the Yeelirrie site (excerpts from URS documentation).
- Drill and samples logs prepared to describe sampling at the historic Kalgoorlie tailings storage facility.

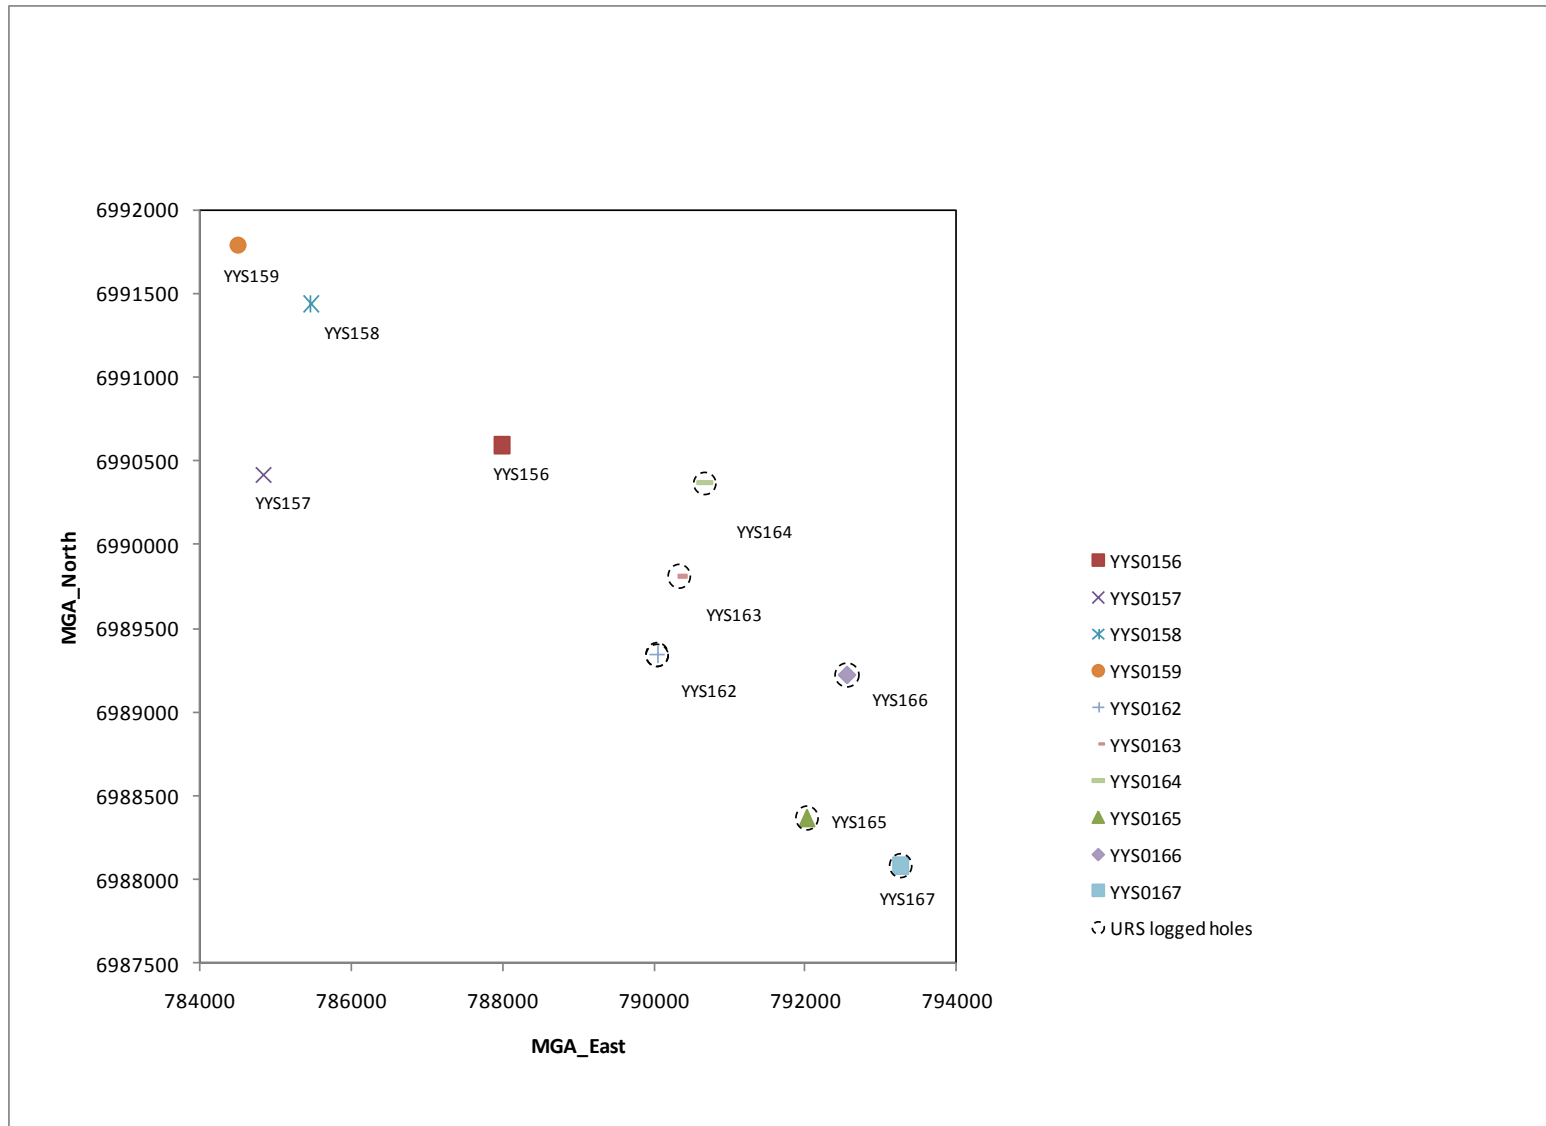


Figure A1.1: Locations of drill-holes at the Yeelirrie project site

**Table A1.1 Sample Log summarising characteristics of samples collected from drilling at the Yeelirrie site**

Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
		YYS156A	0	0.75	4.71	Tube	L							
1		YYS156A	0.75	1.5	9.11	Tube	L	10770	7.98					
		YYS156A	1.4	1.5	0.817	Bag	L			0.2	1.56	98.3	348	90
1		YYS156A	1.5	2.5	10.58	Tube	LT	6160	7.95					
		YYS156A	2.4	2.5	0.753	Bag	LT			4.07	0.92	1480	5236	320
1		YYS156A	3	4	13	Tube	LT	5380	8.47					
		YYS156A	4.4	5.9	32.48	Crushed rock	LT			6.79	0.09	524	1854	145
		YYS156A	5.9	7.5	26.63	Crushed rock	TCQ							
		YYS156A	7.5	8.25	9.1	Tube	CQT							
		YYS156A	8.25	9	9.86	Tube	CQT							
		YYS156A	8.9	9	0.89	Bag	CQ			0.01	0.09	232	821	200
		YYS156A	9	9.75	6.65	Tube	CQ							
		YYS156A	10.5	11.25	7.73	Tube	CQ							
		YYS156A	11.1	11.25	1.85	Bag	CQ			0.01	0.08	29.2	103	130
		YYS156A	11.2	12	1.064	Bag	CQ			0.06	0.1	74.1	262	155
1		YYS156A	11.25	12	10.07	Tube	CQ	8370	7.53					
1		YYS156A	12	12.75	9.41	Tube	CQ							
		YYS156A	12.4	12.5	1.051	Bag	CQ			0.02	0.08	47.9	169	185
		YYS156A	12.75	13.5	9.86	Tube	CQ	9220	7.88					
		YYS156A	13.5	14.25	7.04	Tube	CQ							
		YYS156A	14.25	15	9.58	Tube	CQ							
		YYS156A	14.9	15	0.777	Bag	CQ			0	0.1	23.4	83	145
		YYS156A	15	15.75	11.22	Tube	CQ							
		YYS156A	15.75	16.5	10.9	Tube	CQ							
		YYS156A	16.4	16.5	1.093	Bag	CQ			0	0.06	12.2	43	100
		YYS156A	16.5	17.25	11.4	Tube	CQ							
		YYS156A	17.25	18	11.23	Tube	CQ							
		YYS156A	17.9	18	1.369	Bag	CQ			0	0.08	15	53	105
		YYS157	0	1	9.19	Tube	L							
		YYS157	0.75		0.54	Bag	L			0.02	0.02	39.6	140	80
		YYS157	0.75	1.5	8.73	Tube	TCQ	681	7.88					
		YYS157	1.5	2.25	8.87	Tube	TCQ	206	8.46					
		YYS157	2.25		0.857	Bag	TCQ							
		YYS157	2.8		0.749	Bag	TCQ			3.75	0.09	61	216	60
		YYS157	3.2	3.65	7.36	Tube	TCQ	2290	8.69					
1		YYS157	3.65	4.1	6.61	Tube	TCQ	1638	9.01					

Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
		YYS157	5.2		0.843	Bag	CQ			0.09	0.03	18.9	67	85
		YYS157	6	6.5	8.74	Tube	CQ							
		YYS157	6.5	7	8.02	Tube	CQ							
		YYS157	7		1.055	Bag	CQ			0	0.02	4.6	16	80
		YYS157	7	8	10.44	Tube	CQ							
		YYS157	8	8.5	7.38	Tube	CQ							
		YYS157	9		0.942	Bag	CQ			0	0.03	9.4	33	85
		YYS157	9	9.8	8.74	Tube	CQ							
		YYS157	9.8	10.45	6.8	Tube	CQ							
		YYS157	10.45	11.1	7.3	Tube	CQ							
		YYS157	13.35	14.1	11.74	Tube	CQ							
		YYS157	14.1		0.501	Bag	CQ			0	0.04	5.9	21	80
		YYS157	14.1	15	13.57	Tube	CQ							
		YYS157	15	15.75	10.87	Tube	CQ							
		YYS157	15.75	16.5	8.51	Tube	CQ							
		YYS157	16.5		0.891	Bag	CQ			0	0.04	4.5	16	80
		YYS157	16.5	17.25	11.3	Tube	CQ							
		YYS157	17.25	18	7.95	Tube	CQ							
		YYS158	0	1	11.4	Tube	LT							
		YYS158	1	2	9.61	Tube	LT							
		YYS158	2		0.929	Bag	LT			7.74	0.07	412	1458	105
		YYS158	2	2.5	5.17	Tube	LT							
1		YYS158	2.5	3.5	14.13	Tube	LT							
		YYS158	3.5		0.973	Bag	T			8.1	0.08	32.1	114	50
1		YYS158	3.5	3.75	3.66	Tube	T	3154	8.47					
1		YYS158	3.75	4.5	10.76	Tube	T	4800	8.57					
		YYS158	4.5		1.047	Bag	T			7.74	0.08	216	764	95
		YYS158	4.5	5.25	8.7	Tube	T	1949	7.78					
		YYS158	5.25		0.997	Bag	T							
		YYS158	5.25	5.75	7.1	Tube	T							
		YYS158	5.75		0.44	Bag	T			8.41	0.13	52.3	185	75
		YYS158	5.75	6.6	10.46	Tube	T							
		YYS158	6		0.905	Bag	T							
		YYS158	6.6	7.2	8.16	Tube	T							
		YYS158	7.2		0.242	Bag	T			2.64	0.07	52.9	187	145
		YYS158	7.2	7.5	4.07	Tube	T							
		YYS158	7.5	8.25	11.35	Tube	T							
		YYS158	8.25	9	10.66	Tube	T							

Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
		YYS158	9		1.015	Bag	T			7.88	0.08	205	725	85
		YYS158	9	9.6	7.79	Tube	T							
		YYS158	9.6	10.2	8.4	Tube	CQT							
		YYS158	10		1.1	Bag	CQT							
		YYS158	10.2	11.1	12.23	Tube	CQ							
		YYS158	11.1	12	10.88	Tube	CQ							
		YYS158	12		1.091	Bag	CQ			0.03	0.03	6.6	23	70
		YYS158	12	13.1	13.01	Tube	CQ							
		YYS158	13.1		2.787	Bag	CQ							
		YYS158	13.1	13.7	7.79	Tube	CQ							
		YYS158	13.7		0.38	Bag	CQ							
		YYS158	13.7	14.2	6.65	Tube	CQ							
		YYS158	14.2		0.696	Bag	CQ			0	0.08	10.6	38	125
		YYS158	14.2	14.85	8.98	Tube	CQ							
		YYS158	14.85	15.5	8.73	Tube	CQ							
		YYS158	15.5	15.9	5.33	Bag	CQ							
		YYS158	15.9	16.3	5.55	Bag	CQ							
		YYS158	16.3	17.1	9.48	Bag	CQ			0	0.04	6.9	24	80
		YYS158	17.1	18	13.54	Bag	CQ							
		YYS159	1.5	2.1	7.32	Tube	LT							
		YYS159	2.1	2.7	7.54	Tube	LT			2.31	0.05	34.7	123	90
		YYS159	2.7	3.6	11.54	Tube	T							
		YYS159	3.6	4.5	11.27	Tube	T			5.49	0.06	30.7	109	85
1		YYS159	4.5	5.2	9.42	Tube	TCQ							
		YYS159	5.2	5.9	6.61	Tube	CQT			0.21	0.05	59.3	210	80
		YYS159	5.9	6.9	13.84	Tube	CQT							
		YYS159	7.5	8.15	9.06	Tube	CQ			0.04	0.04	3.4	12	45
		YYS159	8.8	9.2	5.85	Tube	CQ							
		YYS159	9.2	9.8	7.19	Tube	CQ							
		YYS159	10.3	10.85	8.09	Tube	CQ							
		YYS159	10.85	11.4	7.78	Tube	CQ							
		YYS159	11.4	12	8.85	Tube	CQ			0.01	0.04	3.7	13	55
		YYS159	12.6	13.1	7.42	Tube	CQ							
		YYS159	13.5	14.6	13.95	Tube	CQ							
		YYS159	17	18	12.61	Tube	CQ							
	1	YYS162	0.3	0.4	1.01	Grab sample	L	10160	6.65					
	2	YYS162	3.8	3.9	1.04	Grab sample	T							
1	3	YYS162	4.5	4.6	1.59	Grab sample	TCQ	2520	9.1					

Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
	4	YYS162	5.2	5.3	1.86	Grab sample	CQ	2520	9.1					
	5	YYS162	7	7.1	1.41	Grab sample	CQ							
	6	YYS162	9	9.1	1.55	Grab sample	CQ	2600	8.42					
	7	YYS162	10.8	10.9	1.56	Grab sample	CQ							
	8	YYS162	11.8	11.9	2.06	Grab sample	CQ							
	9	YYS162	12.7	12.8	1.36	Grab sample	CQ	2580	9					
	10	YYS162	15	15.1	2.06	Grab sample	CQ	193	8.4					
	11	YYS162	15.2	15.3	1.08	Grab sample	CQ	193	8.4					
	12	YYS162	16.3	16.4	1.54	Grab sample	CQ							
	13	YYS162	17.4	17.5	2.08	Grab sample	CQ							
	14	YYS162	18.8	18.9	1.5	Grab sample	CQ	193	8.4					
	15	YYS162	19.6	19.7	1.43	Grab sample	CQ							
	16	YYS162	20.9	21	2.33	Grab sample	CQ							
	17	YYS162	22.3	22.4	2.17	Grab sample	CQ	245	8.65					
	18	YYS162	23	23.1	1.63	Grab sample	CQ							
	19	YYS162	25.7	25.8	1.23	Grab sample	CQ							
	20	YYS162	27.4	27.5	1.2	Grab sample	CQ							
	21	YYS162	28.2	28.3	2.09	Grab sample	CQ	248	6.71					
	22	YYS162	29.6	29.7	2.2	Grab sample	CQ							
	1	YYS163	0.3	0.4		Grab sample	LQT	5830	8.98					
	2	YYS163	2.9	3		Grab sample	LQT	3350	9.56					
	3	YYS163	7.5	7.65	1.84	Grab sample	CQ	2137	7.83					
	4	YYS163	11	11.1	1.42	Grab sample	Grit	6600	8.07					
	5	YYS163	12.8	13	2.32	Grab sample	CQ							
	6	YYS163	15.7	15.8	1.41	Grab sample	CQ	3220	8.07					
	7	YYS163	18.8	18.9	1.99	Grab sample	CQ	2347	7.2					
1	8	YYS163	23	23.1	0.95	Grab sample	CQ	3920	7.59					
	9	YYS163	26.1	26.2	0.98	Grab sample	CQ	3220	7.61					
	1	YYS164	0.5	0.6	1.1	Grab sample	L	1915	4.91					
1	2	YYS164	4.3	4.4	1.09	Grab sample	LT							
1	3	YYS164	5.2	5.3	1.99	Grab sample	CQT	51.8	6.24					
	4	YYS164	8.1	8.3	2.96	Grab sample	CQ	15.5	7.57					
	5	YYS164	14	14.1	1.55	Grab sample	CQ							
	6	YYS164	15.5	15.6	2.23	Grab sample	Grit							
	7	YYS164	20.3	20.5	2.26	Grab sample	CQ	2710	6.47					
	8	YYS164	23.5	23.7	2.9	Grab sample	CQ							
1	9	YYS164	26.2	26.3	2	Grab sample	Grit							
	10	YYS164	29.4	29.5	2.36	Grab sample	CQ							



Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
	1	YYS165	0.2	0.3	1.04	Grab sample	LT	196.4	8.6					
	2	YYS165	0.7	0.8	1.21	Grab sample	LT	603	8.2					
1	3	YYS165	1.5	1.6	0.65	Grab sample	HT	2245	8.94					
	4	YYS165	5.4	5.5	1.49	Grab sample	CQT	2220	8.99					
1	5	YYS165	6.6	6.7	2.2	Grab sample	Grit	3360	8.92					
	6	YYS165	8.9	9	1.9	Grab sample	CQ	3220	8.2					
	7	YYS165	11.7	11.8	1.51	Grab sample	CQ							
	8	YYS165	14.6	14.8	1.85	Grab sample	CQ	3720	7.55					
	9	YYS165	16	16.1	1.44	Grab sample	CQ							
	10	YYS165	17.4	17.5	1.75	Grab sample	CQ	3290	8.9					
	11	YYS165	18.7	18.8	2.15	Grab sample	CQ	4250	7.62					
	12	YYS165	21.7	21.8	1.66	Grab sample	CQ	3510	8.05					
	13	YYS165	22	22.1	1.71	Grab sample	CQ	3450	7.88					
	14	YYS165	23.8	23.9	2.09	Grab sample	CQ	2316	8.24					
	15	YYS165	26.4	26.5	1.74	Grab sample	CQ	1329	8.53					
	16	YYS165	28	28.1	1.93	Grab sample	CQ							
	17	YYS165	29.8	29.9	1.63	Grab sample	CQ	3450	8.39					
1	1	YYS166	0.4	0.5	1.42	Grab sample	H	1493	6.46					
	2	YYS166	1.8	1.9	1.94	Grab sample	CQT	6450	8.78					
	3	YYS166	3.5	3.6	0.66	Grab sample	CQT	3320	9.38					
	4	YYS166	4	4.1	0.84	Grab sample	CQ	2600	8.22					
	5	YYS166	6.7	6.8	1.39	Grab sample	CQ	1297	7.95					
	6	YYS166	9.3	9.4	1.41	Grab sample	CQ	1229	7.6					
	7	YYS166	11	11.1	1.81	Grab sample	CQ							
	8	YYS166	13.6	13.7	1.34	Grab sample	CQ	248000	7.53					
	9	YYS166	14.7	14.8	1.26	Grab sample	CQ	1672	7.06					
	10	YYS166	16.9	17	1.52	Grab sample	CQ	2420	7					
	11	YYS166	20.1	20.2	2.54	Grab sample	CQ	1737	7.08					
	12	YYS166	21.3	21.4	1.28	Grab sample	CQ	2750	7.41					
	13	YYS166	23.5	23.6	1.43	Grab sample	CQ	3800	7.24					
	14	YYS166	23.9	24	0.88	Grab sample	CQ	3800	7.24					
	15	YYS166	25.7	25.8	1.34	Grab sample	CQ	4860	7.58					
	16	YYS166	26.8	26.9	1.57	Grab sample	CQ	4170	7.48					
	17	YYS166	29.2	29.3	1.54	Grab sample	CQ	4500	7.5					
	1	YYS167	0.3	0.4	1.51	Grab sample	L	261	5.79					
1	2	YYS167	2.3	2.4	1.03	Grab sample	LQT	2016	9.41					
	3	YYS167	3.9	4	1.4	Grab sample	CQT	1071	8.71					
	4	YYS167	5.2	5.3	0.95	Grab sample	CQ							



Selected <sup>[1]</sup>	URS # <sup>[2]</sup>	Drill hole	From	To	Mass	Sample type	Litho type <sup>[3]</sup>	Paste Parameters <sup>[4]</sup>		'Minimal' assay results <sup>[5]</sup>				
								EC μS/cm	pH	TIC	S %	U ppm	U <sub>3</sub> O <sub>8</sub> ppm	V ppm
	5	YYS167	7.3	7.4	1.56	Grab sample	CQ	4400	7.27					
	6	YYS167	9.1	9.2	1.52	Grab sample	CQ	2460	7.69					
	7	YYS167	11.1	11.2	2.17	Grab sample	CQ	2690	7.74					
	8	YYS167	11.8	11.9	0.92	Grab sample	CQ	2690	7.74					
	9	YYS167	14.3	14.4	1.53	Grab sample	CQ	3370	7.9					
	10	YYS167	16.6	16.7	1.8	Grab sample	CQ	4530	7.43					
	11	YYS167	20.4	20.5	1.85	Grab sample	CQ							
1	12	YYS167	23	23.1	2.49	Grab sample	Grit	4360	7.34					
	13	YYS167	24.5	24.6	1.33	Grab sample	CQ	3290	7.31					
	14	YYS167	27.3	27.4	1.37	Grab sample	Grit	2510	7.01					
	15	YYS167	29.3	29.4	2.06	Grab sample	CQ	2270	7.6					
						Minimum		15.5	4.91					
						Median		2690	7.88					
						Maximum		248000	9.56					



## Notes:

- [1] Sample selected for inclusion in the detailed laboratory characterisation programme.
- [2] Sample numbering used by URS during sample collection and logging.
- [3] Based on URS logging information for Boreholes YYS162 to 167. For Boreholes 156A to 159, based on 'minimal' assay results combined with later assessment in the laboratory (with the assistance of BHP geologists).
- [4] Field measurements undertaken by URS (Boreholes YYS162 to 167), laboratory measurements by SRK (Boreholes 156A to 159).
- [5] Boreholes 156A to 159 were not logged in the field. To assist with lithological differentiation, bulk chemical assays were undertaken.



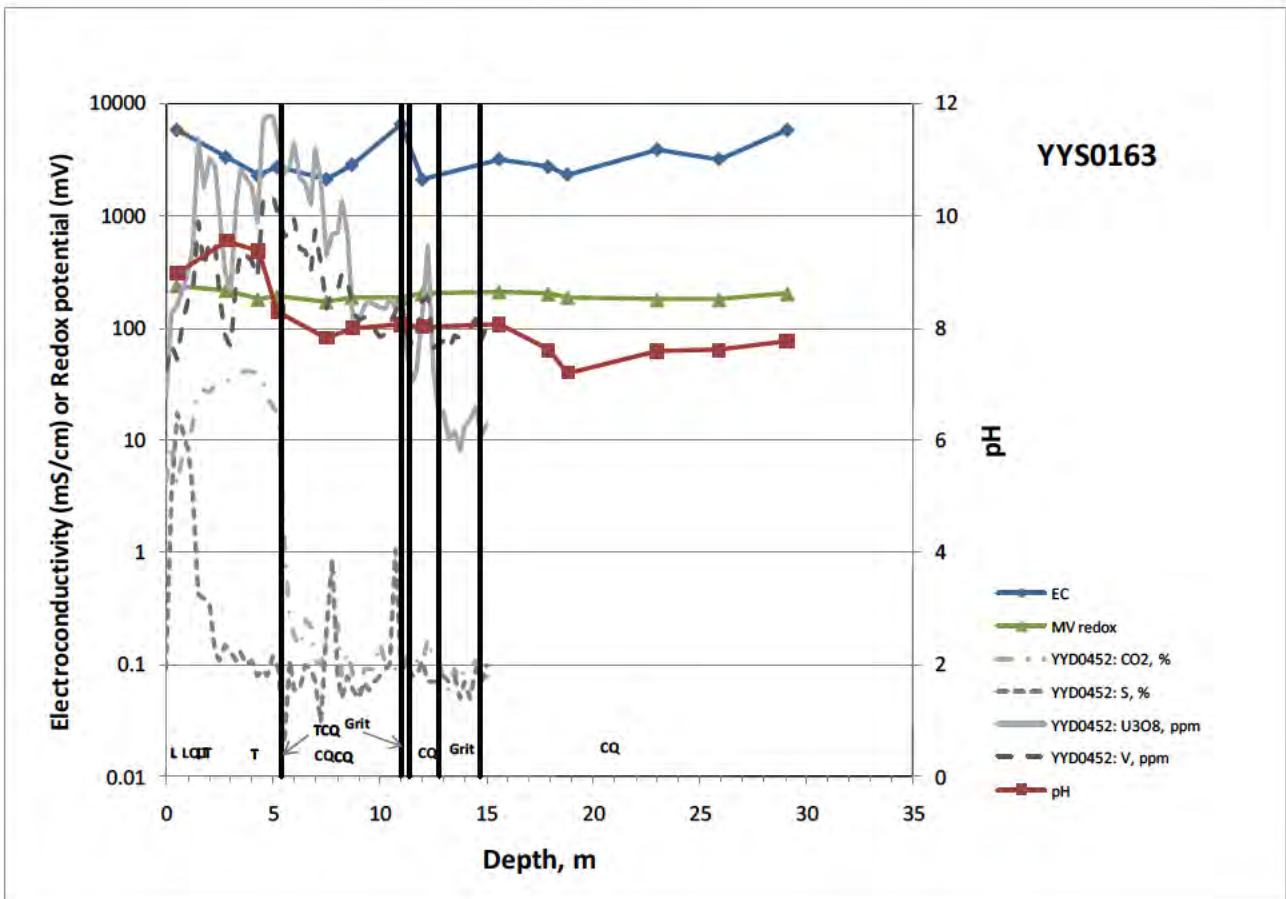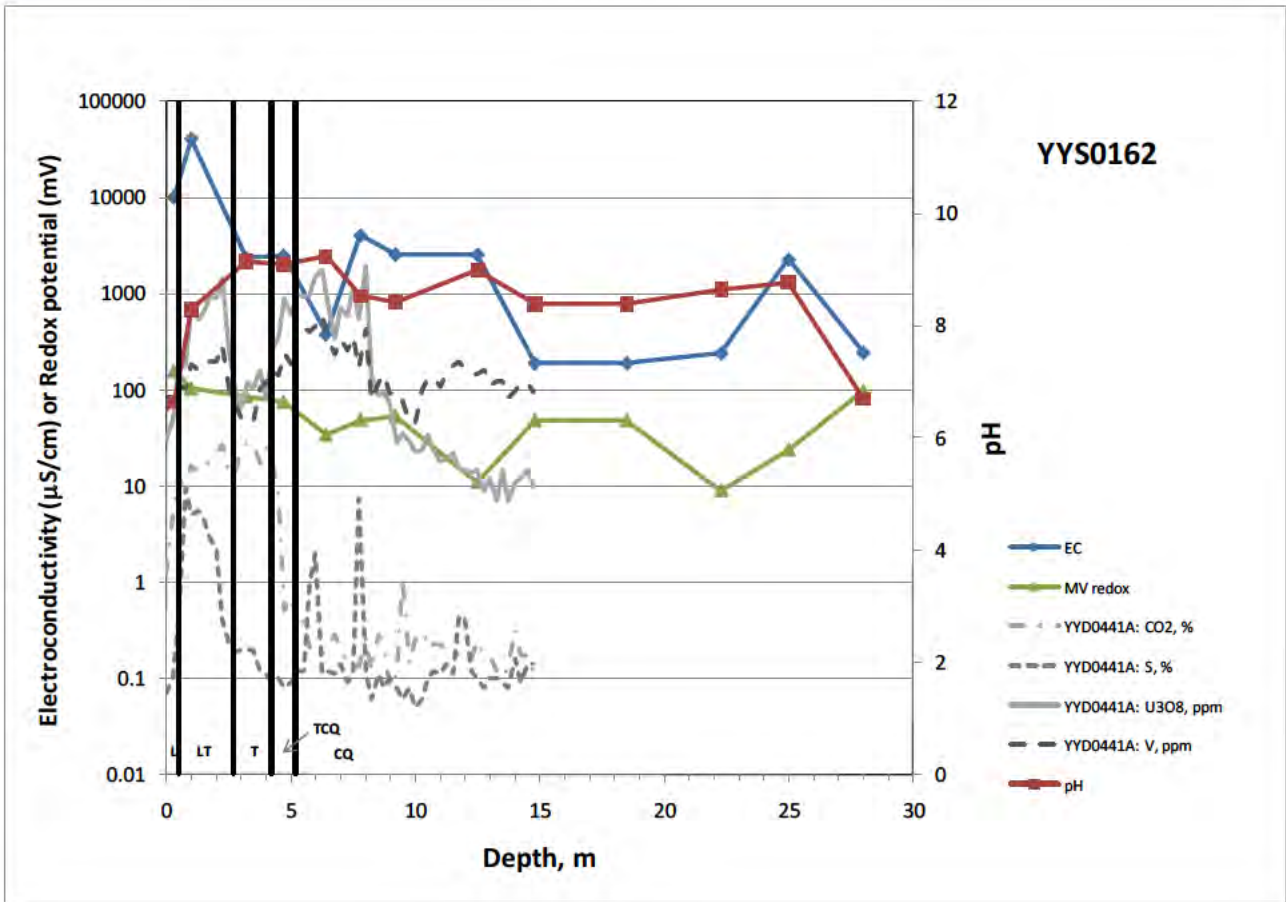

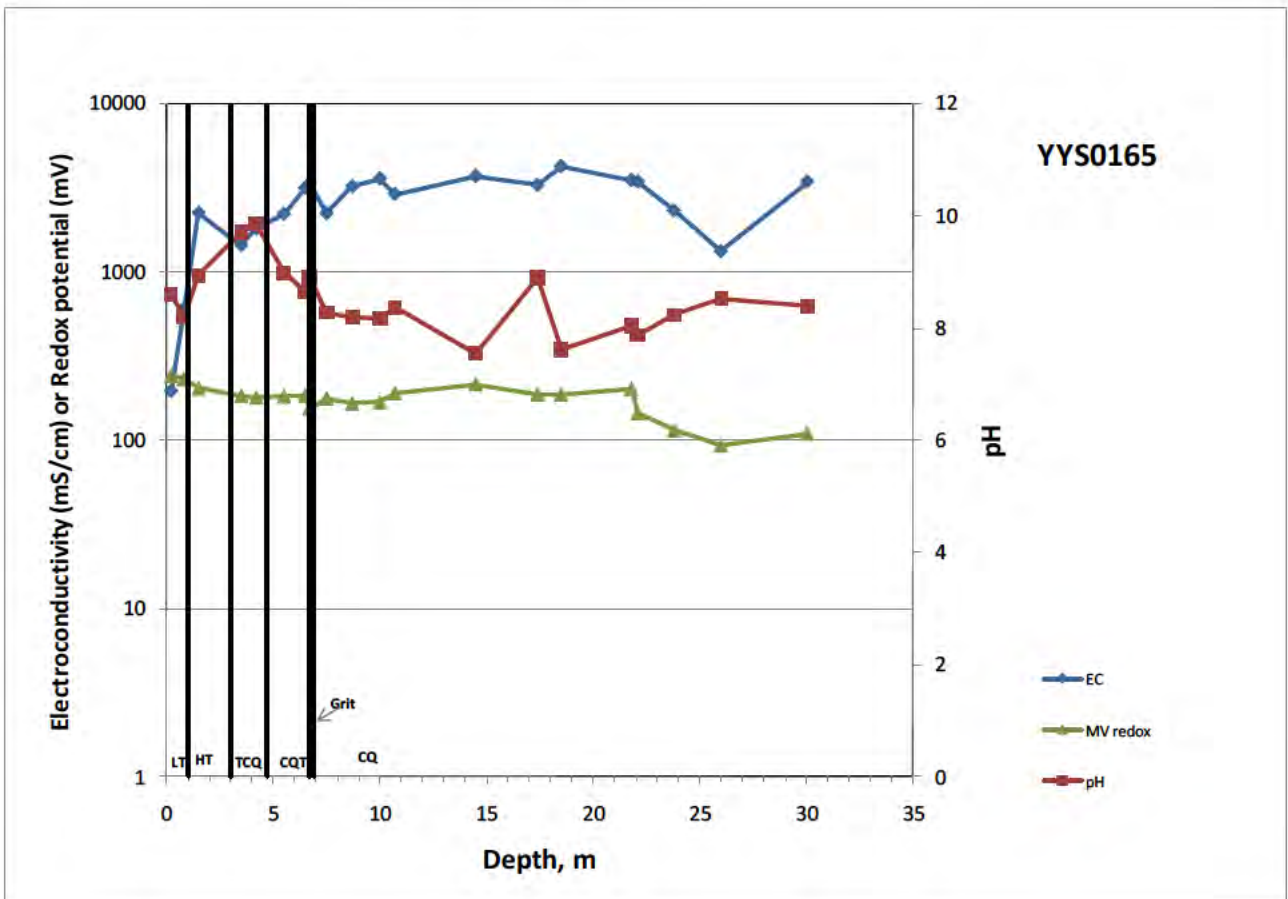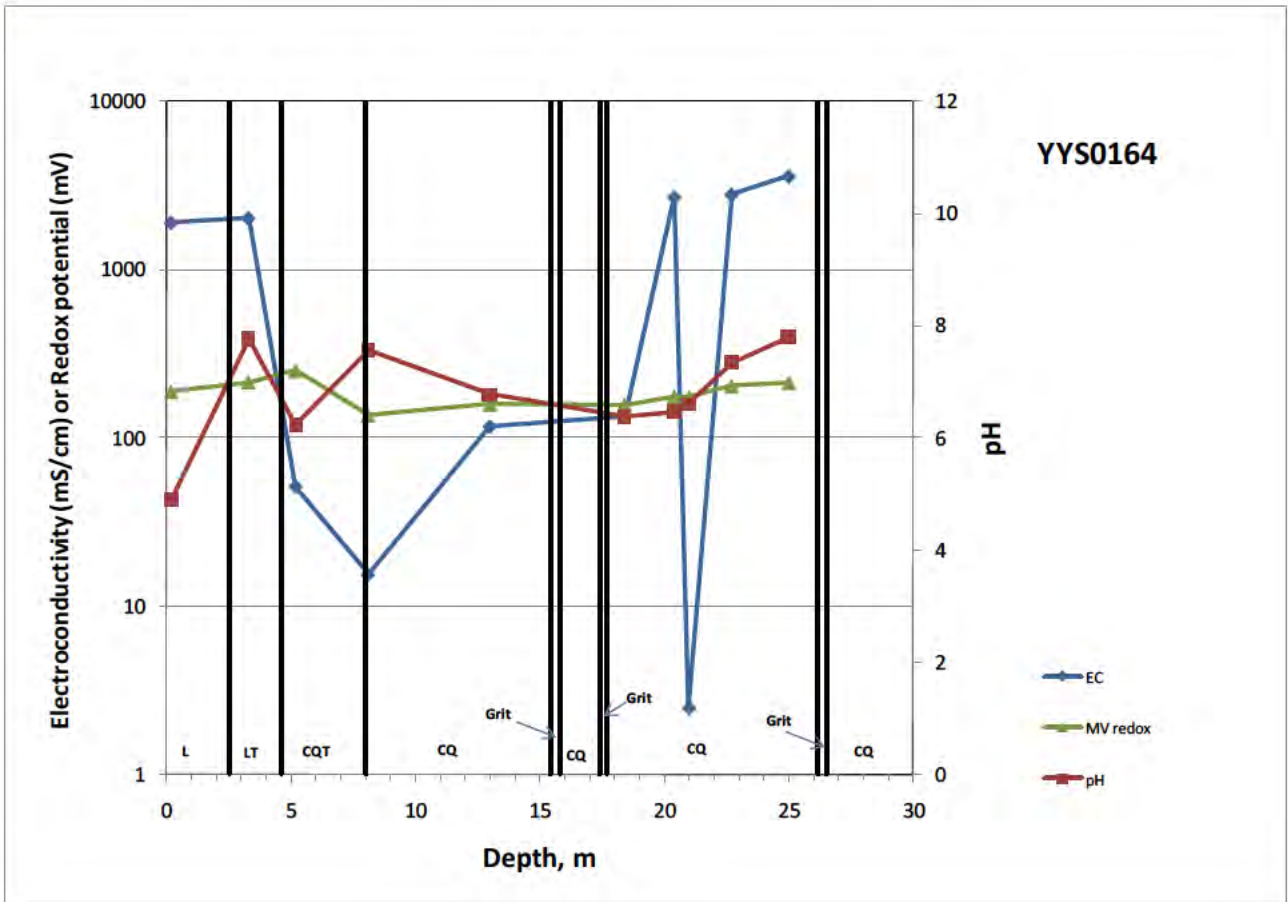

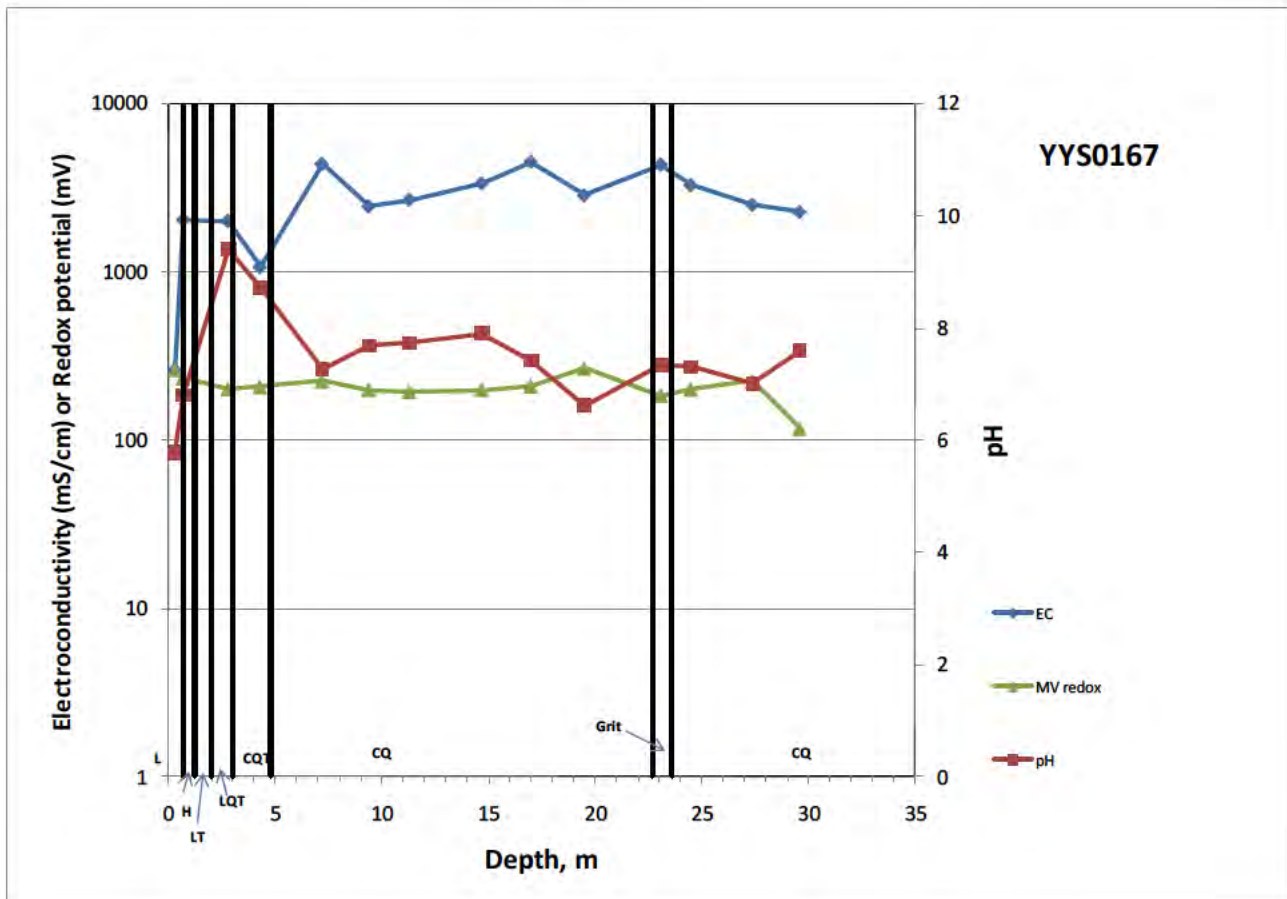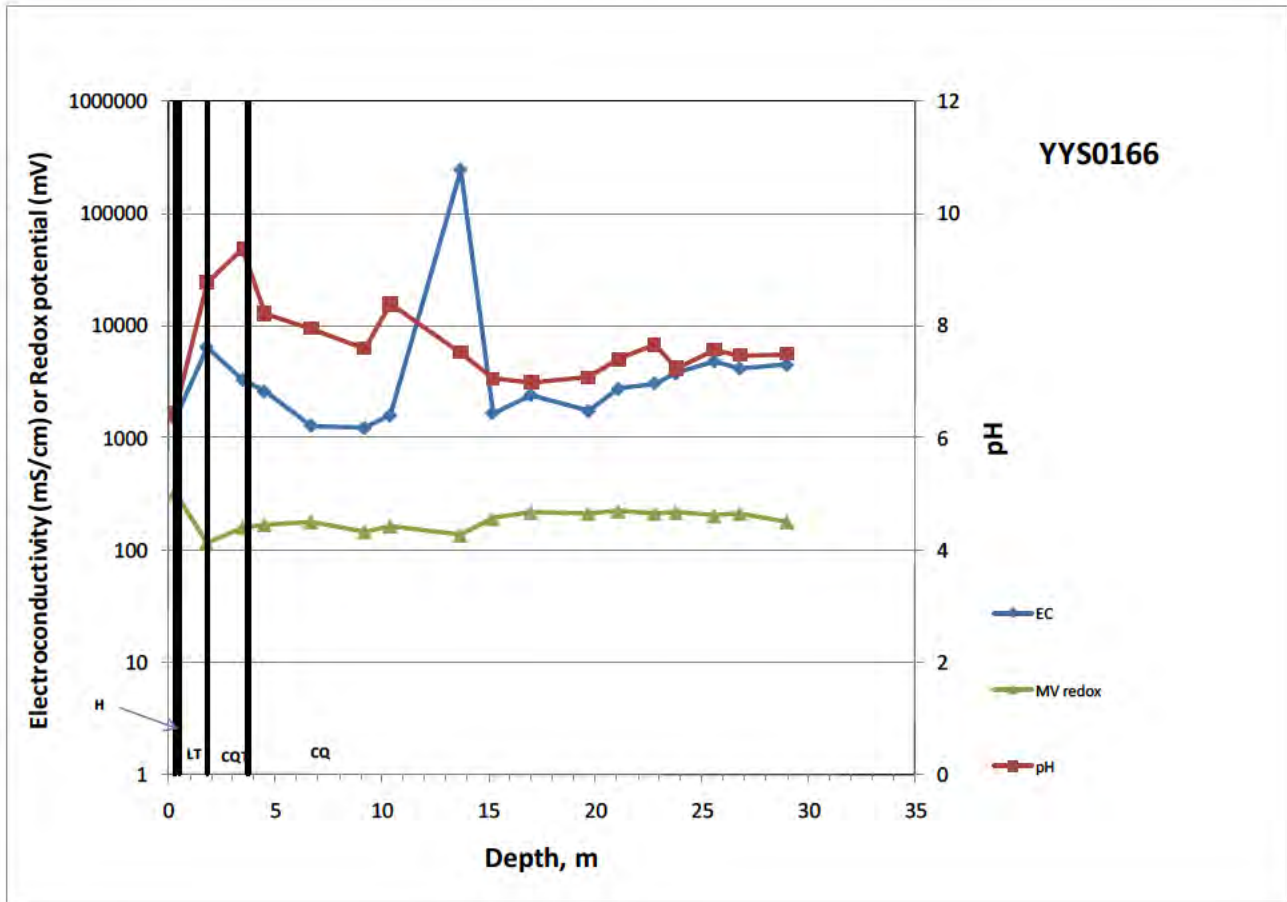

## BOREHOLE YYS0162 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**

 Bore Size: **96 mm**

 Relative Level: **496.60 mRL**

 Drill Type: **Sonic Drilling**

Checked By:

 Total Depth: **30.00 m**

 Coordinates: **6989343.00 mN**

 Drill Model: **300C Prosonic**

 Date Started: **11-8-09**

 Casing Size: **127 mm**
**790048.00 mE**

 Drill Fluid: **N/A**

 Date Finished: **12-8-09**

 Permit No: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	0.30			0		SM	LOAM; Silty SAND, loose, red-brown, angular, poorly graded, dry.				G	Geochem #1	L
	0.50												
	0.95		8/9/8 N=17	1		SM	CARBONATED LOAM; SAND with moderately cemented Quartz (QZ), medium dense, orange-brown with white, reacts with hydrochloric acid (HCl), dry. - Becomes Silty SAND, yellow-brown, low plasticity, reacts highly with HCl, recovered in broken clumps.				X	UD #1 SPT #1	LT
				2			- Becomes red-brown with patchy pale-white.						
	2.50		11/33/17 for 30mm N>50	3			CALCRETE; recovered as broken rock fragments in weakly to moderately cemented Clayey SAND, grey-white, very low strength rock, reacts with HCl.				X	SPT #2	T
	3.80												
	4.00		8/12/21 N=33	4		SM	TRANSITION CALCRETE; recovered as Silty SAND, with 10% QZ content, pale grey-yellow with red-orange staining, sample wet water table at 4.2m. - Becomes red, medium grained QZ grains, weakly cemented. - Becomes moderately cemented.				X	SPT #3 Geochem #3	TCQ
	4.50			5		ML	CLAY-QUARTZ; Sandy SILT, very stiff, red-brown, fined to medium grained, medium plasticity, does not react with HCl.				X	Geochem #4	
	5.20												
	5.50		8/12/23 N=35	6			- Increase 20% QZ content, coarse grained, subangular to subrounded.				X	SPT #4	
	6.50											UD #2	
	7.00			7		CL	Becomes Silty CLAY trace Sand, hard, patchy yellow-brown, low plasticity, homogenous, no reaction to HCl.				X	Geochem #5	CQ
	8.50		50 Blows for 40mm N>50	8		SM	Becomes Silty SAND, moderately cemented.						
						SM-CL	Becomes Clayey SAND / Sandy CLAY, very dense, patchy brown, red and yellow, fine to medium grained QZ.						
	9.00			9		SM	Becomes Silty SAND, yellow-grey, angular, gap graded wet angular QZ grains. - Becomes mottle brown-grey.					SPT #5	
						CL	Becomes Sandy CLAY, patchy pale yellow-dark brown, fine to medium grained sand.				X	Geochem #6	

## BOREHOLE YYS0162 - DRAFT

URS Australia Level 3 20 Terrace Road EAST PERTH WA 6004		Phone 08 9326 0100 Fax 08 9326 0296		Project Reference: <b>Yeelirrie Uranium Project                  Geochemistry / Geotechnical &amp;                  Hydrogeological Drilling and Sampling</b>		Client: <b>BHP Billiton</b>	
Drilling Contractor: <b>Client Contracted - Boart Longyear</b>		Project No.: <b>42907140</b>		Location: <b>Yeelirrie</b>			
Logged By: <b>BN</b>		Bore Size: <b>96 mm</b>		Relative Level: <b>496.60 mRL</b>		Drill Type: <b>Sonic Drilling</b>	
Checked By:		Total Depth: <b>30.00 m</b>		Coordinates: <b>6989343.00 mN</b>		Drill Model: <b>300C Prosonic</b>	
Date Started: <b>11-8-09</b>		Casing Size: <b>127 mm</b>		<b>790048.00 mE</b>		Drill Fluid: <b>N/A</b>	
Date Finished: <b>12-8-09</b>				Permit No: <b>N/A</b>			

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	10.50	>200	30/50 for 40mm N>50	10		GM	CLAY-QUARTZ: Silty Gravel, very dense, yellow-orange-brown, fine to medium grained, angular QZ grains, well graded, moderately cemented, trace black angular gravels.				<input checked="" type="checkbox"/>	SPT #6	
	10.80			11		SC-CH	Becomes Silty Sandy CLAY, hard, pale brown-red, high plasticity.  - Becomes patchy brown-red with yellow, possibly disturbed, very stiff.				<input checked="" type="checkbox"/>	Geochem #7	
	11.80			12		SC-CH	- Becomes hard, red-brown, homogeneous, trace fine grained QZ.				<input checked="" type="checkbox"/>	Geochem #8	
	12.70			13		SC-CH	- Becomes Silty CLAY with 5%, hard, orange-brown, angular fine to medium grained QZ, high plasticity, moist.				<input checked="" type="checkbox"/>	Geochem #9	
	14.00			14		SC-CH	Becomes Clayey SAND, Sandy CLAY, increase QZ sand grains 50%, very stiff, moist.						
	15.00			15		CH	Becomes Silty CLAY with 5% angular fine to medium grained QZ, hard, patchy orange-brown, and yellow, moist.  - Becomes patchy orange-yellow and pale grey.				<input checked="" type="checkbox"/>	Geochem #10	CG
	15.20			16		CH	- Becomes CLAY, with trace 5% QZ, hard, yellow-brown, angular QZ grains, medium to high plasticity, moist, homogeneous, shiny surface results when cut into clay with knife.				<input checked="" type="checkbox"/>	Geochem #11	
	16.30			17		CH	- Becomes Silty CLAY, very stiff, yellow-brown-orange, high plasticity. - With pockets of Silty SAND, pale grey-yellow, angular, moist to wet.				<input checked="" type="checkbox"/>	Geochem #12	
	17.40			18		CH	- Becomes CLAY, with trace 5% QZ, hard, yellow-brown, angular QZ grains, medium to high plasticity, moist, homogeneous, shiny surface results when cut into clay with knife.				<input checked="" type="checkbox"/>	Geochem #13	
	17.50			18		CH	- Becomes CLAY, with trace 5% QZ, hard, yellow-brown, angular QZ grains, medium to high plasticity, moist, homogeneous, shiny surface results when cut into clay with knife.						Lexan #1 17.5-18.2m extra 0.3m
	18.80			19		CH	- Becomes Silty CLAY, very stiff, yellow-brown-orange, high plasticity.				<input checked="" type="checkbox"/>	Geochem #14	
	19.60	>100		19		CH	- Becomes Silty Sandy CLAY, trace 5% QZ grains, hard, pale yellow-brown, high plasticity, homogeneous, moist, smooth surface results when cut with knife.				<input checked="" type="checkbox"/>	Geochem #15 UD #3	
	19.70												
	20.00												

## BOREHOLE YYS0162 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **11-8-09**  
 Date Finished: **12-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **496.60 mRL**  
 Coordinates: **6989343.00 mN  
 790048.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				20		SC-CH	CLAY-QUARTZ; Silty Sandy CLAY, trace 5% QZ grains, hard, pale yellow-brown, high plasticity, homogeneous, moist, smooth surface results when cut with knife. - Becomes pale grey-green.					Lexan #2 19.7-20.9m extra 0.3m	
	20.90			21		CH	Becomes CLAY, hard, grey-pale green, high plasticity, moist. - Becomes CLAY with 5% QZ, fine to medium grained, intact core. - Becomes very stiff.					Geochem #16	
	22.30			22		SC-CH	Becomes Sandy CLAY.					Geochem #17	
	23.00			23								Geochem #18	
	23.20	>200	18/30/48 N>50				- Becomes patchy pale grey-pale green and brown, very stiff.					SPT #7	
	25.70			25								Geochem #19	
	27.40			27			- Becomes stiff, possibly disturbed by drilling water. - Becomes Silty Sandy CLAY, pale green - pale grey, stiff, high plasticity. - Becomes firm.					Geochem #20	
	28.00			28								UD #4	
	28.45						- Becomes hard, pale green-grey and brown.					Geochem #21	
	29.60			29								Geochem #22	
							EOH at 30.0m.						

**Remarks:** 1.0 Monitoring well installed, 2.0m screen from 8.8-10.8m.  
 2.0 Backfilled monitoring well from:  
 EOH - 13.8m: backfilled with core samples  
 13.8-11.8m: Gravel pack  
 11.8-10.8m: Bentonite pellets  
 10.8-8.0m: Gravel pack  
 8.0-7.0m: Bentonite pellets  
 7.0-0m: Gravel pack

## BOREHOLE YYS0163 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **16-8-09**  
 Date Finished: **17-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.20 m**  
 Casing Size: **127 mm**

 Relative Level: **496.30 mRL**  
 Coordinates: **6989813.00 mN  
 790334.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	0.30			0		ML	QUARTZ RICH CARBONATED LOAM; Sandy SILT, disturbed, white - pale pink, fine to medium grained subangular Quartz (QZ), low plasticity, aggressively reacts with hydrochloric acid (HCl).					Geochem#1	LOT
	0.50			0.5								Lexan#1 0.5-2.0m	
	2.00		13/25/32 N>50	2			- Becomes very dense, fine to coarse grained QZ.					SPT#1	
	2.90			2.9								Geochem#2	
	3.00			3			- Becomes Silty SAND, very dense, brown and patchy white, fine to coarse grained QZ, subangular with assorted homogenous pale white chips subrounded 1-3mm, some black Iron (Fe) staining with yellow-brown induration, reacts with HCl.					SPT#1	
	4.00			4			- Becomes Sandy Gravelly CLAY, pale brown - pale grey, disturbed, fine to coarse grained, various sand and gravel particles, brown and black gravels (2-5mm) evident, moderately cemented, trace QZ grains, trace reaction to HCl, trace bright yellow staining.					Geochem#2	
	5.20		11/17/23 for 10mm N>50	5.2			- Sandy CLAY (20% Sand / 80% Clay), hard, pale grey-brown, with fine to medium grained QZ, subangular, reacts gently with HCl, friable, moist, interbedded staining of red-brown.					SPT#2	
	5.61			5.6		ML	- 100-200mm layers of cemented Clay and QZ grains, dark red, fine to medium grained, subangular to subrounded QZ, wet.					UD#1	
	6.06		7/14/20 N=34	6			CLAY-QUARTZ; Sandy SILT/CLAY (20% Sand / 80% Silt/Clay), hard, fine to medium grained, subangular, low plasticity, moist, no reaction HCl.					SPT#3	
	6.70			6.7			- With bright yellow staining, and patchy pale yellow.					Lexan#3 5.2-6.7m	
	6.98		9/16/11 N=27	7			- Becomes Sandy CLAY (40% Sand / 60% Clay), hard, red, fine to medium grained, occasional coarse grained, subangular to subrounded, moist, brown staining on QZ.					UD #2	
	7.50			7.5								SPT #4	
	8.70			8.7			- Becomes more Clay (80%), red-brown with patchy orange, fine to medium grained QZ, evidence of clear crystallisation, no reaction to HCl.					Geochem #3	CO
	8.83		50 for 130mm N>50	8.8			- Trace clear crystallisation.					SPT #5	
				9			- Become red-brown with patchy pale grey.					Lexan #4 8.7-10.2m	

## BOREHOLE YYS0163 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **16-8-09**  
 Date Finished: **17-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.20 m**  
 Casing Size: **127 mm**

 Relative Level: **496.30 mRL**  
 Coordinates: **6989813.00 mN  
 790334.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	10.20			10		CL	CLAY-QUARTZ; Sandy CLAY (40% Sand / 60% Clay), hard, patchy brown-orange and pale yellow-grey, fine to coarse grained QZ, subrounded, moist.					UD #3	CQ
G	11.00			11		SP	GRIT; QZ Sand with Clay, loose, red, coarse grained, uniform graded, subrounded, wet.					Geochem #4 (Grit)	Grit
G	12.00			12		CL	CLAY-QUARTZ; Sandy CLAY (40% Sand / 60% Clay), hard, patchy brown-orange and pale yellow-grey, fine to coarse grained QZ, subrounded, moist. - Becomes more Clay (70%), patchy brown-pale grey, stiff.					Geochem #5	CQ
	12.20											UD #4 (Grit?)	
	12.60		11/17/37 N>50	13		SP	- Becomes hard, patchy red and grey (interbedded colours), fine to coarse grained sand, subrounded.					SPT #6	
	13.20			13		CL	GRIT; QZ Sand with Clay, red, loose, coarse grained, uniform graded, subrounded, wet. - Becomes Sandy CLAY (40% Sand / 60% Clay), red, grit transition zone. - Becomes red-brown, fine to coarse grained, wet.					Lexan #5 13.2-14.7m	Grit
	14.80			15		CH	CLAY-QUARTZ; CLAY with 10% Sand, hard, patchy pale grey-brown, fine grained sand, moist, friable. - Becomes less Sand (5%) patchy brown and grey, high plasticity, homogenous, moist, intact clay core, casing gets stuck due to hard Clay,					UD #5	
G	15.70			16								Geochem #6	
	16.00			17			- Becomes pale brown orange.						
	18.50			18			- Trace subrounded coarse grained QZ.						
G	18.80		19/22/28 for 100mm N>50	19			- Becomes pale brown with more QZ grains 10%, sample disturbed and stretched in rod.					SPT #7 Geochem #7	
				19		CL-CH	- Becomes Sandy CLAY (20% Sand / 80% Clay), very stiff, pale brown - pale red, fine to medium grained QZ, high plasticity, inclusions of rounded to subrounded Clay gravels, friable, moist. Trace small pockets of QZ, coarse grained (10-20mm).						CQ



## BOREHOLE YYS0163 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **16-8-09**  
 Date Finished: **17-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.20 m**  
 Casing Size: **127 mm**

 Relative Level: **496.30 mRL**  
 Coordinates: **6989813.00 mN  
 790334.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	20.20			20		CL-CH	CLAY-QUARTZ; Sandy CLAY (20% Sand / 80% Clay), very stiff, pale brown - pale red, fine to medium grained QZ, high plasticity, inclusions of rounded to subrounded Clay gravels, friable, moist.					UD #6	CC
	20.46			21		CH	Becomes CLAY trace fine grained QZ, hard, pale brown-orange, high plasticity, friable, flaky, moist, homogenous.					Lexan #7 20 2-21 2m extra 0 3m	
				22		CL-CH	Becomes Sandy CLAY (20% Sand / 80% Clay), hard, pale brown - pale grey - green, fine grained sand, flaky. (Sample disturbed, outer layer of core sticks to the rods and only the inside core falls out).						
	23.00			23		CH	- Becomes less Clay (70%), trace pockets of moderately cemented subrounded coarse grained QZ, 15-20mm in size.					Geochem #8	
	23.20			24		CH	Becomes CLAY trace fine grained QZ, hard, pale brown-orange, high plasticity, friable, flaky, moist, homogenous, smooth surface results when cut with a knife.					Lexan #8 23 2-24 3m extra 0 4m	
	24.30			25		CL-CH	Sandy CLAY (30% Sand / 60% Clay), pale grey-brown-green, fine to medium grained, subrounded to subangular QZ, moist.					UD #7	
				26		CH	CLAY with 5% QZ, very stiff - hard, with patchy pale brown-orange and pale grey-green, fine to medium grained sand, high plasticity, moist, homogenous, rapidly dries and hardened when taken out of bags.					Geochem #9	
	26.10			27		CH						Lexan #9 26 2-27 2m extra 0 5m	
	26.20			28		CH							
	29.20			29		CH	- Becomes very stiff-hard, pale grey-pale green with patches of pale brown-orange.					Lexan #10 29 2-30 2m extra 0 5m	

**Remarks:** 1.0 Two monitoring wells installed, screens from 10.5-13.0m and 3.5-5.5m.  
 2.0 Backfilled monitor well from:  
 EOH - 15.0m: backfilled with core samples 8.5-6.5m: Gravel pack  
 15.0-14.0m: Gravel pack 6 5-5 5m: Bentonite pellets  
 14.0-13.0m: Bentonite pellets 5 5-2.5m: Gravel pack  
 13.0-9.5m: Gravel pack 2.5-1.2m: Bentonite pellets  
 9.5-8.5m: Bentonite pellets 1.2-0.0m: Gravel pack



# BOREHOLE YYS0163 - DRAFT

URS Australia  
Level 3  
20 Terrace Road  
EAST PERTH WA 6004

Phone 08 9326 0100  
Fax 08 9326 0296

Project Reference: **Yeelirrie Uranium Project  
Geochemistry / Geotechnical &  
Hydrogeological Drilling and Sampling**

Client: **BHP Billiton**

Location: **Yeelirrie**

Drilling Contractor: **Client Contracted - Boart Longyear**

Project No.: **42907140**

Logged By: **BN**  
Checked By:  
Date Started: **16-8-09**  
Date Finished: **17-8-09**

Bore Size: **96 mm**  
Total Depth: **30.20 m**  
Casing Size: **127 mm**

Relative Level: **496.30 mRL**  
Coordinates: **6989813.00 mN  
790334.00 mE**  
Permit No: **N/A**

Drill Type: **Sonic Drilling**  
Drill Model: **300C Prosonic**  
Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				30		CH	CLAY-QUARTZ; CLAY, hard. EOH at 30.2m.					co
				31								
				32								
				33								
				34								
				35								
				36								
				37								
				38								
				39								

## BOREHOLE YYS0164 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **13-8-09**  
 Date Finished: **15-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **496.70 mRL**  
 Coordinates: **6990368.00 mN  
 790673.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	0.50 0.60			0		SM	LOAM; Silty SAND, loose, red, fine to medium grained, sub-angular, dry with fragments of moderately cemented sand.				Geochem#1	
	1.60 1.84		14/50 for 90mm N>50	1			- Becomes red-brown with highly cemented fragments of Quartz (QZ) grains with trace black grains.				Lexan#1 0.6-1.5m extra 0.3m SPT#1	L
	3.50		N>50 for 100mm	2		SM	CARBONATED LOAM; SILT, white with cemented brown sand with trace black minerals. - Becomes Silty SAND (40% Silt / 60% Sand), disturbed loose, red-brown, fine to medium grained, moist.				Lexan#2 1.6-2.5m SPT#2	LT
	4.30 4.50		N>50 for 140mm	3		SM	- Becomes SAND with trace Clay, very dense, fine to medium grained, poorly graded trace moderately cemented fragments. Contains fragments of weakly cemented Silty Sand with carbonate content reacts with hydrochloric acid (HCl). - Becomes Silty Clayey SAND, loose from drilling, red-brown with weakly cemented fragments of Clay, Sand and Carbonate, grey-white. - Becomes more Silt and Clay content 50%.				Geochem#2 SPT#3	
	5.20 5.50			4		CL	CARBONATED CLAY-QUARTZ; Silty Clayey SAND, red-brown with highly cemented fragments (30-80mm) of Clay, QZ and Carbonate.				Geochem#3	
	6.00 6.33		16/37/13 for 30mm N>50	5		SM	- Becomes Sandy CLAY, red-brown, soft to firm probably disturbed, low to medium plasticity, fine to medium grained QZ grains, angular, moist. - Silty SAND (30% Silt / 70% Sand), weakly cemented, loose, brown-red, fine to medium grained angular QZ, moist. - Becomes SAND with 10% Clay, disturbed, red-brown, fine to medium grained gap graded, moist-wet. - Becomes Silty SAND, red-brown, with fragments of highly cemented Clay and QZ, moist to wet.				UD#1 SPT#4	CQT
	7.40		50 blows for 100mm N>50	6		SM	- With 5-70mm fragments of cemented QZ sand and yellow Clay inclusions, sample was wet due to drilling water for casing.				Lexan#3 6.0-7.4m extra 0.1m SPT #5	
	8.10			7							Geochem #4	
	9.05 9.40		50 blows for 50mm N>50 no recovery	8		SM	CLAY-QUARTZ; Silty SAND (20% Silt / 80% Sand), very dense, red-brown, weakly cemented, fine to medium grained, subangular to subrounded grains, well graded with 20-30mm pockets of highly cemented material, sample was intact, moist to wet. - Sample disturbed recovered as 5-30mm fragments weakly cemented in Silty SAND, red-brown, with black Fe staining, yellow and red faint layering (5-10mm) in fragments. - Disturbed sample, recovered as loose SAND with 10% Clay, red-brown, no reaction to HCl.				Lexan #4 9.4-10.4m melted SPT#6	CQ
				9		SC	Becomes Clayey SAND, disturbed, red-brown, fine to medium grained, angular to subangular QZ sand, high plasticity Clay content.					

## BOREHOLE YYS0164 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **13-8-09**  
 Date Finished: **15-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **496.70 mRL**  
 Coordinates: **6990368.00 mN  
 790673.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				10		SC	CLAY-QUARTZ; Clayey SAND, disturbed, red-brown, fine to medium grained, angular to subangular QZ sand, high plasticity Clay content, moist. - With fragments of highly cemented Clayey SAND, does not react with HCl.						
				11		CL-CH	Becomes Sandy CLAY, red-brown, disturbed, moist. - Becomes fine to medium with occasional coarse grained QZ Sand, with manganese staining.						
				12			- Becomes Sandy CLAY (30% Sand / 70% Clay), hard, moderately cemented, recovered in 5-40mm fragments, moist-dry. - Becomes pale yellow-brown, no reaction to HCl.						
	13.20 13.32			13			- Becomes SAND trace Silt, possible Grit, disturbed, loose.					UD #2 Lexan #5 13.2-13.9m	CQ
	13.90 14.00		50 blows for 90mm N>50	14		CL-CH	Becomes Sandy SILT, very stiff, pale yellow-brown, fine to medium grained QZ. Becomes Sandy CLAY (30% Sand / 70% Clay), hard, high plasticity, pale brown-yellow, with trace pale grey-yellow, fine to medium grained QZ grains, core begins to be more intact.					SPT#7 Geochem #5	
				15		SM	- Becomes pale yellow-brown, 30% fine to medium grained QZ, trace slickensided surfaces. Becomes Silty SAND (20% Silt / 80% Sand), very dense, pale yellow-brown, fine to medium grained QZ, subangular, well graded, weakly cemented, moist.					Geochem #6	Grit
	15.50			16		SP	- Becomes yellow-brown-red with majority medium grained. GRIT; SAND, loose to medium dense, pale grey-brown, subangular, fine to coarse grained sand, moist to wet.						
	16.10			17		SM	CLAY-QUARTZ; Silty SAND (20% Silt / 80% Sand), very dense, pale yellow-brown, fine to medium grained QZ, subangular, well graded, weakly cemented, moist. - Becomes red-brown.					Lexan #6 16.1-17.4m	CQ
				18		SP	GRIT; SAND, loose to medium dense, pale grey-brown, subangular, fine to coarse grained sand, moist to wet.						Grit
	18.40 18.50			19		SM-SC	CLAY-QUARTZ; Clayey SAND (40% Clay / 60% Sand), very dense, grey-brown, fine to medium grained QZ, subangular, well graded, weakly cemented, moist. - Increase SAND content (70%), grey-brown and red.					UD refusal	
						SM-CH	Becomes CLAY/SAND, pale yellow-brown and pale grey.					Lexan #7 18.4-19.7m	CQ

## BOREHOLE YYS0164 - DRAFT

URS Australia Level 3 20 Terrace Road EAST PERTH WA 6004		Phone 08 9326 0100 Fax 08 9326 0296		Project Reference: <b>Yeelirrie Uranium Project                  Geochemistry / Geotechnical &amp;                  Hydrogeological Drilling and Sampling</b>		Client: <b>BHP Billiton</b>	
Drilling Contractor: <b>Client Contracted - Boart Longyear</b>				Project No.: <b>42907140</b>		Location: <b>Yeelirrie</b>	
Logged By: <b>BN</b>		Bore Size: <b>96 mm</b>		Relative Level: <b>496.70 mRL</b>		Drill Type: <b>Sonic Drilling</b>	
Checked By:		Total Depth: <b>30.00 m</b>		Coordinates: <b>6990368.00 mN</b>		Drill Model: <b>300C Prosonic</b>	
Date Started: <b>13-8-09</b>		Casing Size: <b>127 mm</b>		790673.00 mE		Drill Fluid: <b>N/A</b>	
Date Finished: <b>15-8-09</b>				Permit No: <b>N/A</b>			

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
G	20.30			20		CH	CLAY-QUARTZ; Sandy CLAY (20% Sand / 80% Clay), hard, orange-brown, with fine grained Sand, high plasticity, dry to moist.				G	Geochem #7	
				21			- Becomes CLAY trace fine grained QZ, very stiff-hard, pale grey-green, high plasticity, moist, homogeneous. - Becomes orange-brown, hard, refusal of shear vane, experience difficulty pushing casing due to hard Clay. - Becomes pale grey-green.						
	21.70			22		SC-CH	Becomes Clayey SAND / Sandy CLAY, hard, pale grey-green with orange staining, fine to medium grained QZ, moist, refusal of shear vane.				L	UD #3 Lexan #8 21.7-22.8m extra 0.4m	
	21.90			23		CH	Becomes CLAY with 5% fine to coarse grained QZ, hard, pale grey-green, medium - high plasticity, moist, friable.				X	UD #4 SPT #8	CQ
	22.80		10/34/16 for 20mm N>50	24			- Becomes pale orange - pale grey, hard.				G	Geochem #8	
	22.90			25		CL-CH	Becomes Sandy CLAY (30% Sand / 70% Clay), medium to high plasticity, pale grey- pale green with patchy orange staining, fine to medium grained, angular to subangular QZ, moist.				X	UD #5 SPT#9	
	23.50			26		CL-CH	- Becomes Sandy CLAY (40% Sand / 60% Clay), very stiff-stiff, red-brown, fine to medium grained QZ, subangular to subrounded, high plasticity Clay, moist.				G	Geochem #9	Grit
	23.70			27		CH	GRIT: Clayey SAND (20% Clay / 80% Sand), medium dense, red, fine to coarse grained subangular QZ, gap graded, moist to wet. CLAY-QUARTZ; Sandy CLAY (20% Sand / 80% Clay), very stiff, with traces of high plasticity pockets (20-30mm) - Becomes stiff to very stiff, patchy pale grey and pale brown, possibly disturbed by drilling.						
	25.00		6/10/26 N=36	28			- Becomes pale grey-pale green, hard, homogeneous.					UD #6	CQ
	25.20			29			- Trace pockets of red QZ (10-20mm).				G	Geochem #10	
	26.20			EOH at 30.0m.									

**Remarks:** 1.0 Two monitoring wells installed, screens from 25.5-27.5m and 15.0-20.0m.  
 2.0 Backfilled monitor well from:  
 EOH - 28.5m: backfilled with core samples  
 21.0-20.0m: Bentonite pellets  
 28.5-27.5m: Bentonite pellets  
 20.0-14.0m: Gravel pack  
 27.5-25.0m: Gravel pack  
 14.0-13.0m: Bentonite pellets  
 25.0-23.5m: Bentonite pellets  
 13.0-0.0m: Gravel pack  
 23.5-21.0m: Gravel pack

## BOREHOLE YYS0165 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **18-8-09**  
 Date Finished: **19-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.10 m**  
 Casing Size: **127 mm**

 Relative Level: **496.00 mRL**  
 Coordinates: **6988367.00 mN  
 792031.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
G	0.20			0		SC	CARBONATED LOAM; (30% carbonate) Clayey Silty SAND, red-brown, dense, fine to medium grained sand, reacts with hydrochloric acid (HCl), dry. - Increase carbonate content 60%, very dense, red-brown, subangular, poorly graded, slightly cemented, porous, light weight.				☒	Geochem #1	LT
G	0.70										☒	Geochem #2	
X	1.00		22/50 for 130mm N>50	1		SC	CARBONATED HARDPAN; Clayey SAND, very dense, recovered with moderately to highly cemented Iron (Fe) stained fragments, 60% carbonate.  - Trace white Clay inclusions 2-40mm, subrounded.				☒	SPT#1	HT
G	1.50										☒	Geochem #3	
X	2.30		46 for 70mm N>50	2							☒	UD #1	TCQ
X	2.50										☒	SPT #2	
X	2.72			3		SC	TRANSITION CALCRETE; Clayey SAND, dense, red-brown, fine to coarse grained, subangular, moderately cemented, various inclusion of dark grey, pale white (1-2mm), moist, 60% carbonate and 30% Quartz (QZ).  - Becomes speckled pale grey and red-brown, fine to medium grained, subangular, moist, possibly very dense, trace Clay, subrounded weakly cemented (50% Carbonate / 30% QZ / 20% Clay).	∇			☒	Lexan #1 2.5-3.5m extra 0.5m	TCQ
X	3.50		7/9/26 N=35	4							☒	SPT#3	
G	5.40		50 for 130mm N>50	5		SC	CARBONATED CLAY-QUARTZ; Clayey SAND, very dense, red, fine to medium grained, subangular, poorly graded, moist, 10% carbonate.  - Becomes well to poorly graded.				☒	Geochem #4 SPT #4	C&T
G	5.50										☒	Lexan #2 5.5-6.5m extra 0.4m	
X	6.50		N>50 refusal a 90mm	6							☒	SPT #5	GRT
G	6.70			7		SP	Possible GRIT, SAND with 20% Silt/Clay, very dense, dark red, medium to coarse grained, subrounded, gap graded, interbedded sand and high cemented fragments, wet. CLAY-QUARTZ; Silty/Clayey SAND, (30% Silt/Clay / 70% Sand), highly cemented fragments evident in material, no reaction to HCl.  - Note: While drilling through 7.5-8.5m, soft spot between interval.  - Becomes Clayey SAND (40% Clay / 60% Sand), very dense, brown, fine to medium grained, angular to subangular, low reaction to HCl, poorly graded, trace 10-15mm pockets of Sand, moist. - Becomes Clayey SAND (30% Clay / 70% Sand), pale red - pale grey, weakly cemented, fine to coarse grained, subangular to subrounded, moist. - Becomes pale brown, pale yellow. - Sample recovered as broken highly to moderately cemented fragments in Clayey Sand (30% Clay / 70% Sand), trace manganese (Mn) staining, interbedded bands of cemented and non-cemented material, moist (60% loose due to				☒	Geochem #5 (Grit)	
X	7.50			8							☒	UD refusal	CQ
X	7.60										☒	Lexan #3 7.5-8.5m extra 0.5m	
X	8.50		50 blows for 110mm N>50	9							☒	SPT#6	CQ
G	8.90										☒	Geochem #6	
X	10.00										☒		

## BOREHOLE YYS0165 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **18-8-09**  
 Date Finished: **19-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.10 m**  
 Casing Size: **127 mm**

 Relative Level: **496.00 mRL**  
 Coordinates: **6988367.00 mN  
 792031.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	10.07		50 blows for 70mm N>50	10		SC	handling). CLAY-QUARTZ; Clayey SAND, recovered as broken highly to moderately cemented fragments in Clayey Sand (30% Clay / 70% Sand), trace Mn staining, interbedded bands of cemented and non-cemented material, moist, (60% of material loose due to handling).					SPT#7	
				11		CL	Becomes Sandy CLAY (30% Sand / 70% Clay), hard, patchy pale brown-pale orange and pale grey-yellow, black Fe staining, fine to medium grained QZ. (Bottom of lexan tube hot and melted).					Geochem#7	Lexan #4 10 0-11 3m extra 0 2m
G	11.70			12		SM-SC	Becomes Clayey SAND (40% Clay / 60% Sand), very dense, pale brown-pale orange, fine to medium grained Sand, with occasional coarse grained, well graded, moderately cemented, moist to dry. - Sample recovered as broken fragments (20-30mm), weakly cemented, friable. (Possible rock, broken by sonic drilling or harden material due to heat from rock).						
			50 for 110mm N>50	13								SPT#8	Lexan #5 13 2-14 2m squashed
	13.10			14			Becomes Clayey SAND (20% Clay / 80% Sand), very dense, pale brown-pale grey, fine to medium grained, subangular, moderately to highly cemented, dry.					Geochem#8	
	13.20			15			(Retrieve from drill bit a possible Sandstone core, very weak (VV) strength, increase strength in material possibly due from heat of rods.) - Becomes Silty SAND (40% Silt / 60% Sand), dense to very dense (disturbed by drilling), brown-orange, fine to medium grained, subangular to subrounded, poorly graded, non-homogeneous, evident of 10-20mm pockets of rounded highly cemented Sandy CLAY, moist. - Becomes very dense, patchy pale grey-yellow. - Becomes Clayey SAND (20% Clay / 80% Sand), patchy red-brown, pale yellow, grey, fine to medium grained, with 20-30mm highly cemented fragments. (Evidence of interbedded layers of highly cemented Clayey SAND, with pale yellow 1-2mm thick clay staining layers.)					Geochem#9	
G	14.60			16									
	16.00			17								Geochem#10	Lexan #6 16 3-17 3m extra 0 5m
G	16.30			18		CL	Becomes Sandy CLAY (30% Sand / 70% Clay), hard, brown, fine to medium grained sand, subangular to subrounded, with moderately to highly cemented zones, moist.					UD refusal Geochem #10	
	17.30			19								Geotech #1	
G	17.40											Geochem #11	
G	18.00						- With subrounded to rounded Clay cementation. - Trace black-brown Silica cementation.						
G	18.70						- Brecciated formation with various sizes of cemented clay (5-20mm), and black Fe staining fragments, difficult to push UD.					Lexan #7 19 3-20 3m	
	19.30												

## BOREHOLE YYS0165 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **18-8-09**  
 Date Finished: **19-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.10 m**  
 Casing Size: **127 mm**

 Relative Level: **496.00 mRL**  
 Coordinates: **6988367.00 mN  
 792031.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				20		CL	CLAY-QUARTZ; Sandy CLAY.						
G	20.50			21		SM-SC	Becomes Clayey SAND (30% Clay / 70% Sand), very dense, red-brown, patchy yellow, fine to medium grained with trace coarse grained, subangular to subrounded, moist, 20-30mm zones of highly cemented areas, difficult to sample with SPT or UD, moist. - Becomes Clayey SAND (40% Clay / 60% Sand), very dense, patchy pale grey-brown, fined grained, subangular-subrounded, weakly cemented, poorly graded, moist. - Recovered as broken weakly cemented fragments in Clayey SAND. - Interbedded red-brown and pale grey.					Geotech #2	
G	21.70			22								Geochem #12	
G	22.00			22								Geochem #13	
G	22.40			22								Geotech #3	
G	22.30			22								Geochem #3	
	23.00			23								Lexan #8 22 3-23 0m extra 0.2m UD refusal	
G	23.40			24								Geotech #4	
G	23.80			24								Geochem #14	
	24.45			25								Geotech #5	
	25.20			26								Lexan #9 25 2-26 3m extra 0.4m	
G	26.40			27		SM-CL	Recovered as Clayey SAND/Sandy CLAY, very hard, patchy red, orange and grey, VL strength? When hit with point end of geopick, leaves smooth indents, recovered as intact core.					Geochem #15	
G	27.10			28		SM	Becomes Clayey SAND (20% Clay / 80% Sand) medium to coarse grained, subangular to subrounded.  - Recovered as Clayey SAND/Sandy CLAY, very hard, patchy red, orange and grey, possible VL strength?  - Driller no iced easier drilling on last run.					Geochem #16	
G	28.00			29								Lexan #10 28 3-29 3m extra 0.4m	
G	28.30			29								Geotech #7	
G	29.40			29		SM-CL	Becomes Clayey SAND / Sandy CLAY, hard, patchy red, orange and grey with dark purple- red, flaky, moist, dark purple-red accumulated coated surface around core, can be					Geochem #17	
G	29.80												
G	30.00												





# BOREHOLE YYS0165 - DRAFT

URS Australia  
Level 3  
20 Terrace Road  
EAST PERTH WA 6004

Phone 08 9326 0100  
Fax 08 9326 0296

Project Reference: **Yeelirrie Uranium Project  
Geochemistry / Geotechnical &  
Hydrogeological Drilling and Sampling**

Client: **BHP Billiton**

Location: **Yeelirrie**

Drilling Contractor: **Client Contracted - Boart Longyear**

Project No.: **42907140**

Logged By: **BN**  
Checked By:  
Date Started: **18-8-09**  
Date Finished: **19-8-09**

Bore Size: **96 mm**  
Total Depth: **30.10 m**  
Casing Size: **127 mm**

Relative Level: **496.00 mRL**  
Coordinates: **6988367.00 mN  
792031.00 mE**  
Permit No: **N/A**

Drill Type: **Sonic Drilling**  
Drill Model: **300C Prosonic**  
Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				30		SM CL	broken with hand with less difficulty. CLAY-QUARTZ; Clayey SAND / Sandy CLAY, hard, patchy red, orange and grey with dark purple- red, flaky, moist, evidence of core spinning, leaving dark purple-red accumulated surfaces around core, can be broken with hand with less difficulty, no rock characteristics. EOH at 30.1m.					
				31								
				32								
				33								
				34								
				35								
				36								
				37								
				38								
				39								

**Remarks:** 1.0 Two monitoring wells installed, screens from 18.3-16.3m and 6.0-4.0m.  
2.0 Backfilled monitor well from:  
EOH - 22.0m: backfilled with core samples  
14.0-7.0m: Gravel pack  
22.0-19.5m: Gravel pack  
7.0-6.0m: Bentonite pellets  
19.5-18.3m: Bentonite pellets  
6.0-3.5m: Gravel pack  
18.3-15.0m: Gravel pack  
3.5-2.5m: Bentonite pellets  
15.0-14.0m: Bentonite pellets  
2.5-0.0m: Gravel pack

TMC\_SOILOG 42907140.GPJ WCC\_AUS.GDT 13/11/09

## BOREHOLE YYS0166 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **20-8-09**  
 Date Finished: **21-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **496.80 mRL**  
 Coordinates: **6989221.00 mN  
 792552.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
	0.40		50 blows for 50mm N>50	0		SM	LOAM; Silty SAND, medium dense, red-brown, dry.						L
	0.50					SM	HARDPAN; Silty SAND, dense, red, fine to medium grained, subangular to subrounded, poorly graded, dry, weakly cemented, Iron (Fe) oxide cemented (30%), traced carbonate. CARBONATED LOAM; Silty SAND, very dense, recovered with weakly to moderately cemented fragments.					Geochem #1 SPT#1	H
	0.55					SM							Lexan #1 0.5-1.8m extra 0.2m
	1.80		50 blows for 150mm N>50	2		SC	CARBONATED CLAY-QUARTZ; Clayey SAND (20% Clay / 60% Sand / 20% carbonate), red-brown and white, with highly cemented very low (VL) strength rock fragments, possibly Sandstone, brecciated, fine to medium grained, subangular to angular, reacts vigorously with hydrochloric acid (HCl), material powderised and disturbed due to drilling. - Becomes more carbonate 40%.					Geochem#2	CoT
	2.50											SPT#2	
	3.50											Geochem #3	
	4.00		50 blows for 90mm N>50	4		SC	CLAY-QUARTZ; Clayey SAND, red-brown, rock fragments (15-50mm) can be broken by hand, moderately cemented with fine to medium grained, trace coarse grained, less carbonate 10%.  - Clayey SAND (30% Clay / 60% Sand / 10% carbonate), very dense, patchy red and pale grey, fine to medium grained, subangular to subrounded, weakly cemented and trace highly cemented fragments, moist, pale grey material is clay, friable can be broken by one hand, Evidence of intact core within disturbed Clay/Sand.					Geochem #4	CoQ
	5.20											SPT#3	
	5.29											Lexan #2 5.2-6.4m extra 0.3m	
	6.70		36/50 for 30mm N>50	7			- Becomes (20% Clay / 80% Sand), very dense, red-brown, with trace yellow clay, medium to coarse grained, subangular to subrounded, recovered in intact core, friable, (breaks with gentle force from fingers). Evidence of highly cemented interbedded disc, moist to wet, gap graded, non-homogenous. - Increase zones 20-30mm of uniform graded coarse grained Quartz (QZ) sand, evidence of intact core.					Geochem #5 Geotech #1	
	6.80												
	7.70											Geotech #2 UD refusal	
	7.90			8								Lexan #3 7.9-9.1m extra 0.3m	
	8.00											SPT#4 Geochem #6 Geotech #3	
	9.10			9			- Becomes brown-orange. - Becomes more clayey 30%.						
	9.30												
	9.40												

**Remarks:** - Note: For bag samples, at the top the material is softer while the bottom is harder. Material at the bottom could get harder due to heat from drill rods ( here are no splits or barrel between sample and rods).

## BOREHOLE YYS0166 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **20-8-09**  
 Date Finished: **21-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **496.80 mRL**  
 Coordinates: **6989221.00 mN  
 792552.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION	
G	10.20		50 for 70mm N>50	10		SC	CLAY-QUARTZ; Clayey SAND (20% Clay / 80% Sand), very dense, orange-brown, fine to medium grained, subrounded, weakly cemented, friable, gap graded, moist - wet, 10% coarse grained, breaks easily between fingers, trace zones of moderately cemented, no reaction to HCl.				G	Geotech #4	CG	
G	11.00 11.10			11								Geochem #7 SPT#5		
	11.90			12								Lexan #4 11.9-12.9m extra 0.5m		
	12.90			13			CL	- With thin irregular layers of pale yellow clay (1-2mm) and patchy areas of pale grey Clay. Sandy CLAY (40% Sand / 60% Clay) hard, patchy pale brown - pale yellow, fine to medium grained sand, recovered as broken pieces 5-30mm, up to 70mm, moist to dry, possibly due to heat of drill rods.				UD#1		
G	13.60			14								Geochem #8		
G	14.70 14.80			15				- Recovered in intact 60-70mm pieces, dry, weakly cemented breaks with finger pressure. - Becomes (30% Sand / 70% Clay) hard, patchy brown, yellow pale grey and black staining, moist, recovered intact core.				G		Geochem #9 Geotech #5
G	15.50 15.69			16				- Becomes pale grey with orange-red staining, difficult to break with hand, however plastic characteristic remain when hit with hammer, smooth indentations result with hit of geopick.				G		Geotech #6 UD #2
	16.50			17			CL-CH	Becomes patchy interbedded 15-30mm layers of brown, orange, pale grey, very stiff-hard, high plasticity pale grey clay.				X		SPT#6 Geochem #10
G	17.60			18				- Becomes hard, brown with trace red staining, increase sand (30-40%), evidence of moderately cemented zones (30-70mm thick).				G		Geotech #7 UD refusal
	18.40			19				- Becomes pale brown, pale yellow, pale grey and red staining, fine to medium grained, subangular to subrounded.						Lexan #6 18.4-19.6m extra 0.3m  UD #3
	19.60													

## BOREHOLE YYS0166 - DRAFT

URS Australia  
Level 3  
20 Terrace Road  
EAST PERTH WA 6004

Phone 08 9326 0100  
Fax 08 9326 0296

Project Reference: **Yeelirrie Uranium Project  
Geochemistry / Geotechnical &  
Hydrogeological Drilling and Sampling**

Client: **BHP Billiton**

Location: **Yeelirrie**

Drilling Contractor: **Client Contracted - Boart Longyear**

Project No.: **42907140**

Logged By: **BN**  
Checked By:  
Date Started: **20-8-09**  
Date Finished: **21-8-09**

Bore Size: **96 mm**  
Total Depth: **30.00 m**  
Casing Size: **127 mm**

Relative Level: **496.80 mRL**  
Coordinates: **6989221.00 mN  
792552.00 mE**  
Permit No: **N/A**

Drill Type: **Sonic Drilling**  
Drill Model: **300C Prosonic**  
Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
G	20.10			20		CL-CH	CLAY-QUARTZ; Sandy CLAY. (40% Sand / 60% Clay), 30mm layers of red Sand (grit?), medium to coarse grained Sand, subrounded to subangular. - Becomes Sandy CLAY (30% Sand / 70% Clay), hard, patchy layers of red-orange and pale grey-yellow (high plasticity Clay) moist, intact core. - Becomes red-brown with 10-20% coarse grained sand, broken pieces of core in 30-40mm fragments. Evidence of core hardened due to drying out. Last 200mm of core run resembles VL strength rock, material hot to touch.				Geochem #11	CG
G	20.70			21							Geochem #8	
G	21.30			22							Geochem #12	
G	21.50			23							Geochem #9	
G	22.65			24							Lexan #7 21.5-22.6m extra 0.4m, bottom melted	
G	23.50			25							Geochem #13	
G	23.90			26							Geochem #14	
G	24.00			27							Geochem #15	
G	25.70			28							Geochem #10	
G	26.85			29							Geochem #16	
G	26.80			30							Geochem #11	
G	27.00										Geochem #12	
G	27.30										Geochem #13	
G	28.30										Geochem #17	
G	28.70											
G	29.20											
								EOH at 30.0m.				

**Remarks:** 1.0 Two monitoring wells installed, screens from 22.0-25.0m and 4.0-8.0m.  
2.0 Backfilled monitor well from:  
EOH - 27.0m: backfilled with core samples  
20.5-9.0m: Gravel pack  
27.0-26.0m: Gravel pack  
9.0-8.0m: Bentonite pellets  
26.0-25.0m: Bentonite pellets  
8.0-3.5m: Gravel pack  
25.0-21.5m: Gravel pack  
3.5-2.5m: Bentonite pellets  
21.5-20.5m: Bentonite pellets  
2.5-0.0m: Gravel pack

## BOREHOLE YYS0167 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **22-8-09**  
 Date Finished: **23-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **495.60 mRL**  
 Coordinates: **6988083.00 mN  
 793264.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
G	0.30		41/9 for 30mm N>50	0		SM	LOAM; Silty SAND (10% Silt / 90% Sand), medium dense, red-brown, fine to medium grained, subangular to subrounded, poorly graded, dry.				G	Geochem #1 SPT#1	L
	0.50			1		SP	HARDPAN; Silty SAND, Iron (Fe) oxide, black shiny coating, moderately cemented (40%), indurated laminar layers of 20-50mm thick, very dense.				X	Lexan #1 0.5-1.7m extra 0.3m	H
	0.68			SM		CARBONATED LOAM; Silty SAND (20% Silt / 60% Sand / 20% carbonate), very dense, pale-orange with mottled white carbonate, fine to medium grained subrounded to subangular, dry, weakly cemented, reacts with hydrochloric acid (HCl).				L			
G	2.30		14/26/24 for 140mm N>50	2		CL	QUARTZ-RICH CARBONATED LOAM; Sandy CLAY, hard recovered as core pieces weakly cemented, brecciated, fine to medium grained with 5-10% subrounded Clay gravels (1-3mm), dry. - Trace moderately cemented broken core disc (20-30%) with Sandy CLAY.				G	Geochem #2	LOT
	3.00			3		SC	CARBONATED CLAY-QUARTZ; Clayey SAND (10/60% and 30% carbonate) with gravels, very dense, red-brown, fine grained, subangular to subrounded QZ, rounded to subrounded gravels (2-6mm) Clay, moist to wet, intact core. - Recovered in 10-30mm pieces, friable, possibly due to end of run.				X	SPT#2	COT
	3.60			4		SC	- Recovered as Clayey SAND, disturbed due to end of run. - Trace moderately cemented fragments 20-30mm. - Becomes more Sand (70%), medium grained, subrounded, subangular.				G	Geotech #1 Geochem #3	
3.90	5	SC	CLAY-QUARTZ; Clayey SAND (20% Clay / 80% Sand), disturbed - loose, brown, medium grained, trace coarse, subrounded QZ grains, no carbonate reaction.							G	Geochem #4	CQ	
4.30	6		- Becomes Clayey SAND (40% Clay / 60% Sand), very dense, brown with trace red staining, fine to medium grained, subangular to subrounded, well graded, moist to wet, homogenous.								UD#1		
5.20	7		- Becomes more Sandy (80%), disturbed loose, red-brown, fine to coarse grained, majority medium grained, trace 5-20mm moderately cemented, subrounded to subangular, gap to uniform graded, wet. - Clayey SAND (40% Clay / 60% Sand) very dense, red-brown fine to medium grained, subangular to subrounded, well graded, trace coarse grained QZ, moist, intact core, friable breaks easily with fingers. - Observed bottom of UD#2, very intact moderately cemented, pale yellow with black specks. - Clayey SAND (20% Clay / 80% Sand), very dense, brown trace red staining, medium to coarse grained, subangular to subrounded, gap graded, moist, first 200mm loose (disturbed);										Geochem #5 UD #2 refusal
5.30	8		- Sandy CLAY (50% Sand / 50% Clay), hard, pale brown, fine to medium grained, non-homogenous, patchy clay and sand zones, weakly cemented, moist, 1-3mm rounded clay inclusions.									Lexan #3 7.4-8.2m extra 0.4m	SPT#4
6.45	9										Geotech #2 Geochem #6		
7.30			50 for 100mm N>50										
7.40													
7.44													
8.90													
9.10													
9.60													
9.70													

## BOREHOLE YYS0167 - DRAFT

 URS Australia  
 Level 3  
 20 Terrace Road  
 EAST PERTH WA 6004

 Phone 08 9326 0100  
 Fax 08 9326 0296

 Project Reference: **Yeelirrie Uranium Project  
 Geochemistry / Geotechnical &  
 Hydrogeological Drilling and Sampling**

 Client: **BHP Billiton**

 Location: **Yeelirrie**

 Drilling Contractor: **Client Contracted - Boart Longyear**

 Project No.: **42907140**

 Logged By: **BN**  
 Checked By:  
 Date Started: **22-8-09**  
 Date Finished: **23-8-09**

 Bore Size: **96 mm**  
 Total Depth: **30.00 m**  
 Casing Size: **127 mm**

 Relative Level: **495.60 mRL**  
 Coordinates: **6988083.00 mN  
 793264.00 mE**  
 Permit No: **N/A**

 Drill Type: **Sonic Drilling**  
 Drill Model: **300C Prosonic**  
 Drill Fluid: **N/A**

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
				10		CL-SM	CLAY-QUARTZ; Sandy CLAY (50% Sand / 50% Clay), hard, pale brown, fine to medium grained, non-homogenous, patchy clay and sand zones, weakly cemented, moist, 1-3mm rounded clay inclusions.  - Becomes patchy pale brown and yellow.					Lexan #4 9.6-10.7m extra 0.3m	
	10.70											UD#3	
	10.80											Geotech #3	
	11.10			11			- Becomes patchy orange, yellow with trace pale grey, subangular to subrounded, well graded, moist, friable.					Geochem #7	
	11.80					SC	Becomes Clayey SAND (30% Clay / 70% Sand), very dense, red-orange, trace pale yellow Clay pockets 20mm, fine to coarse grained, moist, material disturbed - stretched, friable.					Geochem #8	
	12.80											UD#4	
	12.88			13								Lexan #5 12.8-13.8m bottom melted	
	14.00					CL	Becomes Sandy CLAY (40% Sand / 60% Clay), hard, brown-yellow, fine to medium grained, subangular to subrounded, weakly cemented, intact core, friable, refusal of shear vane, when broken by hand smooth areas evident where clay and sand were cemented.  - 14.8-15.0 m Core hollowed out due to contact surface harden from heat of rods and stuck to inside of rods.					Geotech #4	
	14.30			14								Geochem #9	
	15.00			15								Lexan #6 15.0-15.9m extra 0.6, bottom melted	
	15.90			16			- Becomes (30% Sand / 70% Clay), pale grey - pale green, pale yellow, moist, recovered as broken moderately cemented fragments (Sample required vibration to retrieve). - Becomes patchy orange-brown, yellow and pale grey, breaks with 2 hands, when hit with point of geopick indents 10mm deep with 3-4 cracks, smooth surface, plastic characteristics exist, moist, intact core between 150-200mm. - Becomes friable, breaks easily with fingers recovered as 50-70mm discs.					Geotech #5	
	16.60			17			16.7-17.2 Disturbed hollowed out clay core, 10mm thick shell, inside of sample was pushed and vibrated out, material crumbled. - Becomes (40% Sand / 60% Clay), pale brown, intact core. - Disturbed recovered in 20-50 mm pieces in Sandy CLAY.					Geochem #10	
	18.00			18								Lexan #7 18.0-18.9m bottom melted	
	19.10			19			- Becomes patchy red-orange and yellow, recovered intact core (100-200mm).  - Sample disturbed recovered as broken pieces 20-30mm in Clayey SAND. Required vibration to retrieve sample.					Geotech #6	


## BOREHOLE YYS0167 - DRAFT

URS Australia Level 3 20 Terrace Road EAST PERTH WA 6004		Phone 08 9326 0100 Fax 08 9326 0296		Project Reference: <b>Yeelirrie Uranium Project                  Geochemistry / Geotechnical &amp;                  Hydrogeological Drilling and Sampling</b>		Client: <b>BHP Billiton</b>	
Drilling Contractor: <b>Client Contracted - Boart Longyear</b>				Project No.: <b>42907140</b>		Location: <b>Yeelirrie</b>	
Logged By: <b>BN</b>		Bore Size: <b>96 mm</b>		Relative Level: <b>495.60 mRL</b>		Drill Type: <b>Sonic Drilling</b>	
Checked By:		Total Depth: <b>30.00 m</b>		Coordinates: <b>6988083.00 mN</b>		Drill Model: <b>300C Prosonic</b>	
Date Started: <b>22-8-09</b>		Casing Size: <b>127 mm</b>		<b>793264.00 mE</b>		Drill Fluid: <b>N/A</b>	
Date Finished: <b>23-8-09</b>				Permit No: <b>N/A</b>			

SAMPLE TYPE	DRILL RUN (m)	FIELD SHEAR STRENGTH (kPa)	SPT BLOWS (N)	Depth (m)	Graphic Log	Classification	USC DESCRIPTION OF STRATA Type, plasticity / particle size, colour, secondary / minor components (e.g., "trace"), additional observations	Moisture and Groundwater	Consistency	Relative Density	Sample Interval	Sample Identification	GEOLOGICAL DESCRIPTION
G	20.40			20		CL-SM	CLAY-QUARTZ; Clayey SAND / Sandy CLAY (50% Sand /50% Clay), very dense, pale brown-orange, fine to coarse grained, subangular to subrounded, high plasticity clays, poorly graded, with moderately cemented gravel fragments.				G	Geochem #11	
	21.40			21			- Becomes patchy brown, with orange staining trace pale grey clay, fine to medium grained, friable, moist, recovered as intact core.						
	22.60			22			- Becomes hard, can not penetrate with finger, easily peeled with knife.				L	Lexan #8 21.4-22.6m extra 0.3m	CO
G	23.00			23		SP	- Becomes pale grey. GRIT; interbedded layers of GRIT, medium grained subrounded to subangular, uniform graded, 20-80mm thick, at 100-300mm spacing.				G	Geotech #7 Geochem #12	
G	24.50			24		CL-SM	CLAY-QUARTZ; Clayey SAND / Sandy CLAY, pale grey-green, hard, recovered as 20-40mm pieces, required vibration to retrieve sample.				G	Geochem #13	
	24.60			24			- Becomes very dense, pale grey-green with orange staining, fine to coarse grained, subangular to subrounded, moderately to weakly cemented, shatters with one hit of geopick, possibly VL rock, moist, recovered in 100mm core, 40% of material still can be peeled with knife.					Lexan #9 24.6-25.8m extra 0.3m	
	25.80			25			- Interbedded colours of pale grey and orange-red (10-20mm spaced), broken by finger pressure.				X	SPT#5	
G	26.30			26			- Becomes hard, red with pale grey pockets, fine to coarse grained with majority medium grained, moist.				G	Geotech #8	
	27.30			27			- Becomes patchy pale grey-orange, recovered as 30-80mm core, dried at bottom of bit, disturbed.						
G	27.50			27		SP	27.3-27.4m GRIT layer.				G	Geochem #14 (Grit) UD #5	
	27.60			27		CL-SM	Clayey SAND / Sandy CLAY, interbedded colours of pale grey and orange-red at 10-20mm spacing, can be broken by finger pressure.					Lexan #10 27.5-28.5m extra 0.5m	CO
	29.10			29			- Becomes Sandy CLAY (40% Sand / 60% Clay), hard, pale grey-white, with 10-20% orange staining, fine to coarse grained QZ, subangular to subrounded, moist.						
G	29.30			29			- Sample disturbed, dried and hardened from heat of drill bit, recovered as 20-100mm broken core disc, moist-dry.				G	Geotech #9 Geochem #15	
				EOH			EOH at 30.0m.						

**Remarks:** 1.0 Two monitoring wells installed, screens from 20.0-24.0m and 3.8-7.3m.  
 2.0 Backfilled monitor well from:  
 EOH - 25.0m: backfilled with core samples  
 25.0-24.0m: Bentonite pellets  
 24.0-19.0m: Gravel pack  
 19.0-18.0m: Bentonite pellets  
 18.0-10.0m: Gravel pack  
 10.0-9.5m: Bentonite pack

9.5-8.3m: Gravel pack  
 8.3-7.3m: Bentonite pack  
 7.3-3.0m: Gravel pack  
 3.0-1.5m: Bentonite  
 1.5-0.0m: Gravel pack


SOIL PROFILE										page: 1 of 1		
			Client: Allen Burgess (BHP)									
			Project name:									
Drillhole No. 1		Drill Rig		Inclination		Easting 352602		Bedrock depth (m) N/A				
		Location Kalgoorlie		Type/Diameter 6"		Northing 6603446		Depth to water (m) N/A				
Project No. BHP040		Geologist DvdB		Final Depth (m) 7		Elevation (m) 379.914		Date Drilled 15/06/2007		Date Profiled 16/06/2009		
Depth from (m)	Depth to (m)	Soil Name	Description of the soil			Soil Conditions		Structure of Soil			Additional observations	
			Colour	Particle Description		Moisture condition (disturbed)	Consistency (disturbed)	Zoning	Defects	Cementing	Mechanical deposition	Others
				Coarse -grained soil	Clay-silt							
Size	Shape	Plasticity	Disturbed Material									
0.00	0.50	MEDIUM TO COARSE GRAVEL (GM) with silty sand	light red-grey	poorly graded	angular to sub-angular	dry	very loose				capping material	Samples taken as per BH1 testing summary
0.50	1.00	SILTY SAND (SM) with some clay and fine sub-angular calcite gravel	dark red-brown	well graded	sub-angular	dry	loose				borrow cover material	
1.00	1.50	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown			moist	stiff				borrow cover material	
1.50	2.00	SILTY CLAY (CL) with coarse sand	mottled white			moist	stiff				borrow cover material	
2.00	2.50	SILTY CLAY (CL) with coarse sand	dark red-brown			moist	stiff				borrow cover material	
2.50	3.00	SILTY CLAY (CL) with coarse sand	dark red-brown			moist to wet	stiff				borrow cover material	
3.00	3.50	SILTY CLAY (CL) with coarse sand	dark red-brown			moist	stiff				borrow cover material	
3.50	4.00	SILT (ML) with traces of sand	light red-orange			moist	soft				tailings	
4.00	4.50	SILT (ML) with traces of sand	light red-orange			moist	soft				tailings	Lexan Tube Sample
4.50	5.50	SILTY SAND (SM)	light red-orange	poorly graded	sub-angular	moist	loose				tailings	Lost Material
5.50	6.25	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown			moist	stiff				residual or borrow material	Lexan Tube Samples
6.25	7.00	SILTY CLAY (CL) with fine sub-angular calcite gravel	mottled white			moist	very stiff				residual or borrow material	

**BH1 Testing Summary**

Depth [m]	Description	Sample Weight [kg]	Redox (Eh)		pH		Conductivity		Comment
			Reading [mV]	Temp [°C]	Reading	Temp [°C]	Reading [mS]	Temp [°C]	
0.5	Sample S1.1	0.4							Calibration 1
1.0	Sample S1.2	0.4	83	25	7.51	25	1.014	21.7	
1.5	Sample S1.3	0.3	106	25	7.15	25	1.801	21.4	
2.0	Sample S1.4	0.3	77	25	8.17	25	1.113	21.8	
2.5	Sample S1.5	0.3	64	25	7.01	25	1.474	26.4	
3.0	Sample S1.6	0.3	78	25	7.48	25	2.350	24.3	
3.5	Sample S1.7	0.3	60	25	7.35	25	3.520	25.7	
4.0	Sample S1.8 (Tailings)	0.3	67	25	8.96	25	4.560	23.8	
4 to 4.5	Lexan Tube Sample S1.9 (Tailings)	4.5	N/T	N/T	N/T	N/T	N/T	N/T	
4.5	Sample S1.10 (Tailings)	0.4	63	25	9.69	25	2.230	20.0	
4.5 to 5.5	Lost material								
5.5 to 6.25	Lexan Tube Sample S1.11 (Tested at 6.25m)	10.2	57	25	9.38	25	2.300	23.3	
6.25 to 7	Lexan Tube Sample S1.12	9.5	N/T	N/T	N/T	N/T	N/T	N/T	
7.0	Sample S1.13	0.4	52	25	8.48	25	2.750	26.1	
Total Weight Samples		27.6							
Total Weight Tailings Samples		5.2							

\*N/T - no tests



SOIL PROFILE										page: 1 of 1		
			Client: Allen Burgess (BHP)									
			Project name:									
Drillhole No. 2		Drill Rig		Inclination		Easting 352599		Bedrock depth (m) N/A				
		Location Kalgoorlie		Type/Diameter 6"		Northing 6603446		Depth to water (m) N/A				
Project No. BHP040		Geologist DvdB		Final Depth (m) 8		Elevation (m) 329.813		Date Drilled 15/06/2009		Date Profiled 16/06/2009		
Depth from (m)	Depth to (m)	Soil Name	Description of the soil			Soil Conditions		Structure of Soil			Additional observations	
			Colour	Particle Description		Moisture condition (disturbed)	Consistency (disturbed)	Zoning	Defects	Cementing	Mechanical deposition	Others
				Coarse -grained soil	Clay-silt							
Size	Shape	Plasticity	Disturbed Material									
0.00	0.50	ANGULAR TO SUB-ANGULAR COBBLES with some coarse gravel and sandy silt	light red-grey	poorly graded	angular to sub-angular	dry	very loose				waste rock capping	
0.50	1.00	ANGULAR TO SUB-ANGULAR COBBLES with some coarse gravel and sandy silt	light red-grey	poorly graded	angular to sub-angular	wet	very loose				waste rock capping	Sample wettened during drilling
1.00	1.20	ANGULAR TO SUB-ANGULAR COBBLES with some coarse gravel and sandy silt	light red-grey	poorly graded	angular to sub-angular	dry	very loose				waste rock capping	
1.20	1.50	SILTY SAND (SM) with some clay and fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	dry	loose				cover material	
1.50	2.00	SILTY SAND (SM) with fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	dry	very loose				cover material	
2.00	2.50	SILTY SAND (SM) with fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	dry	loose				cover material	
2.50	3.00	SILTY SAND (SM) with fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	wet	very loose				cover material	Sample wettened during drilling
3.00	3.50	SILTY SAND (SM) with some clay and fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	wet	loose				cover material	
3.50	3.70	SILTY SAND (SM) with some clay and fine sub-angular calcrite gravel	dark red-brown	well graded	sub-angular	wet	loose				cover material	Sample wettened during drilling
3.70	4.00	SILT (ML)	light red- orange			low	dry	soft			tailings	
4.00	4.50	SILT (ML)	light red- orange			low	wet	firm			tailings	Sample placed into tube post drilling
4.50	5.25	SILT (ML)	light red- orange			low	wet	firm			tailings	Sample wettened during drilling
5.25	6.20	SILT (ML)	light red- orange			low	wet	firm			tailings	Sample wettened during drilling
6.20	6.45	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white			medium	moist	very stiff			residual or borrow material	Compacted clay liner
6.45	7.2	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white			medium	moist	very stiff			residual or borrow material	Sample wettened during drilling
7.2	8	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white			medium	moist	very stiff			residual or borrow material	Compacted clay liner
											residual or borrow material	Sample wettened during drilling


Samples taken as per BH2 testing summary tab

Lexan Tube Samples

**BH2 Testing Summary**

Depth [m]	Description	Sample Weight [kg]	Redox (Eh)		pH		Conductivity		Comment
			Reading [mV]	Temp [°C]	Reading	Temp [°C]	Reading [mS]	Temp [°C]	
1.5	Sample S2.1	1.5	81	25	7.31	25	0.520	23.8	Calibration 2
2.0	Sample S2.2	0.4	90	25	7.10	25	0.820	25.0	
2.5	Sample S2.3	1	88	25	6.75	25	1.705	23.0	
3.0	Sample S2.4	0.5	76	25	7.18	25	1.485	24.8	
3.5	Sample S2.5	1	97	25	6.72	25	3.490	26.2	
4.0	Sample S2.6 (Tailings)	0.8	105	25	8.35	25	3.440	26.5	
4.0 to 4.5	Lexan Tube Sample S2.14 (Tailings)	9	N/T	N/T	N/T	N/T	N/T	N/T	
4.5	Sample S2.7 (Tailings)	1.2	95	25	8.21	25	5.550	23.3	
4.5 to 5.25	Lexan Tube Sample S2.8 (Tested at 5.25m) (Tailings)	8.6	70	25	8.33	25	10.120	24.9	
5.25 to 6.0	Lexan Tube Sample S2.9	8.5	N/T	N/T	N/T	N/T	N/T	N/T	
6.0	Sample S2.10	1	69	25	6.91	25	1.900	23.1	
6.0 to 6.45	Lexan Tube Sample S2.11 (Tested at 6.45m)	10.5	126	25	6.41	25	1.240	22.5	
6.45 to 7.2	Lexan Tube Sample S2.12	9.5	N/T	N/T	N/T	N/T	N/T	N/T	
7.2	Sample S2.15	0.8	141	25	6.21	25	1.401	19.1	
7.2 to 8.0	Lexan Tube Sample S2.13	13	N/T	N/T	N/T	N/T	N/T	N/T	
8.0	Sample S2.16	1	180	25	4.50	25	2.560	21.1	Calibration 3
	Total Weight Samples	68.3							
	Total Weight Tailings Samples	19.6							

\*N/T - no tests

SOIL PROFILE										page: 1 of 1				
			Client: Allen Burgess (BHP)											
			Project name:											
Drillhole No. 3		Drill Rig		Inclination		Easting 352582		Bedrock depth (m) N/A						
		Location Kalgoorlie		Type/Diameter 6"		Northing 6603441		Depth to water (m) N/A						
Project No. BHP040		Geologist DvdB		Final Depth (m) 8		Elevation (m) 379.844		Date Drilled 15/06/2009		Date Profiled 16/06/2009				
Depth from (m)	Depth to (m)	Soil Name	Description of the soil			Soil Conditions		Structure of Soil			Additional observations			
			Colour	Particle Description		Moisture condition (disturbed)	Consistency (disturbed)	Zoning	Defects	Cementing	Mechanical deposition	Others		
				Coarse-grained soil	Clay-silt									
Size	Shape	Plasticity	Disturbed Material											
0.0	0.5	ANGULAR TO SUB-ANGULAR COBBLES with some coarse gravel and sandy silt	light red-grey	poorly graded	angular to sub-angular		dry	very loose				waste rock capping cover material	Samples taken as per BH3 testing summary table	
0.5	1.0	SILTY SAND (SM) with medium to coarse sub-angular gravel	light red-grey	poorly graded	angular to sub-angular		dry	very loose				cover material		
1.0	2.0	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white		medium		moist	stiff				cover material		Sample wettened during drilling
2.0	2.7	ANGULAR TO SUB-ANGULAR COBBLES with some coarse gravel and sandy silt	light red-grey	poorly graded	angular to sub-angular		dry	very loose				cover material		
2.7	3.0	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white		medium		moist	stiff				cover material		Compacted clay liner Sample wettened during drilling
3.0	3.6	SILTY SAND (SM) with clay and fine sub-angular calcite gravel	light red-brown	well graded	sub-angular		slightly moist	loose				cover material		
3.6	4.0	SILTY SAND (SM)	light red-orange	poorly graded			slightly moist	loose				tailings		
4.0	4.5	SILTY SAND (SM)	light red-orange	poorly graded			wet	loose				tailings	Sample wettened during drilling	Lexan Tube Samples
4.50	5.25	SILTY SAND (SM)	light red-orange	poorly graded			wet	firm				tailings	Sample wettened during drilling	
5.25	5.75	SANDY SILT (ML)	light red-orange	poorly graded			wet	firm				tailings	Sample wettened during drilling	
5.75	6.0	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white		medium		moist	stiff				residual / borrow material	Compacted clay liner Sample wettened during drilling	
6.0	7.0	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white		medium		moist	stiff				residual / borrow material	Compacted clay liner Sample wettened during drilling	
7.0	8.0	SILTY CLAY (CL) with fine sub-angular calcite gravel	dark red-brown mottled white		medium		wet	very stiff				residual / borrow material	Compacted clay liner Sample wettened during drilling	Sample

### BH3 Testing Summary

Depth [m]	Description	Sample Weight [kg]	Redox (Eh)		pH		Conductivity		Comment
			Reading [mV]	Temp [°C]	Reading	Temp [°C]	Reading [mS]	Temp [°C]	
1.0	Sample S3.1	1.8	131	25	7.59	25	3.320	17.3	Calibration 3
2.0	Sample S3.2	1	150	25	7.75	25	2.750	17.0	
3.0	Sample S3.3	2.4	139	25	8.08	25	3.090	16.3	
4.0	Sample S3.4 (Tailings)	1.2	127	25	9.22	25	2.710	14.9	
4.0 to 4.5	Lexan Tube Sample S3.11 (Tailings)	2.2	N/T	N/T	N/T	N/T	N/T	N/T	
4.5	Sample S3.5 (Tailings)	1.5	145	25	9.19	25	2.050	11.1	
4.5 to 5.25	Lexan Tube Sample S3.6 (Tested at 5.25m) (Tailings)	13	186	25	8.34	25	1.585	14.3	
5.25 to 5.75	Lexan Tube Sample S3.7 (Tailings)	10	N/T	N/T	N/T	N/T	N/T	N/T	
5.75 to 6.0	Bulk Sample S3.10	8.5	155	25	9.35	25	2.000	14.4	
6.0 to 7.0	Lexan Tube Sample S3.8 (Tested at 7m)	15	132	25	8.03	25	1.730	12.8	
8.0	Sample S3.9	1.5	152	25	8.05	25	1.731	11.8	Calibration 4
Total Weight Samples		58.1							
Total Weight Tailings Samples		27.9							

\*N/T - no tests

## Appendix 2: Laboratory Programme

## Methods Used

### Sealed Bottle Roll Tests:

The tests were carried out in glass bottles with Teflon inserts in the lids (to produce a good seal and prevent exchange headspace gases exchanging with atmospheric conditions).

The following procedure was adhered to as closely as possible:

- 1 Weigh out exactly 300 g of sample and add exactly 900 mL of solution (either de-ionised water or barren liquor solution).
- 2 Measure and record the pH, EC and redox conditions.
- 3 Seal vessel and place on shaker/rollers for a period of 72 hours.
- 4 Remove from shakers/rollers and allow solids to settle to provide a clear solution (allow about 1 to 2 hours).
- 5 Open vessel and decant clear solution.
- 6 Pour out a small aliquot (about 20 – 30 mL) and immediately record pH, redox and EC.
- 7 Filter balance of solution through a 0.45 um filtration.
- 8 Separate and preserve as per analytical laboratory requirements to complete the required analyses (Table A2.1).
- 9 Retain the final solid sample in a sealed bag in a cool environment until the solution analyses have been analysed.

### Atmospheric Conditions:

Most tests were undertaken with air occupying the head space in the bottles. However, selected tests were undertaken using a gas mixture comprising 10%CO<sub>2</sub>:90% air. During these latter tests, the bottles were sealed tightly to ensure minimal exchange with air outside the bottle. Filtering for these tests was complete under the same gas conditions, using the setup illustrated in Figure A2.1.

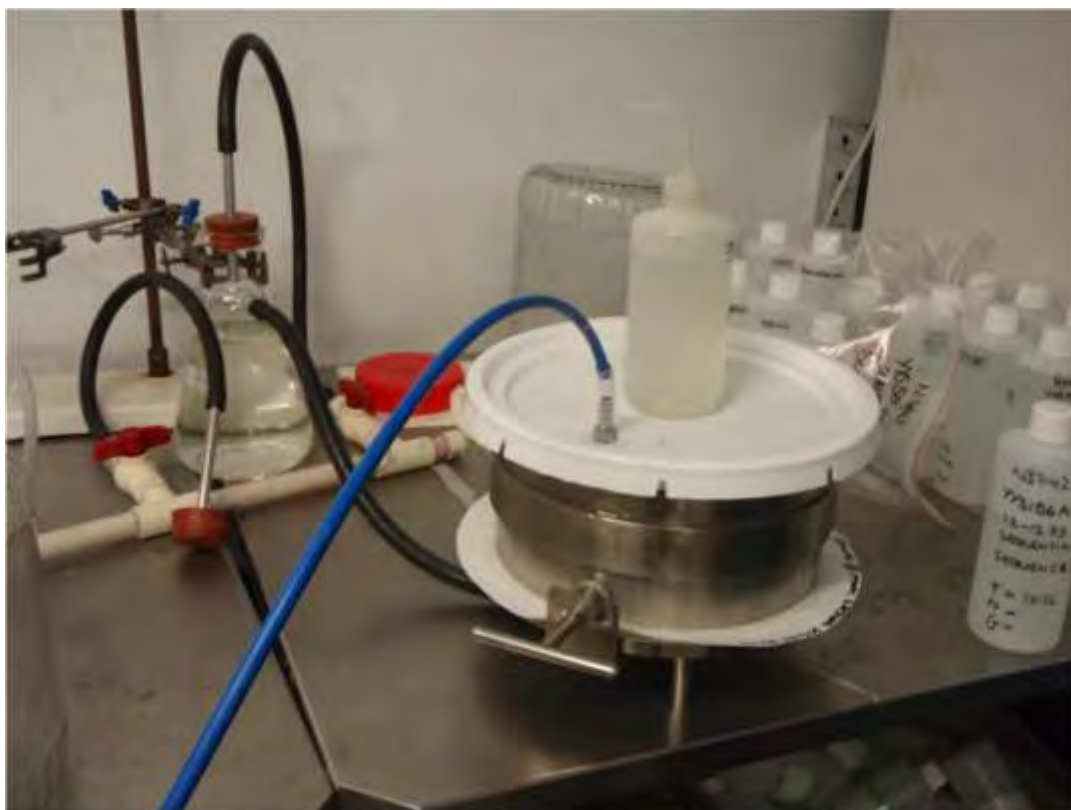


Figure A2.1: Filtering set up to ensure gas conditions remained at required CO<sub>2</sub> level during filtering

### Sequential Atmospheric Test Procedure:


These tests were very similar to the sealed bottle roll tests described in the previous section. However, the solid was contacted by three successive volumes of solution as described in the method below.

The following procedure was adhered to as closely as possible:

- 1 Weigh out exactly 300 g of sample.
- 2 Add exactly 900 mL of deionised water.
- 3 Measure and record the pH, EC and redox conditions.
- 4 After 24 hours remove vessel from shakers/rollers and allow solids to settle to provide a clear solution.
- 5 Record the pH, EC and redox conditions.
- 6 Replace on shaker/rollers and repeat Step 4 at 48 hours.
- 7 At 72 hours remove the vessel from the shaker/rollers and record the pH, EC and redox conditions.
- 8 Allow the solids to settle and decant the clear solution.
- 9 Vacuum filter the slurry sample to remove the solution.
- 10 Filter the clear solution through a 0.45 um filtration and submit for analysis as shown in Table 1 (see Section 5; preserve as per analytical laboratory requirements).
- 11 Reslurry the sample in 900 mL deionised water.
- 12 Repeat Step 3 to 11 twice to generate three sequential leach solutions.
- 13 Retain the final solid sample in a sealed bag in a cool environment until the solution analyses have been analysed.

### Column Tests

Four column pairs were set up to operate in series. The first column in each pair is open to air and operated such that the material drains down and the sample becomes unsaturated between flushing events. The second column is not open to air and maintained saturated with solution at all times. Effluent from the first column is used as inflow for the second column in that pair. The column set-up is shown schematically in Figure A2.2.

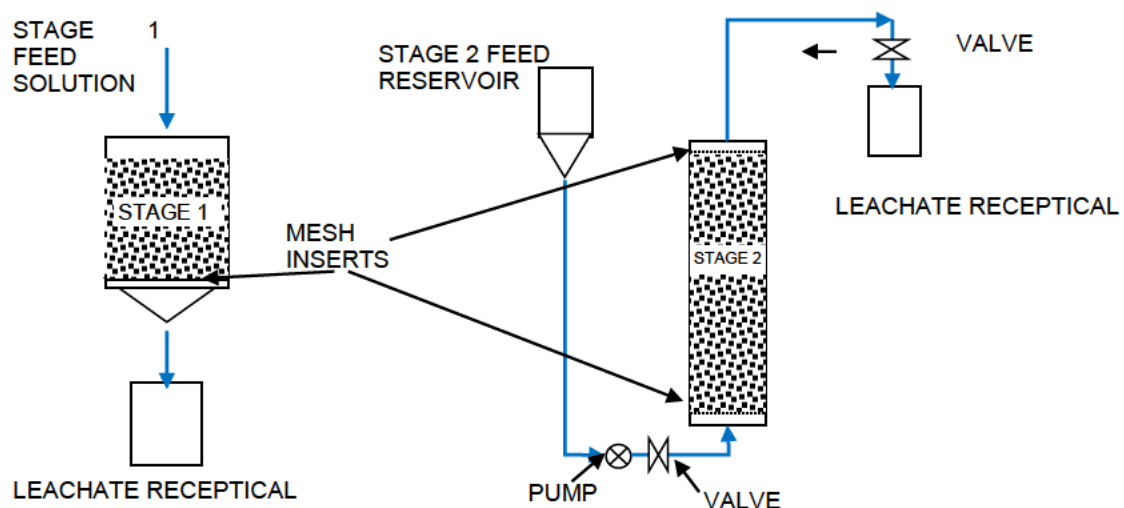

**Figure A2.2: Schematic Diagram for Column Set-Up**

The first stage columns had a diameter of 150 mm and a height of 300 mm. The base of the column was equipped with mesh to retain the solids in the column and a funnel shaped outlet to capture the leachate.

The top of the column was open to atmospheric conditions and had a capacity of about 7 kg of sample (filled to a height of about 250 mm).

The second stage columns had a diameter of 75 mm and a length of 500 mm. The column was sealed at the base and equipped with a removable lid with an airtight seal. Both ends of the column were equipped with an inlet/outlet respectively. The column had a capacity of about 3.5 kg, when filled, and an estimated porespace of about 700 mL. Figure A2.3 is a photograph of a saturated column.

The second stage saturated column was configured with up-flow to ensure saturated conditions are maintained. The column inlet and outlets were equipped with valves to ensure that atmospheric conditions were excluded to the extent possible. The second stage column was equipped with a pump to transfer solution from the inflow reservoir and displace the porewater from the saturated second stage column. Care was taken to not introduce air during the transfer.



**Figure A2.3: Photograph of Saturated Column**

The columns were loaded with the required sample quantities and sealed as required. The column operation was as follows:

- 1 Irrigate column 1 with approximately 1.5 L of water by distributing the flow evenly across the entire surface of the sample.
- 2 Allow the sample to drain and capture the leachate in the leachate receptacle. Measure pH, EC and redox conditions.
- 3 Remove approximately 700 mL of solution and place in second stage column feed reservoir. Filter the balance of the sample through 0.45  $\mu$ m filter medium, preserve as required and submit solution for required analysis.

- 4 Open the outlet valve of the second stage column. Open the inlet valve of the second stage column. Initiate the pump to draw stage 1 leachate solution from the reservoir to pass it through the second stage column. Terminate pumping while a few millilitres of solution remains in the reservoir to preclude air being drawn into the column. Close the inlet valve, close the outlet valve.
- 5 Measure the pH, EC and redox of the leachate. Filter the leachate sample through 0.45 um filter medium, preserve as required and submit solution for required analysis.

Operational difficulties were encountered with several of the columns. Unsaturated Column 1A was loaded with tailings (YC3). The tailings were found to absorb applied water and become virtually impermeable, resulting in extremely long drainage times. To overcome this difficulty, after each sequence the material was removed from the column and re-mixed prior to addition of solution in the next sequence. Nevertheless, drainage times got progressively longer after each sequence. By Sequence 5, it was taking more than a month for the column to drain. The column was terminated after Sequence 6.

Several of the saturated columns, in particular, Columns 1B and 4B were found to be of low permeability and would facilitate only very slow fluid flow. It was necessary to use a pump with a very slow flow rating and allow for long periods of time for each pore volume exchange. In Column 4B, the problem became progressively worse with each pore volume exchange sequence (probably due to Na exchange onto smectite clay, causing swelling, see discussion in main text). Column 4B was terminated after Sequence 3.

## Quality Assurance and Control

The majority of data upon which this report is based were provided by either Amdel or Labmark, both of which are NATA accredited laboratories.

Data review by SRK consisted of comparing analytical results with expected values based on knowledge of material type, sample point of origin, and the experience of the reviewing geochemist. During data reviews, 'common sense' assessments of the data were undertaken to identify any gross errors that have resulted from inappropriate data handling or processing. Typical errors of this type might include shifting of columns relative to their headings, dilution errors and incorrect units (e.g. mg/L instead of µg/L), calculation errors, and sample labelling errors.

For some of the bottle rolls, duplicate tests were operated so that the reproducibility of the data obtained could be assessed:

- Sample YYS158 3.5 m - 3.75 m – de-ionised leach extraction test
- Sample YYS156A 0.7 m - 1.5 m – barren liquor contact test

Results from the duplicate tests showed very similar trends.

In addition to duplicate tests, several 'blank' bottle roll tests were undertaken so that leaching of elements from vessel walls could be assessed. Following these 'blank' tests, most elements were found to be undetectable in the resulting solutions. There was some evidence of small amounts of Ca, Mg, Na and K leaching from walls. The quantities were small relative to those leaching from the solids and so interpretations of the main dataset are not affected.

## Appendix 3: Bulk Chemical Assays

The following appendix documents bulk chemical assay data for the samples studied as part of the current programme. Table A3.1 tabulates all assay results for the samples. Tables A3.2 and A3.3 compare the chemical characteristics of the samples with summary statistics calculated based on data contained within the BHP Billiton chemical database (as of 21<sup>st</sup> December 2009). In general, the chemistry of the samples studied in the current programme lie in the range shown by the Yeelirrie dataset as a whole.



Table A3.1: Bulk Chemical Assays

	Sample #	Material type	Al	Ca	CO2	F	Fe	K	Mg	Mn	Na	P	S	Si	SO4	TOC	
			%	%	%	%	%	%	%	%	%	%	%	%	%	%	
	Detection limit	0.01	0.01	0.07	0.002	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.05	0.05
Detection limit (tails, aging tests)																	
Yeelirrie	YYS156A 0.7-1.5	L/LT	2.06	16.8	14.2	0.44	0.98	0.47	5.77	<0.01	0.49	<0.01	4.49	11.6	6	0.05	
Yeelirrie	YYS156A 1.5-2.5	LT	2.63	8.3	11.5	0.75	1.23	0.63	9.51	0.01	0.67	<0.01	2.05	17.9	3	0.15	
Yeelirrie	YYS156A 11.25-12	CQ	9.48	0.14	0.2	0.08	4.11	1.66	1	0.02	0.64	0.01	0.07	27.4	0.1	0.05	
Yeelirrie	YYS156A 12-12.75	CQ	8.75	0.14	0.2	0.07	3.44	1.43	1.64	0.02	0.67	0.02	0.09	29.1	0.2	<0.05	
Yeelirrie	YYS156A 3-4	LT	3.81	11.2	23	0.46	1.55	0.7	9.93	<0.01	0.45	<0.01	<0.01	13.2	0.1	0.05	
Yeelirrie	YYS157 3.65-4.1	TCQ	3.6	15.6	18.5	0.17	1.67	0.65	3.01	0.02	0.21	0.02	0.03	18.1	0.15	<0.05	
Yeelirrie	YYS158 2.5-3.5	LT	0.37	15.7	31.5	0.54	0.2	0.19	11.4	<0.01	0.35	<0.01	0.04	10.8	0.1	0.1	
Yeelirrie	YYS158 3.5-3.75	T	0.13	16.8	34.6	0.59	0.1	0.12	12.4	<0.01	0.36	<0.01	0.01	7.98	0.15	0.1	
Yeelirrie	YYS158 3.75-4.5	T	0.22	17.4	37.6	0.42	0.16	0.11	12.2	<0.01	0.25	<0.01	0.03	5.86	<0.05	0.05	
Yeelirrie	YYS159 4.5-5.2	TCQ/CQT	7.19	0.98	1.5	0.19	3.03	1.41	2.28	0.1	0.35	0.01	0.01	29.8	<0.05	<0.05	
Yeelirrie	YYS162 4.5-4.5 m	TCQ	2.9	0.61	0.8	0.21	0.99	1.49	2.33	<0.01	0.57	<0.01	0.04	37	0.15	0.05	
Yeelirrie	YYS163 23 -23.1m	CQ	10.8	0.08	0.1	0.09	4.06	2.08	1.66	0.02	0.54	0.01	0.11	25.9	0.4	<0.05	
Yeelirrie	YYS164 26.2-26.3 m	CQ	4.88	0.04	<0.07	0.02	1.6	1.4	0.22	<0.01	0.32	<0.01	0.04	37.8	<0.05	0.15	
Yeelirrie	YYS164 4.3-3.3 m	LT	8.44	0.17	0.2	0.1	3.38	1.53	1.08	0.02	0.54	<0.01	0.1	29.3	0.1	<0.05	
Yeelirrie	YYS164 5.2-5.3 m	CQT	8.39	0.24	0.5	0.05	3.22	1.71	1.29	0.03	0.4	0.01	0.03	30.7	<0.05	<0.05	
Yeelirrie	YYS165 1.5 - 1.6 m	HT	2.54	14.3	17.4	0.33	1.11	0.59	5.85	<0.01	0.13	0.02	0.08	18	0.3	<0.05	
Yeelirrie	YYS165 6.6-6.7 m	CQ	4.32	0.09	0.1	0.13	1.93	1.19	1.16	0.03	0.32	<0.01	0.03	36.8	0.05	<0.05	
Yeelirrie	YYS166 0.4 - 0.5 m	H	5.63	0.05	0.4	0.01	2.31	1.36	0.35	0.03	0.2	<0.01	0.03	36.1	0.4	<0.05	
Yeelirrie	YYS167 2.3 - 2.4 m	LQT	4.63	12.2	15.4	0.13	1.98	1.12	2.96	0.01	0.36	0.02	0.07	20.3	<0.05	0.05	
Yeelirrie	YYS167 23 - 23.1 m	CQ	6.25	0.05	0.1	0.05	2.4	1	0.52	0.01	0.35	<0.01	0.06	35.1	0.1	<0.05	
Yeelirrie	YYHC0075	Palaeochannel sands	1.23	0.11	0.2	0.01	0.68	0.1	0.05	<0.01	0.16	<0.01	0.06	41.8	0.05	0.05	
Yeelirrie	YYHC0059C	Palaeochannel sands	1.35	0.05	0.2	0.02	0.67	0.09	0.09	<0.01	0.51	<0.01	0.09	41.4	0.1	<0.05	
Tails	YM0015	Tails (aging test)	8.99	0.42	1.41		3.53	1.58	1.72	0.02	1.24	<0.01	0.05	28.36			
Tails	YM0046	Tails (aging test)	1.61	13.77	24.09		0.72	0.4	9.37	<0.01	1.12	<0.01	0.08	13.28			
Tails	YM0074	Tails (aging test)	10.64	0.35	1.16		4.31	1.69	1.66	0.02	1.2	0.01	0.05	27.05			
Tails	YM0076	Tails (aging test)	1.61	17.69	35.98		0.73	0.31	10.83	0.03	0.37	0.01	0.03	6.64			
Tail	YC003 Leach Residue	Tails	5.48	6.85	12.3	0.26	2.4	1.04	5.17	0.03	1.45	0.02	0.04	20.3	0.15	0.05	
Kalgoorlie	S1.8 (4 m)	Tails	4.28	8.27	15.4	0.312	1.89	0.84	4.88	0.01	0.69	<0.01	<0.01	20.1	0.55	0.1	
Kalgoorlie	S1.9 (4-4.5 m)	Tails	3.78	8.32	14.3	0.218	2.02	0.86	4.74	0.01	0.55	0.01	0.07	22.6	0.1	0.1	

	Sample #	Material type	Al	Ca	CO2	F	Fe	K	Mg	Mn	Na	P	S	Si	SO4	TOC	
			%	%	%	%	%	%	%	%	%	%	%	%	%	%	
	Detection limit		0.01	0.01	0.07	0.002	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.05	0.05
	Detection limit (tails, aging tests)																
Kalgoorlie	S2.10 (6 m)	Underlying soil	9.59	0.31	0.9	0.05	20	0.32	0.39	0.01	0.64	0.01	0.06	17.7	0.1	<0.05	
Kalgoorlie	S2.11 (6-6.75 m)	Underlying soil	10.5	0.21	0.8	0.042	16.7	0.25	0.31	<0.01	0.59	<0.01	0.05	19	0.1	0.05	
Kalgoorlie	S2.14 (4-4.5 m)	Tails	5.57	8.41	14.1	0.254	5.29	0.81	5.54	0.02	1.1	0.01	0.07	17.3	0.1	0.2	
Kalgoorlie	S2.8 (4.5-5.25 m)	Tails	4.18	8.46	16	0.25	1.84	0.9	5.22	0.02	0.76	0.01	0.02	20.4	0.2	0.05	
Kalgoorlie	S2.9 (5.25-6 m)	Underlying soil	6.31	7.57	13	0.226	7	0.62	4.97	0.01	1.2	<0.01	0.07	16	0.7	0.15	
Kalgoorlie	S3.10 (5.75-6 m)	Underlying soil	5.81	5.77	6.1	0.034	14	0.16	2.21	0.15	1.02	0.06	0.3	20.5	<0.05	<0.05	
Kalgoorlie	S3.11 (3.75 m)	Tails	3	6.92	13.1	0.254	1.37	0.86	3.86	0.01	0.37	<0.01	0.02	25.9	0.1	0.05	
Kalgoorlie	S3.6 (4.5-5.25 m)	Tails	5.44	4.66	4.5	0.034	16	0.12	1.82	0.17	1.22	0.05	0.27	20.6	<0.05	0.1	
Kalgoorlie	S3.7 (5.3-5.75 m)	Tails	2.99	7.98	15.2	0.202	2.58	0.69	4.32	0.02	0.41	<0.01	0.02	23	0.15	0.1	
Kalgoorlie	S3.8 (6-7 m)	Underlying soil	11.4	0.47	1	0.018	14.5	0.17	0.34	0.01	0.48	<0.01	0.06	18.8	<0.05	<0.05	
Kalgoorlie	S3.9 (8 m)	Underlying soil	16.4	0.08	0.5	0.01	4.11	0.08	0.22	<0.01	0.35	<0.01	0.16	21.3	0.15	0.1	

	Sample #	Material type	Ag	As	B	Ba	Be	Bi	Cd	Ce	Co	Cr	Cu	Hg	Li	Mo
			(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
	Detection limit	0.05	0.5	100	10	0.5	0.1	0.1	1	0.2	20	0.5	0.05	4	0.1	
Detection limit (tails, aging tests)					200				100							
Yeelirrie	YYS156A 0.7-1.5	L/LT	<0.05	11.5	100	60	<0.5	<0.1	<0.1	18	3	30	11.5	<0.05	10	1.4
Yeelirrie	YYS156A 1.5-2.5	LT	<0.05	8.5	<100	75	<0.5	<0.1	<0.1	20	4	45	17.5	<0.05	10	2.4
Yeelirrie	YYS156A 11.25-12	CQ	<0.05	21.5	200	250	1.5	0.3	<0.1	70	6	95	30.5	<0.05	20	8
Yeelirrie	YYS156A 12-12.75	CQ	<0.05	13.5	100	220	1	0.2	<0.1	55	4.6	80	19.5	<0.05	15	6.5
Yeelirrie	YYS156A 3-4	LT	<0.05	9.5	<100	40	0.5	<0.1	<0.1	24	4	45	20.5	<0.05	10	2.8
Yeelirrie	YYS157 3.65-4.1	TCQ	<0.05	3.5	<100	100	0.5	0.1	<0.1	23	4.4	50	18.5	<0.05	10	2
Yeelirrie	YYS158 2.5-3.5	LT	<0.05	1.5	<100	40	<0.5	<0.1	<0.1	2	0.8	<20	10	<0.05	5	0.9
Yeelirrie	YYS158 3.5-3.75	T	<0.05	1	<100	20	<0.5	<0.1	<0.1	<1	0.6	<20	7	<0.05	5	1.9
Yeelirrie	YYS158 3.75-4.5	T	<0.05	0.5	<100	50	<0.5	<0.1	<0.1	4	0.6	<20	4	<0.05	5	1.1
Yeelirrie	YYS159 4.5-5.2	TCQ/CQT	<0.05	8.5	100	295	1	0.2	<0.1	36	10.5	80	29.5	<0.05	20	4.5
Yeelirrie	YYS162 4.5-4.5 m	TCQ	<0.05	3	<100	315	0.5	<0.1	<0.1	16	2.8	45	8	<0.05	<4	2.1
Yeelirrie	YYS163 23 -23.1 m	CQ	<0.05	3	<100	205	2	0.3	<0.1	60	8	100	31	<0.05	25	1.5
Yeelirrie	YYS164 26.2-26.3 m	CQ	<0.05	4	<100	315	0.5	0.1	<0.1	27	1.8	45	15	<0.05	25	5.5
Yeelirrie	YYS164 4.3-3.3 m	LT	<0.05	3	<100	285	2	0.2	<0.1	47	6.5	115	19.5	<0.05	25	2.2
Yeelirrie	YYS164 5.2-5.3 m	CQT	<0.05	4	<100	290	1	0.2	<0.1	48	6.5	85	22	<0.05	20	1.9
Yeelirrie	YYS165 1.5 - 1.6 m	HT	<0.05	5	<100	125	0.5	<0.1	<0.1	15	3.4	40	13	<0.05	<4	0.6
Yeelirrie	YYS165 6.6-6.7 m	CQ	<0.05	5	<100	335	1	0.1	<0.1	31	7	70	14	<0.05	<4	2.2
Yeelirrie	YYS166 0.4 - 0.5 m	H	<0.05	3	<100	415	1	0.2	<0.1	36	9.5	70	20	<0.05	15	3.4
Yeelirrie	YYS167 2.3 - 2.4 m	LQT	<0.05	5	<100	320	1	0.1	<0.1	26	4.8	55	17	<0.05	<4	1.7
Yeelirrie	YYS167 23 - 23.1 m	CQ	<0.05	2	<100	290	0.5	0.1	<0.1	36	2.4	70	11	<0.05	20	2.1
Yeelirrie	YYHC0075	Palaeochannel sands	0.05	0.5	--	65	0.5	0.1	<0.1	39	1	105	8.5	<0.05	15	2.1
Yeelirrie	YYHC0059C	Palaeochannel sands	0.25	1	--	60	<0.5	<0.1	<0.1	145	1.8	140	20	<0.05	<4	2.3
Tails	YM0015	Tails (aging test)	<0.05	15.16		400		0.22	<0.1	<100	7.07	137	23.24			5.34
Tails	YM0046	Tails (aging test)	0.05	2.98		<200		<0.1	<0.1	<100	2.86	52	18.76			3.43
Tails	YM0074	Tails (aging test)	<0.05	21.21		400		0.27	<0.1	<100	7.47	128	27.98			5.58
Tails	YM0076	Tails (aging test)	<0.05	2.42		<200		<0.1	<0.1	<100	3.67	76	17.2			5.4
Tail	YC003 Leach Residue	Tails	0.1	15.5	100	230	1	0.2	<0.1	32	6	130	23.5	<0.05	15	13
Kalgoorlie	S1.8 (4 m)	Tails	0.05	13.5	35	210	<0.05	0.2	<0.1	26	4.4	60	21.5	<0.05	5	1.8
Kalgoorlie	S1.9 (4-4.5 m)	Tails	0.05	11	45	235	1	0.1	<0.1	22	3.8	55	16	<0.05	10	2.3
Kalgoorlie	S2.10 (6 m)	Underlying soil	<0.05	15	55	175	0.5	0.3	<0.1	8	5.5	495	22.5	<0.05	5	2.6

	Sample #	Material type	Ag	As	B	Ba	Be	Bi	Cd	Ce	Co	Cr	Cu	Hg	Li	Mo
			(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
	Detection limit	0.05	0.5	100	10	0.5	0.1	0.1	1	0.2	20	0.5	0.05	4	0.1	
Detection limit (tails, aging tests)					200				100							
Kalgoorlie	S2.11 (6-6.75 m)	Underlying soil	<0.05	12	70	125	<0.05	0.3	<0.1	7	6	440	25	<0.05	10	3
Kalgoorlie	S2.14 (4-4.5 m)	Tails	0.1	16	60	205	1	0.3	<0.1	31	8	130	25	<0.05	5	2.1
Kalgoorlie	S2.8 (4.5-5.25 m)	Tails	<0.05	10.5	45	250	1	0.2	<0.1	25	4.4	50	23.5	0.05	5	1.7
Kalgoorlie	S2.9 (5.25-6 m)	Underlying soil	<0.05	10.5	85	165	0.5	0.2	<0.1	22	7.5	190	18.5	<0.05	5	1.6
Kalgoorlie	S3.10 (5.75-6 m)	Underlying soil	0.2	10.5	105	65	0.5	<0.1	<0.1	16	47.5	135	55	<0.05	20	1.9
Kalgoorlie	S3.11 (3.75 m)	Tails	<0.05	13.5	50	230	<0.05	0.2	<0.1	19	2.8	40	19	<0.05	<4	1.8
Kalgoorlie	S3.6 (4.5-5.25 m)	Tails	0.2	11.5	110	60	0.5	<0.1	<0.1	17	47	130	41.5	<0.05	20	1.4
Kalgoorlie	S3.7 (5.3-5.75 m)	Tails	0.05	10.5	55	240	<0.05	0.2	<0.1	20	5.5	70	18	<0.05	<4	1.8
Kalgoorlie	S3.8 (6-7 m)	Underlying soil	<0.05	8.5	160	130	<0.05	0.2	<0.1	6	10.5	365	20	<0.05	10	1.8
Kalgoorlie	S3.9 (8 m)	Underlying soil	<0.05	1	270	100	<0.05	<0.1	<0.1	4	7.5	215	9.5	<0.05	20	0.5

	Sample #	Material type	Ni	Pb	Sb	Sc	Se	Sn	Sr	Th	Tl	U3O8	V	W	Y	Zn
			(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
	Detection limit		1	0.5	0.1	5	0.5	10	5	4	3	4	20	3	1	0.5
	Detection limit (tails, aging tests)															
Yeelirrie	YYS156A 0.7-1.5	L/LT	11	5	<0.1	<5	0.5	<10	700	5	<3	235	85	<3	7	18
Yeelirrie	YYS156A 1.5-2.5	LT	11	7	<0.1	<5	<0.5	<10	355	5	<3	700	165	<3	7	700
Yeelirrie	YYS156A 11.25-12	CQ	15	16.5	0.2	10	<0.5	<10	55	25	<3	70	175	<3	19	46
Yeelirrie	YYS156A 12-12.75	CQ	13	12.5	0.1	10	<0.5	<10	50	20	<3	65	145	<3	13	125
Yeelirrie	YYS156A 3-4	LT	12	6.5	<0.1	5	<0.5	<10	430	10	<3	1100	245	<3	7	34.5
Yeelirrie	YYS157 3.65-4.1	TCQ	14	5.5	<0.1	5	<0.5	<10	280	10	<3	140	60	<3	6	46.5
Yeelirrie	YYS158 2.5-3.5	LT	5	1.5	<0.1	<5	<0.5	<10	500	<4	<3	195	60	<3	<1	145
Yeelirrie	YYS158 3.5-3.75	T	5	1	<0.1	<5	1	<10	550	<4	<3	55	50	<3	<1	265
Yeelirrie	YYS158 3.75-4.5	T	5	1	<0.1	<5	0.5	<10	600	<4	<3	150	75	<3	<1	27
Yeelirrie	YYS159 4.5-5.2	TCQ/CQT	17	9.5	0.2	10	<0.5	<10	80	15	<3	10	120	<3	11	85
Yeelirrie	YYS162 4.5-4.5 m	TCQ	7	3.5	<0.1	<5	<0.5	<10	75	5	<3	45	65	<3	3	14
Yeelirrie	YYS163 23 -23.1 m	CQ	20	14	0.1	15	<0.5	<10	1000	30	<3	15	65	<3	15	38.5
Yeelirrie	YYS164 26.2-26.3 m	CQ	8	15.5	0.1	5	<0.5	<10	40	20	<3	5	45	<3	7	9.5
Yeelirrie	YYS164 4.3-3.3 m	LT	15	13	0.1	10	<0.5	<10	65	15	<3	15	60	<3	13	29.5
Yeelirrie	YYS164 5.2-5.3 m	CQT	14	10.5	0.1	10	<0.5	<10	60	15	<3	20	60	<3	11	37.5
Yeelirrie	YYS165 1.5 - 1.6 m	HT	13	4.5	0.1	<5	<0.5	<10	290	5	<3	165	35	<3	5	18
Yeelirrie	YYS165 6.6-6.7 m	CQ	10	7.5	<0.1	5	<0.5	<10	45	10	<3	10	50	4	9	21
Yeelirrie	YYS166 0.4 - 0.5 m	H	12	9.5	0.1	5	<0.5	<10	50	10	<3	15	45	<3	11	17.5
Yeelirrie	YYS167 2.3 - 2.4 m	LQT	16	7.5	<0.1	5	<0.5	<10	450	5	<3	160	60	<3	9	25
Yeelirrie	YYS167 23 - 23.1 m	CQ	9	8	<0.1	10	<0.5	<10	30	20	<3	15	40	8	11	15
Yeelirrie	YYHC0075	Palaeochannel sands	3	31.5	<0.1	<5	<0.5	<10	10	15	<3	5	<20	<3	13	17.5
Yeelirrie	YYHC0059C	Palaeochannel sands	4	23	<0.1	<5	0.5	<10	35	15	<3	5	<20	10	17	37
Tails	YM0015	Tails (aging test)	45	15.81	0.1	11	<0.5		5560	19.61		226	222		11	40.9
Tails	YM0046	Tails (aging test)	28	5.07	<0.1	<5	<0.5		928	3.07		64.4	84		<10	19.26
Tails	YM0074	Tails (aging test)	46	17.18	<0.1	14	<0.5		4713	20.22		63.68	177		13	45.53
Tails	YM0076	Tails (aging test)	36	4.79	<0.1	<5	<0.5		8184	3.14		90.97	49		<10	12.68
Tail	YC003 Leach Residue	Tails	60	9	0.1	10	<0.5	<10	2100	15	<3	180	230	<3	9	37
Kalgoorlie	S1.8 (4 m)	Tails	13	36.5	<0.1	5	<0.5	<10	2300	10	<3	230	375	<3	7	45
Kalgoorlie	S1.9 (4-4.5 m)	Tails	13	20.5	<0.1	5	<0.5	<10	1800	10	<3	180	210	<3	7	180
Kalgoorlie	S2.10 (6 m)	Underlying soil	22	18	0.4	35	0.5	<10	105	10	<3	215	550	<3	11	185

	Sample #	Material type	Ni	Pb	Sb	Sc	Se	Sn	Sr	Th	Tl	U3O8	V	W	Y	Zn
			(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
	Detection limit	1	0.5	0.1	5	0.5	10	5	4	3	4	20	3	1	0.5	
Detection limit (tails, aging tests)																
Kalgoorlie	S2.11 (6-6.75 m)	Underlying soil	24	9.5	0.3	35	1	<10	95	5	<3	185	475	<3	11	30
Kalgoorlie	S2.14 (4-4.5 m)	Tails	26	400	0.2	10	0.5	<10	1800	15	<3	360	420	<3	8	120
Kalgoorlie	S2.8 (4.5-5.25 m)	Tails	28	225	<0.1	5	<0.5	<10	2900	10	<3	160	195	<3	7	70
Kalgoorlie	S2.9 (5.25-6 m)	Underlying soil	33	205	0.2	15	0.5	<10	900	10	<3	450	340	<3	8	34
Kalgoorlie	S3.10 (5.75-6 m)	Underlying soil	26	115	0.3	45	<0.5	<10	150	<4	<3	15	290	4	28	280
Kalgoorlie	S3.11 (3.75 m)	Tails	9	215	<0.1	<5	<0.5	<10	1200	10	<3	250	210	<3	5	23.5
Kalgoorlie	S3.6 (4.5-5.25 m)	Tails	21	25.5	0.4	50	<0.5	<10	135	<4	<3	15	280	6	34	130
Kalgoorlie	S3.7 (5.3-5.75 m)	Tails	13	200	0.1	5	<0.5	<10	1300	5	<3	205	185	<3	6	41.5
Kalgoorlie	S3.8 (6-7 m)	Underlying soil	38	7	0.3	35	0.5	<10	20	15	<3	125	410	<3	16	30.5
Kalgoorlie	S3.9 (8 m)	Underlying soil	25	3	<0.1	30	<0.5	<10	15	10	<3	5	175	4	24	70

**Table A3.2: Bulk chemical assay data compared to BHP Billiton chemical database – major elements**

Lithology	Element	Al	Ca	Fe	K	Mg	Mn	Na	P	S	Si	
	Units	%	%	%	%	%	%	%	%	%	%	
Average crustal abundance (Bowen, 1979)		8.2	4.1	4.1	2.1	2.3	0.095	2.3	0.1	0.026	27.7	
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)												
Loam (L)	Min	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	
	P5	2.3	0.1	1.1	0.6	0.5	0.010	0.2	0.01	0.050	13.5	
	Median	4.7	1.4	2.3	1.2	3.9	0.030	0.5	0.01	0.135	25.4	
	Mean	4.5	4.0	2.1	1.1	4.8	0.026	0.8	0.01	1.717	25.0	
	P95	6.7	12.5	3.0	1.5	9.2	0.050	2.0	0.02	6.891	35.9	
	Max	6.7	14.8	3.3	1.6	10.2	0.050	2.0	0.03	7.350	36.9	
	n	18	18	18	18	18	18	18	18	18	18	18
	Stdev	1	4.8	0.7	0.3	3.4	0.012	0.6	0.0	2.545	8.2	
L/LT	YY5156 0.7 m - 1.5 m	2.06	16.8	0.98	0.47	5.77	<0.01	0.49	<0.01	6	11.6	
Carbonated loam (LT)	Min	0.1	0.1	0.1	0.1	0.3	0.005	0.1	0.005	0.005	2.3	
	P5	0.9	2.5	0.4	0.3	1.6	0.005	0.2	0.005	0.060	7.9	
	Median	2.4	12.4	1.2	0.6	5.8	0.010	0.5	0.005	2.490	15.2	
	Mean	2.8	12.1	1.3	0.6	6.0	0.011	0.6	0.010	3.740	15.8	
	P95	6.0	20.4	2.7	1.2	11.3	0.030	1.2	0.020	11.572	25.7	
	Max	12.7	25.8	4.7	1.8	13.8	0.160	2.5	0.1	20.690	35.6	
	n	1417	1417	1417	1417	1417	1417	1417	1417	1417	1417	1417
	Stdev	2	5.5	0.7	0.3	3.0	0.009	0.3	0.0	3.942	5.5	
LT	YY5156A 3 m – 4 m	4	11	2	1	10	<0.01	0.5	<0.01	0.1	13	
LT	YY5156A 1.5 m - 2.5 m	3	8	1	1	10	0.01	1	<0.01	3	18	
LT	YY5164 4.3 m - 4.4 m	8	0.2	3	2	1	0.02	1	<0.01	0.1	29	
L/LT	YY5156 0.7 m - 1.5 m	2.06	16.8	0.98	0.47	5.77	<0.01	0.49	<0.01	6	11.6	
Quartz-rich loam (LQ)	Min	2.5	0.1	1.2	0.7	0.1	0.005	0.1	0.005	0.010	19.5	
	P5	3.2	0.1	1.6	0.8	0.1	0.010	0.2	0.005	0.014	23.0	
	Median	4.5	0.2	2.0	1.2	0.5	0.020	0.3	0.010	0.050	35.1	
	Mean	4.8	1.0	2.2	1.2	1.2	0.028	0.4	0.012	0.375	34.3	
	P95	7.4	4.9	3.2	1.6	5.8	0.050	0.9	0.020	2.563	39.2	
	Max	7.4	12.4	3.3	1.7	7.9	0.080	2.0	0.020	4.750	39.8	
	n	28	28	28	28	28	28	28	28	28	28	28
	Stdev	1	2.6	0.6	0.3	2.0	0.016	0.4	0.0	1.087	5.0	

Lithology	Element	Al	Ca	Fe	K	Mg	Mn	Na	P	S	Si	
	Units	%	%	%	%	%	%	%	%	%	%	
Average crustal abundance (Bowen, 1979)		8.2	4.1	4.1	2.1	2.3	0.095	2.3	0.1	0.026	27.7	
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)												
LQT	YY5167 2.3 m - 2.4 m	5	12.2	2.0	1.1	3.0	0.010	0.4	0.02	<0.05	20.3	
Carbonated-quartz-rich loam (LQT)	Min	0.2	0.03	0.1	0.2	0.1	0.005	0.1	0.005	0.005	5.4	
	P5	1.2	0.3	0.6	0.3	0.9	0.005	0.2	0.005	0.040	11.0	
	Median	3.4	7.7	1.6	0.8	4.2	0.020	0.4	0.010	0.185	21.4	
	Mean	3.9	8.6	1.8	0.8	4.7	0.018	0.5	0.012	1.685	21.6	
	P95	8.2	19.6	3.5	1.4	9.9	0.040	1.2	0.030	7.727	34.1	
	Max	9.7	26.5	4.6	1.9	12.3	0.080	2.5	0.1	15.270	39.8	
	n	482	482	482	482	482	482	482	482	482	482	482
	Stdev	2	6.2	0.9	0.3	2.9	0.013	0.3	0.008	2.773	7.2	
LQT	YY5167 2.3 m - 2.4 m	5	12.2	2.0	1.1	3.0	0.010	0.4	0.02	<0.05	20.3	
Carbonated hardpan (HT)	Min	1.9	0.5	0.8	0.4	1.0	0.005	0.1	0.01	0.010	14.1	
	P5	2.6	0.8	1.1	0.5	1.1	0.009	0.2	0.01	0.017	15.1	
	Median	7.5	2.6	3.1	1.2	2.6	0.040	0.3	0.02	0.060	25.2	
	Mean	6.7	5.0	2.9	1.1	3.1	0.032	0.3	0.02	0.108	24.4	
	P95	9.3	15.1	4.1	1.4	7.1	0.050	0.5	0.02	0.346	30.6	
	Max	9.7	16.9	4.1	1.5	7.5	0.050	0.6	0.02	0.710	30.8	
	n	15	15	15	15	15	15	15	15	15	15	15
	Stdev	2	5.1	1.0	0.3	2.0	0.015	0.1	0.01	0.172	5.1	
HT	YY5165 1.5 m - 1.6 m	3	14.3	1.1	0.6	5.9	<0.01	0.1	0.02	0.300	18.0	
Calcrete (T)	Min	0.0	0.1	0.0	0.0	1.9	0.005	0.1	0.005	0.005	2.1	
	P5	0.1	7.8	0.1	0.1	5.4	0.005	0.2	0.005	0.020	5.8	
	Median	1.0	16.5	0.4	0.3	9.9	0.005	0.5	0.010	0.090	10.7	
	Mean	1.2	16.1	0.5	0.4	9.5	0.010	0.5	0.009	0.352	11.4	
	P95	3.4	23.6	1.4	0.8	12.4	0.030	0.9	0.020	1.999	18.9	
	Max	8.2	28.6	3.9	1.8	14.6	0.090	1.7	0.180	12.380	39.0	
	n	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402
	Stdev	1	4.7	0.5	0.2	2.2	0.010	0.2	0.0	1.003	4.4	



Lithology	Element	Al	Ca	Fe	K	Mg	Mn	Na	P	S	Si
	Units	%	%	%	%	%	%	%	%	%	%
Average crustal abundance (Bowen, 1979)		8.2	4.1	4.1	2.1	2.3	0.095	2.3	0.1	0.026	27.7
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)											
T	YY5158 3.75 m - 4.75 m	0.2	17.4	0.2	0.1	12.2	<0.01	0.3	<0.01	<0.05	5.9
T	YY5158 3.5 m - 3.75 m	0.1	16.8	0.1	0.1	12.4	<0.01	0.4	<0.01	0.150	8.0
Transition calcrete (TCQ)	Min	0.1	0.04	0.1	0.1	0.4	0.005	0.1	0.005	0.005	3.3
	P5	0.6	0.2	0.3	0.2	1.8	0.005	0.2	0.005	0.020	6.1
	Median	2.7	13.1	1.2	0.6	8.1	0.020	0.4	0.010	0.080	13.2
	Mean	3.4	12.1	1.5	0.7	7.5	0.020	0.5	0.010	0.417	14.6
	P95	8.8	20.8	3.6	1.5	11.5	0.060	0.8	0.020	2.649	27.5
	Max	13.2	30.0	5.1	2.3	14.4	0.710	1.2	0.1	11.160	37.9
	n	2084	2084	2084	2084	2084	2084	2084	2084	2084	2084
	Stdev	3	6.2	1.0	0.4	2.9	0.025	0.2	0.006	1.152	6.8

Lithology	Element	Al	Ca	Fe	K	Mg	Mn	Na	P	S	Si
	Units	%	%	%	%	%	%	%	%	%	%
Average crustal abundance (Bowen, 1979)		8.2	4.1	4.1	2.1	2.3	0.095	2.3	0.1	0.026	27.7
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)											
TCQ	YYS162 4.5 m - 4.6 m	3	0.6	1.0	1.5	2.3	<0.01	0.6	<0.01	0.150	37.0
TCQ	YYS157 3.65 m - 4.1 m	4	15.6	1.7	0.7	3.0	0.020	0.2	0.02	0.150	18.1
TCQ/CQT	YYS159 4.5 m - 5.2 m	7	1.0	3.0	1.4	2.3	0.100	0.4	0.01	<0.05	29.8
Carbonated Clay-Quartz (CQT)	Min	1.0	0.005	0.4	0.3	0.1	0.005	0.2	0.005	0.005	6.1
	P5	4.4	0.1	1.9	1.1	0.4	0.010	0.3	0.005	0.030	19.9
	Median	8.3	0.1	3.5	1.5	1.0	0.020	0.5	0.010	0.080	29.0
	Mean	8.2	0.7	3.4	1.5	1.4	0.019	0.5	0.013	0.193	28.8
	P95	12.0	4.7	4.8	1.8	4.3	0.030	0.7	0.030	0.600	36.5
	Max	14.1	23.1	6.3	2.5	11.4	0.350	1.2	0.1	10.230	40.8
	n	6281	6281	6281	6281	6281	6281	6281	6281	6281	6281
	Stdev	2	2.3	0.9	0.2	1.4	0.015	0.1	0.01	0.624	5.2
CQT	YYS164 5.2 m - 5.3 m	8	0.2	3.2	1.7	1.3	0.030	0.4	0.01	<0.05	30.7
TCQ/CQT	YYS159 4.5 m - 5.2 m	7	1.0	3.0	1.4	2.3	0.100	0.4	0.01	<0.05	29.8
Clay Quartz (CQ)	Min	2.6	0.005	1.0	0.6	0.2	0.005	0.2	0.005	0.005	11.3
	P5	4.7	0.1	1.9	1.2	0.3	0.005	0.3	0.005	0.040	24.1
	Median	8.7	0.1	3.5	1.6	0.8	0.020	0.5	0.010	0.080	29.5
	Mean	8.4	0.1	3.4	1.5	0.9	0.019	0.5	0.011	0.121	29.9
	P95	11.9	0.1	4.8	1.8	1.7	0.030	0.8	0.020	0.170	36.6
	Max	14.4	13.3	6.1	2.5	9.8	0.440	2.4	0.1	8.480	40.4
	n	2571	2571	2571	2571	2571	2571	2571	2571	2571	2571
	Stdev	2	0.5	0.9	0.2	0.5	0.022	0.1	0.01	0.333	4.0
CQ	YYS156A 12 m - 12.75 m	9	0.1	3.4	1.4	1.6	0.020	0.7	0.02	0.200	29.1
CQ (poss channel sand)	YYS163 23 m - 23.1 m	11	0.1	4.1	2.1	1.7	0.020	0.5	0.01	0.400	25.9

**Table A3.3: Bulk chemical assay data compared to BHP Billiton chemical database – minor and trace elements**

Lithology	Element	Ag	As	Ba	Co	Cr	Cu	Mo	Ni	Pb	Sr	U <sub>3</sub> O <sub>8</sub>	V	Zn
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Average crustal abundance (Bowen, 1979)		0.07	1.5	0.05	20	100	50	1.5	80	14	370	2.8	160	75
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)														
Loam (L)	Min	0.00	0.0	0.00	0	0	0	0	0	0	0	0	0	0
	P5	0.25	2.0	0.01	3	29	9	0.5	11	7	35	15.9	42	18
	Median	0.25	4.0	0.01	5	68	16	2.0	15	10	143	37.5	61	30
	Mean	0.25	7.1	0.01	5	63	17	1.9	15	10	303	97.5	74	31
	P95	0.25	16.0	0.03	7	92	33	3.6	19	13	852	286	113	46
	Max	0.25	16.0	0.03	8	99	35	7.0	20	16	954	294	115	47
	n	18	18	18	18	18	18	18	18	18	18	18	18	18
	Stdev	0	5.3	0.01	1	23	7	1.5	4	2	302	104	30	11
L/LT	YY5156 0.7 m - 1.5 m	<0.05	11.5	0.006	3	30	11.5	1.4	11	5	700	235	85	18
Carbonated loam (LT)	Min	0.25	0.5	0.01	1	10	2	0.5	1	2	56	2.0	5	2
	P5	0.25	3.0	0.01	1	10	6	0.5	4	3	146	25.8	37	8
	Median	0.25	11.0	0.01	3	37	11	2.0	9	8	589	273	111	18
	Mean	0.26	12.5	0.01	3	39	12	1.8	10	8	1627	399	122	21
	P95	0.25	26	0.02	6	72	20	3.0	18	14	6797	1033	234	41
	Max	1.33	47	0.13	47	132	235	10.0	37	90	42110	10843	1733	215
	n	1417	1417	1417	1417	1417	1417	1417	1417	1417	1417	1417	1417	1416
	Stdev	0.07	7.2	0.01	2	19	8	1.2	4	4	3717	589	100	13
LT	YY5156A 3 m – 4 m	<0.05	10	0.0040	4	45	21	3	12	7	430	1100	245	35
LT	YY5156A 1.5 m - 2.5 m	<0.05	9	0.0075	4	45	18	2	11	7	355	700	165	700
LT	YY5164 4.3 m - 4.4 m	<0.05	3	0.0285	7	115	20	2	15	13	65	15	60	30
L/LT	YY5156 0.7 m - 1.5 m	<0.05	11.5	0.0060	3	30	11.5	1.4	11	5	700	235	85	18
Quartz-rich loam (LQ)	Min	0.25	0.5	0.01	2	38	8	0.5	9	5	28	4	32	13
	P5	0.25	0.5	0.01	3	51	9	0.5	9	6	31	5	33	14
	Median	0.25	2.0	0.03	5	63	13	2.0	12	8	60	11.5	45	24
	Mean	0.25	3.0	0.03	5	67	16	1.5	13	12	98	22.4	51	27
	P95	0.25	8.0	0.05	10	90	35	2.7	20	13	259	72	100	51
	Max	0.25	11.0	0.05	12	94	48	3.0	22	113	846	141	117	52
	n	28	28	28	28	28	28	28	28	28	28	28	28	28
	Stdev	0	2.7	0.01	2	13	9	0.8	4	20	157	29.1	21	12

Lithology	Element	Ag	As	Ba	Co	Cr	Cu	Mo	Ni	Pb	Sr	U <sub>3</sub> O <sub>8</sub>	V	Zn
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Average crustal abundance (Bowen, 1979)		0.07	1.5	0.05	20	100	50	1.5	80	14	370	2.8	160	75
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)														
LQT	YY5167 2.3 m - 2.4 m	<0.05	5.0	0.03	5	55	17	1.7	16	8	450	160	60	25
Carbonated-quartz-rich loam (LQT)	Min	0.25	0.5	0.01	1	10	4	0.5	2	2	30	2.0	14	4
	P5	0.25	1.0	0.01	1	20	8	0.5	5	4	61	11.0	29	10
	Median	0.25	8.0	0.01	4	49	13	2.0	12	9	311	84	81	24
	Mean	0.27	10.0	0.01	4	52	14	1.6	12	10	708	189	91	27
	P95	0.25	26.0	0.03	9	91	25	3.0	23	15	2195	674	186	50
	Max	1.48	42.0	0.06	28	131	75	6.0	30	485	30100	2085	374	182
	n	482	482	482	482	482	482	482	482	482	482	482	482	482
	Stdev	0.1	7.9	0.01	2	23	7	0.8	5	22	1821	249	53	16
LQT	YY5167 2.3 m - 2.4 m	<0.05	5.0	0.03	5	55	17	1.7	16	8	450	160	60	25
Carbonated hardpan (HT)	Min	0.25	0.5	0.01	2	26	9	0.5	7	4	76	8	38	15
	P5	0.25	0.9	0.01	3	33	13	0.9	10	6	83	12.9	46	19
	Median	0.25	3.0	0.01	8	80	20	2.0	22	12	148	27	69	37
	Mean	0.25	6.6	0.02	7	73	19	1.6	20	11	446	69	78	37
	P95	0.25	22.6	0.06	10	95	25	2.3	28	14	1756	311	135	53
	Max	0.25	31.0	0.12	10	99	25	3.0	29	14	2863	364	162	54
	n	15	15	15	15	15	15	15	15	15	15	15	15	15
	Stdev	0	8.7	0.03	3	22	5	0.7	6	3	739	107	32	11
HT	YY5165 1.5 m - 1.6 m	<0.05	5.0	0.01	3	40	13	0.6	13	5	290	165	35	18
Calcrete (T)	Min	0.25	0.5	0.01	1	10	1	0.5	1	2	34	8.0	5	1
	P5	0.25	0.5	0.01	1	10	3	0.5	1	2	301	25	18	3
	Median	0.25	5.0	0.01	1	21	7	2.0	4	6	585	246	93	9
	Mean	0.31	6.9	0.01	2	22	8	1.9	5	7	708	724	172	13
	P95	0.25	20.0	0.02	5	47	16	5.0	10	13	987	3218	615	31
	Max	21.16	45.0	0.87	22	112	40	13.0	24	377	100000	11142	1971	711
	n	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402	1402
	Stdev	1	6.8	0.03	2	14	4	1.5	3	11	2706	1180	220	23

Lithology	Element	Ag	As	Ba	Co	Cr	Cu	Mo	Ni	Pb	Sr	U <sub>3</sub> O <sub>8</sub>	V	Zn
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Average crustal abundance (Bowen, 1979)		0.07	1.5	0.05	20	100	50	1.5	80	14	370	2.8	160	75
Summary Statistics taken from BHPBilliton chemical database. SRK sample details given below (grey highlight)														
T	YY5158 3.75 m - 4.75 m	<0.05	0.5	0.01	1	<20	4	1.1	5	1	600	150	75	27
T	YY5158 3.5 m - 3.75 m	<0.05	1.0	0.00	1	<20	7	1.9	5	1	550	55	50	265
Transition calcrete (TCQ)	Min	0.25	0.5	0.01	1	10	1	0.5	1	2	37	6.0	11	1
	P5	0.25	1	0.01	1	10	5	0.5	3	3	90	28	33	6
	Median	0.25	8	0.01	4	38	11	2.0	8	10	568	480	156	17
	Mean	0.27	11	0.02	4	43	12	2.9	9	10	2784	1331	296	20
	P95	0.25	26	0.06	8	92	21	8.0	20	19	11767	5172	951	45
	Max	2.90	119	1.45	109	239	104	23.0	44	43	181600	26682	4698	158
	n	2084	2084	2084	2084	2084	2084	2084	2084	2084	2084	2084	2084	2084
	Stdev	0.1	9.6	0.04	5	25	6	2.4	5	5	11587	2295	393	13
TCQ	YY5162 4.5 m - 4.6 m	<0.05	3.0	0.03	3	45	8	2.1	7	4	75	45	65	14
TCQ	YY5157 3.65 m - 4.1 m	<0.05	3.5	0.01	4	50	19	2.0	14	6	280	140	60	47
TCQ/CQT	YY5159 4.5 m - 5.2 m	<0.05	8.5	0.03	11	80	30	4.5	17	10	50	10	120	85
Carbonated Clay-Quartz (CQT)	Min	0.25	0.5	0.01	1	10	2	0.5	4	2	10	2.0	30	10
	P5	0.25	4.0	0.01	3	50	10	1.0	9	8	48	9	59	17
	Median	0.25	15.0	0.03	5	89	19	4.0	16	15	78	79	141	34
	Mean	0.26	19.7	0.03	5	88	19	4.2	16	15	3147	533	207	34
	P95	0.25	51.0	0.05	8	124	31	9.0	23	25	11870	2786	603	52
	Max	9.25	97.0	0.37	60	1503	106	23.0	40	57	282900	21402	3646	176
	n	6281	6281	6281	6281	6281	6281	6281	6281	6281	6281	6279	6281	6281
	Stdev	0.2	15.4	0.02	2	29	7	2.5	4	5	16057	1229	217	11
CQT	YY5164 5.2 m - 5.3 m	<0.05	4.0	0.03	7	85	22	1.9	14	11	60	20	60	38
TCQ/CQT	YY5159 4.5 m - 5.2 m	<0.05	8.5	0.03	11	80	30	4.5	17	10	80	10	120	85
Clay Quartz (CQ)	Min	0.25	0.5	0.01	1	21	6	0.5	6	2	10	2.0	21	12
	P5	0.25	3.0	0.01	3	51	11	1.0	9	8	45	8.0	57	18
	Median	0.25	8.0	0.03	5	94	20	4.0	16	14	65	21	120	32
	Mean	0.26	12.4	0.03	5	91	20	4.7	16	15	999	126	137	33
	P95	0.25	38.0	0.05	8	128	32	10.0	23	24	846	514	259	48
	Max	4.02	95.0	0.28	81	183	60	24.0	34	69	195400	8870	1794	102
	n	2571	2571	2571	2571	2571	2571	2571	2571	2571	2571	2571	2571	2571
	Stdev	0.1	11.5	0.01	2	24	6	2.7	4	5	8038	458	95	10
CQ	YY5156A 12 m - 12.75 m	<0.05	13.5	0.02	5	80	20	6.5	13	13	50	65	145	125
CQ (poss channel sand)	YY5163 23 m - 23.1 m	<0.05	3.0	0.02	8	100	31	1.5	20	14	1000	15	65	39

## Appendix 4: Bottle Roll Test Results

Leach Extraction #4 YYS158 3.75m - 4.5m	Start	Leach Extraction 4 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	2/04/2010 9 00	3/04/2010 8 30	4/04/2010 10 53	5/04/2010 6 40	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	1 0	2 1	2 9	
Bottle Tare Wt (g)	1633.8				
Solids Mass (g) (wet)	358.9				
Liquor Mass (g)	1076.6			761.35	
Gross Wt (g)	3068.9	3067.9	3062.1	3053.4	
Total Mass	1435.1	1434.1	1428.3	1419.6	
Temp (Deg C)	18.8	18.9	24.8	22.2	
pH	9.09	7.72	7.33	7.27	
ORP (mV Ag/AgCl)	240	218	186	191	192.7
EC (mS/cm)	1.783	2.92	3.11	3.25	
Calcium (µg/L)					126000
Iron (µg/L)					<100
Magnesium (µg/L)					177000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					98800
Silicon (µg/L)					47000
Sodium (µg/L)					447000
Aluminium (µg/L)					28
Antimony (µg/L)					<5
Arsenic (µg/L)					8.6
Barium (µg/L)					57
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					1300
Cadmium (µg/L)					7.4
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					9.1
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					32
Nickel (µg/L)					<5
Selenium (µg/L)					19
Silver (µg/L)					<5
Strontium (µg/L)					2000
Thallium (µg/L)					74
Tin (µg/L)					7.3
Uranium (µg/L)					620
Vanadium (µg/L)					180
Zinc (µg/L)					140
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					1030
Bicarbonate as CaCO3 (mg/L)					1030
Electrical Conductivity (µS/cm)					3600
Ammonia as N (mg N/L)					<1
pH (pH)					8.2
Total Organic Carbon (mg/L)					200
Chloride (mg/L)					470
Bromide (mg/L)					1.7
Fluoride (mg/L)					2
Nitrate (mg/L)					9.9
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					220

Leach Extraction #15 YYS165 1.5m - 1.6m	Start	Leach Extraction 15 (De-ionised water)			
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	27/04/2010 9 00	28/04/2010 9 00	29/04/2010 9 00	30/04/2010 9 00	
CO2 Addition	y	y	y	y	Assay
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1634.5				
Solids Mass (g) (wet)	237.8				
Liquor Mass (g)	713.2				
Gross Wt (g)	2585.5	2583.4	2582.4	2572.2	
Total Mass	951.0	948.9	947.9	937.7	
Temp (Deg C)	21.7	19.5	19.6	22	
pH	9.06	7.57	7.22	7.27	
ORP (mV Ag/AgCl)	173	208	190	238	95
EC (mS/cm)	0.391	1.311	1.665	1.479	
Calcium (µg/L)					84000
Iron (µg/L)					<100
Magnesium (µg/L)					80000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					70000
Silicon (µg/L)					78000
Sodium (µg/L)					190000
Aluminium (µg/L)					<5
Antimony (µg/L)					<5
Arsenic (µg/L)					12
Barium (µg/L)					160
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					670
Cadmium (µg/L)					0.8
Chromium (µg/L)					6
Cobalt (µg/L)					<5
Copper (µg/L)					10
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					9
Nickel (µg/L)					<5
Selenium (µg/L)					<5
Silver (µg/L)					<5
Strontium (µg/L)					930
Thallium (µg/L)					6
Tin (µg/L)					<5
Uranium (µg/L)					350
Vanadium (µg/L)					71
Zinc (µg/L)					98
Mercury (µg/L)					<1
Acidity as CaCO3 (mg/L)					< 20
Total Alkalinity as CaCO3 (mg/L)					720
Bicarbonate as CaCO3 (mg/L)					700
Electrical Conductivity (µS/cm)					1500
Ammonia as N (mg N/L)					< 1
pH (pH)					8.2
Total Organic Carbon (mg/L)					19
Chloride (mg/L)					99
Bromide (mg/L)					< 5
Fluoride (mg/L)					0.7
Nitrate (mg/L)					12
Nitrite (mg/L)					< 0.1
Orthophosphate (mg/L)					< 0.05
Sulphate (mg/L)					18



Leach Extraction #18 YYS166 0.4m - 0.5m	Start	Leach Extraction 18 (De-ionised water)			
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	27/04/2010 9 00	28/04/2010 9 00	29/04/2010 9 00	30/04/2010 9 00	
CO2 Addition	y	y	y	y	Assay
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1632.9				
Solids Mass (g) (wet)	300 2				
Liquor Mass (g)	900 3				
Gross Wt (g)	2833.2	2830.4	2829	2824.9	
Total Mass	1200.3	1197.5	1196.1	1192.0	
Temp (Deg C)	22.5	20.4	19 3	22.1	
pH	8.51	7.19	6.85	6.84	
ORP (mV Ag/AgCl)	165	92	232	255	110
EC (mS/cm)	0 652	1.741	1 076	1.066	
Calcium (µg/L)					9600
Iron (µg/L)					<100
Magnesium (µg/L)					25000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					55000
Silicon (µg/L)					28000
Sodium (µg/L)					190000
Aluminium (µg/L)					<5
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					77
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					700
Cadmium (µg/L)					<0 2
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					<5
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					41
Molybdenum (µg/L)					13
Nickel (µg/L)					<5
Selenium (µg/L)					9
Silver (µg/L)					<5
Strontium (µg/L)					260
Thallium (µg/L)					<5
Tin (µg/L)					6
Uranium (µg/L)					53
Vanadium (µg/L)					7
Zinc (µg/L)					110
Mercury (µg/L)					<1
Acidity as CaCO3 (mg/L)					< 20
Total Alkalinity as CaCO3 (mg/L)					1300
Bicarbonate as CaCO3 (mg/L)					38
Electrical Conductivity (µS/cm)					1200
Ammonia as N (mg N/L)					< 1
pH (pH)					10
Total Organic Carbon (mg/L)					6.2
Chloride (mg/L)					240
Bromide (mg/L)					< 5
Fluoride (mg/L)					< 5
Nitrate (mg/L)					12
Nitrite (mg/L)					< 5
Orthophosphate (mg/L)					< 5
Sulphate (mg/L)					74

Leach Extraction #19 YYS156A 1.5m - 2.5m	Start	Leach Extraction 19 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/03/2010 13 00	31/03/2010 11 30	1/04/2010 12 05	2/04/2010 8 00	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	0 9	2 0	2 8	
Bottle Tare Wt (g)	1630.2				
Solids Mass (g) (wet)	332.4				
Liquor Mass (g)	1002.1			600	
Gross Wt (g)	2963.9	2963.7	2959 2	2938.2	
Total Mass	1333.7	1333.5	1329 0	1308.0	
Temp (Deg C)	22.2	24.5	26 2	19.3	
pH	8.23	7.27	7.27	7 2	
ORP (mV Ag/AgCl)	227	239	200	205	194
EC (mS/cm)	5.85	7.14	7.06	7.01	
Calcium (µg/L)					688000
Iron (µg/L)					<100
Magnesium (µg/L)					189000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					207000
Silicon (µg/L)					37000
Sodium (µg/L)					1110000
Aluminium (µg/L)					35
Antimony (µg/L)					<5
Arsenic (µg/L)					20
Barium (µg/L)					82
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					4300
Cadmium (µg/L)					<5
Chromium (µg/L)					7
Cobalt (µg/L)					<5
Copper (µg/L)					20
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					38
Molybdenum (µg/L)					72
Nickel (µg/L)					8.4
Selenium (µg/L)					23
Silver (µg/L)					<5
Strontium (µg/L)					5400
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					2000
Vanadium (µg/L)					140
Zinc (µg/L)					140
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					486
Bicarbonate as CaCO3 (mg/L)					486
Electrical Conductivity (µS/cm)					8890
Ammonia as N (mg N/L)					<1
pH (pH)					8
Total Organic Carbon (mg/L)					40
Chloride (mg/L)					790
Bromide (mg/L)					1.7
Fluoride (mg/L)					1.5
Nitrate (mg/L)					39
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					2800

Leach Extraction #20 YYS157 3.65m - 4.1m	Start	Leach Extraction 20 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/03/2010 13 05	31/03/2010 11 40	1/04/2010 12 00	2/04/2010 8 05	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	0 9	2 0	2 8	
Bottle Tare Wt (g)	1678.3				
Solids Mass (g) (wet)	321.1				
Liquor Mass (g)	965 8			807.96	
Gross Wt (g)	2964.4	2963.3	2961.4	2949.2	
Total Mass	1286.1	1285.0	1283.1	1270.9	
Temp (Deg C)	22.7	24.5	26.1	19.3	
pH	9.65	7.69	7.47	7.4	
ORP (mV Ag/AgCl)	172	190	178	180	180.9
EC (uS/cm)	434	1498	1675	1945	
Calcium (µg/L)					57900
Iron (µg/L)					<100
Magnesium (µg/L)					55700
Phosphorus (µg/L)					<1000
Potassium (µg/L)					62100
Silicon (µg/L)					46000
Sodium (µg/L)					297000
Aluminium (µg/L)					20
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					23
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					780
Cadmium (µg/L)					<5
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					<5
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					35
Nickel (µg/L)					<5
Selenium (µg/L)					9.6
Silver (µg/L)					<5
Strontium (µg/L)					540
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					87
Vanadium (µg/L)					60
Zinc (µg/L)					120
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					827
Bicarbonate as CaCO3 (mg/L)					827
Electrical Conductivity (µS/cm)					2040
Ammonia as N (mg N/L)					<1
pH (pH)					8.3
Total Organic Carbon (mg/L)					1
Chloride (mg/L)					100
Bromide (mg/L)					<0 5
Fluoride (mg/L)					2.1
Nitrate (mg/L)					0.9
Nitrite (mg/L)					<0 5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					68

Leach Extraction #21 YYS158 3.5m - 3.75m	Start	Leach Extraction 21 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	2/04/2010 10 15	3/04/2010 8 35	4/04/2010 10 56	5/04/2010 7 00	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	0 9	2 0	2 9	
Bottle Tare Wt (g)	1627.3				
Solids Mass (g) (wet)	300 6				
Liquor Mass (g)	901 6			640	
Gross Wt (g)	2829.6	2828.1	2823 5	2817.2	
Total Mass	1202.3	1200.8	1196 2	1189.9	
Temp (Deg C)	20.2	19	24 9	22.3	
pH	8.91	7.52	7.16	7.23	
ORP (mV Ag/AgCl)	235	195	189	179	183.3
EC (mS/cm)	3.54	4.44	3.91	3.94	
Calcium (µg/L)					180000
Iron (µg/L)					<100
Magnesium (µg/L)					237000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					138000
Silicon (µg/L)					44000
Sodium (µg/L)					812000
Aluminium (µg/L)					20
Antimony (µg/L)					<5
Arsenic (µg/L)					6.3
Barium (µg/L)					51
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					2000
Cadmium (µg/L)					7.1
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					12
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					120
Nickel (µg/L)					<5
Selenium (µg/L)					16
Silver (µg/L)					<5
Strontium (µg/L)					2600
Thallium (µg/L)					74
Tin (µg/L)					<5
Uranium (µg/L)					550
Vanadium (µg/L)					110
Zinc (µg/L)					160
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					922
Bicarbonate as CaCO3 (mg/L)					922
Electrical Conductivity (µS/cm)					6420
Ammonia as N (mg N/L)					<1
pH (pH)					8.2
Total Organic Carbon (mg/L)					43
Chloride (mg/L)					1200
Bromide (mg/L)					4
Fluoride (mg/L)					2.5
Nitrate (mg/L)					14
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					460

Leach Extraction #22 YYS156A 12m - 12.75m	Start	Leach Extraction 22 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/03/2010 13 10	31/03/2010 11 50	1/04/2010 11 52	2/04/2010 8 10	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	0 9	1 9	2 8	
Bottle Tare Wt (g)	1630.3				
Solids Mass (g) (wet)	303 2				
Liquor Mass (g)	910 3			646	
Gross Wt (g)	2843.8	2842.2	2837 8	2830.3	
Total Mass	1213.5	1211.9	1207 5	1200.0	
Temp (Deg C)	22.3	24.9	26.1	19.4	
pH	7.73	7.04	6.85	7.27	
ORP (mV Ag/AgCl)	176	200	204	185	186.2
EC (mS/cm)	4.16	3.87	3.62	3.55	
Calcium (µg/L)					70100
Iron (µg/L)					<100
Magnesium (µg/L)					131000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					193000
Silicon (µg/L)					18000
Sodium (µg/L)					1020000
Aluminium (µg/L)					12
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					51
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					4600
Cadmium (µg/L)					<5
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					7.1
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					53
Molybdenum (µg/L)					31
Nickel (µg/L)					<5
Selenium (µg/L)					24
Silver (µg/L)					<5
Strontium (µg/L)					1400
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					34
Vanadium (µg/L)					33
Zinc (µg/L)					170
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					161
Bicarbonate as CaCO3 (mg/L)					161
Electrical Conductivity (µS/cm)					7720
Ammonia as N (mg N/L)					<1
pH (pH)					8.1
Total Organic Carbon (mg/L)					25
Chloride (mg/L)					1500
Bromide (mg/L)					3.6
Fluoride (mg/L)					0.5
Nitrate (mg/L)					51
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					710

Leach Extraction #23 YYS159 4.5m - 5.2m	Start	Leach Extraction 23 (De-ionised water)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/03/2010 13 15	31/03/2010 12 00	1/04/2010 11 45	2/04/2010 8 20	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	0 9	1 9	2 8	
Bottle Tare Wt (g)	1629.3				
Solids Mass (g) (wet)	319.7				
Liquor Mass (g)	959.1			- Not recorded	
Gross Wt (g)	2907.5	2906.7	2903.6	2900.4	
Total Mass	1278.2	1277.4	1274.3	1271.1	
Temp (Deg C)	22.8	24.7	26.4	19.4	
pH	9.25	7.99	7.47	7.49	
ORP (mV Ag/AgCl)	159	181	229	187	235.4
EC (mS/cm)	1.24	2.073	2.39	2.43	
Calcium (µg/L)					51700
Iron (µg/L)					320
Magnesium (µg/L)					47600
Phosphorus (µg/L)					<1000
Potassium (µg/L)					93300
Silicon (µg/L)					36000
Sodium (µg/L)					447000
Aluminium (µg/L)					24
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					9.8
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					1400
Cadmium (µg/L)					<5
Chromium (µg/L)					37
Cobalt (µg/L)					<5
Copper (µg/L)					<5
Lead (µg/L)					<5
Lithium (µg/L)					11
Manganese (µg/L)					5.2
Molybdenum (µg/L)					66
Nickel (µg/L)					<5
Selenium (µg/L)					<5
Silver (µg/L)					<5
Strontium (µg/L)					470
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					33
Vanadium (µg/L)					73
Zinc (µg/L)					140
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					827
Bicarbonate as CaCO3 (mg/L)					827
Electrical Conductivity (µS/cm)					2650
Ammonia as N (mg N/L)					<1
pH (pH)					8.4
Total Organic Carbon (mg/L)					35
Chloride (mg/L)					260
Bromide (mg/L)					0.8
Fluoride (mg/L)					2.9
Nitrate (mg/L)					3.4
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					92

BARREN LIQUOR - for bottle rolls	BARREN LIQUOR
	<b>Assay</b>
Elapsed Time (days)	
Bottle Tare Wt (g)	
Solids Mass (g) (wet)	
Liquor Mass (Barren)g	
Gross Wt (g)	
Total Mass	
ORP (mV)	140.1
Calcium (µg/L)	500
Iron (µg/L)	450
Magnesium (µg/L)	350
Phosphorus (µg/L)	<1000
Potassium (µg/L)	1590000
Silicon (µg/L)	13000
Sodium (µg/L)	44800000
Aluminium (µg/L)	780
Antimony (µg/L)	<5
Arsenic (µg/L)	7900
Barium (µg/L)	10
Beryllium (µg/L)	<5
Bismuth (µg/L)	<5
Boron (µg/L)	30000
Cadmium (µg/L)	<5
Chromium (µg/L)	350
Cobalt (µg/L)	<5
Copper (µg/L)	80
Lead (µg/L)	<5
Lithium (µg/L)	6
Manganese (µg/L)	<5
Molybdenum (µg/L)	2400
Nickel (µg/L)	<5
Selenium (µg/L)	490
Silver (µg/L)	<5
Strontium (µg/L)	60
Thallium (µg/L)	<5
Tin (µg/L)	10
Uranium (µg/L)	100000
Vanadium (µg/L)	35000
Zinc (µg/L)	130
Mercury (µg/L)	<0.1
Acidity as CaCO <sub>3</sub> (mg/L)	<20
Total Alkalinity as CaCO <sub>3</sub> (mg/L)	75300
Bicarbonate as CaCO <sub>3</sub> (mg/L)	<10
Electrical Conductivity (µS/cm)	85600
Ammonia as N (mg N/L)	1.4
pH (pH)	10.9
Total Organic Carbon (mg/L)	1000
Chloride (mg/L)	15000
Bromide (mg/L)	43
Fluoride (mg/L)	<0.5
Nitrate (mg/L)	610
Nitrite (mg/L)	<0.5
Orthophosphate (mg/L)	<0.5
Sulphate (mg/L)	8800

Leach Extraction #24 YYS156 0.7m - 1.5m	Start	Leach Extraction 24 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	22/03/2010 12 14	23/03/2010 12 17	24/03/2010 12 20	25/03/2010 12 21	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1627.5				
Solids Mass (g) (wet)	309				
Liquor Mass (g)	927 9			755.31	
Gross Wt (g)	2863.3	2862.3	2858	2854.5	
Total Mass	1235.8	1234.8	1230 5	1227.0	
Temp (Deg C)	22.8	24.9	25.4	27.3	
pH	10.5	10.27	10.3	10.22	
ORP (mV Ag/AgCl)	202	144	163	153	121.1
EC (mS/cm)	80.4	82.6	74 8	77.6	
Calcium (µg/L)					5760
Iron (µg/L)					<100
Magnesium (µg/L)					2440
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1660000
Silicon (µg/L)					12000
Sodium (µg/L)					42200000
Aluminium (µg/L)					88
Antimony (µg/L)					<5
Arsenic (µg/L)					2300
Barium (µg/L)					98
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					33000
Cadmium (µg/L)					31
Chromium (µg/L)					150
Cobalt (µg/L)					<5
Copper (µg/L)					140
Lead (µg/L)					11
Lithium (µg/L)					<5
Manganese (µg/L)					15
Molybdenum (µg/L)					1600
Nickel (µg/L)					32
Selenium (µg/L)					310
Silver (µg/L)					<5
Strontium (µg/L)					400
Thallium (µg/L)					160
Tin (µg/L)					8.1
Uranium (µg/L)					77000
Vanadium (µg/L)					20000
Zinc (µg/L)					170
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					23200
Bicarbonate as CaCO3 (mg/L)					2180
Electrical Conductivity (µS/cm)					87900
Ammonia as N (mg N/L)					<1
pH (pH)					10 2
Total Organic Carbon (mg/L)					95
Chloride (mg/L)					16000
Bromide (mg/L)					46
Fluoride (mg/L)					<0 5
Nitrate (mg/L)					650
Nitrite (mg/L)					<0 5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					54000



Leach Extraction #25 YYS156A 0.7m - 1.5m	Start	Leach Extraction 25 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	22/03/2010 13 45	23/03/2010 13 54	24/03/2010 13 55	25/03/2010 13 46	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1629.9				
Solids Mass (g) (wet)	321				
Liquor Mass (g)	963.2			791	
Gross Wt (g)	2913.8	2909.4	2907.1	2903.3	
Total Mass	1283.9	1279.5	1277.2	1273.4	
Temp (Deg C)	22.6	27	26.8	27.5	
pH	10.55	10.21	10.27	10.21	
ORP (mV Ag/AgCl)	140	120	141	110	117.5
EC (mS/cm)	87.3	82	78	80.2	
Calcium (µg/L)					3490
Iron (µg/L)					<100
Magnesium (µg/L)					3000
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1820000
Silicon (µg/L)					6610
Sodium (µg/L)					41200000
Aluminium (µg/L)					5.1
Antimony (µg/L)					<5
Arsenic (µg/L)					4200
Barium (µg/L)					20
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					36000
Cadmium (µg/L)					<5
Chromium (µg/L)					230
Cobalt (µg/L)					<5
Copper (µg/L)					110
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					5.4
Molybdenum (µg/L)					2500
Nickel (µg/L)					12
Selenium (µg/L)					420
Silver (µg/L)					<5
Strontium (µg/L)					67
Thallium (µg/L)					86
Tin (µg/L)					<5
Uranium (µg/L)					86000
Vanadium (µg/L)					18000
Zinc (µg/L)					130
Mercury (µg/L)					<0.1
Acidity as CaCO <sub>3</sub> (mg/L)					<20
Total Alkalinity as CaCO <sub>3</sub> (mg/L)					24100
Bicarbonate as CaCO <sub>3</sub> (mg/L)					2240
Electrical Conductivity (µS/cm)					88200
Ammonia as N (mg N/L)					<1
pH (pH)					10.2
Total Organic Carbon (mg/L)					54
Chloride (mg/L)					15000
Bromide (mg/L)					46
Fluoride (mg/L)					<0.5
Nitrate (mg/L)					640
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					49000

Leach Extraction #26 YYS164 4.3m - 4.4m	Start	Leach Extraction 26 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	16/04/2010 11 45	17/04/2010 11 45	18/04/2010 11 45	19/04/2010 11 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1627.9				
Solids Mass (g) (wet)	302.1				
Liquor Mass (g)	908.1				
Gross Wt (g)	2837.9	2805.7	2800.8	2792.2	
Total Mass	1210.0	1177.8	1172.9	1164.3	
Temp (Deg C)	22.6	26	24.8	20.9	
pH	10.76	10.57	10.63	10.68	
ORP (mV Ag/AgCl)	201	170	158	161	102
EC (mS/cm)	88.8	82.6	84.2	84.4	
Calcium (µg/L)					4260
Iron (µg/L)					130
Magnesium (µg/L)					1520
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1900000
Silicon (µg/L)					62000
Sodium (µg/L)					44000000
Aluminium (µg/L)					19
Antimony (µg/L)					<5
Arsenic (µg/L)					6200
Barium (µg/L)					140
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					27000
Cadmium (µg/L)					<5
Chromium (µg/L)					320
Cobalt (µg/L)					<5
Copper (µg/L)					61
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2000
Nickel (µg/L)					<5
Selenium (µg/L)					420
Silver (µg/L)					<5
Strontium (µg/L)					290
Thallium (µg/L)					66
Tin (µg/L)					27
Uranium (µg/L)					77000
Vanadium (µg/L)					27000
Zinc (µg/L)					570
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					70300
Bicarbonate as CaCO3 (mg/L)					1230
Electrical Conductivity (µS/cm)					71800
Ammonia as N (mg N/L)					<1
pH (pH)					10.5
Total Organic Carbon (mg/L)					23
Chloride (mg/L)					14000
Bromide (mg/L)					35
Fluoride (mg/L)					1.6
Nitrate (mg/L)					570
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					7700

Leach Extraction #27 YYS163 23m - 23.1m	Start	Leach Extraction 27 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	16/04/2010 13 45	17/04/2010 13 45	18/04/2010 13 45	19/04/2010 13 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1630.1				
Solids Mass (g) (wet)	282.6				
Liquor Mass (g)	849				
Gross Wt (g)	2761.7	2760.4	2758.8	2753.3	
Total Mass	1131.6	1130.3	1128.7	1123.2	
Temp (Deg C)	22.5	26.1	25.1	21	
pH	10.86	10.71	10.75	10.81	
ORP (mV Ag/AgCl)	160	144	177	135	89
EC (mS/cm)	93.1	67	75	59.9	
Calcium (µg/L)					2660
Iron (µg/L)					<100
Magnesium (µg/L)					35400
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1820000
Silicon (µg/L)					3320
Sodium (µg/L)					44000000
Aluminium (µg/L)					37
Antimony (µg/L)					<5
Arsenic (µg/L)					4700
Barium (µg/L)					47
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					29000
Cadmium (µg/L)					<5
Chromium (µg/L)					350
Cobalt (µg/L)					<5
Copper (µg/L)					41
Lead (µg/L)					6.7
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2100
Nickel (µg/L)					<5
Selenium (µg/L)					440
Silver (µg/L)					<5
Strontium (µg/L)					510
Thallium (µg/L)					<5
Tin (µg/L)					5.5
Uranium (µg/L)					34000
Vanadium (µg/L)					15000
Zinc (µg/L)					410
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					67600
Bicarbonate as CaCO3 (mg/L)					914
Electrical Conductivity (µS/cm)					73200
Ammonia as N (mg N/L)					<1
pH (pH)					10.6
Total Organic Carbon (mg/L)					18
Chloride (mg/L)					16000
Bromide (mg/L)					39
Fluoride (mg/L)					2
Nitrate (mg/L)					640
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					10000

Leach Extraction #28 YYS164 5.2m - 5.3m	Start	Leach Extraction 28 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	16/04/2010 13 45	17/04/2010 13 45	18/04/2010 13 45	19/04/2010 13 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1634.0				
Solids Mass (g) (wet)	300.6				
Liquor Mass (g)	901.1				
Gross Wt (g)	2835.5	2834.4	2828.8	2819.3	
Total Mass	1201.5	1200.4	1194.8	1185.3	
Temp (Deg C)	22.4	21.1	21.7	21.9	
pH	10.81	10.79	10.75	10.72	
ORP (mV Ag/AgCl)	135	214	125	132	116
EC (mS/cm)	92	81	80	80.1	
Calcium (µg/L)					4160
Iron (µg/L)					<100
Magnesium (µg/L)					1400
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1800000
Silicon (µg/L)					76000
Sodium (µg/L)					43900000
Aluminium (µg/L)					<5
Antimony (µg/L)					<5
Arsenic (µg/L)					6700
Barium (µg/L)					8.8
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					25000
Cadmium (µg/L)					<5
Chromium (µg/L)					360
Cobalt (µg/L)					<5
Copper (µg/L)					59
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2000
Nickel (µg/L)					<5
Selenium (µg/L)					410
Silver (µg/L)					<5
Strontium (µg/L)					34
Thallium (µg/L)					<5
Tin (µg/L)					6.9
Uranium (µg/L)					40000
Vanadium (µg/L)					27000
Zinc (µg/L)					560
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					70000
Bicarbonate as CaCO3 (mg/L)					1730
Electrical Conductivity (µS/cm)					70400
Ammonia as N (mg N/L)					<1
pH (pH)					10.5
Total Organic Carbon (mg/L)					24
Chloride (mg/L)					11000
Bromide (mg/L)					32
Fluoride (mg/L)					2.3
Nitrate (mg/L)					490
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					7000

Leach Extraction #29 YYS165 6.6m - 6.7m	Start	Leach Extraction 29 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	23/04/2010 13 45	24/04/2010 13 45	25/04/2010 13 45	26/04/2010 13 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1630.3				
Solids Mass (g) (wet)	301.7				
Liquor Mass (g)	905 2				
Gross Wt (g)	2837.2	2835.5	2835	2805	
Total Mass	1206.9	1205.2	1204.7	1174.7	
Temp (Deg C)	23.8	23.8	21.4	22.3	
pH	10.95	10.73	10.75	10.77	
ORP (mV Ag/AgCl)	98	161	143	105	17
EC (mS/cm)	93.9	82.1	81.1	83.2	
Calcium (µg/L)					4100
Iron (µg/L)					200
Magnesium (µg/L)					2300
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1400000
Silicon (µg/L)					64000000
Sodium (µg/L)					44000000
Aluminium (µg/L)					50
Antimony (µg/L)					8
Arsenic (µg/L)					7700
Barium (µg/L)					240
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					34000
Cadmium (µg/L)					1
Chromium (µg/L)					3300
Cobalt (µg/L)					<5
Copper (µg/L)					51
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2500
Nickel (µg/L)					<5
Selenium (µg/L)					510
Silver (µg/L)					<5
Strontium (µg/L)					600
Thallium (µg/L)					<5
Tin (µg/L)					20
Uranium (µg/L)					110000
Vanadium (µg/L)					37000
Zinc (µg/L)					560
Mercury (µg/L)					1
Acidity as CaCO3 (mg/L)					< 20
Total Alkalinity as CaCO3 (mg/L)					71000
Bicarbonate as CaCO3 (mg/L)					3200
Electrical Conductivity (µS/cm)					73000
Ammonia as N (mg N/L)					1
pH (pH)					11
Total Organic Carbon (mg/L)					740
Chloride (mg/L)					14000
Bromide (mg/L)					37
Fluoride (mg/L)					6.6
Nitrate (mg/L)					610
Nitrite (mg/L)					< 5
Orthophosphate (mg/L)					< 5
Sulphate (mg/L)					2500

Leach Extraction #30 YYS167 2.3m - 2.4m	Start	Leach Extraction 30 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	16/04/2010 13 45	17/04/2010 13 45	18/04/2010 13 45	19/04/2010 13 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1633.6				
Solids Mass (g) (wet)	296.3				
Liquor Mass (g)	888.1				
Gross Wt (g)	2818.1	2818	2815.3	2812	
Total Mass	1184.5	1184.4	1181.7	1178.4	
Temp (Deg C)	22.5	21.1	21.8	21.9	
pH	10.91	10.82	10.79	10.74	
ORP (mV Ag/AgCl)	142	205	156	203	136
EC (mS/cm)	95	81.6	80.3	79.3	
Calcium (µg/L)					3730
Iron (µg/L)					<100
Magnesium (µg/L)					1830
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1890000
Silicon (µg/L)					44000
Sodium (µg/L)					42200000
Aluminium (µg/L)					7.8
Antimony (µg/L)					<5
Arsenic (µg/L)					6700
Barium (µg/L)					210
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					28000
Cadmium (µg/L)					<5
Chromium (µg/L)					350
Cobalt (µg/L)					<5
Copper (µg/L)					59
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					1900
Nickel (µg/L)					<5
Selenium (µg/L)					410
Silver (µg/L)					<5
Strontium (µg/L)					270
Thallium (µg/L)					<5
Tin (µg/L)					5.5
Uranium (µg/L)					44000
Vanadium (µg/L)					28000
Zinc (µg/L)					570
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					72100
Bicarbonate as CaCO3 (mg/L)					1820
Electrical Conductivity (µS/cm)					71500
Ammonia as N (mg N/L)					<1
pH (pH)					10.6
Total Organic Carbon (mg/L)					24
Chloride (mg/L)					16000
Bromide (mg/L)					34
Fluoride (mg/L)					2.2
Nitrate (mg/L)					600
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					9400

Leach Extraction #31 YYS167 23m - 23.1m	Start	Leach Extraction 31 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	27/04/2010 13 45	28/04/2010 13 45	29/04/2010 13 45	30/04/2010 13 45	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1630.5				
Solids Mass (g) (wet)	300 9				
Liquor Mass (g)	902 5				
Gross Wt (g)	2833.7	2827.8	2827.7	2823.6	
Total Mass	1203.2	1197.3	1197 2	1193.1	
Temp (Deg C)	19.7	20.2	19.4	17.4	
pH	11 01	10 91	10 86	10 95	
ORP (mV Ag/AgCl)	65	65	205	229	20
EC (mS/cm)	93.2	76.5	83 2	79	
Calcium (µg/L)					3900
Iron (µg/L)					300
Magnesium (µg/L)					6600
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1400000
Silicon (µg/L)					17000
Sodium (µg/L)					44000000
Aluminium (µg/L)					<50
Antimony (µg/L)					<5
Arsenic (µg/L)					7100
Barium (µg/L)					200
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					30000
Cadmium (µg/L)					1.1
Chromium (µg/L)					3.4
Cobalt (µg/L)					<5
Copper (µg/L)					59
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2500
Nickel (µg/L)					5
Selenium (µg/L)					520
Silver (µg/L)					<5
Strontium (µg/L)					800
Thallium (µg/L)					<5
Tin (µg/L)					5
Uranium (µg/L)					74000
Vanadium (µg/L)					26000
Zinc (µg/L)					470
Mercury (µg/L)					<1
Acidity as CaCO3 (mg/L)					< 20
Total Alkalinity as CaCO3 (mg/L)					70000
Bicarbonate as CaCO3 (mg/L)					2100
Electrical Conductivity (µS/cm)					75000
Ammonia as N (mg N/L)					< 1
pH (pH)					11
Total Organic Carbon (mg/L)					100
Chloride (mg/L)					15000
Bromide (mg/L)					30
Fluoride (mg/L)					5.8
Nitrate (mg/L)					620
Nitrite (mg/L)					< 5
Orthophosphate (mg/L)					< 5
Sulphate (mg/L)					2600

Leach Extraction #33 YYS164 26.2m - 26.3m	Start	Leach Extraction 33 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	23/04/2010 11 30	24/04/2010 11 30	25/04/2010 11 30	26/04/2010 11 30	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1636.3				
Solids Mass (g) (wet)	300.4				
Liquor Mass (g)	902 2				
Gross Wt (g)	2837.3	2836.2	2836.1	2834.5	
Total Mass	1201.0	1199.9	1199 8	1198.2	
Temp (Deg C)	24.1	23.9	21.4	22.6	
pH	11.02	10.88	10.87	10.92	
ORP (mV Ag/AgCl)	189	172	164	172	29
EC (mS/cm)	94.4	81.4	80 9	84.9	
Calcium (µg/L)					3800
Iron (µg/L)					200
Magnesium (µg/L)					9200
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1600000
Silicon (µg/L)					11000
Sodium (µg/L)					53000000
Aluminium (µg/L)					120
Antimony (µg/L)					<5
Arsenic (µg/L)					7800
Barium (µg/L)					46
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					38000
Cadmium (µg/L)					1.1
Chromium (µg/L)					3500
Cobalt (µg/L)					<5
Copper (µg/L)					86
Lead (µg/L)					5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					3100
Nickel (µg/L)					<5
Selenium (µg/L)					560
Silver (µg/L)					<5
Strontium (µg/L)					640
Thallium (µg/L)					10
Tin (µg/L)					<5
Uranium (µg/L)					110000
Vanadium (µg/L)					39000
Zinc (µg/L)					530
Mercury (µg/L)					1
Acidity as CaCO3 (mg/L)					< 20
Total Alkalinity as CaCO3 (mg/L)					74000
Bicarbonate as CaCO3 (mg/L)					2300
Electrical Conductivity (µS/cm)					76000
Ammonia as N (mg N/L)					1.1
pH (pH)					11
Total Organic Carbon (mg/L)					78
Chloride (mg/L)					5100
Bromide (mg/L)					35
Fluoride (mg/L)					6.6
Nitrate (mg/L)					640
Nitrite (mg/L)					< 5
Orthophosphate (mg/L)					< 5
Sulphate (mg/L)					810



Leach Extraction #34 YYS156A 0.7m - 1.5m	Start	Leach Extraction 34 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	2/04/2010 11 30	3/04/2010 8 45	4/04/2010 11 00	5/04/2010 7 10	
CO2	y	y	y	y	
Elapsed Time (days)	0 0	0 9	2 0	2 8	
Bottle Tare Wt (g)	1630.0				
Solids Mass (g) (wet)	310.7				
Liquor Mass (g)	934 8			726	
Gross Wt (g)	2875.3	2872.2	2870.7	2868.7	
Total Mass	1245.3	1242.2	1240.7	1238.7	
Temp (Deg C)	21.7	19	24 9	22.3	
pH	10 55	10.15	9.83	9.7	
ORP (mV Ag/AgCl)	1.36	153	160	196	147.3
EC (mS/cm)	70.1	74.7	73	77.6	
Calcium (µg/L)					6060
Iron (µg/L)					<100
Magnesium (µg/L)					12300
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1670000
Silicon (µg/L)					6220
Sodium (µg/L)					39700000
Aluminium (µg/L)					34
Antimony (µg/L)					<5
Arsenic (µg/L)					2100
Barium (µg/L)					26
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					30000
Cadmium (µg/L)					7.9
Chromium (µg/L)					100
Cobalt (µg/L)					<5
Copper (µg/L)					110
Lead (µg/L)					7.3
Lithium (µg/L)					<5
Manganese (µg/L)					7.5
Molybdenum (µg/L)					1600
Nickel (µg/L)					7.2
Selenium (µg/L)					310
Silver (µg/L)					5.4
Strontium (µg/L)					36
Thallium (µg/L)					55
Tin (µg/L)					16
Uranium (µg/L)					74000
Vanadium (µg/L)					16000
Zinc (µg/L)					280
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					25000
Bicarbonate as CaCO3 (mg/L)					7240
Electrical Conductivity (µS/cm)					86700
Ammonia as N (mg N/L)					1.2
pH (pH)					9.6
Total Organic Carbon (mg/L)					2900
Chloride (mg/L)					15000
Bromide (mg/L)					52
Fluoride (mg/L)					<0 5
Nitrate (mg/L)					670
Nitrite (mg/L)					<0 5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					47000

Leach Extraction #35 YYS163 23.0m - 23.1m	Leach Extraction 35 (Barren liquor)					Assay
	Start inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	96hr bottle roll reading	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	4/05/2010 11 30	
CO2	y	n	n	y	y	
Elapsed Time (days)	0.0	1.0	2.0	3.0	4.0	
Bottle Tare Wt (g)	1628.1					
Solids Mass (g) (wet)	282.1					
Liquor Mass (g)	846.1					
Gross Wt (g)	2756	2754.9	2750.5	2750	2746	
Total Mass	1127.9	1126.8	1122.4	1121.9	1117.9	
Temp (Deg C)	20.2	25	23.1	24	18.5	
pH	10.94	10.62	10.66	10.62	10.51	
ORP (mV Ag/AgCl)	151	138	190	113	145	35
EC (mS/cm)	91.3	50.2	65.1	50.4	39.7	
Calcium (µg/L)						100
Iron (µg/L)						<100
Magnesium (µg/L)						88000
Phosphorus (µg/L)						<1000
Potassium (µg/L)						1700000
Silicon (µg/L)						7500
Sodium (µg/L)						44000000
Aluminium (µg/L)						<5
Antimony (µg/L)						<5
Arsenic (µg/L)						5300
Barium (µg/L)						78
Beryllium (µg/L)						<5
Bismuth (µg/L)						<5
Boron (µg/L)						28000
Cadmium (µg/L)						7
Chromium (µg/L)						71
Cobalt (µg/L)						<5
Copper (µg/L)						93
Lead (µg/L)						8
Lithium (µg/L)						<5
Manganese (µg/L)						<5
Molybdenum (µg/L)						2400
Nickel (µg/L)						<5
Selenium (µg/L)						550
Silver (µg/L)						<5
Strontium (µg/L)						660
Thallium (µg/L)						180
Tin (µg/L)						13
Uranium (µg/L)						85000
Vanadium (µg/L)						16000
Zinc (µg/L)						420
Mercury (µg/L)						<1
Acidity as CaCO3 (mg/L)						< 20
Total Alkalinity as CaCO3 (mg/L)						79000
Bicarbonate as CaCO3 (mg/L)						190
Electrical Conductivity (µS/cm)						77000
Ammonia as N (mg N/L)						< 1
pH (pH)						8.3
Total Organic Carbon (mg/L)						16
Chloride (mg/L)						23000
Bromide (mg/L)						46
Fluoride (mg/L)						< 5
Nitrate (mg/L)						740
Nitrite (mg/L)						< 5
Orthophosphate (mg/L)						< 5
Sulphate (mg/L)						12000

Leach Extraction #36 YYS164 5.2m-5.3m	Leach Extraction 36 (Barren liquor)					Assay
	Start inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	96hr bottle roll reading	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	4/05/2010 11 30	
CO2	y	n	n	y	y	
Elapsed Time (days)	0 0	1 0	2 0	3 0	4 0	
Bottle Tare Wt (g)	1630.1					
Solids Mass (g) (wet)	300.9					
Liquor Mass (g)	902.7					
Gross Wt (g)	2833.4	2831.3	2829.2	2826.7	2820.7	
Total Mass	1203.3	1201.2	1199.1	1196.6	1190.6	
Temp (Deg C)	20.1	25.1	22.8	24.6	19.2	
pH	10.89	10.54	10.63	10.52	10.46	
ORP (mV Ag/AgCl)	123	159	198	139	138	39
EC (mS/cm)	90.3	77.8	79.3	77.9	78.4	
Calcium (µg/L)						3300
Iron (µg/L)						<100
Magnesium (µg/L)						2400
Phosphorus (µg/L)						<1000
Potassium (µg/L)						1900000
Silicon (µg/L)						61000
Sodium (µg/L)						43000000
Aluminium (µg/L)						<5
Antimony (µg/L)						<5
Arsenic (µg/L)						7300
Barium (µg/L)						48
Beryllium (µg/L)						<5
Bismuth (µg/L)						<5
Boron (µg/L)						23000
Cadmium (µg/L)						<0.2
Chromium (µg/L)						75
Cobalt (µg/L)						<5
Copper (µg/L)						66
Lead (µg/L)						<5
Lithium (µg/L)						<5
Manganese (µg/L)						<5
Molybdenum (µg/L)						2300
Nickel (µg/L)						<5
Selenium (µg/L)						500
Silver (µg/L)						<5
Strontium (µg/L)						510
Thallium (µg/L)						<5
Tin (µg/L)						9
Uranium (µg/L)						74000
Vanadium (µg/L)						24000
Zinc (µg/L)						660
Mercury (µg/L)						<1
Acidity as CaCO3 (mg/L)						< 20
Total Alkalinity as CaCO3 (mg/L)						79000
Bicarbonate as CaCO3 (mg/L)						220
Electrical Conductivity (µS/cm)						74000
Ammonia as N (mg N/L)						< 1
pH (pH)						8.5
Total Organic Carbon (mg/L)						18
Chloride (mg/L)						20000
Bromide (mg/L)						36
Fluoride (mg/L)						< 5
Nitrate (mg/L)						700
Nitrite (mg/L)						< 5
Orthophosphate (mg/L)						< 5
Sulphate (mg/L)						8200

Leach Extraction #37 YYS165 6.6m - 6.7m	Leach Extraction 37 (Barren liquor)					Assay
	Start inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	96hr bottle roll reading	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	4/05/2010 11 30	
CO2	y	n	n	y	y	
Elapsed Time (days)	0.0	1.0	2.0	3.0	4.0	
Bottle Tare Wt (g)	1632.4					
Solids Mass (g) (wet)	301.8					
Liquor Mass (g)	907.1					
Gross Wt (g)	2840.3	2840	2837.6	2835.3	2833.2	
Total Mass	1207.9	1207.6	1205.2	1202.9	1200.8	
Temp (Deg C)	19.7	25.1	23.2	23.9	19.7	
pH	11.08	10.57	10.65	10.6	10.52	
ORP (mV Ag/AgCl)	92	117	200	187	148	48
EC (mS/cm)	89.7	85	82.8	79	81.8	
Calcium (µg/L)						3200
Iron (µg/L)						200
Magnesium (µg/L)						3500
Phosphorus (µg/L)						<1000
Potassium (µg/L)						1900000
Silicon (µg/L)						55000
Sodium (µg/L)						45000000
Aluminium (µg/L)						<5
Antimony (µg/L)						<5
Arsenic (µg/L)						7500
Barium (µg/L)						270
Beryllium (µg/L)						<5
Bismuth (µg/L)						<5
Boron (µg/L)						26000
Cadmium (µg/L)						<0.2
Chromium (µg/L)						77
Cobalt (µg/L)						<5
Copper (µg/L)						120
Lead (µg/L)						<5
Lithium (µg/L)						<5
Manganese (µg/L)						<5
Molybdenum (µg/L)						2600
Nickel (µg/L)						<5
Selenium (µg/L)						530
Silver (µg/L)						<5
Strontium (µg/L)						1000
Thallium (µg/L)						8
Tin (µg/L)						12
Uranium (µg/L)						91000
Vanadium (µg/L)						27000
Zinc (µg/L)						680
Mercury (µg/L)						<1
Acidity as CaCO3 (mg/L)						< 20
Total Alkalinity as CaCO3 (mg/L)						81000
Bicarbonate as CaCO3 (mg/L)						210
Electrical Conductivity (µS/cm)						76000
Ammonia as N (mg N/L)						< 1
pH (pH)						10
Total Organic Carbon (mg/L)						24
Chloride (mg/L)						23000
Bromide (mg/L)						39
Fluoride (mg/L)						6
Nitrate (mg/L)						730
Nitrite (mg/L)						< 5
Orthophosphate (mg/L)						< 5
Sulphate (mg/L)						9600

Leach Extraction #38 YYS167 2.3m - 2.4m	Start	Leach Extraction 38 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	
CO2	y	Y	y	y	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1630.2				
Solids Mass (g) (wet)	291.4				
Liquor Mass (g)	874.4				
Gross Wt (g)	2794.4	2794.3	2793.4	2792.1	
Total Mass	1164.2	1164.1	1163.2	1161.9	
Temp (Deg C)	20.6	19.2	16.8	19.3	
pH	10.89	10.72	10.53	10.16	
ORP (mV Ag/AgCl)	201	146	231	203	120
EC (mS/cm)	78.4	78.2	64.9	83.7	
Calcium (µg/L)					2200
Iron (µg/L)					<50
Magnesium (µg/L)					11000
Phosphorus (µg/L)					<100
Potassium (µg/L)					1500000
Silicon (µg/L)					55000
Sodium (µg/L)					43000000
Aluminium (µg/L)					<50
Antimony (µg/L)					<5
Arsenic (µg/L)					2300
Barium (µg/L)					550
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					25000
Cadmium (µg/L)					5.8
Chromium (µg/L)					85
Cobalt (µg/L)					<5
Copper (µg/L)					30
Lead (µg/L)					4
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2000
Nickel (µg/L)					24
Selenium (µg/L)					95
Silver (µg/L)					<5
Strontium (µg/L)					1200
Thallium (µg/L)					40
Tin (µg/L)					<5
Uranium (µg/L)					82000
Vanadium (µg/L)					29000
Zinc (µg/L)					90
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					0.1
Total Alkalinity as CaCO3 (mg/L)					75000
Bicarbonate as CaCO3 (mg/L)					5300
Electrical Conductivity (µS/cm)					238000
Ammonia as N (mg N/L)					1
pH (pH)					10
Total Organic Carbon (mg/L)					2400
Chloride (mg/L)					19000
Bromide (mg/L)					92
Fluoride (mg/L)					17
Nitrate (mg/L)					150
Nitrite (mg/L)					0.59
Orthophosphate (mg/L)					3.4
Sulphate (mg/L)					3600

Leach Extraction #39 YYS167 23m - 23.1m	Start	Leach Extraction 39 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	
CO2	y	Y	y	y	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1630.0				
Solids Mass (g) (wet)	301 2				
Liquor Mass (g)	905				
Gross Wt (g)	2833.6	2833.6	2832 3	2829.5	
Total Mass	1203.6	1203.6	1202 3	1199.5	
Temp (Deg C)	20.5	19.2	16 6	15.3	
pH	11 07	10 82	10 63	10 52	
ORP (mV Ag/AgCl)	57	109	215	210	110
EC (mS/cm)	82.7	75.5	83 5	83.5	
Calcium (µg/L)					2500
Iron (µg/L)					150
Magnesium (µg/L)					37000
Phosphorus (µg/L)					<100
Potassium (µg/L)					1400000
Silicon (µg/L)					24000
Sodium (µg/L)					41000000
Aluminium (µg/L)					70
Antimony (µg/L)					<5
Arsenic (µg/L)					1200
Barium (µg/L)					430
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					26000
Cadmium (µg/L)					13
Chromium (µg/L)					78
Cobalt (µg/L)					<1
Copper (µg/L)					21
Lead (µg/L)					17
Lithium (µg/L)					8
Manganese (µg/L)					<5
Molybdenum (µg/L)					2100
Nickel (µg/L)					34
Selenium (µg/L)					77
Silver (µg/L)					<5
Strontium (µg/L)					1500
Thallium (µg/L)					64
Tin (µg/L)					<5
Uranium (µg/L)					78000
Vanadium (µg/L)					25000
Zinc (µg/L)					190
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					< 0.1
Total Alkalinity as CaCO3 (mg/L)					72000
Bicarbonate as CaCO3 (mg/L)					4500
Electrical Conductivity (µS/cm)					258000
Ammonia as N (mg N/L)					1.9
pH (pH)					10
Total Organic Carbon (mg/L)					2300
Chloride (mg/L)					18000
Bromide (mg/L)					87
Fluoride (mg/L)					25
Nitrate (mg/L)					140
Nitrite (mg/L)					0.52
Orthophosphate (mg/L)					0.53
Sulphate (mg/L)					3400

Leach Extraction #40 YYS164 26.2m - 26.3m	Start	Leach Extraction 40 (Barren liquor)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	30/04/2010 11 30	1/05/2010 11 30	2/05/2010 11 30	3/05/2010 11 30	
CO2	y	Y	y	y	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1628.9				
Solids Mass (g) (wet)	300 3				
Liquor Mass (g)	900 3				
Gross Wt (g)	2828.9	2826.4	2826 3	2823	
Total Mass	1200.0	1197.5	1197.4	1194.1	
Temp (Deg C)	21.2	19.4	16 5	15.1	
pH	11 08	10.76	10 6	10.49	
ORP (mV Ag/AgCl)	276	163	263	132	100
EC (mS/cm)	93.4	76.2	85 2	84.5	
Calcium (µg/L)					2800
Iron (µg/L)					220
Magnesium (µg/L)					64000
Phosphorus (µg/L)					<100
Potassium (µg/L)					1300000
Silicon (µg/L)					16000
Sodium (µg/L)					41000000
Aluminium (µg/L)					150
Antimony (µg/L)					<5
Arsenic (µg/L)					1100
Barium (µg/L)					110
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					28000
Cadmium (µg/L)					<5
Chromium (µg/L)					78
Cobalt (µg/L)					<1
Copper (µg/L)					26
Lead (µg/L)					45
Lithium (µg/L)					15
Manganese (µg/L)					<5
Molybdenum (µg/L)					2500
Nickel (µg/L)					17
Selenium (µg/L)					73
Silver (µg/L)					<5
Strontium (µg/L)					1900
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					16000
Vanadium (µg/L)					29000
Zinc (µg/L)					90
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					< 0.1
Total Alkalinity as CaCO3 (mg/L)					72000
Bicarbonate as CaCO3 (mg/L)					2900
Electrical Conductivity (µS/cm)					227000
Ammonia as N (mg N/L)					1.2
pH (pH)					10
Total Organic Carbon (mg/L)					1300
Chloride (mg/L)					18000
Bromide (mg/L)					90
Fluoride (mg/L)					27
Nitrate (mg/L)					140
Nitrite (mg/L)					0.63
Orthophosphate (mg/L)					0.38
Sulphate (mg/L)					3400

CONTROL #41 DI water - Air	Start	CONTROL 41 (No Solid - DI water - Air)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	23/03/2010 12 05	24/03/2010 12 30	25/03/2010 11 34	26/03/2010 11 42	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1632.0				
Solids Mass (g) (wet)	0				
Liquor Mass (DI water)g	900 2			884	
Gross Wt (g)	2531.1	2527.5	2525.4	2522.5	
Total Mass	900 2	895 5	893.4	890 5	
Temp (Deg C)	23.2	25.1	26.1	29.4	
pH	9.59	9.52	9.59	8.43	
ORP (mV Ag/AgCl)	184	122	169	175	193.9
EC (µS/cm)	19.8	42	50	51	
Calcium (µg/L)					1200
Iron (µg/L)					<100
Magnesium (µg/L)					189
Phosphorus (µg/L)					<1000
Potassium (µg/L)					3980
Silicon (µg/L)					328
Sodium (µg/L)					3630
Aluminium (µg/L)					12
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					<5
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					96
Cadmium (µg/L)					<5
Chromium (µg/L)					<5
Cobalt (µg/L)					<5
Copper (µg/L)					<5
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					10
Nickel (µg/L)					<5
Selenium (µg/L)					<5
Silver (µg/L)					<5
Strontium (µg/L)					5.3
Thallium (µg/L)					<5
Tin (µg/L)					<5
Uranium (µg/L)					22
Vanadium (µg/L)					5.3
Zinc (µg/L)					150
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					36
Bicarbonate as CaCO3 (mg/L)					36
Electrical Conductivity (µS/cm)					39
Ammonia as N (mg N/L)					<1
pH (pH)					7.8
Total Organic Carbon (mg/L)					1.9
Chloride (mg/L)					2.6
Bromide (mg/L)					<0 5
Fluoride (mg/L)					<0 5
Nitrate (mg/L)					<0 5
Nitrite (mg/L)					<0 5
Orthophosphate (mg/L)					<0 5
Sulphate (mg/L)					1.3



CONTROL #42	Start	CONTROL 42 (No Solid - DI water - CO2)			
		inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings
DI water - CO2					
Time	11/05/2010 12 05	12/05/2010 12 05	13/05/2010 12 05	14/05/2010 12 05	
CO2 Addition	y	y	y	y	Assay
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1629.9				
Solids Mass (g) (wet)	0				
Liquor Mass (DI water)g	900				
Gross Wt (g)	2529.9	2528.2	2525	2450.4	
Total Mass	900 0	898 3	895.1	820 5	
Temp (Deg C)	19.1	17	13.9	13.8	
pH	9	7.55	7.04	6.66	
ORP (mV Ag/AgCl)	131	281	237	251	58
EC (uS/cm)	26	113	125	145	
Calcium (µg/L)					1500
Iron (µg/L)					<50
Magnesium (µg/L)					<500
Phosphorus (µg/L)					2000
Potassium (µg/L)					17000
Silicon (µg/L)					200
Sodium (µg/L)					16000
Aluminium (µg/L)					<50
Antimony (µg/L)					<5
Arsenic (µg/L)					<5
Barium (µg/L)					<20
Beryllium (µg/L)					<1
Bismuth (µg/L)					< 1
Boron (µg/L)					110
Cadmium (µg/L)					<0.2
Chromium (µg/L)					<1
Cobalt (µg/L)					<1
Copper (µg/L)					<5
Lead (µg/L)					<1
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					<5
Nickel (µg/L)					<5
Selenium (µg/L)					<1
Silver (µg/L)					<5
Strontium (µg/L)					9
Thallium (µg/L)					<1
Tin (µg/L)					<5
Uranium (µg/L)					79
Vanadium (µg/L)					11
Zinc (µg/L)					95
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					25
Total Alkalinity as CaCO3 (mg/L)					30
Bicarbonate as CaCO3 (mg/L)					30
Electrical Conductivity (µS/cm)					380
Ammonia as N (mg N/L)					0.03
pH (pH)					8.2
Total Organic Carbon (mg/L)					< 5
Chloride (mg/L)					20
Bromide (mg/L)					< 20
Fluoride (mg/L)					< 0.5
Nitrate (mg/L)					< 0.02
Nitrite (mg/L)					< 0.02
Orthophosphate (mg/L)					0.08
Sulphate (mg/L)					< 5

CONTROL #43 BARREN LIQ - Air	Start	CONTROL 43 (No Solid - BARREN LIQ - Air)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	23/03/2010 12 05	24/03/2010 12 30	25/03/2010 11 34	26/03/2010 11 42	
Elapsed Time (days)	0 0	1 0	2.0	3 0	
Bottle Tare Wt (g)	1630.8				
Solids Mass (g) (wet)	0				
Liquor Mass (Barren)g	900.1			870	
Gross Wt (g)	2530.9	2513.1	2509.8	2507.9	
Total Mass	900.1	882.3	879.0	877.1	
Temp (Deg C)	22	25.1	26.1	28.9	
pH	10.97	11	10.94	10.91	
ORP (mV Ag/AgCl)	91	107	111	120	117
EC (mS/cm)	98.2	93	97.6	97.4	
Calcium (µg/L)					590
Iron (µg/L)					130
Magnesium (µg/L)					310
Phosphorus (µg/L)					<1000
Potassium (µg/L)					1610000
Silicon (µg/L)					13000
Sodium (µg/L)					42200000
Aluminium (µg/L)					490
Antimony (µg/L)					<5
Arsenic (µg/L)					8400
Barium (µg/L)					17
Beryllium (µg/L)					<5
Bismuth (µg/L)					<5
Boron (µg/L)					31000
Cadmium (µg/L)					<5
Chromium (µg/L)					400
Cobalt (µg/L)					<5
Copper (µg/L)					76
Lead (µg/L)					<5
Lithium (µg/L)					<5
Manganese (µg/L)					<5
Molybdenum (µg/L)					2400
Nickel (µg/L)					<5
Selenium (µg/L)					500
Silver (µg/L)					<5
Strontium (µg/L)					66
Thallium (µg/L)					<5
Tin (µg/L)					12
Uranium (µg/L)					100000
Vanadium (µg/L)					36000
Zinc (µg/L)					58
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					<20
Total Alkalinity as CaCO3 (mg/L)					77200
Bicarbonate as CaCO3 (mg/L)					186
Electrical Conductivity (µS/cm)					85700
Ammonia as N (mg N/L)					1
pH (pH)					10.9
Total Organic Carbon (mg/L)					590
Chloride (mg/L)					14000
Bromide (mg/L)					48
Fluoride (mg/L)					<0.5
Nitrate (mg/L)					630
Nitrite (mg/L)					<0.5
Orthophosphate (mg/L)					<0.5
Sulphate (mg/L)					7000

CONTROL #44 BARREN LIQ - CO2	Start	CONTROL 44 (No Solid - BARREN LIQ - CO2)			Assay
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	
Time	11/05/2010 12 05	12/05/2010 12 05	13/05/2010 12 05	14/05/2010 12 05	
CO2 Addition	y	y	y	y	
Elapsed Time (days)	0 0	1 0	2 0	3 0	
Bottle Tare Wt (g)	1629.8				
Solids Mass (g) (wet)	0				
Liquor Mass (Barren)g	900 6			870	
Gross Wt (g)	2530.4	2529.2	2528.7	2527.7	
Total Mass	900 6	899.4	898.9	897 9	
Temp (Deg C)	17.8	17	13 8	13.9	
pH	11.2	10.91	10.71	10.58	
ORP (mV Ag/AgCl)	140	219	144	134	110
EC (mS/cm)	91.1	93.1	93 8	9 6	
Calcium (µg/L)					3200
Iron (µg/L)					<50
Magnesium (µg/L)					600
Phosphorus (µg/L)					<100
Potassium (µg/L)					1400000
Silicon (µg/L)					32000
Sodium (µg/L)					42000000
Aluminium (µg/L)					<50
Antimony (µg/L)					<5
Arsenic (µg/L)					2700
Barium (µg/L)					60
Beryllium (µg/L)					<1
Bismuth (µg/L)					< 1
Boron (µg/L)					28000
Cadmium (µg/L)					<5
Chromium (µg/L)					63
Cobalt (µg/L)					<1
Copper (µg/L)					150
Lead (µg/L)					11
Lithium (µg/L)					<5
Manganese (µg/L)					9
Molybdenum (µg/L)					1900
Nickel (µg/L)					6
Selenium (µg/L)					100
Silver (µg/L)					<5
Strontium (µg/L)					110
Thallium (µg/L)					<5
Tin (µg/L)					10
Uranium (µg/L)					79000
Vanadium (µg/L)					38000
Zinc (µg/L)					290
Mercury (µg/L)					<0.1
Acidity as CaCO3 (mg/L)					< 0.1
Total Alkalinity as CaCO3 (mg/L)					76000
Bicarbonate as CaCO3 (mg/L)					3800
Electrical Conductivity (µS/cm)					222000
Ammonia as N (mg N/L)					1.3
pH (pH)					11
Total Organic Carbon (mg/L)					630
Chloride (mg/L)					18000
Bromide (mg/L)					84
Fluoride (mg/L)					22
Nitrate (mg/L)					150
Nitrite (mg/L)					0.51
Orthophosphate (mg/L)					0.61
Sulphate (mg/L)					3300

SEQUENTIAL #1	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YYS158 3.75m 4.75m	22/03/2010 11:42	23/03/2010 11:42	24/03/2010 11:42	25/03/2010 11:42		25/03/2010 15:00	26/03/2010 15:00	27/03/2010 15:00	28/03/2010 15:00		28/03/2010 10:20	29/03/2010 10:20	30/03/2010 10:20	31/03/2010 10:20	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1629.0					1629.0					1629.0				
Solids Mass (g) (wet)	314.3					491.3					359.6				
Liquor Mass (g)	943.8					1474.7					1082				
Gross Wt (g)	2887.1					3595.6					3066				
Total Mass (solid+liquor) g	1258.1					1966					1441.6				
Temp (Deg C)	24.4	26.2	24.9	25.6		25.7	28.3	25.9	23.6		21.7	24.9	22.9	23.7	
pH	8.7	9.08	8.94	8.78		9.01	9.12	9.22	9.17		9.74	9.59	9.32	9.42	
ORP (mV Ag/AgCl)	340	173	180	111	168.4	163	192	193	130	169.3	180	175	215	236	406.7
EC (uS/cm)	1931	2190	2110	2190		244	578	625	663		137	287	316	353	
Calcium (µg/L)					20100					8720					8080
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					32400					17000					18700
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					62500					22300					12000
Silicon (µg/L)					5380					4520					3930
Sodium (µg/L)					356000					74600					25800
Aluminium (µg/L)					33					26					19
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					<5					<5					<5
Barium (µg/L)					33					15					11
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					750					340					180
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					5.9					<5					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					37					7.9					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					5.1					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					570					200					190
Thallium (µg/L)					26					<5					<5
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					290					240					180
Vanadium (µg/L)					110					120					100
Zinc (µg/L)					140					95					69
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					970
Total Alkalinity as CaCO3 (mg/L)					190					210					<20
Bicarbonate as CaCO3 (mg/L)					165					179					<10
Electrical Conductivity (µS/cm)					2250					705					6840
Ammonia as N (mg N/L)					<2					<1					<2
pH (pH)					8.6					8.7					1.9
Total Organic Carbon (mg/L)					2.5					2.4					1.2
Chloride (mg/L)					500					68					6.8
Bromide (mg/L)					1.1					<0.5					<0.5
Fluoride (mg/L)					1.8					1.8					0.7
Nitrate (mg/L)					7.9					1					1400
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					250					50					7.5

SEQUENTIAL #2	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YYS156A 3m 4m	22/03/2010 11:42	23/03/2010 11:42	24/03/2010 11:42	25/03/2010 11:42		26/03/2010 8:43	27/03/2010 8:43	28/03/2010 8:43	29/03/2010 8:43		29/03/2010 12:00	30/03/2010 12:00	31/03/2010 12:00	10/4/2010 12:00	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1633.6					1633.6					1633.6				
Solids Mass (g) (wet)	325.4					306.1					424.6				
Liquor Mass (g)	977.5					922.1					1274.5				
Gross Wt (g)	2335.8					2961.9					3332.6				
Total Mass (solid+liquor) g	1302.9					1228.2					1699.1				
Temp (Deg C)	24	26.3	25.2	26		21.7	24.8	23.6	22.9		22.7	24.9	26	24.1	
pH	8.75	9.02	8.96	8.74		9.7	9.26	9.17	9.03		10.01	9.46	9.3	9.34	
ORP (mV Ag/AgCl)	200	143	115	167	172.5	218	184	189	161	166	162	209	166	225	166.6
EC (uS/cm)	2327	2780	2780	3400		688	977	1161	1082		212	507	562	586	
Calcium (µg/L)					15600					6510					4130
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					14200					3920					2270
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					130000					40000					26400
Silicon (µg/L)					18000					14000					11000
Sodium (µg/L)					645000					186000					78700
Aluminium (µg/L)					28					28					23
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					48					45					21
Barium (µg/L)					15					5.1					<5
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					3300					1300					610
Cadmium (µg/L)					<5					9.4					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					5.6					5.8					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					110					28					7.2
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					10					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					280					74					43
Thallium (µg/L)					17					290					<5
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					1900					2100					1000
Vanadium (µg/L)					600					600					450
Zinc (µg/L)					120					110					110
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					295					417					270
Bicarbonate as CaCO3 (mg/L)					295					314					197
Electrical Conductivity (µS/cm)					3240					1180					555
Ammonia as N (mg N/L)					<2					<1					<1
pH (pH)					7.8					9.1					9.1
Total Organic Carbon (mg/L)					3.4					3.2					1.6
Chloride (mg/L)					580					84					9.1
Bromide (mg/L)					1.4					<0.5					<0.5
Fluoride (mg/L)					3.7					3.6					2.7
Nitrate (mg/L)					95					3.2					<0.5
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					310					52					6.6

SEQUENTIAL #3	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YS162 4.5m 4.6m															
Time	16/04/2010 12:12	17/04/2010 11:42	18/04/2010 11:42	19/04/2010 11:42		19/04/2010 8:43	20/04/2010 8:43	21/04/2010 8:43	22/04/2010 8:43		22/04/2010 8:43	23/04/2010 8:43	24/04/2010 8:43	25/04/2010 8:43	
Elapsed Time (days)	0.0	1.0	2.0	3.0			4.0	5.0	6.0			7.0	8.0	9.0	
Bottle Tare Wt (g)	1630.0					1630.0					1630.0				
Solids Mass (g) (wet)	300.9					364.2					436.3				
Liquor Mass (g)	902.4					1091.1					1311.7				
Gross Wt (g)	2833.3					3078.9					3378.0				
Total Mass (solid+liquor) g	1203.3					1455.3					1748				
Temp (Deg C)	23.2	26.1	25	21.4		23.7	22.5	21.6	23.1		24.5	25.4	24.4	21.7	
pH	9.08	8.95	8.8	8.88		9.63	9.59	9.54	9.41		9.8	9.69	9.9	9.38	
ORP (mV Ag/AgCl)	45	139	197	206	210	141	155	176	192	177	194	197	238	116	130
EC (mS/cm)	3.55	3.44	2.88	2.23		0.865	1.034	0.642	0.734		0.207	0.337	0.768	0.425	
Calcium (µg/L)					20900					2800					1700
Iron (µg/L)					560					<100					<100
Magnesium (µg/L)					15700					1160					700
Phosphorus (µg/L)					<100					<100					<1000
Potassium (µg/L)					104000					26400					18000
Silicon (µg/L)					19000					17000					15000
Sodium (µg/L)					627000					135000					77000
Aluminium (µg/L)					680					26					69
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					27					28					22
Barium (µg/L)					18					<5					<5
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					2700					860					370
Cadmium (µg/L)					<5					<5					2.6
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					<5					<5					10
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					37					<5					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					<5					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					330					22					19
Thallium (µg/L)					<5					120					43
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					97					120					150
Vanadium (µg/L)					400					600					360
Zinc (µg/L)					93					120					130
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					142					202					180
Bicarbonate as CaCO3 (mg/L)					112					122					180
Electrical Conductivity (µS/cm)					2950					676					370
Ammonia as N (mg N/L)					<2					<2					<1
pH (pH)					8.6					9.2					8.1
Total Organic Carbon (mg/L)					4.7					4.6					27
Chloride (mg/L)					740					75					16
Bromide (mg/L)					<0.5					<0.5					<5
Fluoride (mg/L)					1.9					2.7					2.1
Nitrate (mg/L)					8.6					0.7					<0.1
Nitrite (mg/L)					<0.5					<0.5					<0.1
Orthophosphate (mg/L)					<0.5					<0.5					<0.05
Sulphate (mg/L)					500					46					<5

SEQUENTIAL #5	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
ITS165 1.5m 1.6m	16/04/2010 12:12	17/04/2010 11:42	18/04/2010 11:42	19/04/2010 11:42		19/04/2010 8:43	20/04/2010 8:43	21/04/2010 8:43	22/04/2010 8:43		22/04/2010 8:43	23/04/2010 8:43	24/04/2010 8:43	25/04/2010 8:43	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1627.4					1627.4					1627.4				
Solids Mass (g) (wet)	237.1					244.1					349.8				
Liquor Mass (g)	711					694.5					1054.2				
Gross Wt (g)	2575.5					2616.2					3031.2				
Total Mass (solid+liquor) g	348.1					938.6					1404.0				
Temp (Deg C)	23.3	26.1	25.7	20.3		22.9	22	21.5	27.8		25.8	25.7	23.7	22	
pH	8.83	8.53	8.55	8.63		9.28	8.96	8.51	8.4		8.87	8.9	8.87	8.59	
ORP (mV Ag/AgCl)	45	126	164	170	180	129	160	202	213	182	362	172	238	132	120
EC (uS/cm)	564	675	745	731		246	427	375	414		175.7	253	334	327	
Calcium (µg/L)					17300					10700					10000
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					8670					4440					4000
Phosphorus (µg/L)					<100					<100					<1000
Potassium (µg/L)					29500					21300					17000
Silicon (µg/L)					31000					28000					27000
Sodium (µg/L)					112000					60000					27000
Aluminium (µg/L)					<5					8.9					<5
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					<5					<5					<5
Barium (µg/L)					31					18					29
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					250					160					110
Cadmium (µg/L)					10					<5					2.9
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					<5					15					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					<5					<5					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					<5					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					140					80					92
Thallium (µg/L)					110					93					62
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					51					70					48
Vanadium (µg/L)					76					87					73
Zinc (µg/L)					96					130					100
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					154					164					130
Bicarbonate as CaCO3 (mg/L)					138					142					110
Electrical Conductivity (µS/cm)					703					340					260
Ammonia as N (mg N/L)					<2					<1					<1
pH (pH)					8.4					8.5					8.4
Total Organic Carbon (mg/L)					6.4					4.7					< 5
Chloride (mg/L)					110					16					11
Bromide (mg/L)					<0.5					<0.5					< 5
Fluoride (mg/L)					1.1					1.6					< 0.5
Nitrate (mg/L)					14					2.7					0.3
Nitrite (mg/L)					<0.5					<0.5					< 0.1
Orthophosphate (mg/L)					<0.5					<0.5					< 0.05
Sulphate (mg/L)					58					31					4.1

SEQUENTIAL #6	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YS166 0.4m 0.5m	16/04/2010 12:12	17/04/2010 11:42	18/04/2010 11:42	19/04/2010 11:42		27/04/2010 8:43	28/04/2010 8:43	29/04/2010 8:43	30/04/2010 8:43		30/04/2010 8:43	1/05/2010 8:43	2/05/2010 8:43	3/05/2010 8:43	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1629.6					1629.6					1629.6				
Solids Mass (g) (wet)	300.3					380.9					367.7				
Liquor Mass (g)	904.9					1144.9					1106				
Gross Wt (g)	2575.5					2816.2					3031.2				
Total Mass (solid+liquor) g	1205.2					1525.8					1473.7				
Temp (Deg C)	18.7	20.3	22.7	18		20.6	20.2	23	18.2		23.6	20.4	19.1	16.6	
pH	8.44	8.4	8.27	8.21		8.89	8.51	8.03	8.5		9.14	8.7	8.33	8.3	
ORP (mV Ag/AgCl)	212	172	246	230	160	223	184	162	212	110	153	199	190	163	210
EC (uS/cm)	760	841	921	919		65.7	129	149	146.9		67.9	92.4	62.5	71.9	
Calcium (µg/L)					3800					<100					<500
Iron (µg/L)					<100					<100					<50
Magnesium (µg/L)					10000					<500					<500
Phosphorus (µg/L)					<1000					<1000					2300
Potassium (µg/L)					23000					18000					3500
Silicon (µg/L)					17000					15000					29000
Sodium (µg/L)					140000					32000					13000
Aluminium (µg/L)					<5					360					<50
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					<5					<5					<5
Barium (µg/L)					56					<5					<5
Beryllium (µg/L)					<5					<5					<1
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					450					410					220
Cadmium (µg/L)					13					<0.2					9.8
Chromium (µg/L)					6					<5					6
Cobalt (µg/L)					<5					<5					<1
Copper (µg/L)					12					<5					<5
Lead (µg/L)					<5					<5					<1
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					35					19					6
Molybdenum (µg/L)					28					33					15
Nickel (µg/L)					<5					<5					<1
Selenium (µg/L)					<5					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					130					7					<5
Thallium (µg/L)					220					<5					360
Tin (µg/L)					<5					24					<5
Uranium (µg/L)					<5					51					<5
Vanadium (µg/L)					8					18					9
Zinc (µg/L)					200					96					150
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					50
Total Alkalinity as CaCO3 (mg/L)					39					250					24
Bicarbonate as CaCO3 (mg/L)					39					<20					24
Electrical Conductivity (µS/cm)					890					120					160
Ammonia as N (mg N/L)					<1					<1					<0.01
pH (pH)					7.3					7.3					8.6
Total Organic Carbon (mg/L)					18					6.3					18
Chloride (mg/L)					160					15					11
Bromide (mg/L)					<5					<5					<5
Fluoride (mg/L)					<0.5					0.8					0.61
Nitrate (mg/L)					5.2					<0.1					<0.1
Nitrite (mg/L)					<0.1					<0.1					<0.02
Orthophosphate (mg/L)					<0.5					<0.5					0.12
Sulphate (mg/L)					23					<15					<5



SEQUENTIAL #8	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
Y/S164 4.3m 4.4m	27/04/2010 8:43	28/04/2010 8:43	29/04/2010 8:43	30/04/2010 8:43		30/04/2010 8:43	1/05/2010 8:43	2/05/2010 8:43	3/05/2010 8:43		3/05/2010 8:43	4/05/2010 8:43	5/05/2010 8:43	6/05/2010 8:43	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1631.9					1631.9					1631.9				
Solids Mass (g) (wet)	301.0					381.4					361.6				
Liquor Mass (g)	905.8					1145.7					1086.5				
Gross Wt (g)	2538.5					3158.9					3080.0				
Total Mass (solid+liquor) g	1206.8					1527.1					1448.1				
Temp (Deg C)	22.2	20.8	23.1	23		21.8	20.8	23.3	22.3		20	19.1	17.8	20.1	
pH	8.76	8.61	8.48	8.64		9.35	9.29	9.07	9.06		9.48	9.44	9.32	9.14	
ORP (mV Ag/AgCl)	173	162	226	193	160	162	174	170	190	150	184	139	182	163	210
EC (uS/cm)	2300	2510	2530	2500		242	454	505	514		96.9	256	309	229	
Calcium (µg/L)					12000					300					<500
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					15000					500					<500
Phosphorus (µg/L)					<1000					<1000					2100
Potassium (µg/L)					69000					21000					6100
Silicon (µg/L)					18000					21000					44000
Sodium (µg/L)					450000					88000					39000
Aluminium (µg/L)					<5					<5					100
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					9					9					8
Barium (µg/L)					44					<5					0.02
Beryllium (µg/L)					<5					<5					<20
Bismuth (µg/L)					<5					<5					< 1
Boron (µg/L)					2600					1100					760
Cadmium (µg/L)					9.5					<0.2					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<1
Copper (µg/L)					7					<5					<5
Lead (µg/L)					<5					<5					<1
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					76					14					<5
Nickel (µg/L)					<5					<5					<1
Selenium (µg/L)					13					<5					<1
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					200					7					<5
Thallium (µg/L)					180					360					140
Tin (µg/L)					<5					7					<5
Uranium (µg/L)					13					16					<5
Vanadium (µg/L)					58					96					86
Zinc (µg/L)					110					79					99
Mercury (µg/L)					<0.1					<1					<0.1
Acidity as CaCO3 (mg/L)					< 20					< 20					50
Total Alkalinity as CaCO3 (mg/L)					120					1000					64
Bicarbonate as CaCO3 (mg/L)					120					29					64
Electrical Conductivity (µS/cm)					2400					430					270
Ammonia as N (mg N/L)					< 1					< 1					0.03
pH (pH)					8					7.5					8.3
Total Organic Carbon (mg/L)					18					13					18
Chloride (mg/L)					600					56					12
Bromide (mg/L)					2.3					< 5					< 5
Fluoride (mg/L)					3.7					2.2					4.3
Nitrate (mg/L)					4					0.3					< 0.1
Nitrite (mg/L)					< 0.1					< 0.1					< 0.02
Orthophosphate (mg/L)					< 0.5					< 0.05					0.24
Sulphate (mg/L)					310					33					< 5

SEQUENTIAL #9	Sequence 1					Sequence 2				Sequence 3					
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YYS156A 1.5m 2.5m	22/03/2010 11:42	23/03/2010 11:42	24/03/2010 11:42	25/03/2010 11:42		26/03/2010 13:35	27/03/2010 13:35	28/03/2010 13:35	29/03/2010 13:35		29/03/2010 12:00	30/03/2010 12:00	31/03/2010 12:00	10/4/2010 12:00	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1695.4					1695.4					1695.4				
Solids Mass (g) (wet)	336.7					506.3					491.7				
Liquor Mass (g)	1011					1520.3					1477.5				
Gross Wt (g)	3042.8					3721.8					3664.5				
Total Mass (solid+liquor) g	1347.7					2026.6					1969.2				
Temp (Deg C)	19.4	18.5	21.8	23.8		25.2	26.2	23.7	23.2		23.2	25.3	26	26.6	
pH	7.95	8.35	8.26	8.28		8.48	8.38	8.32	8.46		8.44	8.22	8.36	8.33	
ORP (mV Ag/AgCl)	203	206	209	218	203.2	189	201	164	183	202.6	193	227	233	221	207.1
EC (mS/cm)	6.16	6.59	6.6	6.65		2.18	3.47	3.51	3.48		1.169	2.64	2.68	2.76	
Calcium (µg/L)					640000					642000					694000
Iron (µg/L)					<100					110					<100
Magnesium (µg/L)					95300					49700					33500
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					203000					72500					38000
Silicon (µg/L)					10000					10000					11000
Sodium (µg/L)					1030000					261000					61800
Aluminium (µg/L)					28					29					21
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					12					7					5.8
Barium (µg/L)					60					52					47
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					3600					1200					610
Cadmium (µg/L)					<5					<5					27
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					10					8.7					6.6
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					9.1					5					<5
Molybdenum (µg/L)					99					21					5.4
Nickel (µg/L)					17					16					16
Selenium (µg/L)					23					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					6000					4800					4200
Thallium (µg/L)					<5					<5					120
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					360					260					180
Vanadium (µg/L)					84					79					71
Zinc (µg/L)					160					140					150
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					85					68					56
Bicarbonate as CaCO3 (mg/L)					85					68					56
Electrical Conductivity (µS/cm)					7510					3070					2420
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					7.9					7.8					7.7
Total Organic Carbon (mg/L)					6.1					2.3					1.1
Chloride (mg/L)					890					97					14
Bromide (mg/L)					1.6					<0.5					<0.5
Fluoride (mg/L)					1.5					1.4					1.3
Nitrate (mg/L)					38					3.8					0.6
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					3200					2100					1700

SEQUENTIAL #10	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
Y/S151 3.65m 4.1m	23/03/2010 9:50	24/03/2010 9:50	25/03/2010 9:50	26/03/2010 9:50		26/03/2010 14:20	27/03/2010 13:35	28/03/2010 9:35	29/03/2010 13:35		30/03/2010 8:30	31/03/2010 8:30	1/04/2010 8:30	2/04/2010 8:30	
Time															
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1633.1					1633.1					1633.1				
Solids Mass (g) (wet)	329.7					371.5					384.5				
Liquor Mass (g)	990.6					1116.2					1155.9				
Gross Wt (g)	2953.1					3196.7					3173.3				
Total Mass (solid+liquor) g	1320.3					1487.7					1540.4				
Temp (Deg C)	20	19.9	23.5	25.7		26.1	26.2	23.6	25.6		18.1	19.5	20.6	22.3	
pH	9.81	9.27	9.01	8.95		9.73	9.21	9.26	9.26		9.81	9.42	9.41	9.14	
ORP (mV Ag/AgCl)	175	182	177	184	152.6	182	148	130	184	154	232	225	243	182	160.6
EC (uS/cm)	631	845	1218	938		206	38	413	432		118.9	278	315	323	
Calcium (µg/L)					5730					3370					3590
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					3440					1450					1520
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					22700					14000					12600
Silicon (µg/L)					25000					26000					25000
Sodium (µg/L)					154000					64000					43900
Aluminium (µg/L)					36					39					31
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					7					<5					<5
Barium (µg/L)					<5					<5					<5
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					630					380					300
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					6.5					<5					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					71					9.9					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					<5					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					56					34					31
Thallium (µg/L)					79					150					110
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					86					41					36
Vanadium (µg/L)					170					130					83
Zinc (µg/L)					120					110					120
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					224					190					157
Bicarbonate as CaCO3 (mg/L)					180					136					117
Electrical Conductivity (µS/cm)					1030					384					297
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					8.8					9					8.8
Total Organic Carbon (mg/L)					2.9					1.2					1.5
Chloride (mg/L)					110					9.1					2.2
Bromide (mg/L)					1.4					<0.5					<0.5
Fluoride (mg/L)					2.8					2.2					1.5
Nitrate (mg/L)					1.3					<0.5					<0.5
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					95					22					15

SEQUENTIAL #11	Sequence 1					Sequence 2				Sequence 3					
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
YYS158 3.5m 3.75m	31/03/2010 15:00	1/04/2010 15:00	2/04/2010 15:00	3/04/2010 15:00		3/04/2010 11:20	4/04/2010 11:20	5/04/2010 11:20	6/04/2010 11:20		6/04/2010 10:30	7/04/2010 10:30	8/04/2010 10:30	9/04/2010 10:30	
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Bottle Tare Wt (g)	1630.5					1630.5					1630.5				
Solids Mass (g) (wet)	292.6					473.8					535.4				
Liquor Mass (g)	878.9					1421.9					1606.6				
Gross Wt (g)	2721.5					3525.9					3772				
Total Mass (solid+liquor) g	1171.5					1895.7					2142				
Temp (Deg C)	25.6	25.7	24.7	20		19	25	27.2	22.6		21.6	23.7	22.4	22.1	
pH	8.65	8.72	8.8	8.88		9.96	9.28	9.18	9.28		9.76	9.45	9.53	9.28	
ORP (mV Ag/AgCl)	216	192	202	194	420.6	176	160	189	172	190	182	220	206	207	190
EC (mS/cm)	3.5	3.97	4.1	3.29		4.48	0.911	0.92	0.942		0.229	0.426	0.393	0.427	
Calcium (µg/L)					46800					11800					7530
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					79900					19100					10800
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					98900					29900					14000
Silicon (µg/L)					3680					3160					4020
Sodium (µg/L)					700000					130000					44200
Aluminium (µg/L)					28					21					20
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					5.1					<5					<5
Barium (µg/L)					28					11					12
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					1100					580					360
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					<5					<5					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					170					32					8.3
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					16					5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					1300					260					150
Thallium (µg/L)					<5					69					81
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					190					110					86
Vanadium (µg/L)					39					72					79
Zinc (µg/L)					88					83					76
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					430					<20					<20
Total Alkalinity as CaCO3 (mg/L)					<20					168					162
Bicarbonate as CaCO3 (mg/L)					<10					120					105
Electrical Conductivity (µS/cm)					6960					927					327
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					2.3					9.1					9.2
Total Organic Carbon (mg/L)					3.7					4.1					7.6
Chloride (mg/L)					1200					120					21
Bromide (mg/L)					<0.5					<0.5					<0.5
Fluoride (mg/L)					1.6					1.2					1.6
Nitrate (mg/L)										1.4					<0.5
Nitrite (mg/L)					<0.5					<0.5					1.8
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					460					80					13

SEQUENTIAL #12	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
Y/S158 3.5m 3.75m DUP	1/04/2010 14:00	2/04/2010 14:00	3/04/2010 14:00	4/04/2010 14:00		4/04/2010 11:20	5/04/2010 11:20	6/04/2010 11:20	7/04/2010 11:20		7/04/2010 11:50	8/04/2010 11:50	9/04/2010 11:50	10/04/2010 11:50	
Elapsed Time (days)	0.0	1.0	2.0	3.0			4.0	5.0	6.0			7.0	8.0	9.0	
Bottle Tare Wt (g)	1630.5					1630.5					1630.5				
Solids Mass (g) (wet)	291.9					519.2					611.7				
Liquor Mass (g)	877.2					1558.8					1836.6				
Gross Wt (g)	2798.7					3708.1					4079.2				
Total Mass (solid+liquor) g	1168.1					2078					2448.3				
Temp (Deg C)	23.6	25.7	20.3	24.9		20.9	22.8	22.5	21.9		24	22.9	21.7	23	
pH	8.65	8.79	8.87	8.67		9.58	9.38	9.27	9.35		9.43	9.44	9.44	9.31	
ORP (mV Ag/AgCl)	214	148	159	172	274.2	165	154	190	231	200	179	180	182	158	200
EC (mS/cm)	3.79	4.02	3.28	3.15		0.444	0.925	1.072	1.006		0.157	0.309	0.434	0.400	
Calcium (µg/L)					46200					11900					7800
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					78900					19800					11900
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					89700					30000					13100
Silicon (µg/L)					3580					2970					3870
Sodium (µg/L)					677000					133000					49500
Aluminium (µg/L)					27					54					23
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					<5					<5					<5
Barium (µg/L)					28					15					7.7
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					1200					650					360
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					<5					<5					11
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					160					43					8.9
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					15					8.2					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					1300					310					160
Thallium (µg/L)					<5					<5					<5
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					180					110					78
Vanadium (µg/L)					37					72					70
Zinc (µg/L)					120					71					82
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					151					164					159
Bicarbonate as CaCO3 (mg/L)					144					110					101
Electrical Conductivity (µS/cm)					3790					945					320
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					8.4					9.1					9.1
Total Organic Carbon (mg/L)					3.8					2.6					2.2
Chloride (mg/L)					700					130					23
Bromide (mg/L)					2.3					<0.5					<0.5
Fluoride (mg/L)					2					1.2					1
Nitrate (mg/L)					11					1.7					<0.5
Nitrite (mg/L)					<0.5					<0.5					2
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					300					82					14

SEQUENTIAL #13	Sequence 1				Sequence 2				Sequence 3						
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
Y15156A 12m 12.75m	1/04/2010 14:00	2/04/2010 12:00	3/04/2010 14:00	4/04/2010 14:00		4/04/2010 10:40	5/04/2010 11:20	6/04/2010 11:20	7/04/2010 11:20		7/04/2010 11:50	8/04/2010 11:50	9/04/2010 11:50	10/04/2010 11:50	
Elapsed Time (days)	0.0	0.9	2.0	3.0			4.0	5.0	6.0			7.0	8.0	9.0	
Bottle Tare Wt (g)	1634.5					1634.5					1634.5				
Solids Mass (g) (wet)	302.0					532.4					452.7				
Liquor Mass (g)	909.1					1599.2					1358.1				
Gross Wt (g)	2847.4					3766					3445.2				
Total Mass (solid+liquor) g	1211.1					2131.6					1810.8				
Temp (Deg C)	232	26	20.6	24.9		22.4	22	23.6	21.2		23.3	23.1	22	23.4	
pH	8.19	8.38	8.44	8.11		8.96	8.62	8.52	8.5		9.06	9.09	9.08	888	
ORP (mV Ag/AgCl)	200	184	173	181	263.8	180	148	218	213	220	201	184	155	139	210
EC (mS/cm)	3.9	3.74	4.02	3.37		0.571	1.176	0.866	1.22		0.0835	0.1927	0.301	0.317	
Calcium (µg/L)					50400					7310					1820
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					94500					12200					1270
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					211000					47600					14700
Silicon (µg/L)					8650					6830					6290
Sodium (µg/L)					1070000					179000					43900
Aluminium (µg/L)					25					19					19
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					8.3					5.8					9.9
Barium (µg/L)					42					45					8.2
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					4900					1400					720
Cadmium (µg/L)					<5					5.9					<5
Chromium (µg/L)					<5					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					5.5					<5					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					6.1					<5					<5
Molybdenum (µg/L)					390					130					46
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					28					9.2					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					1400					210					30
Thallium (µg/L)					<5					77					59
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					<5					7.4					<5
Vanadium (µg/L)					23					32					42
Zinc (µg/L)					150					120					120
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					49					52					57
Bicarbonate as CaCO3 (mg/L)					49					52					57
Electrical Conductivity (µS/cm)					6570					1230					261
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					7.5					7.6					7.7
Total Organic Carbon (mg/L)					2.9					2					4.2
Chloride (mg/L)					1700					250					34
Bromide (mg/L)					11					<0.5					<0.5
Fluoride (mg/L)					2.5					1.1					1
Nitrate (mg/L)					49					6.1					0.7
Nitrite (mg/L)					<0.5					<0.5					0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					740					120					32

SEQUENTIAL #14	Sequence 1					Sequence 2					Sequence 3				
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 3 Liquor
Time	2/04/2010 11:00	3/04/2010 11:00	4/04/2010 11:00	5/04/2010 11:00		5/04/2010 12:15	6/04/2010 12:15	7/04/2010 12:15	8/04/2010 12:15		9/04/2010 12:00	10/04/2010 12:00	11/04/2010 12:00	12/04/2010 12:00	
Elapsed Time (days)	0.0	1.0	2.0	3.0			4.0	5.0	6.0			7.0	8.0	9.0	
Bottle Tare Wt (g)	1631.6					1631.6					1631.6				
Solids Mass (g) (wet)	314.1					457.5					433.6				
Liquor Mass (g)	943.5					1374.3					1301.9				
Gross Wt (g)	2889.1					3463.4					3367.2				
Total Mass (solid+liquor) g	1257.6					1831.8					1735.5				
Temp (Deg C)	21	20.1	25.7	24.3		24	22.8	25.4	24.1		22	21.9	23.3	20.6	
pH	9.14	9.09	8.84	8.78		9.66	9.38	9.22	9.08		9.61	9.31	9.23	9.18	
ORP (mV Ag/AgCl)	172	152	191	188	252.9	151	153	221	143	190	204	124	157	238	163
EC (uS/cm)	1046	1571	1666	156		183	474	537	538		132	332	357	372	
Calcium (µg/L)					6460					2450					3400
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					4900					1200					1450
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					38300					20500					18300
Silicon (µg/L)					23000					24000					19000
Sodium (µg/L)					266000					86400					68200
Aluminium (µg/L)					32					28					<5
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					21					23					9.8
Barium (µg/L)					<5					<5					<5
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					1100					640					310
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					20					16					9.9
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					<5					<5					<5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					140					30					7.6
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					<5					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					73					22					18
Thallium (µg/L)					<5					<5					240
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					12					<5					<5
Vanadium (µg/L)					160					200					100
Zinc (µg/L)					110					47					61
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					215					213					194
Bicarbonate as CaCO3 (mg/L)					177					156					170
Electrical Conductivity (µS/cm)					1590					498					305
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					8.8					9					8.6
Total Organic Carbon (mg/L)					1.3					7.7					9.8
Chloride (mg/L)					300					24					3.5
Bromide (mg/L)					<0.5					<0.5					<0.5
Fluoride (mg/L)					4.8					3.3					1.5
Nitrate (mg/L)					1.2					<0.5					<0.5
Nitrite (mg/L)					<0.5					2.2					0.9
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					110					9.6					2.8

PALEOCHANNEL SANDS YYHC0075 64m - 65m	Sequence 1 - BARREN LIQUOR					Sequence 2 - DI WATER				
	Start Seq 1- Barr	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2 -DI	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor
Time	14/05/2010 11 00	15/05/2010 11 00	16/05/2010 11 00	17/05/2010 11 00		18/05/2010 12 15	19/05/2010 12 15	20/05/2010 12 15	21/05/2010 12 15	
Elapsed Time (days)	0.0	1.0	2.0	3.0			4.0	5.0	6.0	
Bottle Tare Wt (g)	1631.1					1631.1				
Solids Mass (g) (wet)	300.0					290.9				
Liquor Mass (g)	901.1					872.5				
Gross Wt (g)	2832					2769.1				
Total Mass (solid+liquor) g	1201.1					1163.4				
Temp (Deg C)	14.7	18.6	21.2	15		14.8	15.6	17.3	15.1	
pH	11.08	11	11.01	11.05		10.9	10.98	10.84	10.74	
ORP (mV Ag/AgCl)	182	58	222	226	110	189	174	231	160	85
EC (mS/cm)	87	86	83.9	84.1		4.05	5.51	5.53	5.47	
Calcium (µg/L)					4400					1600
Iron (µg/L)					<100					<100
Magnesium (µg/L)					31000					<1000
Phosphorus (µg/L)					<100					<1000
Potassium (µg/L)					1500000					45000
Silicon (µg/L)					49000					2700
Sodium (µg/L)					44000000					1400000
Aluminium (µg/L)					70					6900
Antimony (µg/L)					<5					<5
Arsenic (µg/L)					280					130
Barium (µg/L)					230					6
Beryllium (µg/L)					<5					<5
Bismuth (µg/L)					< 1000					<5
Boron (µg/L)					28000					1500
Cadmium (µg/L)					<5					<0.2
Chromium (µg/L)					77					8
Cobalt (µg/L)					<5					<5
Copper (µg/L)					5					39
Lead (µg/L)					13					<5
Lithium (µg/L)					18					17
Manganese (µg/L)					<5					<5
Molybdenum (µg/L)					2000					79
Nickel (µg/L)					11					<5
Selenium (µg/L)					89					17
Silver (µg/L)					<5					<5
Strontium (µg/L)					4400					20
Thallium (µg/L)					33					26
Tin (µg/L)					<5					<5
Uranium (µg/L)					<5					2000
Vanadium (µg/L)					33000					2200
Zinc (µg/L)					120					170
Mercury (µg/L)					<0.1					<0.1
Acidity as CaCO3 (mg/L)					< 0.1					< 20
Total Alkalinity as CaCO3 (mg/L)					69000					2400
Bicarbonate as CaCO3 (mg/L)					< 10					< 20
Electrical Conductivity (µS/cm)					206000					5800
Ammonia as N (mg N/L)					1.7					< 1
pH (pH)					11					10
Total Organic Carbon (mg/L)					1300					< 10
Chloride (mg/L)					17000					540
Bromide (mg/L)					92					2.3
Fluoride (mg/L)					24					1.8
Nitrate (mg/L)					130					15
Nitrite (mg/L)					0.55					< 0.1
Orthophosphate (mg/L)					0.52					< 0.5
Sulphate (mg/L)					3300					230



PALEOCHANNEL SANDS YYHC0059C 55m - 56m	Sequence 1 - BARREN LIQUOR				Sequence 2 - D.I WATER					
	Start Seq 1- Barr	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2- DI	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor
Time	14/05/2010 11 00	15/05/2010 11 00	16/05/2010 11 00	17/05/2010 11 00		18/05/2010 12 15	19/05/2010 12 15	20/05/2010 12 15	21/05/2010 12 15	
Elapsed Time (days)	0 0	1 0	2 0	3 0			4 0	5 0	6 0	
Bottle Tare Wt (g)	1629.4					1629.4				
Solids Mass (g) (wet)	299.1					307.1				
Liquor Mass (g)	897.4					920.3				
Gross Wt (g)	2825.4					2835.4				
Total Mass (solid+liquor) g	1196.5					1227.4				
Temp (Deg C)	15	18.6	21.2	14.6		15	15.7	17.8	15.1	
pH	11.06	10.91	10.89	10.92		10.99	11.08	10.96	10.91	
ORP (mV Ag/AgCl)	60	88	262	246	150	115	204	212	182	83
EC (mS/cm)	63	85.7	79.2	82.8		7.95	9.06	8.39	9	
Calcium (µg/L)					3600					2500
Iron (µg/L)					330					<100
Magnesium (µg/L)					14000					1100
Phosphorus (µg/L)					<100					<1000
Potassium (µg/L)					1300000					90000
Silicon (µg/L)					19000					11000
Sodium (µg/L)					40000000					2500000
Aluminium (µg/L)					510					430
Antimony (µg/L)					<5					<5
Arsenic (µg/L)					420					190
Barium (µg/L)					280					10
Beryllium (µg/L)					<1					<5
Bismuth (µg/L)					<1					<5
Boron (µg/L)					27000					2700
Cadmium (µg/L)					<5					0.2
Chromium (µg/L)					75					16
Cobalt (µg/L)					<1					<5
Copper (µg/L)					<5					64
Lead (µg/L)					16					<5
Lithium (µg/L)					51					7
Manganese (µg/L)					<5					<5
Molybdenum (µg/L)					1800					110
Nickel (µg/L)					6					<5
Selenium (µg/L)					72					27
Silver (µg/L)					<5					<5
Strontium (µg/L)					1000					150
Thallium (µg/L)					<5					<5
Tin (µg/L)					<5					<5
Uranium (µg/L)					<5					3800
Vanadium (µg/L)					34000					3700
Zinc (µg/L)					95					160
Mercury (µg/L)					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<0.1					<20
Total Alkalinity as CaCO3 (mg/L)					74000					4700
Bicarbonate as CaCO3 (mg/L)					1500					<20
Electrical Conductivity (µS/cm)					232000					9500
Ammonia as N (mg N/L)					1.4					<1
pH (pH)					11					11
Total Organic Carbon (mg/L)					1700					<10
Chloride (mg/L)					19000					1000
Bromide (mg/L)					89					3.6
Fluoride (mg/L)					24					2.7
Nitrate (mg/L)					140					29
Nitrite (mg/L)					0.36					<0.1
Orthophosphate (mg/L)					0.4					1.8
Sulphate (mg/L)					3600					410

Bottle 1 S1.9.4.0 4.5	Sequence 1				Sequence 2				Sequence 3				Final		
	inc Head	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings		48 hour bottle readings	72 hour bottle readings
Time	10/12/2009 10:45	11/12/2009 12:01	12/12/2009 12:01	13/12/2009 12:01		14/12/2009 9:45	15/12/2009 10:15	16/12/2009 10:15	17/12/2009 10:15		19/12/2009 17:00	20/12/2009 17:00	21/12/2009 15:20	22/12/2009 16:00	
Elapsed Time (days)	0.0	1.1	2.1	3.1	3.1					6.1					9.0
Solids Mass (g) (wet)	628.86					764.73					773.07				
Solids + Liquor Mass (g)	2507.44			2499.35		2321					3032.35		2814.35	2812.35	
Liquor Mass	1880.58				1661	1556.27				2069.76					752.61
Temp (Deg C)	20.2	21.1	19.9	25.2		21.1	25.2	25.8	22.7		21.9	27	27.7	27	
pH	9.81	9.76	9.82	9.61		10.29	10.04	9.95	9.95		10.06	9.89	9.84	9.8	
ORP (mV Ag/AgCl)	199	175	201	171		206	213	217	164		242	210	184	193	
EC (uS/cm)	2556	2662	2735	2810		317	866	841	872		196.7	521	1052	641	
Calcium (µg/L)					4320					1390					2370
Iron (µg/L)					<100					<100					120
Magnesium (µg/L)					1360					326					789
Phosphorus (µg/L)					<100					<100					250
Potassium (µg/L)					29000					10400					7660
Silicon (µg/L)					180000					17000					2500
Sodium (µg/L)					540000					161000					87200
Aluminium (µg/L)					76					93					270
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					180					120					52
Barium (µg/L)					8.5					<5					7.2
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					1700					680					310
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					5.6					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					7.4					<5					5.1
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					32					5.8					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					9.4					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					710					140					160
Thallium (µg/L)					<5					<5					<5
Tin (µg/L)					5.6					<5					30
Uranium (µg/L)					650					320					180
Vanadium (µg/L)					12000					6000					2200
Zinc (µg/L)					33					<5					11
Mercury (µg/L)					0.2					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					322					349					-
Bicarbonate as CaCO3 (mg/L)					204					213					-
Carbonate as CaCO3 (mg/L)					118					136					-
Hydroxide as CaCO3 (mg/L)					<10					<10					-
Electrical Conductivity (µS/cm)					2600					824					385
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					9.2					9.3					8.3
Total Organic Carbon (mg/L)					6.1					3.8					8
Chloride (mg/L)					310					29					3.2
Bromide (mg/L)					1.9					1.8					<0.5
Fluoride (mg/L)					3.8					2.3					1.5
Nitrate (mg/L)					44					2.3					<0.5
Nitrite (mg/L)					<0.5					0.6					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					480					44					5.9

Bottle 2 S2.9 5.25 6.0	Sequence 1				Sequence 2				Sequence 3				Final		
	Start Seq 1	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 1 Liquor	Start Seq 2	24 hour bottle readings	48 hour bottle readings	72 hour bottle readings	Sequence 2 Liquor	Start Seq 3	24 hour bottle readings		48 hour bottle readings	72 hour bottle readings
Time	10/12/2009 11:00	11/12/2009 12:01	12/12/2009 12:01	13/12/2009 12:01		16/12/2009 9:40	17/12/2009 12:01		19/12/2009 17:15		20/12/2009 16:30	21/12/2009 15:30	22/12/2009 16:25	23/12/2009 15:30	
Elapsed Time (days)	0.0	1.0	2.0	3.0					6.4			7.3	8.4	9.3	
Solids Mass (g) (wet)	474.02					433.87					402.81				428.35
Solids + Liquor Mass (g)	1895.78			1887.55		1815.19					1619.9		1600.55	1570.55	
Liquor Mass	1421.76				1038.18	1381.32				473.51	1217.09				1300.58
Temp (Deg C)	19.7	20.4	20.2	24.5		22.4	20.9		25		23.1	28.8	27.3	26.9	
pH	10	9.82	9.79	9.76		10.3	10.1		10.01		10.27	9.98	9.97	9.92	
ORP (mV Ag/AgCl)	156	165	192	184		171	212		221		214	159	210	212	
EC (uS/cm)	1542	4470	4560	4400		701	1540		1581		366	2095	1163	1132	
Calcium (µg/L)					3210					2210					3330
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					820					381					602
Phosphorus (µg/L)					270					510					170
Potassium (µg/L)					48600					12200					8320
Silicon (µg/L)					180000					18000					2980
Sodium (µg/L)					1080000					253000					161000
Aluminium (µg/L)					160					310					170
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					210					120					78
Barium (µg/L)					8.6					11					14
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					1700					940					580
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					6.9					<5					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					23					24					9.7
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					68					11					9.7
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					42					8.4					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					280					72					99
Thallium (µg/L)					<5					<5					<5
Tin (µg/L)					<5					47					240
Uranium (µg/L)					56000					9200					3500
Vanadium (µg/L)					3100					2300					1400
Zinc (µg/L)					18					5.9					7
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					1190					-					-
Bicarbonate as CaCO3 (mg/L)					803					-					-
Carbonate as CaCO3 (mg/L)					383					-					-
Hydroxide as CaCO3 (mg/L)					<10					-					-
Electrical Conductivity (µS/cm)					5240					1180					784
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					9.4					8.8					8.4
Total Organic Carbon (mg/L)					4.2					23					5.8
Chloride (mg/L)					750					88					10
Bromide (mg/L)					3.1					<0.5					<0.5
Fluoride (mg/L)					7.2					4.3					2.2
Nitrate (mg/L)					51					<0.5					25
Nitrite (mg/L)					<0.5					<0.5					1.6
Orthophosphate (mg/L)					<0.5					0.61					<0.5
Sulphate (mg/L)					480					51					7.1

Bottle 3 SZ-14 4.0 4.9	Sequence 1				Sequence 2				Sequence 3				Final		
	Start Seq 1 19/12/2009 11:15	24 hour bottle readings 11/12/2009 12:01	48 hour bottle readings 12/12/2009 12:01	72 hour bottle readings 13/12/2009 12:01	Sequence 1 Liquor	Start Seq 2 15/12/2009 10:15	24 hour bottle readings 16/12/2009 10:15	48 hour bottle readings 17/12/2009 12:01	72 hour bottle readings 18/12/2009 9:45	Sequence 2 Liquor	Start Seq 3 19/12/2009 16:30	24 hour bottle readings 20/12/2009 17:00		48 hour bottle readings 21/12/2009 18:40	72 hour bottle readings 22/12/2009 16:25
Elapsed Time (days)	0.0	1.0	2.0	3.0											
Solids Mass (g) (wet)	451.52					372.89	4.0	5.1	6.0		286.55	7.0	8.0	9.0	243.32
Solids + Liquor Mass (g)	1806.08			1794.08		1590.12					1232.22			1135.88	
Liquor Mass	1354.56					1217.23				319.14	945.67				265.26
Temp (Deg C)	19.7	20.6	20.6	24.9		22.1	27.6	21.4	21.9		22.1	27.2	27.3	27.1	
pH	9.98	9.69	9.73	9.6		10.34	9.97	10.06	10.04		10.26	9.83	9.79	9.76	
ORP (mV Ag/AgCl)	169	181	204	178		164	209	184	175		175	167	146	216	
EC (uS/cm)	1635	4580	4500	4220		734	1490	1562	1575		512	1133	1202	1278	
Calcium (µg/L)					4620					3600					2560
Iron (µg/L)					<100					<100					<100
Magnesium (µg/L)					1210					636					415
Phosphorus (µg/L)					220					650					110
Potassium (µg/L)					57600					19400					8370
Silicon (µg/L)					240000					35000					4220
Sodium (µg/L)					1110000					351000					149000
Aluminium (µg/L)					110					250					180
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					340					280					130
Barium (µg/L)					10					19					19
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					2400					1500					610
Cadmium (µg/L)					<5					<5					<5
Chromium (µg/L)					9.5					5.3					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					13					24					21
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					93					21					<5
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					27					6.8					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					600					140					110
Thallium (µg/L)					<5					<5					<5
Tin (µg/L)					7.6					61					16
Uranium (µg/L)					21000					6000					2200
Vanadium (µg/L)					12000					10000					3700
Zinc (µg/L)					15					7.1					6.1
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					680					-					-
Bicarbonate as CaCO3 (mg/L)					546					-					-
Carbonate as CaCO3 (mg/L)					133					-					-
Hydroxide as CaCO3 (mg/L)					<10					-					-
Electrical Conductivity (µS/cm)					5530					1660					715
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					9					8.8					8.6
Total Organic Carbon (mg/L)					8.1					45					5.5
Chloride (mg/L)					860					120					12
Bromide (mg/L)					2.3					<0.5					<0.5
Fluoride (mg/L)					6.1					4.9					2.7
Nitrate (mg/L)					<0.5					<0.5					<0.5
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					590					100					11

Bottle 4 S3.8 6.0 .0	Sequence 1					Sequence 2				Sequence 3				Final
	Start Seq 1 10/12/2009 11:30	24 hour bottle readings 11/12/2009 12:01	48 hour bottle readings 12/12/2009 12:01	72 hour bottle readings 13/12/2009 12:01	Sequence 1 Liquor	Start Seq 2 17/12/2009 11:00	24 hour bottle readings 19/12/2009 17:00	48 hour bottle readings 20/12/2009 16:45	Sequence 2 Liquor	Start Seq 3 22/12/2009 16:00	24 hour bottle readings 23/12/2009 9:30	48 hour bottle readings 24/12/2009 9:30	Sequence 3 Liquor	
Elapsed Time (days)	0.0	1.0	2.0	3.0										
Solids Mass (g) (wet)	662.32					722.29		6.3		705.55	7.0	8.0		612.38
Solids + Liquor Mass (g)	2649.3					3062.16				2943.36		2902.7		
Liquor Mass	1986.98				635.21	2339.87				2237.81			627.29	
Temp (Deg C)	19.6	20.5	20.4	25.4		21.4		25.6		22.7	27.2	25.2		
pH	9.51	8.76	8.73	8.59		9.58		9.06		9.48	9.17	9.19		
ORP (mV Ag/AgCl)	157	178	206	178		184		235		225	215	212		
EC (uS/cm)	376	2123	2092	2030		259		831		85.4	596	606		
Calcium (µg/L)					5700				1960					1010
Iron (µg/L)					<100				<100					<100
Magnesium (µg/L)					1740				329					202
Phosphorus (µg/L)					330				<100					<100
Potassium (µg/L)					5270				1500					1580
Silicon (µg/L)					160000				17000					3670
Sodium (µg/L)					485000				140000					83500
Aluminium (µg/L)					15				56					87
Antimony (µg/L)					<5				<5					<5
Arsenic (µg/L)					5.1				<5					<5
Barium (µg/L)					45				18					11
Beryllium (µg/L)					<5				<5					<5
Bismuth (µg/L)					<5				<5					<5
Boron (µg/L)					370				480					470
Cadmium (µg/L)					<5				<5					<5
Chromium (µg/L)					<5				<5					<5
Cobalt (µg/L)					<5				<5					<5
Copper (µg/L)					25				15					5.8
Lead (µg/L)					<5				<5					<5
Lithium (µg/L)					<5				<5					<5
Manganese (µg/L)					7.4				<5					<5
Molybdenum (µg/L)					45				39					25
Nickel (µg/L)					7.5				<5					<5
Selenium (µg/L)					7.7				<5					<5
Silver (µg/L)					<5				<5					<5
Strontium (µg/L)					51				26					6.3
Thallium (µg/L)					<5				<5					<5
Tin (µg/L)					170				38					11
Uranium (µg/L)					1400				530					280
Vanadium (µg/L)					8.5				8					<5
Zinc (µg/L)					3.2				<5					17
Mercury (µg/L)					<0.1				<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20				<20					<20
Total Alkalinity as CaCO3 (mg/L)					-				297					229
Bicarbonate as CaCO3 (mg/L)					-				261					229
Carbonate as CaCO3 (mg/L)					-				36					<10
Hydroxide as CaCO3 (mg/L)					-				<10					<10
Electrical Conductivity (µS/cm)					2380				656					351
Ammonia as N (mg N/L)					<1				<1					<1
pH (pH)					8.6				8.7					8.6
Total Organic Carbon (mg/L)					29				9.1					6.6
Chloride (mg/L)					240				15					5.1
Bromide (mg/L)					1.2				<0.5					<0.5
Fluoride (mg/L)					1.1				2.7					2.6
Nitrate (mg/L)					0.6				<0.5					1.1
Nitrite (mg/L)					<0.5				<0.5					<0.5
Orthophosphate (mg/L)					<0.5				<0.5					<0.5
Sulphate (mg/L)					430				45					9.1

Bottle 6 S3_ 5.25 6.00	Sequence 1				Sequence 2				Sequence 3				Final		
	Start Seq 1 28/01/2010 10:45	24 hour bottle readings 29/01/2010 10:20	48 hour bottle readings 30/01/2010 10:10	72 hour bottle readings 31/01/2010 18:00	Sequence 1 Liquor	Start Seq 2 3/02/2010 16:00	24 hour bottle readings 4/02/2010 15:30	48 hour bottle readings 5/02/2010 14:45	72 hour bottle readings 6/02/2010 19:15	Sequence 2 Liquor	Start Seq 3 10/02/2010 11:20	24 hour bottle readings 11/02/2010 13:27		48 hour bottle readings 12/02/2010 15:00	72 hour bottle readings 13/02/2010 19:46
Elapsed Time (days)	0.0	1.0	2.0	3.3											
Solids Mass (g) (wet)	1183.3					1969.03					1552.82				
Solids + Liquor Mass (g)	4733.16	4725.8	4722.8	4712.8		4755.8	4728.8	4721.8	4692.8		4732.8	4718.8	4692.8	4668.8	
Liquor Mass	3549.87					2786.77					3179.98				
Temp (Deg C)	22.3	23.9	24.2	28.9		26.3	28.2	26.5	31.1		24.6	26.9	30	29.5	
pH	10.22	9.76	9.8	9.6		10.27	10	10.03	9.75		10.26	9.86	9.73	9.75	
ORP (mV Ag/AgCl)	195	210	177	195		180	190	184	192		164	180	170	145	
EC (uS/cm)	1059	2298	2270	2424		584	1156	1169	1347		246.2	840	880	776	
Calcium (µg/L)					2660					1910					2380
Iron (µg/L)					110					<100					<100
Magnesium (µg/L)					1520					611					595
Phosphorus (µg/L)					<100					<100					<100
Potassium (µg/L)					30200					13700					14500
Silicon (µg/L)					3910					4770					5180
Sodium (µg/L)					744000					312000					271000
Aluminium (µg/L)					170					230					1100
Antimony (µg/L)					<5					<5					<5
Arsenic (µg/L)					140					120					120
Barium (µg/L)					19					6.8					6.6
Beryllium (µg/L)					<5					<5					<5
Bismuth (µg/L)					<5					<5					<5
Boron (µg/L)					2400					1200					900
Cadmium (µg/L)					11					<5					<5
Chromium (µg/L)					7.5					6.9					<5
Cobalt (µg/L)					<5					<5					<5
Copper (µg/L)					32					7.8					5
Lead (µg/L)					<5					<5					<5
Lithium (µg/L)					<5					<5					<5
Manganese (µg/L)					<5					<5					<5
Molybdenum (µg/L)					58					15					12
Nickel (µg/L)					<5					<5					<5
Selenium (µg/L)					7.1					<5					<5
Silver (µg/L)					<5					<5					<5
Strontium (µg/L)					1200					250					210
Thallium (µg/L)					3600					2100					6.8
Tin (µg/L)					<5					<5					<5
Uranium (µg/L)					6000					2200					1900
Vanadium (µg/L)					3500					3000					2700
Zinc (µg/L)					11					7.8					93
Mercury (µg/L)					<0.1					<0.1					<0.1
Acidity as CaCO3 (mg/L)					<20					<20					<20
Total Alkalinity as CaCO3 (mg/L)					524					409					477
Bicarbonate as CaCO3 (mg/L)					306					291					352
Carbonate as CaCO3 (mg/L)															
Hydroxide as CaCO3 (mg/L)															
Electrical Conductivity (µS/cm)					2910					1200					1050
Ammonia as N (mg N/L)					<1					<1					<1
pH (pH)					9.4					9.1					9.1
Total Organic Carbon (mg/L)					3.2					2.9					2.0
Chloride (mg/L)					370					76					24
Bromide (mg/L)					1.7					1.4					3.6
Fluoride (mg/L)					5.9					3.8					3.7
Nitrate (mg/L)					58					10					2.2
Nitrite (mg/L)					<0.5					<0.5					<0.5
Orthophosphate (mg/L)					<0.5					<0.5					<0.5
Sulphate (mg/L)					380					87					42

## Appendix 5: Column Test Results

COLUMN 1A		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6
Tails Residue + DI water	Start						
Date Started		12/3/2010	29/3/2010	15/4/2010	21/4/2010	17/5/2010	30/6/2010
Date Completed		22/3/2010	8/4/2010	16/4/2010	13/5/2010	25/6/2010	23/7/2010
Elapsed Time (days)		10	10	1	22	39	23
Solids Mass (g) (wet)	7286	7286	7286				
Final Liquor Mass discharge (g)		1589	1314	1260.34	1427	1277.2	421.37
Calcium (µg/L)		404	573	985	1100	700	800
Iron (µg/L)		170	<100	<100	<100	< 100	< 100
Magnesium (µg/L)		1440	830	360	600	1000	900
Phosphorus (µg/L)		<100	<100	<100	<100	< 100	< 100
Potassium (µg/L)		562000	325000	72800	160000	75000	87000
Silicon (µg/L)		7480	8150	4030	5700	5400	5700
Sodium (µg/L)		12700000	7550000	1380000	3500000	1800000	1700000
Aluminium (µg/L)		65	76	43	50	41	30
Antimony (µg/L)		<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		850	660	200	580	460	600
Barium (µg/L)		100	61	14	30	43	37
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5
Boron (µg/L)		14000	9600	2800	8300	5800	9200
Cadmium (µg/L)		<5	<5	<5	0.2	<0.2	<0.2
Chromium (µg/L)		150	100	15	64	42	56
Cobalt (µg/L)		<5	<5	<5	<5	<5	<5
Copper (µg/L)		26	20	<5	8	6	<5
Lead (µg/L)		<5	<5	<5	<5	<5	<5
Lithium (µg/L)		<5	<5	<5	<5	<5	<5
Manganese (µg/L)		<5	<5	<5	<5	<5	<5
Molybdenum (µg/L)		680	370	48	130	54	32
Nickel (µg/L)		<5	<5	<5	<5	<5	<5
Selenium (µg/L)		83	51	<5	25	6	<5
Silver (µg/L)		<5	<5	<5	<5	<5	<5
Strontium (µg/L)		190	170	100	130	320	230
Thallium (µg/L)		<5	<5	<5	<5	<5	<5
Tin (µg/L)		<5	<5	<5	<5	<5	<5
Uranium (µg/L)		130000	71000	12000	33000	12000	10000
Vanadium (µg/L)		19000	15000	8600	19000	15000	18000
Zinc (µg/L)		170	150	270	550	150	350
Mercury (µg/L)		<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO <sub>3</sub> (mg/L)		<20	<20	<20	< 20	< 20	< 20
Total Alkalinity as CaCO <sub>3</sub> (mg/L)		23700	12100	2240	8600	3400	4900
Bicarbonate as CaCO <sub>3</sub> (mg/L)		5250	2430	666	21	1300	420
Electrical Conductivity (µS/cm)		37700	21900	6020	13000	6100	5900
Ammonia as N (mg N/L)		<2	<2	<1	< 1	< 1	< 1
pH (pH)		10	10.2	10.2	10	9.9	9.8
Total Organic Carbon (mg/L)		23	9.8	2.8	6.6	17	12
Chloride (mg/L)		5300	2800	540	1400	260	140
Bromide (mg/L)		14	7.3	1.4	< 10	< 5	0.9
Fluoride (mg/L)		8.3	5.9	2.2	< 10	< 5	6.7
Nitrate (mg/L)		140	67	15	35	40	< 0.1
Nitrite (mg/L)		<0.5	<0.5	<0.5	< 10	< 5	< 0.1
Orthophosphate (mg/L)		<0.5	<0.5	<0.5	< 10	< 5	< 0.5
Sulphate (mg/L)		2400	1500	310	930	190	130
ORP (mV)		130	140	149	160	150	150



COLUMN 1B		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10	Sequence 11
YYS156A 11.25m - 12m	Start											
Date Started		23/3/2010	8/4/2010	20/4/2010	17/5/2010	25/6/2010	13/9/2010	30/9/2010	10/10/2010	18/10/2010	1/11/2010	9/11/2010
Date Completed		7/4/2010	20/4/2010	17/5/2010	25/6/2010	13/9/2010	30/9/2010	1/10/2010	11/10/2010	19/10/2010	2/11/2010	10/11/2010
Elapsed Time (days)		15	12	27	39	80	17	1	1	1	1	1
Solids Mass (g) (wet)	2671	7286	7286									
Liquor To Displace 1BV (g)		867.4	812.6	772.12	981.66	881.59	798.7	714.49	764.19	759.79	648.51	725.29
Calcium (µg/L)		10100	3620	2700	2000	1500	2000	<10000	1700	2100	<5000	1000
Iron (µg/L)		<100	<100	<100	<100	<100	<100	<10000	<1000	<1000	<500	60
Magnesium (µg/L)		391000	125000	56000	20000	11000	20000	<10000	2300	1600	<5000	600
Phosphorus (µg/L)		<100	<100	<100	200	<1000	200	<10000	7400	2000	13000	540
Potassium (µg/L)		806000	500000	400000	250000	230000	250000	130000	90000	64000	52000	46000
Silicon (µg/L)		3880	2380	2500	5300	280	5300	2600	<100	1600	50000	4100
Sodium (µg/L)		10100000	7380000	5200000	4800000	3000000	4800000	2000000	1600000	960000	720000	490000
Aluminium (µg/L)		54	9.6	<5	<5	15	<5	940	57	57	77	60
Antimony (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		140	170	250	330	310	330	270	310	280	280	370
Barium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<1
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<10
Boron (µg/L)		9400	6700	7500	9500	10000	9500	8600	8200	7100	5700	8400
Cadmium (µg/L)		15	18	<0.2	<0.2	18	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)		76	68	59	52	31	52	10	<5	<5	<5	<1
Cobalt (µg/L)		<5	<5	<5	<5	<5	<5	10	<5	<5	<5	<1
Copper (µg/L)		16	6.2	11	<5	8	<5	190	<5	<5	350	200
Lead (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<1
Lithium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<10
Manganese (µg/L)		6.1	<5	<5	<5	<5	<5	36	<5	<5	<5	<5
Molybdenum (µg/L)		1300	1500	1100	490	670	490	520	210	130	94	89
Nickel (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<1
Selenium (µg/L)		150	81	89	65	26	65	19	7	<5	<5	2
Silver (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Strontium (µg/L)		940	330	210	120	87	120	75	48	31	23	21
Thallium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Tin (µg/L)		420	610	670	700	620	700	630	420	320	320	310
Uranium (µg/L)		64000	53000	44000	32000	24000	32000	19000	11000	6800	4600	3600
Vanadium (µg/L)		1200	1200	1800	2500	2000	2500	2300	2700	2600	2500	3600
Zinc (µg/L)		150	82	100	73	90	73	170	170	160	130	110
Mercury (µg/L)		<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		<20	<20	<20	<20	<20	<20	<20	<20	<20	<20	<20
Total Alkalinity as CaCO3 (mg/L)		7430	6290	6200	5700	5200	5700	2800	1900	840	1300	960
Bicarbonate as CaCO3 (mg/L)		4170	3570	1200	2700	470	2700	1200	700	840	250	190
Electrical Conductivity (µS/cm)		35300	23900	18000	14000	11000	14000	7700	5100	3200	3000	2400
Ammonia as N (mg N/L)		<2	<1	<1	<1	<1	<1	<1	<1	<1	<1	0.08
pH (pH)		9.3	9.4	9.6	9.4	9.7	9.4	9.8	9.8	8.1	9.7	9.8
Total Organic Carbon (mg/L)		6.6	7.8	<10	5.3	<5	5.3	18	730	<5	<5	<5
Chloride (mg/L)		8900	6900	3700	1900	1700	1900	1000	530	260	150	74
Bromide (mg/L)		11	6.1	15	<0.5	5.1	<0.5	<5	<1.8	1.1	1.5	<5
Fluoride (mg/L)		5.1	1.6	5.8	8.8	10	8.8	8.9	13	13	12	14
Nitrate (mg/L)		220	230	120	40	19	40	7.9	3.7	2100	0.8	<0.02
Nitrite (mg/L)		<0.5	<0.5	<0.1	<0.1	<5	<0.1	10	<5	<10	1.6	0
Orthophosphate (mg/L)		<0.5	<0.5	<0.5	<0.5	<0.5	<0.5	<5	1.2	0.8	1.4	0.6
Sulphate (mg/L)		4300	3600	2000	1100	1000	1100	620	330	680	110	21
ORP (mV)		140	186	70	190	53	190	200	95	210	150	Ins Sample

COLUMN 2A		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10
YYS158 3.75m - 4.5m	Start										
Date Started		19/3/2010	31/3/2010	6/4/2010	12/4/2010	19/4/2010	27/4/2010	3/5/2010	10/5/2010	14/5/2010	18/5/2010
Date Completed		23/3/2010	1/4/2010	7/4/2010	13/4/2010	20/4/2010	28/4/2010	4/5/2010	11/5/2010	15/5/2010	19/5/2010
Elapsed Time (days)		4	1	1	1	1	1	1	1	1	1
Solids Mass (g) (wet)	8219	7286	7286								
Final Liquor Mass discharge (g)		1438.83	1380.23	1359	1313.79	1354.64	1363.47	1383	1382.69	1422.7	1393.26
Calcium (µg/L)		61600	16000	18000	30500	23300	19000	13000	13000	12000	11000
Iron (µg/L)		<100	<100	<100	<100	<100	<100	<100	<100	<50	<100
Magnesium (µg/L)		79000	19900	22100	38500	29000	24000	18000	16000	15000	14000
Phosphorus (µg/L)		<100	<100	<100	<100	<100	<1000	5000	<1000	<1000	< 100
Potassium (µg/L)		136000	44200	52100	81400	66600	36000	51000	40000	34000	35000
Silicon (µg/L)		3050	1280	1520	2110	2030	1700	1800	1700	3900	1700
Sodium (µg/L)		886000	279000	325000	478000	361000	240000	83000	220000	210000	160000
Aluminium (µg/L)		26	120	27	<5	<5	<5	<5	<5	<50	<5
Antimony (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		7.5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Barium (µg/L)		15	8	<5	<5	<5	<5	<5	<5	<5	<5
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Boron (µg/L)		1100	460	530	700	560	490	410	460	410	450
Cadmium (µg/L)		<5	<5	<5	<5	<5	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Cobalt (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Copper (µg/L)		5.3	<5	<5	<5	<5	<5	<5	<5	<5	<5
Lead (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Lithium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Manganese (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Molybdenum (µg/L)		100	29	27	23	17	13	13	15	17	47
Nickel (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Selenium (µg/L)		25	9	8.9	<5	<5	<5	11	<5	<1	10
Silver (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Strontium (µg/L)		1500	360	410	640	480	360	300	260	240	210
Thallium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<1	<5
Tin (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Uranium (µg/L)		53	13	14	66	39	43	56	42	80	51
Vanadium (µg/L)		66	36	41	47	46	38	48	47	41	51
Zinc (µg/L)		170	160	90	170	110	130	160	140	140	150
Mercury (µg/L)		<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		300	290	310	<20	<20	< 20	<20	< 20	25	< 20
Total Alkalinity as CaCO3 (mg/L)		104	59	63	83	72	72	78	950	50	72
Bicarbonate as CaCO3 (mg/L)		104	59	63	83	72	72	35	27	50	73
Electrical Conductivity (µS/cm)		5260	1620	1780	2690	2180	1600	1600	1500	1200	1100
Ammonia as N (mg N/L)		<1	<1	<1	<1	<1	<1	<1	<1	0.04	< 1
pH (pH)		7.9	7.8	7.7	8.1	8.1	7.9	8	9.1	8.5	8
Total Organic Carbon (mg/L)		2.6	3.9	1.5	1.2	2.7	8.9	10	7.1	< 5	< 10
Chloride (mg/L)		1200	380	440	770	600	360	360	400	290	220
Bromide (mg/L)		1.5	3.9	<0.5	<0.5	1.3	< 5	<5	< 5	< 5	1.5
Fluoride (mg/L)		<0.5	<0.5	<0.5	0.7	0.6	< 5	0.9	< 5	2.5	0.9
Nitrate (mg/L)		23	8	6.8	11	10	8.1	5.4	< 5	1.6	4.2
Nitrite (mg/L)		<0.5	<0.5	<0.5	<0.5	<0.5	< 5	<0.1	< 5	0.24	< 0.1
Orthophosphate (mg/L)		<0.5	<0.5	<0.5	<0.5	<0.5	< 0.5	< 0.5	< 5	0.07	< 0.5
Sulphate (mg/L)		450	120	140	300	220	49	130	170	55	110
ORP (mV)		180	210	210	220	220	110	170	230	70	110

COLUMN 2B		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10
YYS156A 0.7m - 1.5m	Start										
Date Started		26/3/2010	7/4/2010	16/4/2010	28/4/2010	5/5/2010	18/5/2010	26/5/2010	3/6/2010	11/6/2010	22/6/2010
Date Completed		6/4/2010	16/4/2010	28/4/2010	5/5/2010	18/5/2010	26/5/2010	3/6/2010	11/6/2010	22/6/2010	5/7/2010
Elapsed Time (days)		11	9	12	7	13	8	8	8	11	13
Solids Mass (g) (wet)	2783.2										
Liquor to displace 1 BV (g)		947	895	879	813.81	859.21	874.34	889.32	890.72	825.48	813.92
Calcium (µg/L)		626000	406000	480000	440000	500000	500000	490000	470000	480000	500000
Iron (µg/L)		<100	<100	<100	<100	<100	<100	<100	<100	<100	<100
Magnesium (µg/L)		839000	276000	210000	160000	160000	140000	140000	127000	130000	120000
Phosphorus (µg/L)		<100	<100	<1000	<1000	<1000	< 1000	<100	<100	<100	<100
Potassium (µg/L)		952000	493000	410000	370000	370000	330000	310000	270000	230000	240000
Silicon (µg/L)		11000	9340	9700	9500	8000	8200	19000	19000	20000	9500
Sodium (µg/L)		6950000	3300000	2200000	1500000	1000000	780000	810000	690000	620000	550000
Aluminium (µg/L)		110	7.2	<5	<5	<5	<5	<5	<5	<5	<5
Antimony (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		45	33	28	24	23	23	19	20	19	16
Barium (µg/L)		58	33	18	21	24	23	20	19	20	20
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Boron (µg/L)		47000	28000	16000	12000	10000	7900	6900	5400	4900	4200
Cadmium (µg/L)		6.2	6.2	2.8	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Cobalt (µg/L)		5.2	<5	<5	<5	<5	<5	<5	<5	<5	<5
Copper (µg/L)		14	11	<5	36	5	5	<5	<5	<5	<5
Lead (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Lithium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Manganese (µg/L)		17	5.7	<5	<5	<5	<5	<5	<5	<5	<5
Molybdenum (µg/L)		770	200	87	67	53	51	35	45	23	34
Nickel (µg/L)		9.6	5.2	<5	<5	12	13	15	13	15	17
Selenium (µg/L)		170	16	23	25	19	18	26	23	22	12
Silver (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Strontium (µg/L)		21000	8200	6400	5600	5800	5900	5400	5500	5500	5500
Thallium (µg/L)		<5	<5	<5	10	<5	<5	<5	<5	<5	<5
Tin (µg/L)		170	270	110	170	420	120	370	250	290	230
Uranium (µg/L)		210	200	100	150	49	56	69	84	78	89
Vanadium (µg/L)		180	190	140	150	130	130	110	130	120	110
Zinc (µg/L)		64	130	66	67	81	86	99	95	96	86
Mercury (µg/L)		<0.1	<0.1	1	1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		890	20	< 20	23	< 20	< 20	< 20	< 20	< 20	< 20
Total Alkalinity as CaCO3 (mg/L)		125	106	99	770	94	80	79	93	74	87
Bicarbonate as CaCO3 (mg/L)		125	106	99	22	94	80	79	93	74	87
Electrical Conductivity (µS/cm)		22800	14200	10000	8800	7100	6300	5600	5300	5000	3700
Ammonia as N (mg N/L)		<1	<1	<1	<1	<1	<1	<1	<1	<1	<1
pH (pH)		7.9	7.9	8.1	7.9	7.9	8	7.7	8	7.8	7.7
Total Organic Carbon (mg/L)		28	17	80	12	< 10	10	6	6.6	9.2	< 5
Chloride (mg/L)		5100	1100	< 5	1100	620	500	340	300	240	280
Bromide (mg/L)		8.1	1.3	< 5	< 10	2.8	2.4	< 0.5	< 0.5	< 0.5	0.8
Fluoride (mg/L)		4.5	2.8	< 5	< 10	3.4	3.6	3.5	3.3	3.8	3.2
Nitrate (mg/L)		120	33	25	24	19	12	9.3	9.4	8.4	6.3
Nitrite (mg/L)		<0.5	<0.5	< 5	< 10	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1
Orthophosphate (mg/L)		<0.5	<0.5	< 5	< 10	< 0.5	< 0.5	< 0.5	< 0.5	< 0.5	< 0.5
Sulphate (mg/L)		9100	9100	1400	4400	3100	3100	2400	2300	2200	2400
ORP (mV)		190	214	110	280	110	120	200	190	190	190

COLUMN 3A		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10
YYS156A 1.5m -2.5m	Start										
Date Started		31/3/2010	12/4/2010	19/4/2010	27/4/2010	3/5/2010	10/5/2010	17/5/2010	24/5/2010	8/6/2010	17/6/2010
Date Completed		8/4/2010	13/4/2010	20/4/2010	28/4/2010	5/5/2010	11/5/2010	18/5/2010	25/5/2010	9/6/2010	18/6/2010
Elapsed Time (days)		8	1	1	1	2	1	1	1	1	1
Solids Mass (g) (wet)	5323.6	7286	7286								
Final Liquor Mass discharge (g)		1617.48	1270	1502.88	1244.5	1434.49	1376.65	1379.32	1417.02	1374.4	1428.08
Calcium (µg/L)		2010000	293000	398000	440000	420000	460000	480000	530000	400000	490000
Iron (µg/L)		<100	<100	<100	<100	<100	<100	<100	<100	<100	<100
Magnesium (µg/L)		1470000	156000	130000	120000	110000	100000	100000	62000	200000	110000
Phosphorus (µg/L)		<100	<100	<100	<1000	<1000	<1000	<1000	<1000	<100	<100
Potassium (µg/L)		1250000	305000	276000	240000	250000	200000	190000	99000	260000	130000
Silicon (µg/L)		15000	12000	12000	15000	19000	16000	13000	9000	21000	24000
Sodium (µg/L)		12000000	2080000	1540000	1100000	550000	410000	290000	89000	1500000	650000
Aluminium (µg/L)		42	<5	<5	<5	<5	<5	<5	<5	<5	<5
Antimony (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		46	22	18	18	19	12	14	8	5	6
Barium (µg/L)		530	52	46	42	46	40	42	30	30	20
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Boron (µg/L)		18000	8300	7100	5000	4800	3500	2800	1200	770	580
Cadmium (µg/L)		<5	<5	<5	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Cobalt (µg/L)		9.7	<5	<5	<5	<5	<5	<5	<5	<5	<5
Copper (µg/L)		23	<5	<5	8	<5	10	6	7	5	<5
Lead (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Lithium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Manganese (µg/L)		110	<5	<5	<5	<5	8	<5	<5	<5	<5
Molybdenum (µg/L)		900	76	50	28	19	12	21	<5	<5	<5
Nickel (µg/L)		31	<5	<5	<5	8	<5	9	11	16	15
Selenium (µg/L)		330	<5	<5	<5	12	<5	8	6	14	17
Silver (µg/L)		6.3	<5	<5	<5	<5	<5	<5	<5	<5	<5
Strontium (µg/L)		36000	4200	3900	4300	2100	3700	4000	3500	3100	2800
Thallium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Tin (µg/L)		6	<5	<5	<5	<5	<5	<5	<5	<5	<5
Uranium (µg/L)		550	500	380	370	410	330	230	120	93	98
Vanadium (µg/L)		140	160	130	120	130	89	90	69	56	59
Zinc (µg/L)		270	270	130	140	150	130	160	100	200	170
Mercury (µg/L)		<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		26	<20	<20	<20	<20	<20	510	<20	<20	<20
Total Alkalinity as CaCO3 (mg/L)		135	146	129	120	140	460	<20	64	62	64
Bicarbonate as CaCO3 (mg/L)		135	146	129	120	100	<20	<20	65	62	64
Electrical Conductivity (µS/cm)		57900	9630	8160	6700	5500	3600	5900	2400	2100	2000
Ammonia as N (mg N/L)		1	<1	<1	<1	<1	<1	<1	<1	<1	<1
pH (pH)		7.6	8.3	8.2	8.3	8.2	6.8	2.3	7.8	7.5	7.7
Total Organic Carbon (mg/L)		28	18	7	19	37	11	<10	<10	7.3	6.6
Chloride (mg/L)		18000	80	26	6.4	3.8	<5	1.4	8.4	<0.5	<0.5
Bromide (mg/L)		48	<0.5	<0.5	<5	<5	<0.5	<0.5	<0.5	<0.5	<0.5
Fluoride (mg/L)		<0.5	1.4	1.8	1.7	1	1.1	1.9	1.5	1.5	1.4
Nitrate (mg/L)		840	6.1	4.5	5.7	5.1	6.5	4.7	0.9	<0.1	<0.1
Nitrite (mg/L)		<0.5	<0.5	2.2	<0.1	<0.1	1.2	<0.1	<0.1	<0.1	<0.1
Orthophosphate (mg/L)		<0.5	<0.5	<0.5	<0.05	<0.5	<0.05	<0.5	<0.5	<0.5	<0.5
Sulphate (mg/L)		6200	6100	5600	1100	6700	7600	3000	1700	1300	1200
ORP (mV)		210	238	236	120	170	180	240	150	210	220

COLUMN 3B		Sequence 1	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10
YYS158 2.5m - 3.5m	Start										
Date Started		9/4/2010	19/4/2010	27/4/2010	8/5/2010	18/5/2010	26/5/2010	26/5/2010	2/6/2010	10/6/2010	18/6/2010
Date Completed		19/4/2010	27/4/2010	8/5/2010	16/5/2010	26/5/2010	2/6/2010	2/6/2010	10/6/2010	18/6/2010	29/6/2010
Elapsed Time (days)		10	8	11	8	8	7	7	8	8	11
Solids Mass (g) (wet)	2948.4										
Liquor to displace 1 BV (g)		772.38	775.65	1010.66	755.74	941.13	770	789.21	770	775.17	779.7
Calcium (µg/L)		465000	430000	420000	430000	420000	470000	460000	510000	530000	460000
Iron (µg/L)		<100	<100	<100	<100	<100	<100	<100	<100	<100	<100
Magnesium (µg/L)		447000	340000	210000	190000	180000	180000	130000	51000	41000	95000
Phosphorus (µg/L)		<100	<1000	<1000	<1000	<1000	<1000	<100	<100	<100	<100
Potassium (µg/L)		478000	390000	320000	290000	250000	260000	150000	71000	50000	120000
Silicon (µg/L)		9130	11000	13000	14000	11000	12000	19000	19000	21000	11000
Sodium (µg/L)		3780000	2900000	1800000	1400000	1100000	930000	740000	60000	34000	590000
Aluminium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Antimony (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Arsenic (µg/L)		22	24	18	16	17	15	10	6	8	7
Barium (µg/L)		42	40	38	37	35	36	19	25	18	18
Beryllium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Bismuth (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Boron (µg/L)		10000	8600	7800	6300	5400	4600	5300	2600	2200	1900
Cadmium (µg/L)		19	12	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)		8.1	<5	<5	<5	6	<5	<5	<5	<5	<5
Cobalt (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Copper (µg/L)		<5	8	5	<5	12	7	6	13	<5	<5
Lead (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Lithium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Manganese (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Molybdenum (µg/L)		170	130	76	61	51	47	53	19	25	15
Nickel (µg/L)		6.1	<5	<5	<5	12	10	11	14	14	9
Selenium (µg/L)		38	38	21	14	26	16	37	19	25	11
Silver (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Strontium (µg/L)		8100	7400	5200	5000	5000	4700	4400	3800	3400	3300
Thallium (µg/L)		<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Tin (µg/L)		660	410	370	310	390	450	310	290	280	320
Uranium (µg/L)		450	450	390	400	310	260	260	180	160	190
Vanadium (µg/L)		120	150	110	100	130	94	79	67	66	61
Zinc (µg/L)		91	77	63	62	77	76	94	82	97	84
Mercury (µg/L)		<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		<20	<20	<20	<20	<20	<20	<20	<20	<20	<20
Total Alkalinity as CaCO3 (mg/L)		139	140	1100	1000	120	110	130	96	93	97
Bicarbonate as CaCO3 (mg/L)		139	140	30	30	120	110	130	96	93	97
Electrical Conductivity (µS/cm)		16700	13000	10000	8700	7400	6600	7400	3900	3600	3200
Ammonia as N (mg N/L)		<1	<1	<1	<1	<1	<1	<1	<1	<1	<1
pH (pH)		8.2	8.1	8	8	8.2	8.1	8	7.8	7.9	7.7
Total Organic Carbon (mg/L)		14	26	6.5	6.1	<10	<10	8.4	12	<5	6.2
Chloride (mg/L)		2500	<5	1200	950	590	480	720	390	270	410
Bromide (mg/L)		2.6	<5	<10	<10	3.3	2.4	<0.5	<0.5	<0.5	1.1
Fluoride (mg/L)		1.5	<5	<10	<10	2.7	2.6	2.7	1.7	1.5	2.1
Nitrate (mg/L)		100	65	28	33	22	18	27	14	9.3	8.1
Nitrite (mg/L)		<0.5	<5	<10	<10	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1
Orthophosphate (mg/L)		<0.5	<5	<10	<10	<0.5	<0.5	<0.5	<0.5	<0.5	<0.5
Sulphate (mg/L)		7800	1800	5600	4600	3700	3300	3000	2000	1700	2700
ORP (mV)		233	100	130	140	94	130	210	200	210	140

COLUMN 4A	YC BARREN	Sequence 1	Sequence - mistake	Sequence - Flush	Sequence 2	Sequence 3	Sequence 4	Sequence 5	Sequence 6	Sequence 7	Sequence 8	Sequence 9	Sequence 10
YYS159 4.5m - 5.2m	FEED LIQUOR												
Date Started	Start	21/4/2010	27/4/2010	29/4/2010	30/4/2010	5/5/2010	10/5/2010	17/5/2010	24/5/2010	29/9/2010	4/10/2010	10/10/2010	14/10/2010
Date Completed		22/4/2010	28/4/2010	30/4/2010	30/4/2010	6/5/2010	11/5/2010	18/5/2010	25/5/2010	30/9/2010	5/10/2010	11/10/2010	15/10/2010
Elapsed Time (days)	0	1	1	1	1	1	1	1	1	1	1	1	1
Solids Mass (g) (wet)	5904.7	7286			7286								
Final Liquor Mass discharge (g)		1314.8	1466.7	1379	1590.91	1278.51	1453	1370.53	1395.68	988.6	1336.09	1471.59	1358.95
Calcium (µg/L)	1100	11400	4100	5000	3600	2400	5000	4400	3500	1700	1900	3100	3100
Iron (µg/L)	200	<100	<100	200	300	100	200	<50	<100	<100	<100	2800	<100
Magnesium (µg/L)	<500	380000	8400	6300	6900	2000	260	1100	<1000	800	800	1600	1000
Phosphorus (µg/L)	2100	<100	<1000	<1000	<1000	<1000	4000	2400	6100	6100	7200	14000	80000
Potassium (µg/L)	1600000	1200000	650000	1100000	1400000	1600000	2100000	1400000	1600000	2400000	1700000	1800000	1900000
Silicon (µg/L)	52000	26000	21000	42000	44000	65000	99000	180000	110000	81000	100000	64000	65000
Sodium (µg/L)	52000000	27400000	16000000	34000000	43000000	44000000	52000000	49000000	57000000	96000000	56000000	73000000	73000000
Aluminium (µg/L)	170	<5	<5	<5	<5	<5	88	<50	74	70	33	350	110
Antimony (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	<5	14	<5	<5	<5
Arsenic (µg/L)	13000	3900	990	8500	1100	1400	7400	4400	12000	7700	8700	7500	8000
Barium (µg/L)	6	<5	9	<5	<5	<5	<5	11	<5	6	<5	<5	<5
Beryllium (µg/L)	<5	<5	<5	<5	<5	<5	<5	<1	<5	<5	<5	<5	<5
Bismuth (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Boron (µg/L)	56000	16000	7700	35000	41000	46000	51000	48000	60000	62000	72000	64000	66000
Cadmium (µg/L)	1.5	<5	0.3	0.8	0.5	<0.2	<0.2	<5	<0.2	<0.2	<0.2	<0.2	<0.2
Chromium (µg/L)	3000	220	42	2500	3000	3400	76	51	2400	350	320	280	320
Cobalt (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Copper (µg/L)	110	37	25	53	58	72	73	33	50	130	200	95	95
Lead (µg/L)	<5	<5	8	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Lithium (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	<5	7	<5	350	<5
Manganese (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5	<5
Molybdenum (µg/L)	2500	1900	1100	2500	2500	2600	2600	2200	2300	2900	3000	2700	2800
Nickel (µg/L)	25	13	8	15	14	15	20	30	25	31	34	30	31
Selenium (µg/L)	600	370	170	440	550	630	620	120	650	610	700	500	540
Silver (µg/L)	<5	<5	<5	<5	<5	<5	<5	<5	9	<5	<5	<5	<5
Strontium (µg/L)	57	1400	160	200	250	250	230	350	230	230	270	210	210
Thallium (µg/L)	9	<5	<5	<5	<5	<5	<5	<1	<5	<5	<5	<5	<5
Tin (µg/L)	6	19	8	<5	<5	<5	21	<5	41	36	35	7	30
Uranium (µg/L)	48000	20000	16000	29000	49000	51000	45000	39000	52000	55000	35000	55000	56000
Vanadium (µg/L)	110000	20000	11000	39000	41000	53000	63000	74000	84000	88000	100000	100000	110000
Zinc (µg/L)	1600	480	250	620	560	1100	1700	130	2200	1300	1600	1300	1600
Mercury (µg/L)	< 0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	<0.1	0.1	0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)	< 20	<20	< 20	< 20	< 20	<20	< 20	< 0.1	< 20	<20	<20	<20	<20
Total Alkalinity as CaCO3 (mg/L)	79000	38000	26000	52000	64000	124000	92000	83000	84000	135000	120000	83000	84000
Bicarbonate as CaCO3 (mg/L)	110	3230	5900	3100	4900	<20	95	< 10	1200	2700	670	<20	<20
Electrical Conductivity (µS/cm)	78000	60000	38000	63000	74000	83000	81000	275000	78000	25000	24000	76000	76000
Ammonia as N (mg N/L)	< 1	<1	< 1	< 1	< 1	<1	< 1	0.38	< 1	<1	<1	2.8	7
pH (pH)	11	10.1	9.9	10	10	10	11	11	11	11	11	11	11
Total Organic Carbon (mg/L)	770	29	89	55	28	<20	39	32	< 20	3200	860	8800	710
Chloride (mg/L)	15000	13000	5300	9400	11000	20000	19000	22000	21000	22000	20000	14000	10000
Bromide (mg/L)	< 5	28	< 5	35	41	<0.5	57	240	91	99	96	67	59
Fluoride (mg/L)	8.8	2.6	< 5	6.2	< 5	18	8.4	42	28	22	25	23	24
Nitrate (mg/L)	850	440	300	570	700	<0.1	960	180	800	850	840	560	500
Nitrite (mg/L)	< 5	<0.5	< 5	< 5	< 5	<0.1	< 5	1.8	< 5	<5	<5	<5	<5
Orthophosphate (mg/L)	< 0.05	<0.5	< 5	< 5	< 5	16	< 5	8.7	16	18	20	14	13
Sulphate (mg/L)	2900	8800	1100	2100	2200	9700	13000	4400	10000	11000	10000	9800	6700
ORP (mV)	26	146	56	50	41	77	39	86	31	200	140	62	77

COLUMN 4B		Sequence 1	Sequence 2	Sequence 3
YYS156A 12-12.75m	Start			
Date Started		22/4/2010	3/5/2010	10/5/2010
Date Completed		3/5/2010	10/5/2010	24/5/2010
Elapsed Time (days)		11	7	14
Solids Mass (g) (wet)	2558.9			
Liquor to displace 1 BV (g)		828.07	1092.69	786.21
Calcium (µg/L)		9300	9400	3200
Iron (µg/L)		<100	<100	<100
Magnesium (µg/L)		490000	420000	74000
Phosphorus (µg/L)		<1000	< 1000	800
Potassium (µg/L)		1400000	1100000	1500000
Silicon (µg/L)		2200	12000	2900
Sodium (µg/L)		20000000	20000000	61000000
Aluminium (µg/L)		<5	<5	66
Antimony (µg/L)		<5	<5	<5
Arsenic (µg/L)		250	160	470
Barium (µg/L)		11	28	61
Beryllium (µg/L)		<5	<5	<5
Bismuth (µg/L)		<5	<5	<5
Boron (µg/L)		7700	6600	14000
Cadmium (µg/L)		<0.2	4	<0.2
Chromium (µg/L)		25	43	92
Cobalt (µg/L)		<5	<6	<5
Copper (µg/L)		34	1400	13
Lead (µg/L)		<5	120	23
Lithium (µg/L)		<5	<5	13
Manganese (µg/L)		<5	<5	7
Molybdenum (µg/L)		4500	3300	3700
Nickel (µg/L)		6	10	10
Selenium (µg/L)		440	390	540
Silver (µg/L)		<5	<6	8
Strontium (µg/L)		1600	1200	500
Thallium (µg/L)		<5	11	<5
Tin (µg/L)		69	670	1800
Uranium (µg/L)		22000	20000	57000
Vanadium (µg/L)		530	660	1200
Zinc (µg/L)		120	340	950
Mercury (µg/L)		<0.1	<0.1	<0.1
Acidity as CaCO3 (mg/L)		< 20	< 20	<20
Total Alkalinity as CaCO3 (mg/L)		18000	15000	47000
Bicarbonate as CaCO3 (mg/L)		120	3700	6700
Electrical Conductivity (µS/cm)		56000	54000	65000
Ammonia as N (mg N/L)		< 1	< 1	<1
pH (pH)		9.5	9.5	9.9
Total Organic Carbon (mg/L)		19	22	<5
Chloride (mg/L)		21000	20000	14000
Bromide (mg/L)		55	74	54
Fluoride (mg/L)		< 5	5.9	9
Nitrate (mg/L)		710	560	260
Nitrite (mg/L)		< 5	< 5	130
Orthophosphate (mg/L)		< 5	< 5	<5
Sulphate (mg/L)		9000	9000	7900
ORP (mV)		33	91	100

## Appendix 6: Tails Ageing Test Results











## Chemical assay of residues from 8 month aging tests (composition of initial residues given for comparison)

IDENT	Al	Ca	CO2	F	Fe	K	Mg	Mn	Na	P	S	Si	SO4	TOC	Ag
UNITS	%	%	%	%	%	%	%	%	%	%	%	%	%	%	ppm
DETECTION LIMIT	0.01	0.01	0.07	0.01	0.01	0.01	0.01	0.005	0.01	0.005	0.01	0.01	0.05	0.05	0.1
YM0015 (Initial residue)	8.99	0.42	1.41		3.53	1.58	1.72	0.02	1.24	<0.01	0.05	28.36			
YM0015 OPEN A	8.51	0.34	1.8	0.14	3.32	1.47	1.59	0.015	1.76	0.02	0.11	27.1	0.3	0.05	<0.1
YM0015 OPEN B	8.32	0.33	1.8	0.14	3.36	1.4	1.55	0.015	1.85	0.015	0.11	26.9	0.35	<0.05	<0.1
YM0015 CLOSE A	8.37	0.34	1.4	0.13	3.37	1.4	1.56	0.015	1.56	0.02	0.07	27.3	0.25	<0.05	<0.1
YM0015 CLOSE B	8.66	0.35	1.2	0.14	3.42	1.48	1.61	0.015	0.9	0.025	0.05	28.3	0.05	0.05	<0.1
YM0046 (Initial residue)	1.61	13.77	24.09		0.72	0.4	9.37	<0.01	1.12	<0.01	0.08	13.28			0.05
YM0046 OPEN A	1.63	13.5	22.4	0.66	0.66	0.39	8.89	0.005	1.56	0.01	0.1	13.3	0.4	<0.05	<0.1
YM0046 OPEN B	1.58	13.6	22.8	0.67	0.64	0.39	9.03	0.01	1.41	0.01	0.09	13	0.35	0.1	0.2
YM0046 CLOSE A	1.56	13.8	24.2	0.67	0.62	0.38	9.14	0.005	1.13	0.01	0.06	13	0.3	0.1	<0.1
YM0046 CLOSE B	1.58	13.7	24.6	0.66	0.64	0.39	9.08	0.005	1.44	0.01	0.03	13.1	0.4	0.1	0.1
YM0074 (Initial residue)	10.64	0.35	1.16		4.31	1.69	1.66	0.02	1.2	0.01	0.05	27.05			<0.05
YM0074 OPEN A	9.76	0.32	1.4	0.13	4.1	1.55	1.53	0.025	1.55	0.025	0.1	25.3	0.25	0.05	<0.1
YM0074 OPEN B	9.93	0.32	1.2	0.13	4.09	1.58	1.59	0.025	1.09	0.03	0.07	25.6	0.15	<0.05	<0.1
YM0074 CLOSE A	10	0.33	1.4	0.13	4.05	1.52	1.58	0.025	1.46	0.025	0.06	25.6	0.25	<0.05	<0.1
YM0074 CLOSE B	10.1	0.35	1.2	0.13	4.1	1.57	1.6	0.025	0.93	0.03	0.05	26.1	0.1	<0.05	<0.1
YM0076 (Initial residue)	1.61	17.69	35.98		0.73	0.31	10.83	0.03	0.37	0.01	0.03	6.64			<0.05
YM0076 OPEN A	1.59	17	34.8	0.34	0.66	0.29	10.3	0.03	0.43	0.02	0.04	6.56	0.2	0.05	<0.1
YM0076 OPEN B	1.62	17.1	35	0.32	0.66	0.3	10.4	0.03	0.43	0.02	0.04	6.64	0.2	0.15	<0.1
YM0076 CLOSE A	1.65	17.1	35.6	0.33	0.7	0.31	10.3	0.035	0.37	0.02	0.04	6.74	0.2	0.05	<0.1
YM0076 CLOSE B	1.59	17.1	35.6	0.33	0.65	0.3	10.4	0.03	0.41	0.015	0.03	6.61	0.2	0.15	<0.1

## Chemical assay of residues from 8 month aging tests (composition of initial residues given for comparison)

IDENT	As	B	Ba	Be	Bi	Cd	Ce	Co	Cr	Cu	Hg	Li	Mo	Ni	Pb
UNITS	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
DETECTION LIMIT	0.5	5	10	0.5	0.1	0.1	1	0.2	20	0.5	0.05	4	0.1	2	0.5
YM0015 (Initial residue)	15.16		400		0.22	<0.1	<100	7.07	137	23.24			5.34	45	15.81
YM0015 OPEN A	15.5	80	340	1	0.2	<0.1	48	6	135	20	<0.05	10	6	43	15
YM0015 OPEN B	16	80	340	1.5	0.2	<0.1	49	6	125	19.5	<0.05	15	7	46	14.5
YM0015 CLOSE A	15.5	110	340	1.5	0.3	<0.1	49	6.5	130	21	<0.05	15	6.5	45	16.5
YM0015 CLOSE B	15	120	340	1.5	0.2	<0.1	52	6.5	125	20	<0.05	15	6	46	16.5
YM0046 (Initial residue)	2.98		<200		<0.1	<0.1	<100	2.86	52	18.76			3.43	28	5.07
YM0046 OPEN A	2.5	20	80	<0.5	<0.1	<0.1	10	2.4	45	14.5	<0.05	5	3.3	21	5
YM0046 OPEN B	2.5	20	80	<0.5	<0.1	<0.1	10	2.4	45	13	<0.05	5	3.3	20	4
YM0046 CLOSE A	2	10	80	<0.5	<0.1	<0.1	10	2.6	45	12	<0.05	5	3.6	22	4.5
YM0046 CLOSE B	2.5	10	80	<0.5	<0.1	<0.1	10	2.2	50	9.5	0.05	5	3	19	4
YM0074 (Initial residue)	21.21		400		0.27	<0.1	<100	7.47	128	27.98			5.58	46	17.18
YM0074 OPEN A	20	160	340	1.5	0.2	<0.1	55	6	135	26.5	<0.05	15	7	41	14.5
YM0074 OPEN B	19.5	140	340	1.5	0.2	<0.1	56	6.5	145	23	<0.05	15	7	44	16
YM0074 CLOSE A	20	90	340	1.5	0.2	<0.1	56	6.5	145	23.5	<0.05	15	6.5	43	16.5
YM0074 CLOSE B	20	90	360	1.5	0.2	<0.1	56	7	145	28	<0.05	15	7	45	17
YM0076 (Initial residue)	2.42		<200		<0.1	<0.1	<100	3.67	76	17.2			5.4	36	4.79
YM0076 OPEN A	2.5	30	180	<0.5	<0.1	<0.1	10	3.4	65	13	0.05	5	6	30	4.5
YM0076 OPEN B	3	30	200	<0.5	<0.1	<0.1	10	3.4	70	13.5	<0.05	5	5.5	30	4.5
YM0076 CLOSE A	3	10	180	<0.5	<0.1	<0.1	10	3.4	65	12.5	0.05	5	6	31	4
YM0076 CLOSE B	3	10	180	<0.5	<0.1	<0.1	10	3.2	70	13.5	0.05	5	5.5	30	4

## Chemical assay of residues from 8 month aging tests (composition of initial residues given for comparison)

IDENT	Sb	Sc	Se	Sn	Sr	Th	Tl	U3O8	V	W	Y	Zn
UNITS	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
DETECTION LIMIT	0.5	5	0.5	10	5	4	3	4	20	3	1	0.5
YM0015 (Initial residue)	0.1	11	<0.5		5560	19.61		226	222		11	40.9
YM0015 OPEN A	<0.5	10	<0.5	<10	5420	20	<3	135	385	<3	10	37
YM0015 OPEN B	<0.5	10	<0.5	<10	4940	15	<3	140	380	<3	10	36.5
YM0015 CLOSE A	<0.5	10	<0.5	<10	5320	20	<3	120	370	<3	10	39.5
YM0015 CLOSE B	<0.5	10	<0.5	<10	5260	20	<3	85	340	<3	10	41
YM0046 (Initial residue)	<0.1	<5	<0.5		928	3.07		64.4	84		<10	19.26
YM0046 OPEN A	<0.5	<5	<0.5	<10	880	5	<3	60	145	<3	3	15
YM0046 OPEN B	<0.5	<5	<0.5	<10	880	5	<3	60	140	<3	3	14.5
YM0046 CLOSE A	<0.5	<5	<0.5	<10	940	5	<3	55	135	<3	3	17.5
YM0046 CLOSE B	<0.5	<5	<0.5	<10	900	5	<3	65	145	<3	3	13.5
YM0074 (Initial residue)	<0.1	14	<0.5		4713	20.22		63.68	177		13	45.53
YM0074 OPEN A	<0.5	15	<0.5	<10	4340	20	<3	60	240	<3	12	41.5
YM0074 OPEN B	<0.5	15	<0.5	<10	4520	20	<3	50	240	<3	12	43
YM0074 CLOSE A	<0.5	15	<0.5	<10	4500	15	<3	55	245	<3	12	44
YM0074 CLOSE B	<0.5	15	<0.5	<10	4760	15	<3	45	240	<3	12	47
YM0076 (Initial residue)	<0.1	<5	<0.5		8184	3.14		90.97	49		<10	12.68
YM0076 OPEN A	<0.5	<5	<0.5	<10	7820	10	<3	105	110	<3	3	14
YM0076 OPEN B	<0.5	<5	<0.5	<10	8180	10	<3	105	95	<3	3	13.5
YM0076 CLOSE A	<0.5	<5	<0.5	<10	7960	5	<3	100	90	<3	3	14
YM0076 CLOSE B	<0.5	<5	<0.5	<10	7800	10	<3	105	95	<3	3	15

Mineralogical composition of residues from 8 month aging tests (composition of initial residues given for comparison)

	Quartz	Calcite	Dolomite	Albite	Microcline	Anatase	Carnotite	Kaolin	Smectite	Illite/ Mica	Sepiolite	Palygorskite	Goethite	Celestine	Gypsum	Halite
YM0015 (Initial residue)	34		1	1	5	<1	0.4	45	5	6			2	1		<1
YM0015-Closed A. 8 months	36	2	1	1	4	<1		43	5	2		4	1			
YM0015-Open A. 8 months	36	2	1	1	4	<1		42	6	2		4	1			
YM0046 (Initial residue)	5	13	38	1	2			6	22	1	8				3	1
YM0046-Closed A. 8 months	5	17	39					4	31		5					
YM0046-Open A. 8 months	4	17	39					4	30		5					
YM0074 (Initial residue)	23		1	1	4	<1	0.2	53	4	3		7	2	1		1
YM0074-Closed A. 8 months	24	1	2	1	3	<1		53	3	3		7	2			
YM0074-Open A. 8 months	23	1	2	1	3	<1		53	3	3		8	2			
YM0076 (Initial residue)	3	3	78	1	1		0.3	7	4					2	1	<1
YM0076-Closed A. 8 months	3	2	79		<1			5	10							
YM0076-Open A. 8 months	3	2	80		<1			5	10							




## Appendix 7: Particle Size Distributions

Sample: YYS 159 4.5-5.2m  
 Operator: Tim O'Connell  
 Submitter: SRK Consulting  
 File: L:\...\3813\000-038.SMP

Test Number: Avg of 2      Model: Fraunhofer, 1.331  
 Analyzed: 2/08/2010 2:30:25PM      Material: Fraunhofer / Water  
 Reported: 5/08/2010 11:25:41AM      Background: Water RI 1.331  
 Background: 2/08/2010 1:34:55PM      Smoothing: Medium

### Combined Report

#### Volume Frequency vs. Diameter

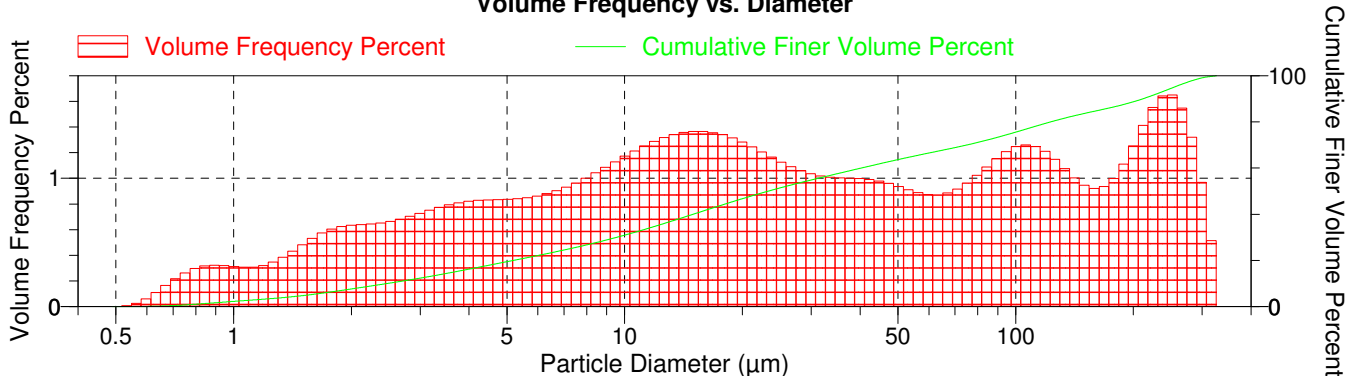

### Summary Report

#### Analysis Conditions

FlowRate: 12.0 l/m      Ultrasonic intensity: 50 %  
 Circulation time: 120 sec      Ultrasonic time: 120 sec

#### Particle Properties

Refractive Index: (Re)0.000, (Im)0.000  
 Density: 1.000 g/cm<sup>3</sup>  
 Smoothing: Medium  
 Truncate intensity data: No  
 Minimum signal fraction: 16.0 %

#### Analysis Liquid Properties

Refractive Index: 1.331  
 Viscosity: 0.798 cp  
 Temperature: 29.790 °C

#### User Parameters

Parameter 1: 0.000      Parameter 2: 0.000      Parameter 3: 0.000

#### Sample

Sample Concentration: 0.00523 %  
 Obscuration: 10.3 %

#### Volume Distribution Arithmetic Statistics

	Std Dev of 2		Std Dev of 2
Mean	64.84	0.007	Mode
Median	23.28	0.104	252.0
			0.000

#### Peaks

Peak Number	% of Dist.*	% of Dist. Std Dev of 2		Mean Std Dev of 2		Median Std Dev of 2		Mode
		Mean	Std Dev	Mean	Std Dev	Median	Std Dev	
1	64.5	17.22	1.2	12.14	0.120	15.45		
2	17.7	106.0	1.3	103.0	1.178	106.2		
3	14.9	234.1	0.2	232.7	0.498	252.0		

\* Peaks must comprise at least 5.00 % of the distribution.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:41AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
344.747	325.462	334.965	100.0	0.0	0.0
325.462	307.256	316.228	99.4	0.6	0.0
307.256	290.068	298.538	98.5	1.0	0.0
290.068	273.842	281.838	97.1	1.3	0.1
273.842	258.523	266.073	95.6	1.6	0.1
258.523	244.062	251.189	93.9	1.7	0.1
244.062	230.409	237.137	92.3	1.6	0.2
230.409	217.520	223.872	90.7	1.5	0.2
217.520	205.353	211.349	89.3	1.4	0.2
205.353	193.865	199.526	88.1	1.2	0.3
193.865	183.021	188.365	87.0	1.1	0.3
183.021	172.783	177.828	86.0	1.0	0.2
172.783	163.117	167.880	85.0	0.9	0.2
163.117	153.993	158.489	84.1	0.9	0.2
153.993	145.378	149.624	83.2	0.9	0.2
145.378	137.246	141.254	82.2	1.0	0.1
137.246	129.569	133.352	81.1	1.1	0.1
129.569	122.321	125.893	79.9	1.2	0.0
122.321	115.478	118.850	78.7	1.2	0.0
115.478	109.018	112.202	77.5	1.2	0.1
109.018	102.920	105.925	76.2	1.3	0.2
102.920	97.163	100.000	75.0	1.2	0.2
97.163	91.728	94.406	73.8	1.2	0.3
91.728	86.596	89.125	72.6	1.2	0.3
86.596	81.752	84.140	71.5	1.1	0.4
81.752	77.179	79.433	70.5	1.0	0.4
77.179	72.862	74.989	69.5	1.0	0.4
72.862	68.786	70.795	68.6	0.9	0.4
68.786	64.938	66.834	67.7	0.9	0.4
64.938	61.306	63.096	66.9	0.9	0.4
61.306	57.876	59.566	66.0	0.9	0.4
57.876	54.639	56.234	65.1	0.9	0.4
54.639	51.582	53.088	64.2	0.9	0.3
51.582	48.697	50.119	63.2	0.9	0.3
48.697	45.973	47.315	62.3	1.0	0.3
45.973	43.401	44.668	61.3	1.0	0.3
43.401	40.973	42.170	60.3	1.0	0.3
40.973	38.681	39.811	59.3	1.0	0.2
38.681	36.517	37.584	58.3	1.0	0.2
36.517	34.475	35.481	57.3	1.0	0.2
34.475	32.546	33.497	56.3	1.0	0.2
32.546	30.726	31.623	55.3	1.0	0.2
30.726	29.007	29.854	54.2	1.0	0.2
29.007	27.384	28.184	53.2	1.1	0.1
27.384	25.852	26.607	52.1	1.1	0.1
25.852	24.406	25.119	51.0	1.1	0.1
24.406	23.041	23.714	49.8	1.2	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250, Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:41AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
23.041	21.752	22.387	48.6	1.2	0.1
21.752	20.535	21.135	47.3	1.2	0.1
20.535	19.387	19.953	46.0	1.3	0.1
19.387	18.302	18.836	44.7	1.3	0.1
18.302	17.278	17.783	43.4	1.3	0.1
17.278	16.312	16.788	42.0	1.4	0.1
16.312	15.399	15.849	40.7	1.4	0.1
15.399	14.538	14.962	39.3	1.4	0.1
14.538	13.725	14.125	37.9	1.4	0.1
13.725	12.957	13.335	36.6	1.3	0.2
12.957	12.232	12.589	35.3	1.3	0.2
12.232	11.548	11.885	34.0	1.3	0.2
11.548	10.902	11.220	32.8	1.3	0.2
10.902	10.292	10.593	31.5	1.2	0.2
10.292	9.716	10.000	30.4	1.2	0.2
9.716	9.173	9.441	29.2	1.1	0.2
9.173	8.660	8.913	28.2	1.1	0.2
8.660	8.175	8.414	27.1	1.0	0.2
8.175	7.718	7.943	26.1	1.0	0.2
7.718	7.286	7.499	25.2	1.0	0.2
7.286	6.879	7.079	24.2	0.9	0.2
6.879	6.494	6.683	23.3	0.9	0.1
6.494	6.131	6.310	22.4	0.9	0.1
6.131	5.788	5.957	21.6	0.9	0.1
5.788	5.464	5.623	20.7	0.8	0.1
5.464	5.158	5.309	19.9	0.8	0.1
5.158	4.870	5.012	19.1	0.8	0.1
4.870	4.597	4.732	18.2	0.8	0.1
4.597	4.340	4.467	17.4	0.8	0.1
4.340	4.097	4.217	16.6	0.8	0.1
4.097	3.868	3.981	15.8	0.8	0.1
3.868	3.652	3.758	14.9	0.8	0.1
3.652	3.447	3.548	14.1	0.8	0.1
3.447	3.255	3.350	13.4	0.8	0.1
3.255	3.073	3.162	12.6	0.7	0.1
3.073	2.901	2.985	11.9	0.7	0.1
2.901	2.738	2.818	11.2	0.7	0.1
2.738	2.585	2.661	10.5	0.7	0.1
2.585	2.441	2.512	9.9	0.7	0.1
2.441	2.304	2.371	9.2	0.7	0.1
2.304	2.175	2.239	8.6	0.6	0.1
2.175	2.054	2.113	7.9	0.6	0.1
2.054	1.939	1.995	7.3	0.6	0.0
1.939	1.830	1.884	6.7	0.6	0.0
1.830	1.728	1.778	6.1	0.6	0.0
1.728	1.631	1.679	5.5	0.6	0.0
1.631	1.540	1.585	5.0	0.5	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:41AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.540	1.454	1.496	4.5	0.5	0.0
1.454	1.372	1.413	4.1	0.4	0.0
1.372	1.296	1.334	3.7	0.4	0.0
1.296	1.223	1.259	3.3	0.3	0.0
1.223	1.155	1.189	3.0	0.3	0.0
1.155	1.090	1.122	2.7	0.3	0.0
1.090	1.029	1.059	2.4	0.3	0.0
1.029	0.972	1.000	2.1	0.3	0.0
0.972	0.917	0.944	1.8	0.3	0.0
0.917	0.866	0.891	1.4	0.3	0.0
0.866	0.818	0.841	1.1	0.3	0.0
0.818	0.772	0.794	0.8	0.3	0.0
0.772	0.729	0.750	0.6	0.3	0.0
0.729	0.688	0.708	0.4	0.2	0.0
0.688	0.649	0.668	0.2	0.2	0.0
0.649	0.613	0.631	0.1	0.1	0.0
0.613	0.579	0.596	0.0	0.1	0.0
0.579	0.546	0.562	0.0	0.0	0.0
0.546	0.516	0.531	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:41AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

## Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
300.000	99.1	100.000	75.6	20.000	46.7	4.000	16.2
250.000	94.6	80.000	71.1	10.000	31.0	2.000	7.6
200.000	88.7	60.000	66.5	8.000	26.7	1.000	2.2
150.000	83.7	40.000	59.9	6.000	22.1		



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:42AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
326.451	100.0	74.940	70.0	14.971	40.0	2.472	10.0
253.490	95.0	54.323	65.0	12.075	35.0	1.546	5.0
211.320	90.0	40.245	60.0	9.536	30.0	0.517	0.0
162.736	85.0	30.252	55.0	7.216	25.0		
122.745	80.0	23.277	50.0	5.195	20.0		
97.327	75.0	18.516	45.0	3.667	15.0		




Sample: YYS 159 4.5-5.2m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-038.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 2:30:25PM  
Reported: 5/08/2010 11:25:42AM  
Background: 2/08/2010 1:34:55PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

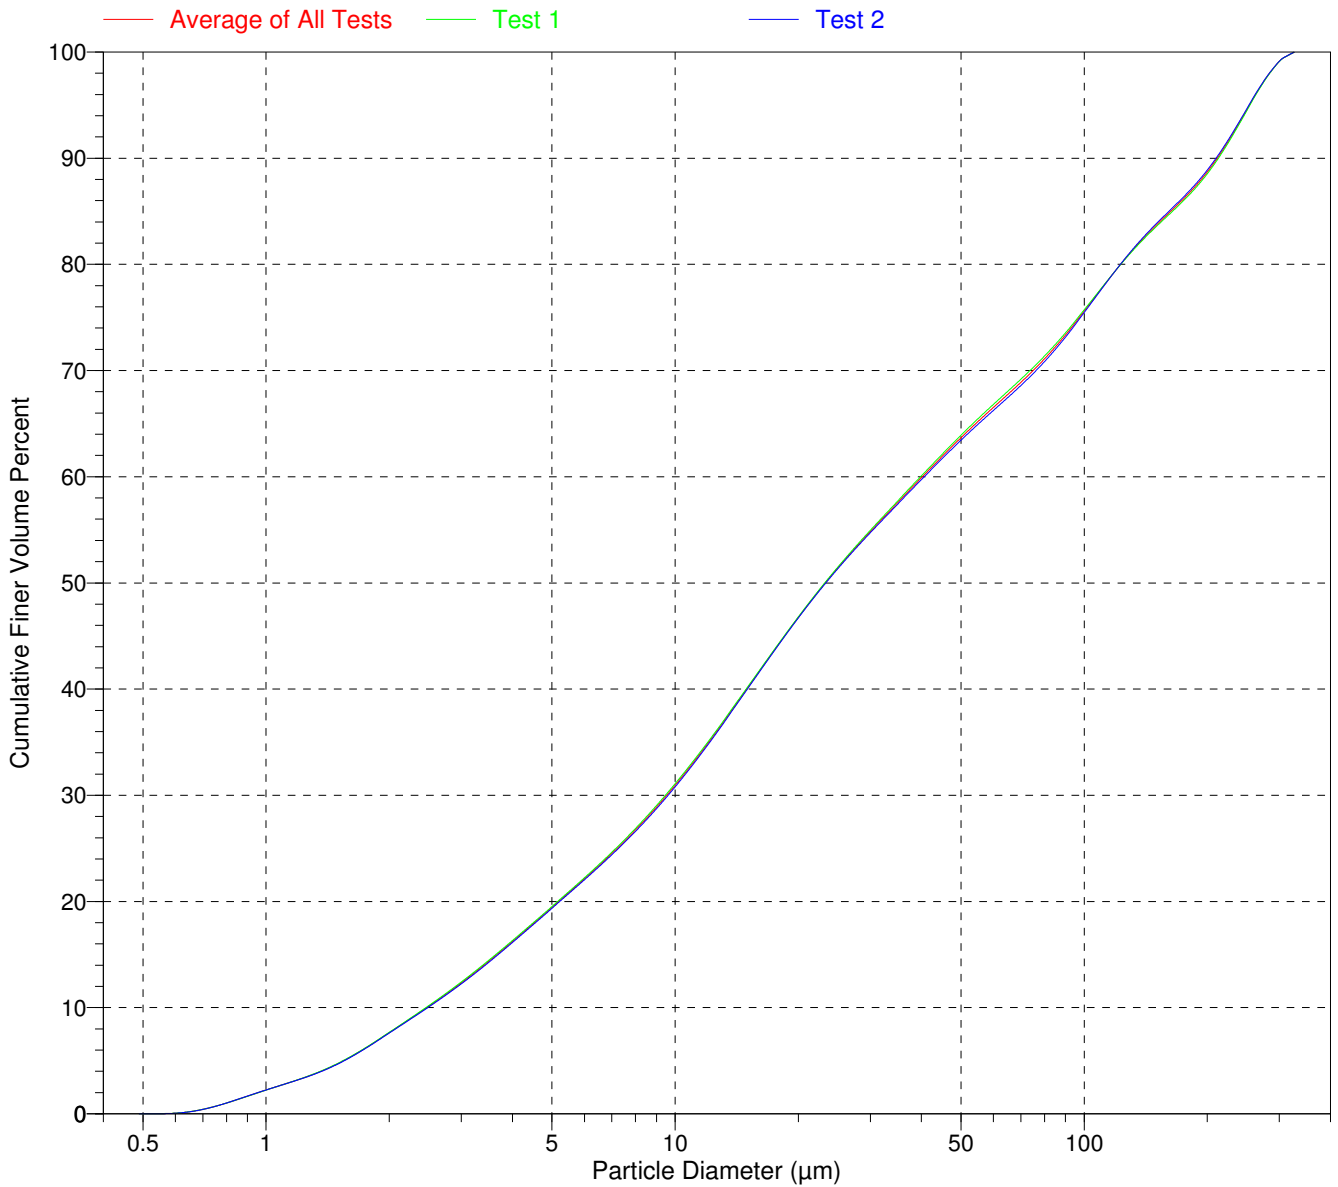






Sample: YYS 158 3.75-4.5m
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2
Analyzed: 2/08/2010 11:30:43AM
Reported: 5/08/2010 11:24:11AM
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

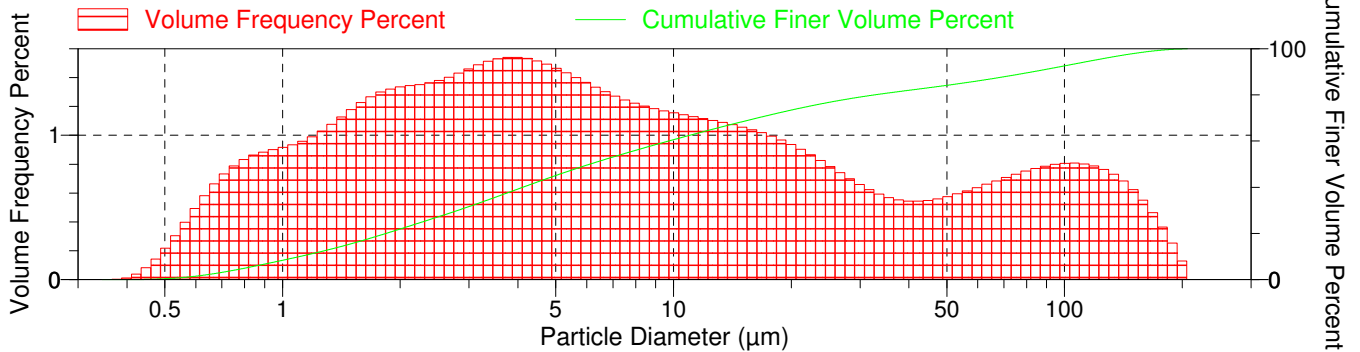

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 24.815 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00312 %
Obscuration: 14.0 %

Volume Distribution Arithmetic Statistics

Table with 5 columns: Mean, Std Dev of 2, Mode, Std Dev of 2. Rows for Mean and Median.

Peaks

Table with 8 columns: Peak Number, % of Dist. of Dist.\*, % of Dist. Std Dev of 2, Mean, Mean Std Dev of 2, Median, Median Std Dev of 2, Mode. Rows for Peak 1 and Peak 2.

\* Peaks must comprise at least 5.00 % of the distribution.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2

Analyzed: 2/08/2010 11:30:43AM

Reported: 5/08/2010 11:24:11AM

Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331

Material: Fraunhofer / Water

Background: Water RI 1.331

Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
217.520	205.353	211.349	100.0	0.0	0.0
205.353	193.865	199.526	99.9	0.1	0.0
193.865	183.021	188.365	99.6	0.3	0.1
183.021	172.783	177.828	99.2	0.4	0.1
172.783	163.117	167.880	98.8	0.5	0.2
163.117	153.993	158.489	98.2	0.6	0.3
153.993	145.378	149.624	97.6	0.6	0.4
145.378	137.246	141.254	96.9	0.7	0.4
137.246	129.569	133.352	96.2	0.7	0.5
129.569	122.321	125.893	95.4	0.8	0.6
122.321	115.478	118.850	94.6	0.8	0.6
115.478	109.018	112.202	93.8	0.8	0.7
109.018	102.920	105.925	93.0	0.8	0.7
102.920	97.163	100.000	92.2	0.8	0.7
97.163	91.728	94.406	91.4	0.8	0.7
91.728	86.596	89.125	90.6	0.8	0.7
86.596	81.752	84.140	89.8	0.8	0.7
81.752	77.179	79.433	89.1	0.8	0.7
77.179	72.862	74.989	88.4	0.7	0.7
72.862	68.786	70.795	87.7	0.7	0.7
68.786	64.938	66.834	87.0	0.7	0.6
64.938	61.306	63.096	86.3	0.7	0.6
61.306	57.876	59.566	85.7	0.6	0.6
57.876	54.639	56.234	85.1	0.6	0.6
54.639	51.582	53.088	84.5	0.6	0.6
51.582	48.697	50.119	83.9	0.6	0.6
48.697	45.973	47.315	83.3	0.6	0.6
45.973	43.401	44.668	82.8	0.5	0.5
43.401	40.973	42.170	82.2	0.5	0.5
40.973	38.681	39.811	81.7	0.5	0.5
38.681	36.517	37.584	81.1	0.6	0.5
36.517	34.475	35.481	80.6	0.6	0.5
34.475	32.546	33.497	80.0	0.6	0.5
32.546	30.726	31.623	79.4	0.6	0.5
30.726	29.007	29.854	78.7	0.7	0.5
29.007	27.384	28.184	78.0	0.7	0.5
27.384	25.852	26.607	77.3	0.7	0.5
25.852	24.406	25.119	76.5	0.8	0.5
24.406	23.041	23.714	75.6	0.8	0.5
23.041	21.752	22.387	74.8	0.9	0.6
21.752	20.535	21.135	73.9	0.9	0.6
20.535	19.387	19.953	72.9	0.9	0.6
19.387	18.302	18.836	72.0	1.0	0.6
18.302	17.278	17.783	71.0	1.0	0.6
17.278	16.312	16.788	69.9	1.0	0.6
16.312	15.399	15.849	68.9	1.0	0.6
15.399	14.538	14.962	67.8	1.1	0.6



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 11:30:43AM  
Reported: 5/08/2010 11:24:11AM  
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
14.538	13.725	14.125	66.8	1.1	0.6
13.725	12.957	13.335	65.7	1.1	0.6
12.957	12.232	12.589	64.6	1.1	0.6
12.232	11.548	11.885	63.5	1.1	0.5
11.548	10.902	11.220	62.3	1.1	0.5
10.902	10.292	10.593	61.2	1.1	0.5
10.292	9.716	10.000	60.0	1.2	0.5
9.716	9.173	9.441	58.9	1.2	0.5
9.173	8.660	8.913	57.7	1.2	0.4
8.660	8.175	8.414	56.5	1.2	0.4
8.175	7.718	7.943	55.2	1.2	0.4
7.718	7.286	7.499	54.0	1.2	0.4
7.286	6.879	7.079	52.7	1.3	0.4
6.879	6.494	6.683	51.4	1.3	0.4
6.494	6.131	6.310	50.1	1.3	0.3
6.131	5.788	5.957	48.7	1.4	0.3
5.788	5.464	5.623	47.3	1.4	0.3
5.464	5.158	5.309	45.9	1.4	0.3
5.158	4.870	5.012	44.4	1.5	0.3
4.870	4.597	4.732	42.9	1.5	0.3
4.597	4.340	4.467	41.4	1.5	0.4
4.340	4.097	4.217	39.9	1.5	0.4
4.097	3.868	3.981	38.3	1.5	0.4
3.868	3.652	3.758	36.8	1.5	0.4
3.652	3.447	3.548	35.3	1.5	0.4
3.447	3.255	3.350	33.7	1.5	0.4
3.255	3.073	3.162	32.3	1.5	0.4
3.073	2.901	2.985	30.8	1.5	0.4
2.901	2.738	2.818	29.4	1.4	0.3
2.738	2.585	2.661	28.0	1.4	0.3
2.585	2.441	2.512	26.6	1.4	0.3
2.441	2.304	2.371	25.2	1.4	0.3
2.304	2.175	2.239	23.9	1.4	0.3
2.175	2.054	2.113	22.5	1.3	0.3
2.054	1.939	1.995	21.2	1.3	0.3
1.939	1.830	1.884	19.9	1.3	0.2
1.830	1.728	1.778	18.6	1.3	0.2
1.728	1.631	1.679	17.3	1.3	0.2
1.631	1.540	1.585	16.1	1.2	0.2
1.540	1.454	1.496	14.9	1.2	0.2
1.454	1.372	1.413	13.8	1.1	0.2
1.372	1.296	1.334	12.7	1.1	0.1
1.296	1.223	1.259	11.7	1.0	0.1
1.223	1.155	1.189	10.7	1.0	0.1
1.155	1.090	1.122	9.7	1.0	0.1
1.090	1.029	1.059	8.8	0.9	0.1
1.029	0.972	1.000	7.9	0.9	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 11:30:43AM  
Reported: 5/08/2010 11:24:11AM  
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
0.972	0.917	0.944	7.0	0.9	0.1
0.917	0.866	0.891	6.1	0.9	0.1
0.866	0.818	0.841	5.2	0.9	0.1
0.818	0.772	0.794	4.4	0.8	0.0
0.772	0.729	0.750	3.6	0.8	0.0
0.729	0.688	0.708	2.9	0.7	0.0
0.688	0.649	0.668	2.2	0.7	0.0
0.649	0.613	0.631	1.7	0.6	0.0
0.613	0.579	0.596	1.2	0.5	0.0
0.579	0.546	0.562	0.8	0.4	0.0
0.546	0.516	0.531	0.5	0.3	0.0
0.516	0.487	0.501	0.3	0.2	0.0
0.487	0.460	0.473	0.1	0.1	0.0
0.460	0.434	0.447	0.0	0.1	0.0
0.434	0.410	0.422	0.0	0.0	0.0
0.410	0.387	0.398	0.0	0.0	0.0
0.387	0.365	0.376	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 11:30:43AM  
Reported: 5/08/2010 11:24:11AM  
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

## Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
200.000	100.0	60.000	86.1	8.000	56.0	1.000	8.3
150.000	97.9	40.000	82.0	6.000	49.6	0.500	0.4
100.000	92.6	20.000	73.4	4.000	39.2		
80.000	89.6	10.000	60.6	2.000	21.9		



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 11:30:43AM  
Reported: 5/08/2010 11:24:11AM  
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
205.977	100.0	16.374	70.0	4.118	40.0	1.108	10.0
118.690	95.0	12.513	65.0	3.415	35.0	0.804	5.0
82.825	90.0	9.708	60.0	2.810	30.0	0.366	0.0
54.372	85.0	7.633	55.0	2.282	25.0		
32.645	80.0	6.110	50.0	1.841	20.0		
22.094	75.0	4.983	45.0	1.461	15.0		




Sample: YYS 158 3.75-4.5m  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-034.SMP

Test Number: Avg of 2  
Analyzed: 2/08/2010 11:30:43AM  
Reported: 5/08/2010 11:24:11AM  
Background: 2/08/2010 10:53:40AM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

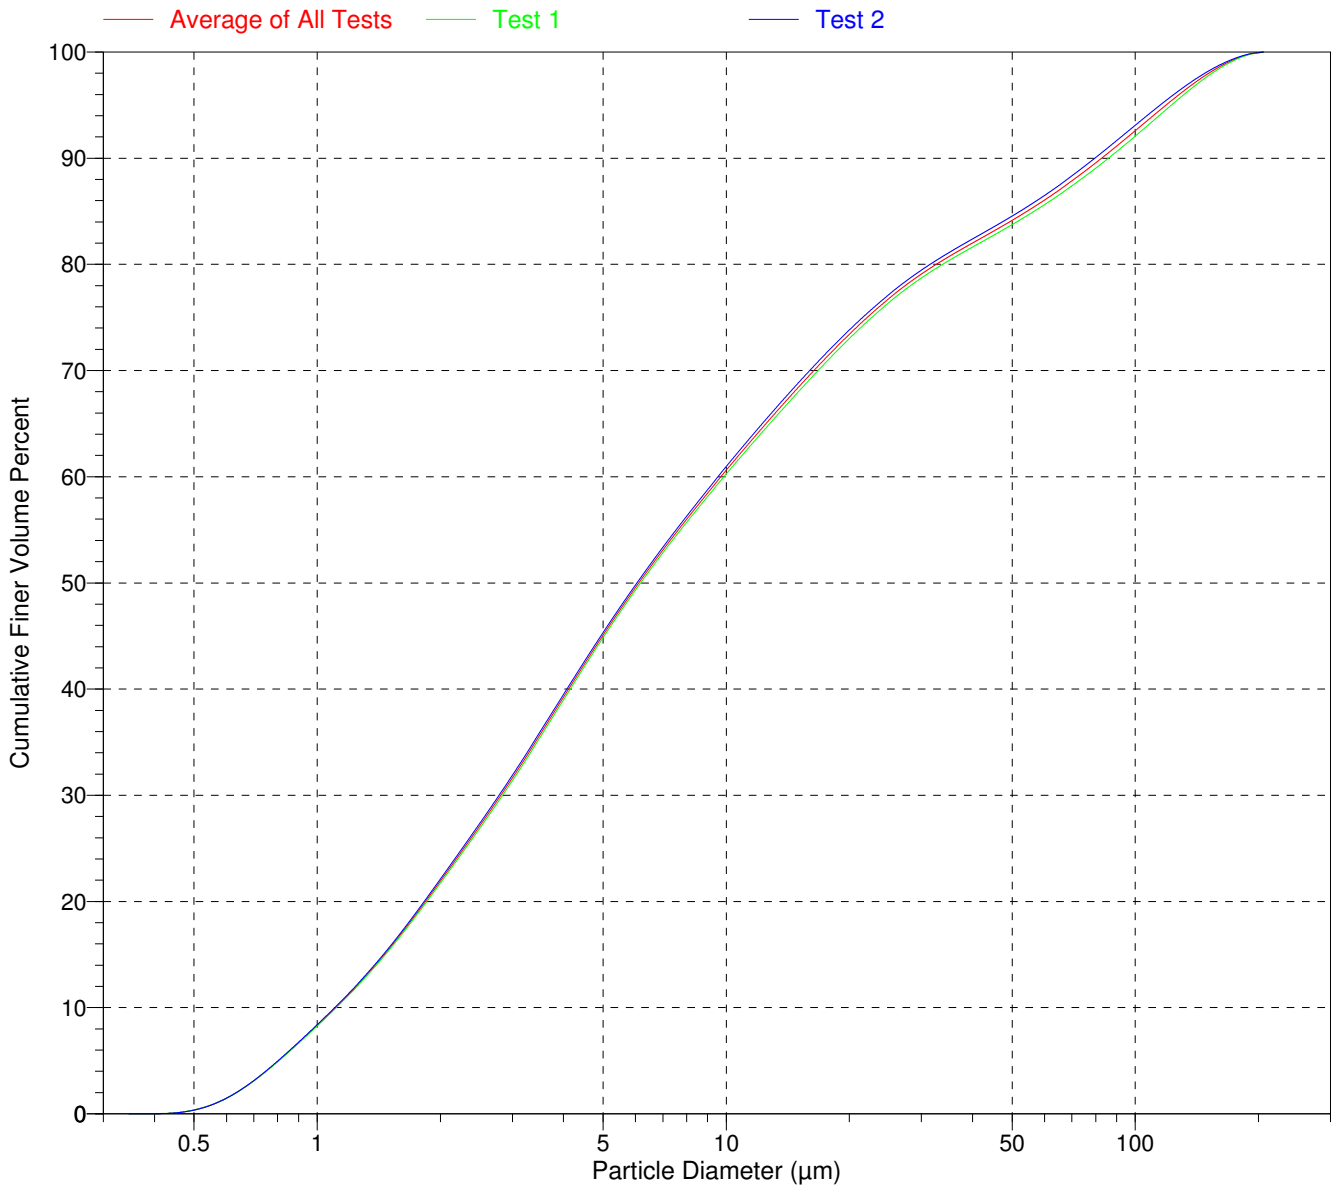




Sample: YYS 158 2.5-3.5
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2
Analyzed: 30/07/2010 4:34:57PM
Reported: 5/08/2010 11:22:19AM
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

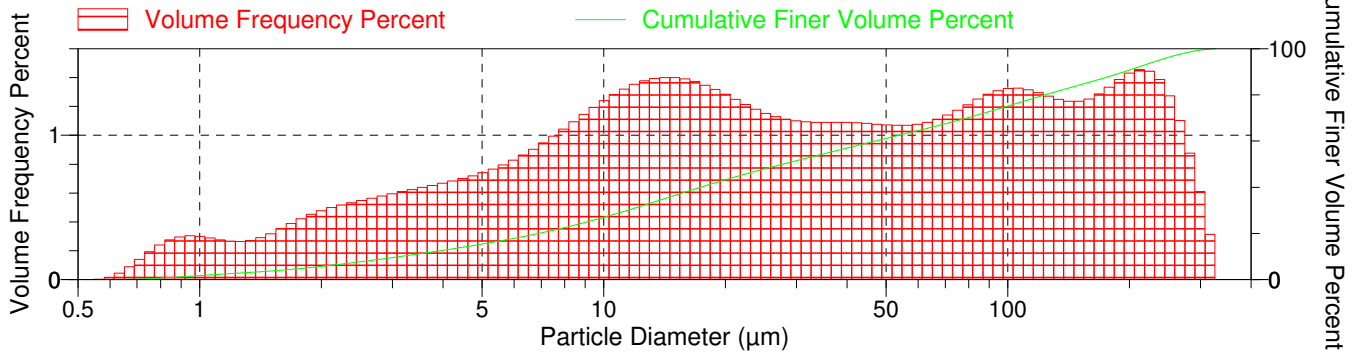

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 26.515 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00445 %
Obscuration: 7.5 %

Volume Distribution Arithmetic Statistics

Table with 6 columns: Mean, Std Dev of 2, Mode, Std Dev of 2, Median, Std Dev of 2. Values: Mean 64.83, Std Dev of 2 0.990, Mode 212.0, Std Dev of 2 0.000, Median 27.71, Std Dev of 2 0.041.





# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
344.747	325.462	334.965	100.0	0.0	0.0
325.462	307.256	316.228	99.7	0.3	0.0
307.256	290.068	298.538	99.0	0.6	0.1
290.068	273.842	281.838	98.1	0.9	0.1
273.842	258.523	266.073	97.0	1.1	0.2
258.523	244.062	251.189	95.8	1.3	0.3
244.062	230.409	237.137	94.4	1.4	0.4
230.409	217.520	223.872	92.9	1.4	0.5
217.520	205.353	211.349	91.5	1.5	0.5
205.353	193.865	199.526	90.0	1.4	0.6
193.865	183.021	188.365	88.7	1.4	0.6
183.021	172.783	177.828	87.3	1.3	0.6
172.783	163.117	167.880	86.0	1.3	0.6
163.117	153.993	158.489	84.8	1.3	0.6
153.993	145.378	149.624	83.5	1.2	0.6
145.378	137.246	141.254	82.3	1.2	0.5
137.246	129.569	133.352	81.1	1.3	0.5
129.569	122.321	125.893	79.8	1.3	0.4
122.321	115.478	118.850	78.5	1.3	0.4
115.478	109.018	112.202	77.2	1.3	0.4
109.018	102.920	105.925	75.9	1.3	0.4
102.920	97.163	100.000	74.5	1.3	0.3
97.163	91.728	94.406	73.2	1.3	0.3
91.728	86.596	89.125	71.9	1.3	0.3
86.596	81.752	84.140	70.7	1.2	0.3
81.752	77.179	79.433	69.5	1.2	0.3
77.179	72.862	74.989	68.3	1.2	0.3
72.862	68.786	70.795	67.2	1.1	0.3
68.786	64.938	66.834	66.1	1.1	0.3
64.938	61.306	63.096	65.0	1.1	0.3
61.306	57.876	59.566	63.9	1.1	0.3
57.876	54.639	56.234	62.8	1.1	0.2
54.639	51.582	53.088	61.8	1.1	0.2
51.582	48.697	50.119	60.7	1.1	0.2
48.697	45.973	47.315	59.6	1.1	0.2
45.973	43.401	44.668	58.5	1.1	0.1
43.401	40.973	42.170	57.4	1.1	0.1
40.973	38.681	39.811	56.3	1.1	0.1
38.681	36.517	37.584	55.3	1.1	0.1
36.517	34.475	35.481	54.2	1.1	0.1
34.475	32.546	33.497	53.1	1.1	0.0
32.546	30.726	31.623	52.0	1.1	0.0
30.726	29.007	29.854	50.9	1.1	0.0
29.007	27.384	28.184	49.8	1.1	0.0
27.384	25.852	26.607	48.6	1.1	0.0
25.852	24.406	25.119	47.5	1.2	0.0
24.406	23.041	23.714	46.3	1.2	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
23.041	21.752	22.387	45.1	1.2	0.0
21.752	20.535	21.135	43.8	1.3	0.0
20.535	19.387	19.953	42.5	1.3	0.0
19.387	18.302	18.836	41.2	1.3	0.0
18.302	17.278	17.783	39.9	1.3	0.0
17.278	16.312	16.788	38.5	1.4	0.0
16.312	15.399	15.849	37.1	1.4	0.0
15.399	14.538	14.962	35.7	1.4	0.0
14.538	13.725	14.125	34.3	1.4	0.0
13.725	12.957	13.335	32.9	1.4	0.0
12.957	12.232	12.589	31.5	1.4	0.0
12.232	11.548	11.885	30.2	1.4	0.1
11.548	10.902	11.220	28.9	1.3	0.1
10.902	10.292	10.593	27.6	1.3	0.1
10.292	9.716	10.000	26.4	1.2	0.1
9.716	9.173	9.441	25.2	1.2	0.1
9.173	8.660	8.913	24.0	1.1	0.1
8.660	8.175	8.414	22.9	1.1	0.1
8.175	7.718	7.943	21.9	1.0	0.1
7.718	7.286	7.499	20.9	1.0	0.1
7.286	6.879	7.079	19.9	0.9	0.1
6.879	6.494	6.683	19.0	0.9	0.0
6.494	6.131	6.310	18.2	0.9	0.0
6.131	5.788	5.957	17.4	0.8	0.0
5.788	5.464	5.623	16.6	0.8	0.0
5.464	5.158	5.309	15.8	0.8	0.0
5.158	4.870	5.012	15.1	0.7	0.0
4.870	4.597	4.732	14.3	0.7	0.0
4.597	4.340	4.467	13.6	0.7	0.0
4.340	4.097	4.217	13.0	0.7	0.0
4.097	3.868	3.981	12.3	0.7	0.0
3.868	3.652	3.758	11.6	0.7	0.1
3.652	3.447	3.548	11.0	0.6	0.1
3.447	3.255	3.350	10.4	0.6	0.1
3.255	3.073	3.162	9.8	0.6	0.1
3.073	2.901	2.985	9.2	0.6	0.1
2.901	2.738	2.818	8.6	0.6	0.1
2.738	2.585	2.661	8.0	0.6	0.1
2.585	2.441	2.512	7.5	0.5	0.1
2.441	2.304	2.371	7.0	0.5	0.1
2.304	2.175	2.239	6.4	0.5	0.1
2.175	2.054	2.113	5.9	0.5	0.1
2.054	1.939	1.995	5.5	0.5	0.1
1.939	1.830	1.884	5.0	0.5	0.1
1.830	1.728	1.778	4.6	0.4	0.1
1.728	1.631	1.679	4.2	0.4	0.1
1.631	1.540	1.585	3.9	0.4	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.540	1.454	1.496	3.5	0.3	0.1
1.454	1.372	1.413	3.2	0.3	0.1
1.372	1.296	1.334	3.0	0.3	0.0
1.296	1.223	1.259	2.7	0.3	0.0
1.223	1.155	1.189	2.4	0.3	0.0
1.155	1.090	1.122	2.2	0.3	0.0
1.090	1.029	1.059	1.9	0.3	0.0
1.029	0.972	1.000	1.6	0.3	0.0
0.972	0.917	0.944	1.3	0.3	0.0
0.917	0.866	0.891	1.0	0.3	0.0
0.866	0.818	0.841	0.7	0.3	0.0
0.818	0.772	0.794	0.5	0.2	0.0
0.772	0.729	0.750	0.3	0.2	0.0
0.729	0.688	0.708	0.1	0.1	0.0
0.688	0.649	0.668	0.1	0.1	0.0
0.649	0.613	0.631	0.0	0.0	0.0
0.613	0.579	0.596	0.0	0.0	0.0
0.579	0.546	0.562	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

## Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
300.000	99.4	100.000	75.2	20.000	43.2	4.000	12.7
250.000	96.3	80.000	70.2	10.000	27.0	2.000	5.7
200.000	90.8	60.000	64.6	8.000	22.5	1.000	1.7
150.000	84.2	40.000	57.0	6.000	17.9		



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
326.451	100.0	79.152	70.0	17.368	40.0	3.141	10.0
236.374	95.0	61.423	65.0	14.118	35.0	1.828	5.0
193.554	90.0	46.969	60.0	11.453	30.0	0.548	0.0
155.609	85.0	36.034	55.0	9.100	25.0		
123.528	80.0	27.714	50.0	6.901	20.0		
99.200	75.0	21.667	45.0	4.847	15.0		




Sample: YYS 158 2.5-3.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-032.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:34:57PM  
Reported: 5/08/2010 11:22:19AM  
Background: 30/07/2010 4:22:49PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

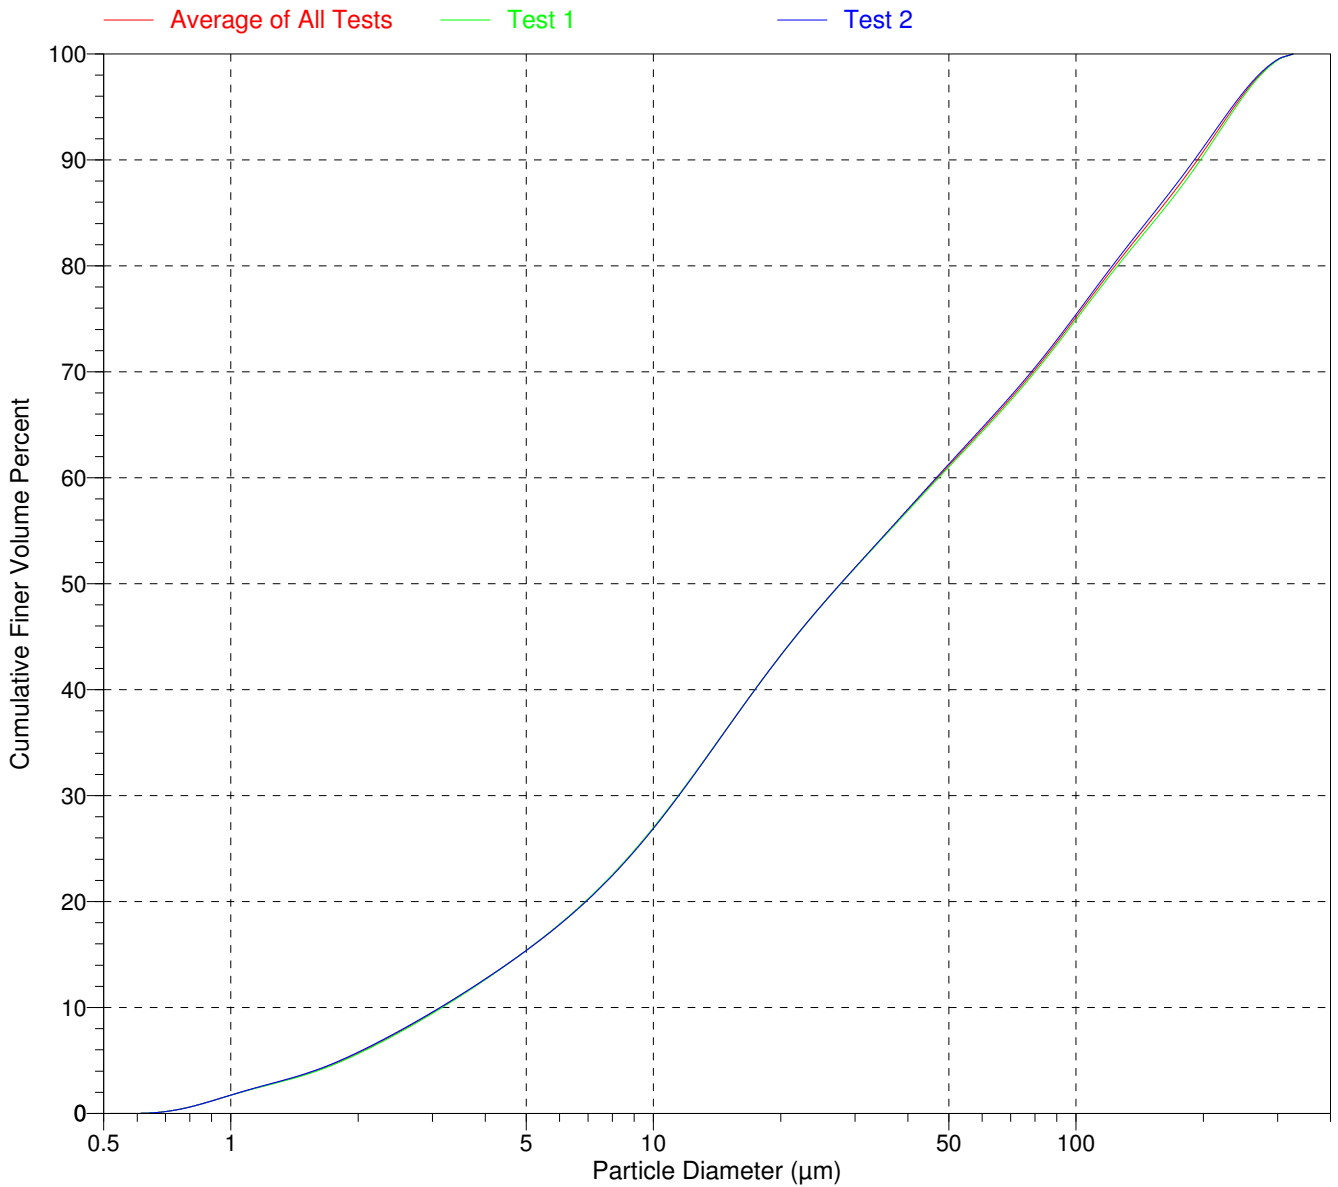




Sample: YYS 156A 12-12.75
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2
Analyzed: 30/07/2010 2:00:22PM
Reported: 3/08/2010 11:36:52AM
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

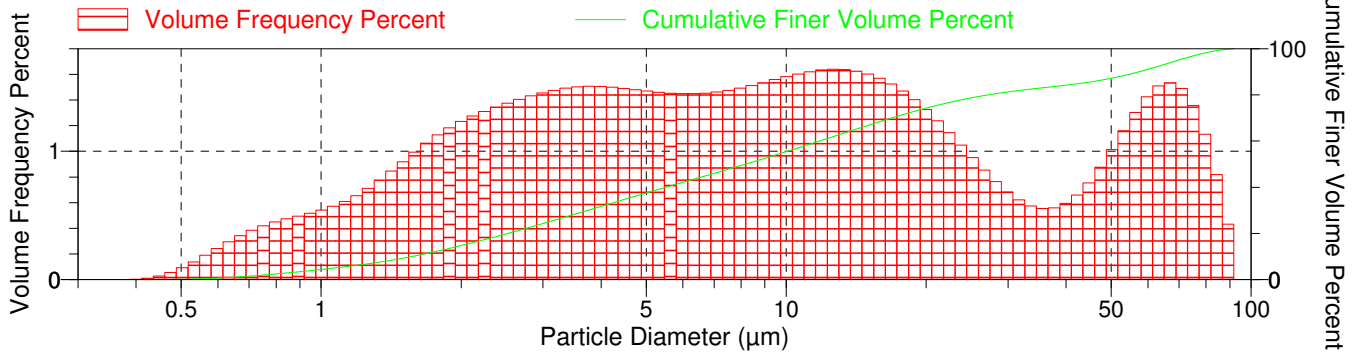

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 28.235 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00258 %
Obscuration: 9.2 %

Volume Distribution Arithmetic Statistics

Table with 5 columns: Mean, Std Dev of 2, Mode, Std Dev of 2. Rows for Mean and Median.

Peaks

Table with 8 columns: Peak Number, % of Dist. of Dist.\*, % of Dist. Std Dev of 2, Mean, Mean Std Dev of 2, Median, Median Std Dev of 2, Mode. Rows for peaks 1, 2, and 3.

\* Peaks must comprise at least 5.00 % of the distribution.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
97.163	91.728	94.406	100.0	0.0	0.0
91.728	86.596	89.125	99.5	0.5	0.0
86.596	81.752	84.140	98.7	0.8	0.0
81.752	77.179	79.433	97.5	1.1	0.0
77.179	72.862	74.989	96.2	1.4	0.1
72.862	68.786	70.795	94.7	1.5	0.1
68.786	64.938	66.834	93.2	1.5	0.1
64.938	61.306	63.096	91.6	1.5	0.1
61.306	57.876	59.566	90.2	1.4	0.1
57.876	54.639	56.234	88.9	1.3	0.1
54.639	51.582	53.088	87.8	1.2	0.1
51.582	48.697	50.119	86.8	1.0	0.1
48.697	45.973	47.315	85.9	0.9	0.1
45.973	43.401	44.668	85.2	0.7	0.1
43.401	40.973	42.170	84.5	0.7	0.2
40.973	38.681	39.811	83.9	0.6	0.2
38.681	36.517	37.584	83.3	0.6	0.2
36.517	34.475	35.481	82.8	0.6	0.2
34.475	32.546	33.497	82.2	0.6	0.2
32.546	30.726	31.623	81.6	0.6	0.2
30.726	29.007	29.854	80.9	0.7	0.2
29.007	27.384	28.184	80.1	0.8	0.2
27.384	25.852	26.607	79.3	0.9	0.2
25.852	24.406	25.119	78.3	1.0	0.2
24.406	23.041	23.714	77.3	1.1	0.2
23.041	21.752	22.387	76.1	1.2	0.2
21.752	20.535	21.135	74.9	1.2	0.2
20.535	19.387	19.953	73.5	1.3	0.2
19.387	18.302	18.836	72.1	1.4	0.2
18.302	17.278	17.783	70.7	1.5	0.2
17.278	16.312	16.788	69.1	1.5	0.2
16.312	15.399	15.849	67.6	1.6	0.2
15.399	14.538	14.962	66.0	1.6	0.3
14.538	13.725	14.125	64.3	1.6	0.3
13.725	12.957	13.335	62.7	1.6	0.3
12.957	12.232	12.589	61.1	1.6	0.3
12.232	11.548	11.885	59.4	1.6	0.3
11.548	10.902	11.220	57.8	1.6	0.3
10.902	10.292	10.593	56.2	1.6	0.3
10.292	9.716	10.000	54.6	1.6	0.3
9.716	9.173	9.441	53.1	1.6	0.3
9.173	8.660	8.913	51.5	1.5	0.3
8.660	8.175	8.414	50.0	1.5	0.3
8.175	7.718	7.943	48.5	1.5	0.3
7.718	7.286	7.499	47.0	1.5	0.3
7.286	6.879	7.079	45.6	1.5	0.3
6.879	6.494	6.683	44.1	1.5	0.3





# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250, Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
6.494	6.131	6.310	42.7	1.4	0.3
6.131	5.788	5.957	41.2	1.4	0.2
5.788	5.464	5.623	39.8	1.5	0.2
5.464	5.158	5.309	38.3	1.5	0.2
5.158	4.870	5.012	36.8	1.5	0.2
4.870	4.597	4.732	35.4	1.5	0.2
4.597	4.340	4.467	33.9	1.5	0.2
4.340	4.097	4.217	32.4	1.5	0.2
4.097	3.868	3.981	30.9	1.5	0.2
3.868	3.652	3.758	29.4	1.5	0.1
3.652	3.447	3.548	27.9	1.5	0.1
3.447	3.255	3.350	26.4	1.5	0.1
3.255	3.073	3.162	24.9	1.5	0.1
3.073	2.901	2.985	23.4	1.5	0.1
2.901	2.738	2.818	22.0	1.4	0.1
2.738	2.585	2.661	20.6	1.4	0.1
2.585	2.441	2.512	19.2	1.4	0.1
2.441	2.304	2.371	17.9	1.3	0.1
2.304	2.175	2.239	16.6	1.3	0.1
2.175	2.054	2.113	15.3	1.3	0.1
2.054	1.939	1.995	14.1	1.2	0.1
1.939	1.830	1.884	12.9	1.2	0.1
1.830	1.728	1.778	11.8	1.1	0.1
1.728	1.631	1.679	10.7	1.1	0.1
1.631	1.540	1.585	9.7	1.0	0.0
1.540	1.454	1.496	8.8	0.9	0.0
1.454	1.372	1.413	8.0	0.8	0.0
1.372	1.296	1.334	7.2	0.8	0.0
1.296	1.223	1.259	6.5	0.7	0.0
1.223	1.155	1.189	5.8	0.7	0.0
1.155	1.090	1.122	5.2	0.6	0.0
1.090	1.029	1.059	4.6	0.6	0.0
1.029	0.972	1.000	4.1	0.5	0.0
0.972	0.917	0.944	3.6	0.5	0.0
0.917	0.866	0.891	3.1	0.5	0.0
0.866	0.818	0.841	2.6	0.5	0.0
0.818	0.772	0.794	2.2	0.4	0.0
0.772	0.729	0.750	1.8	0.4	0.0
0.729	0.688	0.708	1.4	0.4	0.0
0.688	0.649	0.668	1.0	0.3	0.0
0.649	0.613	0.631	0.7	0.3	0.0
0.613	0.579	0.596	0.5	0.2	0.0
0.579	0.546	0.562	0.3	0.2	0.0
0.546	0.516	0.531	0.2	0.1	0.0
0.516	0.487	0.501	0.1	0.1	0.0
0.487	0.460	0.473	0.0	0.1	0.0
0.460	0.434	0.447	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

## Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
0.434	0.410	0.422	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
80.000	98.3	20.000	74.3	6.000	42.1	1.000	4.4
60.000	91.1	10.000	55.4	4.000	31.7	0.500	0.1
40.000	84.2	8.000	49.4	2.000	14.7		



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
92.006	100.0	16.849	70.0	5.514	40.0	1.567	10.0
69.602	95.0	14.053	65.0	4.534	35.0	1.067	5.0
57.326	90.0	11.788	60.0	3.743	30.0	0.399	0.0
42.850	85.0	9.855	55.0	3.087	25.0		
27.134	80.0	8.174	50.0	2.522	20.0		
20.656	75.0	6.724	45.0	2.026	15.0		




Sample: YYS 156A 12-12.75  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-029.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 2:00:22PM  
Reported: 3/08/2010 11:36:52AM  
Background: 30/07/2010 1:30:14PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

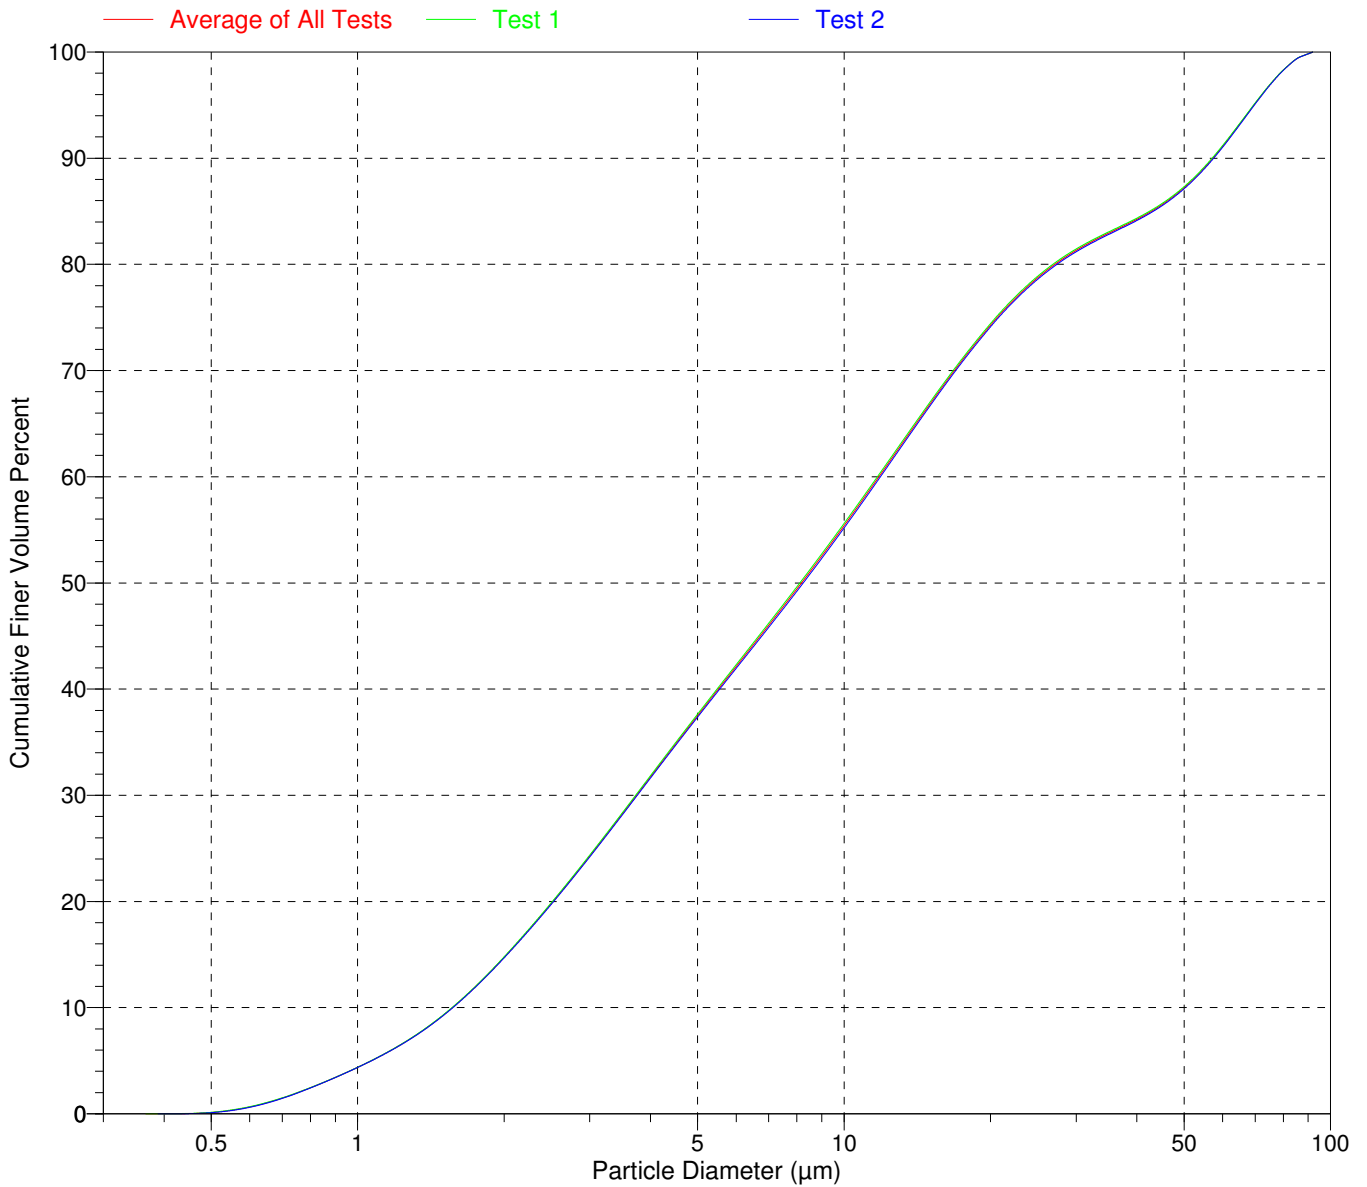




Sample: YYS 156A 11.25-12
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2
Analyzed: 30/07/2010 3:13:08PM
Reported: 3/08/2010 11:40:41AM
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

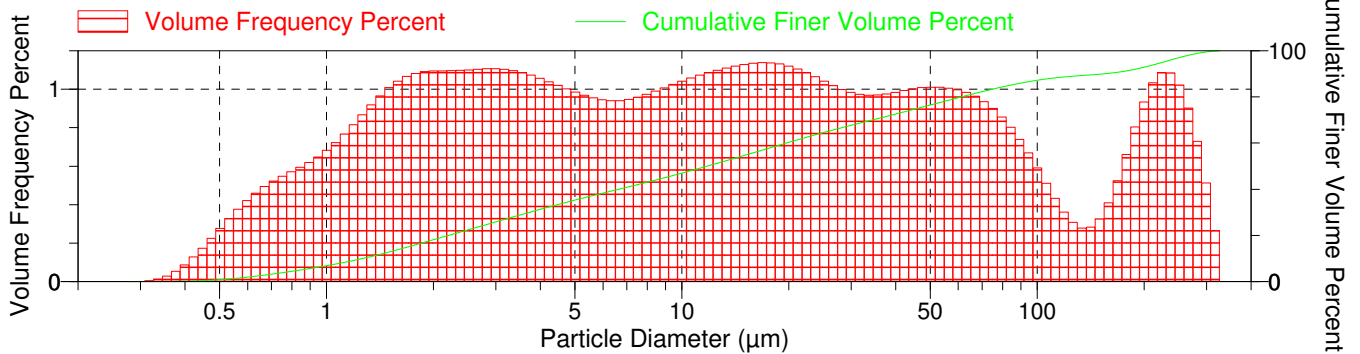

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 30.095 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00666 %
Obscuration: 23.7 %

Volume Distribution Arithmetic Statistics

Table with 5 columns: Mean, Std Dev of 2, Mode, Std Dev of 2. Rows include Mean (42.51), Median (11.78), and other statistics.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
344.747	325.462	334.965	100.0	0.0	0.0
325.462	307.256	316.228	99.7	0.3	0.0
307.256	290.068	298.538	99.2	0.5	0.1
290.068	273.842	281.838	98.5	0.7	0.2
273.842	258.523	266.073	97.5	0.9	0.3
258.523	244.062	251.189	96.5	1.0	0.3
244.062	230.409	237.137	95.4	1.1	0.4
230.409	217.520	223.872	94.3	1.1	0.5
217.520	205.353	211.349	93.3	1.0	0.5
205.353	193.865	199.526	92.4	0.9	0.5
193.865	183.021	188.365	91.6	0.8	0.5
183.021	172.783	177.828	90.9	0.7	0.5
172.783	163.117	167.880	90.4	0.5	0.4
163.117	153.993	158.489	90.0	0.4	0.4
153.993	145.378	149.624	89.7	0.3	0.3
145.378	137.246	141.254	89.4	0.3	0.3
137.246	129.569	133.352	89.1	0.3	0.2
129.569	122.321	125.893	88.8	0.3	0.2
122.321	115.478	118.850	88.5	0.4	0.2
115.478	109.018	112.202	88.0	0.4	0.2
109.018	102.920	105.925	87.5	0.5	0.3
102.920	97.163	100.000	86.9	0.6	0.3
97.163	91.728	94.406	86.2	0.7	0.3
91.728	86.596	89.125	85.5	0.7	0.3
86.596	81.752	84.140	84.7	0.8	0.3
81.752	77.179	79.433	83.8	0.9	0.3
77.179	72.862	74.989	82.9	0.9	0.3
72.862	68.786	70.795	82.0	0.9	0.3
68.786	64.938	66.834	81.0	1.0	0.3
64.938	61.306	63.096	80.0	1.0	0.3
61.306	57.876	59.566	79.0	1.0	0.3
57.876	54.639	56.234	78.0	1.0	0.2
54.639	51.582	53.088	77.0	1.0	0.2
51.582	48.697	50.119	76.0	1.0	0.2
48.697	45.973	47.315	75.0	1.0	0.2
45.973	43.401	44.668	74.0	1.0	0.1
43.401	40.973	42.170	73.0	1.0	0.1
40.973	38.681	39.811	72.0	1.0	0.1
38.681	36.517	37.584	71.1	1.0	0.1
36.517	34.475	35.481	70.1	1.0	0.1
34.475	32.546	33.497	69.1	1.0	0.1
32.546	30.726	31.623	68.1	1.0	0.1
30.726	29.007	29.854	67.2	1.0	0.0
29.007	27.384	28.184	66.2	1.0	0.0
27.384	25.852	26.607	65.1	1.0	0.0
25.852	24.406	25.119	64.1	1.0	0.0
24.406	23.041	23.714	63.0	1.1	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
23.041	21.752	22.387	61.9	1.1	0.0
21.752	20.535	21.135	60.8	1.1	0.0
20.535	19.387	19.953	59.7	1.1	0.0
19.387	18.302	18.836	58.6	1.1	0.0
18.302	17.278	17.783	57.4	1.1	0.0
17.278	16.312	16.788	56.3	1.1	0.0
16.312	15.399	15.849	55.2	1.1	0.0
15.399	14.538	14.962	54.0	1.1	0.0
14.538	13.725	14.125	52.9	1.1	0.0
13.725	12.957	13.335	51.8	1.1	0.0
12.957	12.232	12.589	50.7	1.1	0.0
12.232	11.548	11.885	49.6	1.1	0.0
11.548	10.902	11.220	48.6	1.1	0.0
10.902	10.292	10.593	47.5	1.1	0.0
10.292	9.716	10.000	46.5	1.0	0.1
9.716	9.173	9.441	45.4	1.0	0.1
9.173	8.660	8.913	44.4	1.0	0.1
8.660	8.175	8.414	43.4	1.0	0.1
8.175	7.718	7.943	42.5	1.0	0.1
7.718	7.286	7.499	41.5	1.0	0.1
7.286	6.879	7.079	40.6	0.9	0.1
6.879	6.494	6.683	39.6	0.9	0.1
6.494	6.131	6.310	38.7	0.9	0.1
6.131	5.788	5.957	37.7	0.9	0.2
5.788	5.464	5.623	36.8	1.0	0.2
5.464	5.158	5.309	35.8	1.0	0.2
5.158	4.870	5.012	34.8	1.0	0.2
4.870	4.597	4.732	33.8	1.0	0.2
4.597	4.340	4.467	32.8	1.0	0.2
4.340	4.097	4.217	31.8	1.0	0.2
4.097	3.868	3.981	30.7	1.1	0.2
3.868	3.652	3.758	29.6	1.1	0.2
3.652	3.447	3.548	28.5	1.1	0.2
3.447	3.255	3.350	27.4	1.1	0.2
3.255	3.073	3.162	26.3	1.1	0.2
3.073	2.901	2.985	25.2	1.1	0.2
2.901	2.738	2.818	24.1	1.1	0.2
2.738	2.585	2.661	23.0	1.1	0.2
2.585	2.441	2.512	21.9	1.1	0.2
2.441	2.304	2.371	20.8	1.1	0.1
2.304	2.175	2.239	19.7	1.1	0.1
2.175	2.054	2.113	18.6	1.1	0.1
2.054	1.939	1.995	17.5	1.1	0.1
1.939	1.830	1.884	16.4	1.1	0.1
1.830	1.728	1.778	15.4	1.1	0.1
1.728	1.631	1.679	14.3	1.1	0.1
1.631	1.540	1.585	13.3	1.0	0.0





# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.540	1.454	1.496	12.3	1.0	0.0
1.454	1.372	1.413	11.3	1.0	0.0
1.372	1.296	1.334	10.4	0.9	0.0
1.296	1.223	1.259	9.5	0.9	0.0
1.223	1.155	1.189	8.7	0.8	0.0
1.155	1.090	1.122	7.9	0.8	0.0
1.090	1.029	1.059	7.2	0.7	0.0
1.029	0.972	1.000	6.5	0.7	0.0
0.972	0.917	0.944	5.9	0.6	0.0
0.917	0.866	0.891	5.3	0.6	0.0
0.866	0.818	0.841	4.7	0.6	0.0
0.818	0.772	0.794	4.1	0.6	0.0
0.772	0.729	0.750	3.6	0.5	0.0
0.729	0.688	0.708	3.0	0.5	0.0
0.688	0.649	0.668	2.5	0.5	0.0
0.649	0.613	0.631	2.1	0.5	0.0
0.613	0.579	0.596	1.7	0.4	0.0
0.579	0.546	0.562	1.3	0.4	0.0
0.546	0.516	0.531	1.0	0.3	0.0
0.516	0.487	0.501	0.7	0.3	0.0
0.487	0.460	0.473	0.5	0.2	0.0
0.460	0.434	0.447	0.3	0.2	0.0
0.434	0.410	0.422	0.2	0.1	0.0
0.410	0.387	0.398	0.1	0.1	0.0
0.387	0.365	0.376	0.0	0.1	0.0
0.365	0.345	0.355	0.0	0.0	0.0
0.345	0.325	0.335	0.0	0.0	0.0
0.325	0.307	0.316	0.0	0.0	0.0
0.307	0.290	0.299	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
300.000	99.5	100.000	87.2	20.000	60.3	4.000	31.3
250.000	97.0	80.000	84.4	10.000	47.0	2.000	18.1
200.000	92.9	60.000	79.7	8.000	43.1	1.000	6.9
150.000	89.9	40.000	72.6	6.000	38.3	0.500	0.8



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
326.451	100.0	34.303	70.0	6.646	40.0	1.264	10.0
225.135	95.0	25.656	65.0	4.919	35.0	0.844	5.0
153.907	90.0	19.673	60.0	3.725	30.0	0.300	0.0
83.570	85.0	15.265	55.0	2.866	25.0		
61.173	80.0	11.778	50.0	2.207	20.0		
45.957	75.0	8.948	45.0	1.694	15.0		




Sample: YYS 156A 11.25-12  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-030.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 3:13:08PM  
Reported: 3/08/2010 11:40:41AM  
Background: 30/07/2010 2:25:01PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

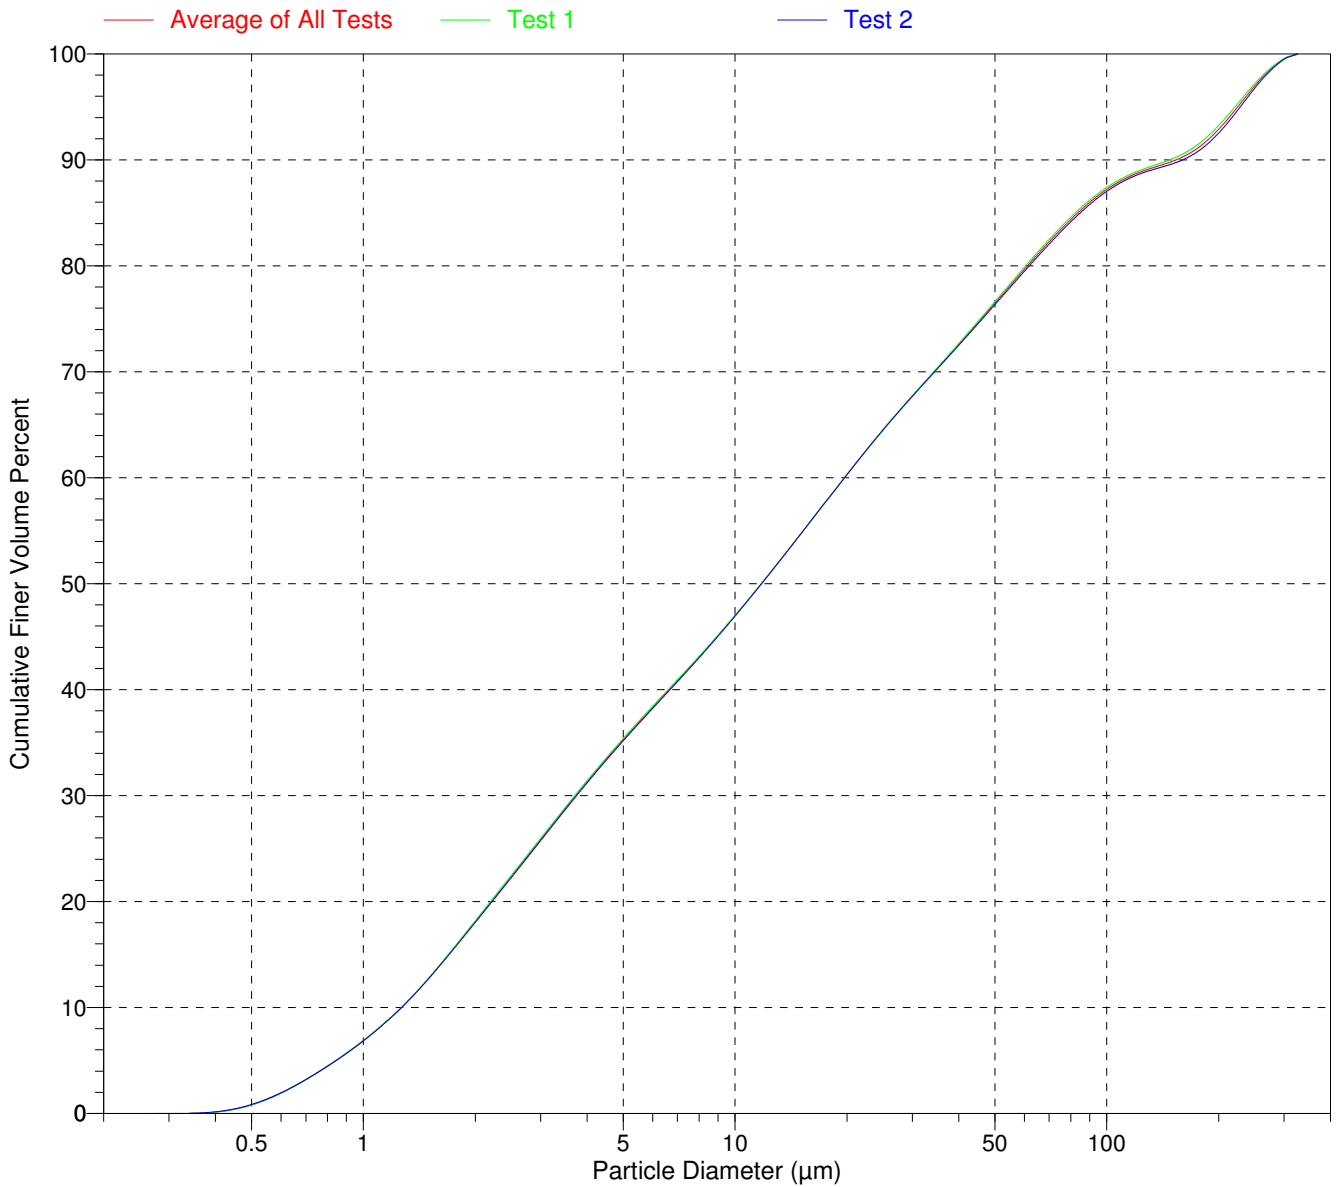




Sample: YYS 156A 1.5-2.5
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2
Analyzed: 30/07/2010 4:05:26PM
Reported: 3/08/2010 12:05:27PM
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

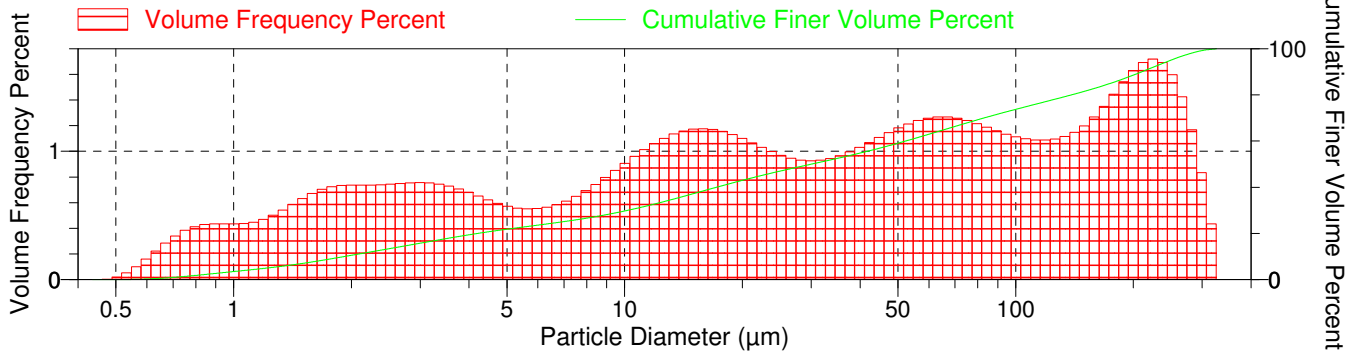

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 29.420 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00542 %
Obscuration: 12.3 %

Volume Distribution Arithmetic Statistics

Table with 6 columns: Mean, Median, Std Dev of 2, Mode, Std Dev of 2. Values: Mean 69.00, Median 30.02, Std Dev of 2 1.049, Mode 224.6, Std Dev of 2 0.000.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
344.747	325.462	334.965	100.0	0.0	0.0
325.462	307.256	316.228	99.5	0.5	0.0
307.256	290.068	298.538	98.7	0.9	0.0
290.068	273.842	281.838	97.5	1.2	0.0
273.842	258.523	266.073	96.1	1.4	0.1
258.523	244.062	251.189	94.4	1.6	0.1
244.062	230.409	237.137	92.8	1.7	0.1
230.409	217.520	223.872	91.0	1.7	0.1
217.520	205.353	211.349	89.3	1.7	0.2
205.353	193.865	199.526	87.7	1.6	0.2
193.865	183.021	188.365	86.2	1.5	0.2
183.021	172.783	177.828	84.7	1.4	0.2
172.783	163.117	167.880	83.4	1.3	0.2
163.117	153.993	158.489	82.1	1.3	0.2
153.993	145.378	149.624	80.9	1.2	0.3
145.378	137.246	141.254	79.8	1.1	0.3
137.246	129.569	133.352	78.7	1.1	0.4
129.569	122.321	125.893	77.6	1.1	0.4
122.321	115.478	118.850	76.5	1.1	0.5
115.478	109.018	112.202	75.4	1.1	0.6
109.018	102.920	105.925	74.3	1.1	0.7
102.920	97.163	100.000	73.2	1.1	0.7
97.163	91.728	94.406	72.1	1.1	0.8
91.728	86.596	89.125	70.9	1.2	0.8
86.596	81.752	84.140	69.7	1.2	0.8
81.752	77.179	79.433	68.5	1.2	0.8
77.179	72.862	74.989	67.2	1.2	0.8
72.862	68.786	70.795	66.0	1.3	0.8
68.786	64.938	66.834	64.7	1.3	0.7
64.938	61.306	63.096	63.4	1.3	0.7
61.306	57.876	59.566	62.2	1.3	0.7
57.876	54.639	56.234	60.9	1.2	0.6
54.639	51.582	53.088	59.7	1.2	0.6
51.582	48.697	50.119	58.6	1.2	0.6
48.697	45.973	47.315	57.4	1.1	0.6
45.973	43.401	44.668	56.3	1.1	0.7
43.401	40.973	42.170	55.2	1.1	0.7
40.973	38.681	39.811	54.2	1.0	0.7
38.681	36.517	37.584	53.2	1.0	0.7
36.517	34.475	35.481	52.3	1.0	0.7
34.475	32.546	33.497	51.3	0.9	0.7
32.546	30.726	31.623	50.4	0.9	0.7
30.726	29.007	29.854	49.5	0.9	0.7
29.007	27.384	28.184	48.5	0.9	0.7
27.384	25.852	26.607	47.6	0.9	0.7
25.852	24.406	25.119	46.6	1.0	0.7
24.406	23.041	23.714	45.6	1.0	0.7



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250, Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
23.041	21.752	22.387	44.6	1.0	0.7
21.752	20.535	21.135	43.5	1.1	0.7
20.535	19.387	19.953	42.4	1.1	0.6
19.387	18.302	18.836	41.3	1.1	0.6
18.302	17.278	17.783	40.1	1.2	0.6
17.278	16.312	16.788	38.9	1.2	0.6
16.312	15.399	15.849	37.8	1.2	0.5
15.399	14.538	14.962	36.6	1.2	0.5
14.538	13.725	14.125	35.4	1.2	0.5
13.725	12.957	13.335	34.3	1.1	0.4
12.957	12.232	12.589	33.2	1.1	0.4
12.232	11.548	11.885	32.1	1.1	0.4
11.548	10.902	11.220	31.1	1.0	0.3
10.902	10.292	10.593	30.2	1.0	0.3
10.292	9.716	10.000	29.3	0.9	0.3
9.716	9.173	9.441	28.4	0.8	0.2
9.173	8.660	8.913	27.6	0.8	0.2
8.660	8.175	8.414	26.9	0.7	0.2
8.175	7.718	7.943	26.2	0.7	0.2
7.718	7.286	7.499	25.6	0.6	0.2
7.286	6.879	7.079	24.9	0.6	0.2
6.879	6.494	6.683	24.4	0.6	0.2
6.494	6.131	6.310	23.8	0.6	0.2
6.131	5.788	5.957	23.2	0.6	0.2
5.788	5.464	5.623	22.7	0.6	0.2
5.464	5.158	5.309	22.1	0.6	0.2
5.158	4.870	5.012	21.6	0.6	0.2
4.870	4.597	4.732	21.0	0.6	0.2
4.597	4.340	4.467	20.3	0.6	0.2
4.340	4.097	4.217	19.7	0.7	0.2
4.097	3.868	3.981	19.0	0.7	0.2
3.868	3.652	3.758	18.3	0.7	0.2
3.652	3.447	3.548	17.6	0.7	0.2
3.447	3.255	3.350	16.8	0.7	0.2
3.255	3.073	3.162	16.1	0.8	0.2
3.073	2.901	2.985	15.3	0.8	0.2
2.901	2.738	2.818	14.6	0.8	0.2
2.738	2.585	2.661	13.8	0.7	0.1
2.585	2.441	2.512	13.1	0.7	0.1
2.441	2.304	2.371	12.3	0.7	0.1
2.304	2.175	2.239	11.6	0.7	0.1
2.175	2.054	2.113	10.9	0.7	0.1
2.054	1.939	1.995	10.1	0.7	0.1
1.939	1.830	1.884	9.4	0.7	0.1
1.830	1.728	1.778	8.7	0.7	0.1
1.728	1.631	1.679	8.0	0.7	0.1
1.631	1.540	1.585	7.3	0.7	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.540	1.454	1.496	6.7	0.6	0.1
1.454	1.372	1.413	6.1	0.6	0.1
1.372	1.296	1.334	5.5	0.5	0.1
1.296	1.223	1.259	5.0	0.5	0.1
1.223	1.155	1.189	4.6	0.5	0.1
1.155	1.090	1.122	4.1	0.4	0.1
1.090	1.029	1.059	3.7	0.4	0.1
1.029	0.972	1.000	3.3	0.4	0.1
0.972	0.917	0.944	2.8	0.4	0.0
0.917	0.866	0.891	2.4	0.4	0.0
0.866	0.818	0.841	2.0	0.4	0.0
0.818	0.772	0.794	1.5	0.4	0.0
0.772	0.729	0.750	1.2	0.4	0.0
0.729	0.688	0.708	0.8	0.3	0.0
0.688	0.649	0.668	0.5	0.3	0.0
0.649	0.613	0.631	0.3	0.2	0.0
0.613	0.579	0.596	0.2	0.2	0.0
0.579	0.546	0.562	0.1	0.1	0.0
0.546	0.516	0.531	0.0	0.0	0.0
0.516	0.487	0.501	0.0	0.0	0.0
0.487	0.460	0.473	0.0	0.0	0.0





# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
300.000	99.2	100.000	73.7	20.000	43.0	4.000	19.4
250.000	95.1	80.000	69.2	10.000	29.7	2.000	10.5
200.000	88.6	60.000	63.0	8.000	26.6	1.000	3.5
150.000	81.6	40.000	54.8	6.000	23.6	0.500	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
326.451	100.0	82.976	70.0	17.190	40.0	1.921	10.0
248.774	95.0	65.840	65.0	13.432	35.0	1.218	5.0
210.004	90.0	52.248	60.0	10.184	30.0	0.461	0.0
174.632	85.0	40.423	55.0	6.918	25.0		
138.697	80.0	30.019	50.0	4.211	20.0		
106.657	75.0	22.286	45.0	2.833	15.0		




Sample: YYS 156A 1.5-2.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-031.SMP

Test Number: Avg of 2  
Analyzed: 30/07/2010 4:05:26PM  
Reported: 3/08/2010 12:05:27PM  
Background: 30/07/2010 3:34:03PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

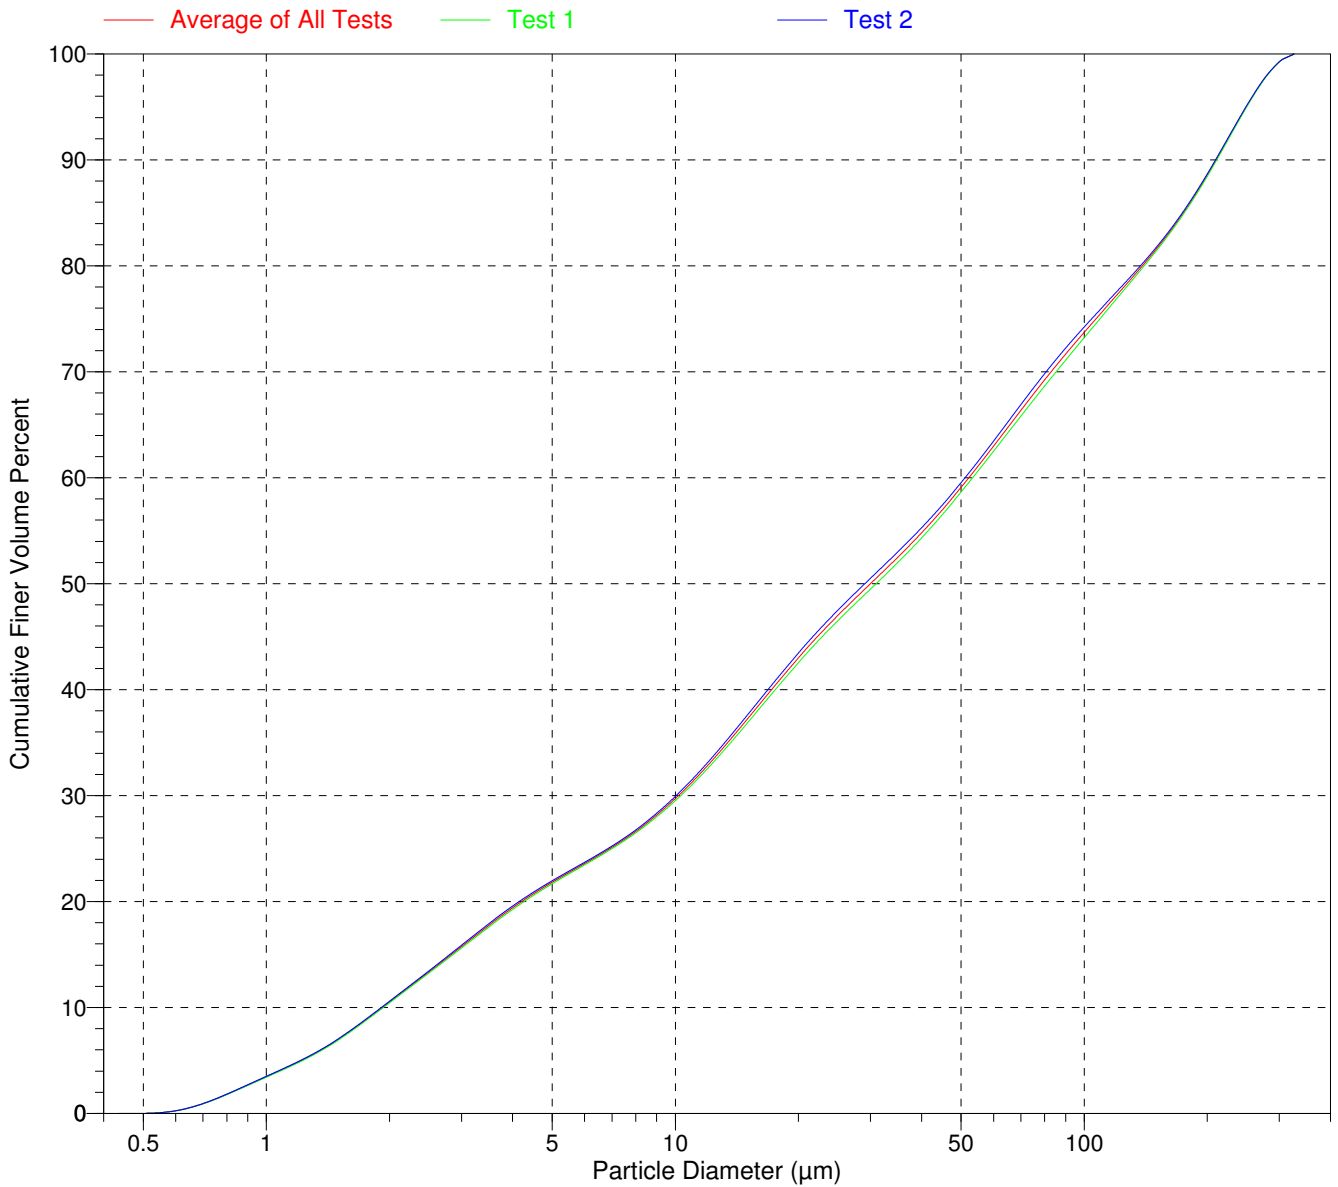




Sample: YYS 156A 0.7-1.5
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2
Analyzed: 29/07/2010 2:22:30PM
Reported: 3/08/2010 11:35:10AM
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

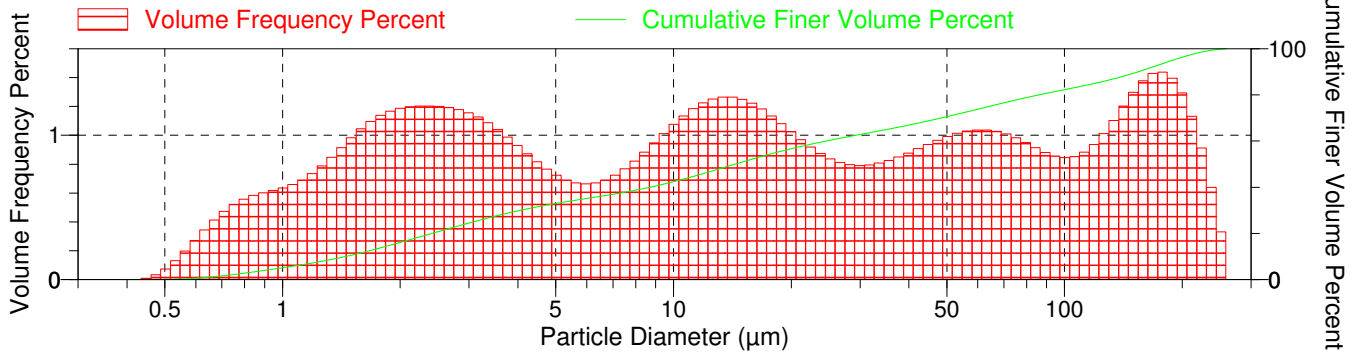

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 27.100 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00413 %
Obscuration: 13.4 %

Volume Distribution Arithmetic Statistics

Table with 5 columns: Mean, Std Dev of 2, Mode, Std Dev of 2. Rows for Mean and Median.

Peaks

Table with 8 columns: Peak Number, % of Dist. of Dist.\*, % of Dist. Std Dev of 2, Mean, Mean Std Dev of 2, Median, Median Std Dev of 2, Mode.

\* Peaks must comprise at least 5.00 % of the distribution.



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
273.842	258.523	266.073	100.0	0.0	0.0
258.523	244.062	251.189	99.6	0.4	0.0
244.062	230.409	237.137	99.0	0.7	0.1
230.409	217.520	223.872	98.1	0.9	0.2
217.520	205.353	211.349	96.9	1.1	0.3
205.353	193.865	199.526	95.6	1.3	0.4
193.865	183.021	188.365	94.2	1.4	0.5
183.021	172.783	177.828	92.8	1.4	0.6
172.783	163.117	167.880	91.4	1.4	0.6
163.117	153.993	158.489	90.0	1.4	0.7
153.993	145.378	149.624	88.7	1.3	0.8
145.378	137.246	141.254	87.5	1.2	0.8
137.246	129.569	133.352	86.4	1.1	0.8
129.569	122.321	125.893	85.4	1.0	0.8
122.321	115.478	118.850	84.5	0.9	0.8
115.478	109.018	112.202	83.6	0.9	0.8
109.018	102.920	105.925	82.7	0.9	0.8
102.920	97.163	100.000	81.9	0.8	0.8
97.163	91.728	94.406	81.0	0.9	0.7
91.728	86.596	89.125	80.1	0.9	0.7
86.596	81.752	84.140	79.2	0.9	0.6
81.752	77.179	79.433	78.3	1.0	0.5
77.179	72.862	74.989	77.3	1.0	0.5
72.862	68.786	70.795	76.3	1.0	0.4
68.786	64.938	66.834	75.2	1.0	0.3
64.938	61.306	63.096	74.2	1.0	0.3
61.306	57.876	59.566	73.2	1.0	0.2
57.876	54.639	56.234	72.1	1.0	0.1
54.639	51.582	53.088	71.1	1.0	0.1
51.582	48.697	50.119	70.1	1.0	0.0
48.697	45.973	47.315	69.2	1.0	0.0
45.973	43.401	44.668	68.2	0.9	0.0
43.401	40.973	42.170	67.3	0.9	0.0
40.973	38.681	39.811	66.5	0.9	0.1
38.681	36.517	37.584	65.6	0.8	0.1
36.517	34.475	35.481	64.8	0.8	0.0
34.475	32.546	33.497	64.0	0.8	0.0
32.546	30.726	31.623	63.2	0.8	0.0
30.726	29.007	29.854	62.4	0.8	0.0
29.007	27.384	28.184	61.6	0.8	0.0
27.384	25.852	26.607	60.8	0.8	0.0
25.852	24.406	25.119	59.9	0.8	0.1
24.406	23.041	23.714	59.1	0.9	0.1
23.041	21.752	22.387	58.1	0.9	0.1
21.752	20.535	21.135	57.2	1.0	0.1
20.535	19.387	19.953	56.1	1.0	0.2
19.387	18.302	18.836	55.1	1.1	0.2



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
18.302	17.278	17.783	53.9	1.1	0.3
17.278	16.312	16.788	52.7	1.2	0.3
16.312	15.399	15.849	51.5	1.2	0.4
15.399	14.538	14.962	50.3	1.3	0.4
14.538	13.725	14.125	49.0	1.3	0.5
13.725	12.957	13.335	47.7	1.3	0.5
12.957	12.232	12.589	46.5	1.3	0.5
12.232	11.548	11.885	45.3	1.2	0.6
11.548	10.902	11.220	44.1	1.2	0.6
10.902	10.292	10.593	42.9	1.1	0.6
10.292	9.716	10.000	41.9	1.1	0.6
9.716	9.173	9.441	40.9	1.0	0.6
9.173	8.660	8.913	39.9	0.9	0.6
8.660	8.175	8.414	39.0	0.9	0.5
8.175	7.718	7.943	38.2	0.8	0.5
7.718	7.286	7.499	37.5	0.8	0.4
7.286	6.879	7.079	36.7	0.7	0.4
6.879	6.494	6.683	36.0	0.7	0.3
6.494	6.131	6.310	35.4	0.7	0.2
6.131	5.788	5.957	34.7	0.7	0.2
5.788	5.464	5.623	34.0	0.7	0.1
5.464	5.158	5.309	33.4	0.7	0.0
5.158	4.870	5.012	32.6	0.7	0.0
4.870	4.597	4.732	31.9	0.8	0.1
4.597	4.340	4.467	31.0	0.8	0.1
4.340	4.097	4.217	30.2	0.9	0.1
4.097	3.868	3.981	29.2	0.9	0.2
3.868	3.652	3.758	28.2	1.0	0.2
3.652	3.447	3.548	27.2	1.0	0.2
3.447	3.255	3.350	26.1	1.1	0.2
3.255	3.073	3.162	25.0	1.1	0.2
3.073	2.901	2.985	23.8	1.2	0.1
2.901	2.738	2.818	22.6	1.2	0.1
2.738	2.585	2.661	21.5	1.2	0.1
2.585	2.441	2.512	20.3	1.2	0.1
2.441	2.304	2.371	19.0	1.2	0.1
2.304	2.175	2.239	17.8	1.2	0.0
2.175	2.054	2.113	16.6	1.2	0.0
2.054	1.939	1.995	15.5	1.2	0.0
1.939	1.830	1.884	14.3	1.2	0.0
1.830	1.728	1.778	13.2	1.1	0.0
1.728	1.631	1.679	12.1	1.1	0.0
1.631	1.540	1.585	11.0	1.0	0.0
1.540	1.454	1.496	10.0	1.0	0.0
1.454	1.372	1.413	9.1	0.9	0.0
1.372	1.296	1.334	8.3	0.8	0.0
1.296	1.223	1.259	7.5	0.8	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.223	1.155	1.189	6.8	0.7	0.0
1.155	1.090	1.122	6.1	0.7	0.0
1.090	1.029	1.059	5.4	0.7	0.0
1.029	0.972	1.000	4.8	0.6	0.0
0.972	0.917	0.944	4.2	0.6	0.0
0.917	0.866	0.891	3.6	0.6	0.0
0.866	0.818	0.841	3.0	0.6	0.0
0.818	0.772	0.794	2.4	0.6	0.0
0.772	0.729	0.750	1.9	0.5	0.0
0.729	0.688	0.708	1.4	0.5	0.0
0.688	0.649	0.668	1.0	0.4	0.0
0.649	0.613	0.631	0.7	0.3	0.0
0.613	0.579	0.596	0.4	0.3	0.0
0.579	0.546	0.562	0.2	0.2	0.0
0.546	0.516	0.531	0.1	0.1	0.0
0.516	0.487	0.501	0.0	0.1	0.0
0.487	0.460	0.473	0.0	0.0	0.0
0.460	0.434	0.447	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

## Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
250.000	99.8	80.000	78.9	10.000	42.4	2.000	16.1
200.000	96.3	60.000	73.8	8.000	38.7	1.000	5.1
150.000	89.4	40.000	67.0	6.000	35.1	0.500	0.1
100.000	82.3	20.000	56.7	4.000	29.8		





# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
259.309	100.0	48.318	70.0	8.707	40.0	1.450	10.0
188.830	95.0	35.018	65.0	5.937	35.0	0.990	5.0
153.987	90.0	24.506	60.0	4.054	30.0	0.423	0.0
119.506	85.0	18.242	55.0	3.076	25.0		
86.042	80.0	14.360	50.0	2.412	20.0		
64.128	75.0	11.402	45.0	1.895	15.0		




Sample: YYS 156A 0.7-1.5  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-026.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 2:22:30PM  
Reported: 3/08/2010 11:35:10AM  
Background: 29/07/2010 1:50:13PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

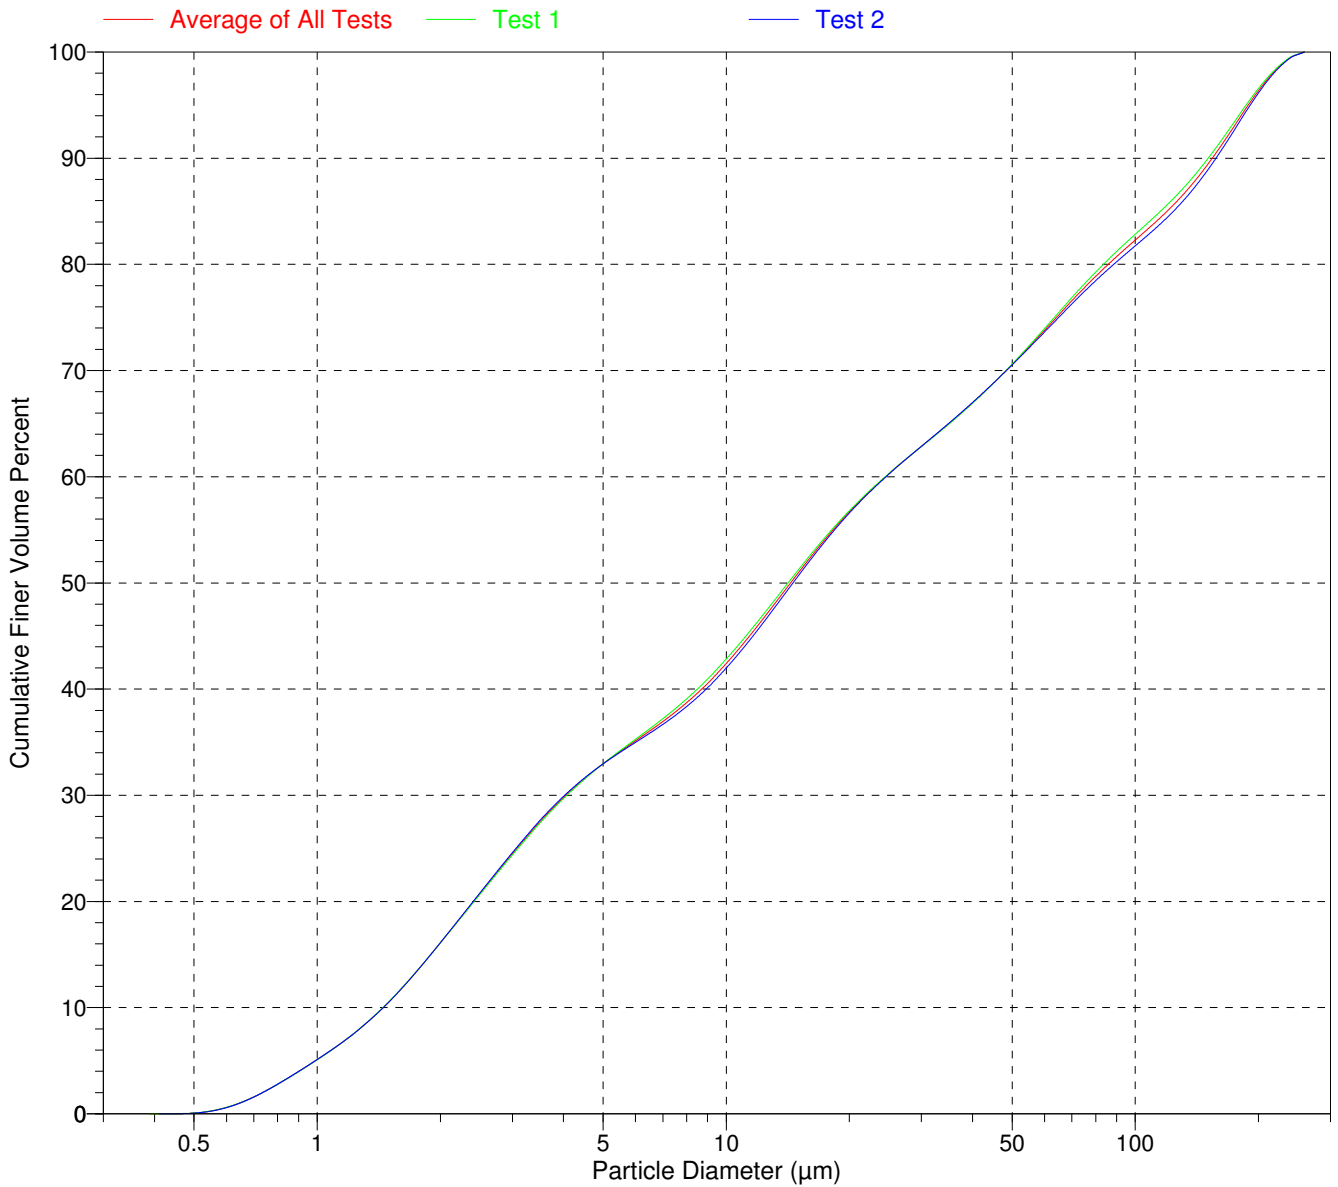




Sample: YC3 Tails
Operator: Tim O'Connell
Submitter: SRK Consulting
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2
Analyzed: 29/07/2010 1:09:13PM
Reported: 3/08/2010 11:31:10AM
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331
Material: Fraunhofer / Water
Background: Water RI 1.331
Smoothing: Medium

Combined Report

Volume Frequency vs. Diameter

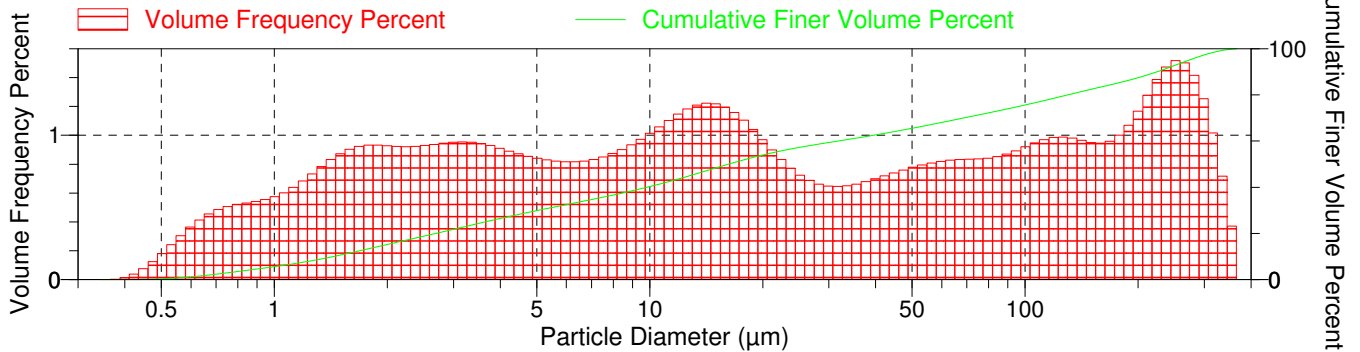

Summary Report

Analysis Conditions

FlowRate: 12.0 l/m
Circulation time: 120 sec

Ultrasonic intensity: 50 %
Ultrasonic time: 120 sec

Particle Properties

Refractive Index: (Re)0.000, (Im)0.000
Density: 1.000 g/cm³
Smoothing: Medium
Truncate intensity data: No
Minimum signal fraction: 16.0 %

Analysis Liquid Properties

Refractive Index: 1.331
Viscosity: 0.798 cp
Temperature: 26.045 °C

User Parameters

Parameter 1: 0.000

Parameter 2: 0.000

Parameter 3: 0.000

Sample

Sample Concentration: 0.00825 %
Obscuration: 24.4 %

Volume Distribution Arithmetic Statistics

Table with 5 columns: Mean, Std Dev of 2, Mode, Std Dev of 2. Rows include Mean (64.73), Median (16.22), Std Dev of 2 (1.512), and Mode (252.0).



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 2

Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
386.812	365.174	375.837	100.0	0.0	0.0
365.174	344.747	354.813	99.6	0.4	0.0
344.747	325.462	334.965	98.9	0.7	0.1
325.462	307.256	316.228	97.8	1.0	0.2
307.256	290.068	298.538	96.6	1.3	0.3
290.068	273.842	281.838	95.1	1.4	0.5
273.842	258.523	266.073	93.6	1.5	0.6
258.523	244.062	251.189	92.1	1.5	0.7
244.062	230.409	237.137	90.7	1.5	0.9
230.409	217.520	223.872	89.3	1.4	1.0
217.520	205.353	211.349	88.0	1.3	1.0
205.353	193.865	199.526	86.8	1.2	1.1
193.865	183.021	188.365	85.8	1.1	1.1
183.021	172.783	177.828	84.8	1.0	1.1
172.783	163.117	167.880	83.8	1.0	1.1
163.117	153.993	158.489	82.9	0.9	1.0
153.993	145.378	149.624	81.9	1.0	0.9
145.378	137.246	141.254	81.0	1.0	0.8
137.246	129.569	133.352	80.0	1.0	0.7
129.569	122.321	125.893	79.0	1.0	0.5
122.321	115.478	118.850	78.0	1.0	0.4
115.478	109.018	112.202	77.0	1.0	0.3
109.018	102.920	105.925	76.1	0.9	0.2
102.920	97.163	100.000	75.2	0.9	0.1
97.163	91.728	94.406	74.3	0.9	0.1
91.728	86.596	89.125	73.4	0.9	0.0
86.596	81.752	84.140	72.6	0.9	0.0
81.752	77.179	79.433	71.7	0.8	0.1
77.179	72.862	74.989	70.9	0.8	0.1
72.862	68.786	70.795	70.1	0.8	0.2
68.786	64.938	66.834	69.2	0.8	0.2
64.938	61.306	63.096	68.4	0.8	0.2
61.306	57.876	59.566	67.6	0.8	0.2
57.876	54.639	56.234	66.8	0.8	0.2
54.639	51.582	53.088	66.0	0.8	0.3
51.582	48.697	50.119	65.2	0.8	0.2
48.697	45.973	47.315	64.4	0.8	0.2
45.973	43.401	44.668	63.7	0.7	0.2
43.401	40.973	42.170	63.0	0.7	0.2
40.973	38.681	39.811	62.3	0.7	0.1
38.681	36.517	37.584	61.6	0.7	0.1
36.517	34.475	35.481	60.9	0.7	0.0
34.475	32.546	33.497	60.3	0.6	0.0
32.546	30.726	31.623	59.7	0.6	0.0
30.726	29.007	29.854	59.0	0.6	0.0
29.007	27.384	28.184	58.3	0.7	0.0
27.384	25.852	26.607	57.7	0.7	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 3

Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
25.852	24.406	25.119	56.9	0.7	0.1
24.406	23.041	23.714	56.2	0.8	0.2
23.041	21.752	22.387	55.3	0.8	0.2
21.752	20.535	21.135	54.4	0.9	0.3
20.535	19.387	19.953	53.4	1.0	0.3
19.387	18.302	18.836	52.4	1.0	0.3
18.302	17.278	17.783	51.3	1.1	0.3
17.278	16.312	16.788	50.1	1.2	0.3
16.312	15.399	15.849	48.9	1.2	0.2
15.399	14.538	14.962	47.7	1.2	0.1
14.538	13.725	14.125	46.5	1.2	0.0
13.725	12.957	13.335	45.3	1.2	0.0
12.957	12.232	12.589	44.1	1.2	0.1
12.232	11.548	11.885	43.0	1.1	0.2
11.548	10.902	11.220	41.9	1.1	0.3
10.902	10.292	10.593	40.8	1.1	0.4
10.292	9.716	10.000	39.8	1.0	0.4
9.716	9.173	9.441	38.8	1.0	0.4
9.173	8.660	8.913	37.9	0.9	0.5
8.660	8.175	8.414	37.0	0.9	0.5
8.175	7.718	7.943	36.1	0.9	0.5
7.718	7.286	7.499	35.3	0.8	0.5
7.286	6.879	7.079	34.4	0.8	0.5
6.879	6.494	6.683	33.6	0.8	0.5
6.494	6.131	6.310	32.8	0.8	0.5
6.131	5.788	5.957	32.0	0.8	0.5
5.788	5.464	5.623	31.1	0.8	0.5
5.464	5.158	5.309	30.3	0.8	0.5
5.158	4.870	5.012	29.5	0.8	0.5
4.870	4.597	4.732	28.6	0.9	0.5
4.597	4.340	4.467	27.8	0.9	0.5
4.340	4.097	4.217	26.9	0.9	0.4
4.097	3.868	3.981	25.9	0.9	0.4
3.868	3.652	3.758	25.0	0.9	0.4
3.652	3.447	3.548	24.1	0.9	0.4
3.447	3.255	3.350	23.1	1.0	0.3
3.255	3.073	3.162	22.2	1.0	0.3
3.073	2.901	2.985	21.2	1.0	0.3
2.901	2.738	2.818	20.3	0.9	0.3
2.738	2.585	2.661	19.3	0.9	0.2
2.585	2.441	2.512	18.4	0.9	0.2
2.441	2.304	2.371	17.5	0.9	0.2
2.304	2.175	2.239	16.6	0.9	0.2
2.175	2.054	2.113	15.6	0.9	0.2
2.054	1.939	1.995	14.7	0.9	0.1
1.939	1.830	1.884	13.8	0.9	0.1
1.830	1.728	1.778	12.8	0.9	0.1



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 4

Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Class

High Diameter (µm)	Low Diameter (µm)	Average Diameter (µm)	Cumulative Volume Finer (Percent)	Volume Frequency (Percent)	Cum. Vol. Standard Deviation (2 tests)
1.728	1.631	1.679	11.9	0.9	0.1
1.631	1.540	1.585	11.0	0.9	0.1
1.540	1.454	1.496	10.1	0.9	0.1
1.454	1.372	1.413	9.3	0.8	0.1
1.372	1.296	1.334	8.5	0.8	0.1
1.296	1.223	1.259	7.8	0.7	0.1
1.223	1.155	1.189	7.1	0.7	0.1
1.155	1.090	1.122	6.5	0.6	0.1
1.090	1.029	1.059	5.9	0.6	0.0
1.029	0.972	1.000	5.3	0.6	0.0
0.972	0.917	0.944	4.8	0.6	0.0
0.917	0.866	0.891	4.2	0.5	0.0
0.866	0.818	0.841	3.7	0.5	0.0
0.818	0.772	0.794	3.2	0.5	0.0
0.772	0.729	0.750	2.7	0.5	0.0
0.729	0.688	0.708	2.2	0.5	0.0
0.688	0.649	0.668	1.7	0.5	0.0
0.649	0.613	0.631	1.3	0.4	0.0
0.613	0.579	0.596	1.0	0.4	0.0
0.579	0.546	0.562	0.7	0.3	0.0
0.546	0.516	0.531	0.4	0.2	0.0
0.516	0.487	0.501	0.2	0.2	0.0
0.487	0.460	0.473	0.1	0.1	0.0
0.460	0.434	0.447	0.1	0.1	0.0
0.434	0.410	0.422	0.0	0.0	0.0
0.410	0.387	0.398	0.0	0.0	0.0
0.387	0.365	0.376	0.0	0.0	0.0



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 5

Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Size Table

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
350.000	99.7	100.000	75.6	10.000	40.3	1.000	5.6
300.000	97.3	80.000	72.2	8.000	36.6	0.500	0.3
250.000	92.8	60.000	68.1	6.000	32.5		
200.000	87.5	40.000	62.7	4.000	26.5		
150.000	82.4	20.000	54.0	2.000	15.2		



# Particle & Surface Sciences Pty. Limited

PO Box 1926, Gosford, NSW, Australia 2250. Tel: (61) 02 43 237822 Fax: (61) 02 43 237629 Email: info@pss.aus.net

Saturn DigiSizer 5200 V1.12

Saturn DigiSizer 5200 V1.12

5200 LSHU V2.01 S/N 227

Page 6

Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

### Report by Volume Percent

Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)	Low Diameter (µm)	Cumulative Volume Finer (Percent)
366.284	100.0	68.512	70.0	9.835	40.0	1.439	10.0
272.105	95.0	47.980	65.0	7.160	35.0	0.940	5.0
223.980	90.0	31.687	60.0	5.048	30.0	0.366	0.0
175.150	85.0	21.300	55.0	3.650	25.0		
130.085	80.0	16.217	50.0	2.694	20.0		
96.112	75.0	12.783	45.0	1.974	15.0		





Sample: YC3 Tails  
Operator: Tim O'Connell  
Submitter: SRK Consulting  
File: L:\...\3813\000-025.SMP

Test Number: Avg of 2  
Analyzed: 29/07/2010 1:09:13PM  
Reported: 3/08/2010 11:31:10AM  
Background: 29/07/2010 12:36:48PM

Model: Fraunhofer, 1.331  
Material: Fraunhofer / Water  
Background: Water RI 1.331  
Smoothing: Medium

**Cumulative Finer Volume Percent vs. Diameter**

